

## TECHNICAL MANUAL

### ENGINEERING SERIES FOR AIRCRAFT REPAIR

## AEROSPACE METALS - GENERAL DATA AND USAGE FACTORS

This manual supersedes TO 1-1A-9 dated 5 June 2025.

DISTRIBUTION STATEMENT A - Approved for public release; distribution is unlimited. PA Case Number 11-03010. Submit recommended changes or problems with this Technical Order to 406 SCMS/GUEE, Robins AFB, GA 31098. Questions concerning technical content shall be referred to AFLCMC/EZPT.

Published Under Authority of the Secretary of the Air Force and by Direction of the Chief of the Naval Air Systems Command.

---

## 26 JUNE 2025



INSERT LATEST CHANGED PAGES. DESTROY SUPERSEDED PAGES.

LIST OF EFFECTIVE PAGES

NOTE The portion of the text affected by the changes is indicated by a vertical line in the outer margins of the page. Changes to illustrations are indicated by shaded or screened areas, or by miniature pointing hands.

Dates of issue for original and changed pages are:  
Original . . . . .0 . . . . .26 June 2025

TOTAL NUMBER OF PAGES IN THIS PUBLICATION IS 360, CONSISTING OF THE FOLLOWING:

Page No.	*Change No.	Page No.	*Change No.	Page No.	*Change No.
Title . . . . .	0				
A . . . . .	0				
i - xxii . . . . .	0				
1-1 . . . . .	0				
1-2 Blank . . . . .	0				
2-1 - 2-92 . . . . .	0				
3-1 - 3-75 . . . . .	0				
3-76 Blank . . . . .	0				
4-1 - 4-22 . . . . .	0				
5-1 - 5-15 . . . . .	0				
5-16 Blank . . . . .	0				
6-1 - 6-12 . . . . .	0				
7-1 - 7-13 . . . . .	0				
7-14 Blank . . . . .	0				
8-1 - 8-22 . . . . .	0				
9-1 - 9-15 . . . . .	0				
9-16 Blank . . . . .	0				
A-1 - A-54 . . . . .	0				
Glossary 1 - Glossary 10 . . . . .	0				

\* Zero in this column indicates an original page.



## TABLE OF CONTENTS

Chapter	Page
LIST OF ILLUSTRATIONS . . . . .	xii
LIST OF TABLES . . . . .	xii
INTRODUCTION . . . . .	xv
SAFETY SUMMARY . . . . .	xviii
1 INTRODUCTION . . . . .	1-1
1.1 INTRODUCTION . . . . .	1-1
1.1.1 General Information . . . . .	1-1
1.1.2 Instructions . . . . .	1-1
1.2 WELDING . . . . .	1-1
2 FERROUS (STEEL) ALLOYS . . . . .	2-1
2.1 CLASSIFICATION . . . . .	2-1
2.1.1 Society of Automotive Engineers (SAE) Numbering System . . . . .	2-1
2.1.2 Carbon Steels . . . . .	2-2
2.1.3 Nickel Steels . . . . .	2-2
2.1.4 Chromium Steels . . . . .	2-2
2.1.5 Chromium-Nickel Steels . . . . .	2-2
2.1.6 Chrome-Vanadium Steels . . . . .	2-3
2.1.7 Chrome Molybdenum Steels . . . . .	2-3
2.2 PRINCIPLES OF HEAT TREATMENT OF STEELS . . . . .	2-3
2.2.1 Hardening . . . . .	2-3
2.3 QUENCHING PROCEDURE . . . . .	2-4
2.3.1 Quenching Medium . . . . .	2-4
2.3.2 Straightening of Parts Warped in Quenching . . . . .	2-5
2.3.3 Tempering (Drawing) . . . . .	2-5
2.3.4 Normalizing . . . . .	2-6
2.3.5 Case Hardening . . . . .	2-6
2.3.5.1 Flame Hardening/Softening . . . . .	2-6
2.3.5.2 Induction Hardening/Heating . . . . .	2-6
2.3.6 Carburizing . . . . .	2-6
2.3.7 Cyaniding . . . . .	2-7
2.3.8 Nitriding . . . . .	2-7
2.4 HEAT TREATING EQUIPMENT . . . . .	2-8
2.4.1 Furnaces . . . . .	2-8
2.4.2 Heat Treating Furnaces/Baths . . . . .	2-8
2.5 HEAT CONTROL: TEMPERATURE MEASURING EQUIPMENT, FURNACE TEMPERATURE UNIFORMITY SURVEY, AND SYSTEM ACCURACY TESTS (SATs) . . . . .	2-8
2.5.1 Controlling, Monitoring, and Recording Equipment . . . . .	2-8
2.5.2 Field Test Instruments . . . . .	2-8
2.5.3 TC . . . . .	2-8
2.5.4 Temperature Control and Uniformity Testing . . . . .	2-9
2.5.4.1 SAT . . . . .	2-9
2.5.4.1.2 SAT Procedure . . . . .	2-9
2.5.4.1.3 SAT Report Requirements . . . . .	2-10
2.5.4.1.5 Modification Offset . . . . .	2-10
2.5.4.2 TEMPERATURE UNIFORMITY SURVEY (TUS) . . . . .	2-10
2.5.4.2.2 Initial TUS Requirement . . . . .	2-11



## TABLE OF CONTENTS - CONTINUED

Chapter		Page
2.5.4.2.3	Quarterly TUS Requirement . . . . .	2-11
2.5.4.2.4	Annual TUS Requirement . . . . .	2-11
2.5.4.3	TUS Procedure . . . . .	2-11
2.5.4.4	Temperature Uniformity Pass/Fail Requirements . . . . .	2-11
2.5.4.5	TUS Data and TUS Reports . . . . .	2-11
2.5.4.5.2	TUS Survey Report Requirements . . . . .	2-12
2.5.4.6	Failed TUS Procedures . . . . .	2-12
2.5.4.6.2	Modification Offset . . . . .	2-12
2.6	SALT BATH CONTROL . . . . .	2-15
2.6.1	Quenching Tanks and Liquids . . . . .	2-15
2.7	HEAT TREATING PROCEDURES . . . . .	2-15
2.7.1	Newly Fabricated Parts . . . . .	2-15
2.7.2	Initial Furnace Temperatures . . . . .	2-15
2.7.3	Soaking Periods . . . . .	2-15
2.7.4	Hardening . . . . .	2-16
2.7.5	Tempering (Drawing) . . . . .	2-16
2.7.6	Annealing . . . . .	2-16
2.7.7	Normalizing . . . . .	2-16
2.7.8	Carburizing . . . . .	2-16
2.7.9	Records . . . . .	2-16
2.8	HARDNESS TESTING . . . . .	2-16
2.8.1	General . . . . .	2-16
2.8.2	Tensile Strength . . . . .	2-16
2.8.3	Hardness-Tensile Strength Relationship . . . . .	2-16
2.8.4	Specification Cross Reference . . . . .	2-17
2.9	GENERAL HEAT TREATING TEMPERATURES, COMPOSITION (CHEMICAL) AND CHARACTERISTICS OF VARIOUS STEEL AND STEEL ALLOYS . . . . .	2-26
2.9.1	1010 Low Carbon . . . . .	2-26
2.9.2	1015 Low Carbon . . . . .	2-26
2.9.3	1020 Low Carbon . . . . .	2-26
2.9.4	1022 Low Carbon . . . . .	2-27
2.9.5	1025 Low Carbon . . . . .	2-27
2.9.6	Corten, Low Carbon, Low Alloy . . . . .	2-27
2.9.7	NAXAC9115 Low Carbon, Low Alloy . . . . .	2-28
2.9.8	1035 Medium Carbon . . . . .	2-28
2.9.9	1040 Medium Carbon . . . . .	2-29
2.9.10	1045 Medium Carbon . . . . .	2-29
2.9.11	1050 Medium Carbon . . . . .	2-29
2.9.12	1055 High Carbon . . . . .	2-29
2.9.13	1060 High Carbon . . . . .	2-30
2.9.14	1070 High Carbon . . . . .	2-30
2.9.15	1080 High Carbon . . . . .	2-30
2.9.16	1095 High Carbon . . . . .	2-31
2.9.17	1112 Free Cutting . . . . .	2-31
2.9.18	1117 Carbon (Free Cutting Steel) . . . . .	2-31
2.9.19	1137 Carbon, Free Cutting . . . . .	2-32
2.9.20	2317 Nickel Alloy . . . . .	2-32
2.9.21	2330 Nickel Alloy . . . . .	2-33
2.9.22	2340 Nickel Alloy . . . . .	2-33
2.9.23	2515 Nickel Alloy . . . . .	2-33
2.9.24	3115 Steel Nickel Chromium Alloy . . . . .	2-34
2.9.25	3140 Nickel Chrome Alloy . . . . .	2-34
2.9.26	3310 Nickel - Chromium Alloy . . . . .	2-35
2.9.27	4037 Molydenum Alloy . . . . .	2-35
2.9.28	4130 Chromium - Molydenum Alloy . . . . .	2-35



## TABLE OF CONTENTS - CONTINUED

Chapter		Page
2.9.29	4135 Chromium Molybdenum Alloy . . . . .	2-36
2.9.30	17-22A(V) Structural (Ultra High Strength) Low Alloy . . . . .	2-36
2.9.31	4137CO . . . . .	2-36
2.9.32	4140 Medium Carbon Chromium - Molybdenum (Nitriding Grade) . . . . .	2-37
2.9.33	SAE 4330 V Mod . . . . .	2-37
2.9.34	4150 Chromium-Molybdenum . . . . .	2-38
2.9.35	521000 High Carbon, High Chromium Alloy . . . . .	2-38
2.9.36	LADISH D-6-A Low Alloy High Strength . . . . .	2-38
2.9.37	Nitralloy 135 Mod Steel Ultra High Strength (Nitriding Grade) . . . . .	2-39
2.9.38	4337 and 4340 Steel Nickel - Chromium Molybdenum Alloy . . . . .	2-39
2.9.39	4615 Steel Nickel Molybdenum Alloy . . . . .	2-40
2.9.40	4620 Steel Nickel Molybdenum Alloy . . . . .	2-41
2.9.41	4640 Steel Nickel Molybdenum . . . . .	2-41
2.9.42	6150 and 6152 Chromium Vanadium Alloy . . . . .	2-42
2.9.43	8615 Steel-Nickel-Chromium-Molybdenum Alloy . . . . .	2-42
2.9.44	8617 Steel-Nickel-Chromium-Molybdenum Alloy . . . . .	2-42
2.9.45	8620 Nickel-Chromium-Molybdenum-Alloy . . . . .	2-43
2.9.46	8630 Steel Nickel-Chromium-Molybdenum Alloy . . . . .	2-44
2.9.47	8640 Steel Nickel-Chromium-Molybdenum . . . . .	2-44
2.9.48	8735 Steel Nickel-Chromium-Molybdenum . . . . .	2-44
2.9.49	8740 Steel Nickel-Chromium-Molybdenum . . . . .	2-45
2.9.50	9260, 9261 and 9262 Steel Silicon . . . . .	2-45
2.9.51	9310 Steel Nickel Chromium-Molybdenum (Electric Furnace Steel) . . . . .	2-45
2.9.52	Type 301 Steel Austenitic Stainless . . . . .	2-46
2.9.53	Type 302 Steel Austenitic Stainless . . . . .	2-47
2.9.54	Type 303 and Type 303Se, Steel Austenitic Stainless . . . . .	2-47
2.9.55	Type 304 and Type 304L Steel Austenitic Stainless . . . . .	2-47
2.9.56	Type 314 Steel-Austenitic Stainless . . . . .	2-48
2.9.57	Type 316 and Type 317 Steel Austenitic Stainless . . . . .	2-48
2.9.58	Type 321 Steel Austenitic Stainless . . . . .	2-49
2.9.59	Types 347 and Type 348 Steel Austenitic Stainless . . . . .	2-49
2.9.60	Type 414 Steel Martensitic Stainless . . . . .	2-50
2.9.61	Type 403, Type 410, and Type 416 Steel-Martensitic Stainless . . . . .	2-50
2.9.62	Type 420 Steel Martensitic Stainless . . . . .	2-50
2.9.63	Type 431 Steel Martensitic Stainless . . . . .	2-51
2.9.64	PH13-8Mo Steel, Martensitic Stainless, Precipitation Hardening . . . . .	2-51
2.9.65	PH15-5 Steel, Martensitic Stainless, Precipitation Hardening . . . . .	2-52
2.9.66	17-4PH Steel, Martensitic Stainless, Precipitation Hardening . . . . .	2-53
2.9.67	17-7PH Steel Martensitic Stainless (Precipitation Hardening) . . . . .	2-53
2.9.68	Type 440A, Type 440B, Type 550C, and Type 440C Steel Martensitic Stainless . . . . .	2-53
2.9.69	15-7-Molybdenum Steel Martensitic Stainless . . . . .	2-54
2.9.70	PH14-8 Molybdenum . . . . .	2-54
2.9.71	19-9DL 19-9DX . . . . .	2-55
2.9.72	AM-350 Steel - Age Hardening Stainless . . . . .	2-55
2.9.73	AM-355 Steel - Age Hardening Stainless . . . . .	2-56
2.9.74	HNM Steel - Age Hardening Stainless . . . . .	2-56
2.9.75	16-15-6 Steel - Iron - Chromium - Nickel - Alloy . . . . .	2-56
2.9.76	V57 Steel - Nickel Chromium Stainless (Austenitic) . . . . .	2-57
2.9.77	V36 Steel Cobalt Base - Chromium-Nickel-Alloy . . . . .	2-57
2.9.78	W152 Steel Cobalt Chromium Tungsten Corrosion Resistant Alloy . . . . .	2-57
2.9.79	Haynes Alloy No. 151 Cobalt Base Corrosion Resistant Alloy . . . . .	2-58
2.9.80	GMR-235 Nickel Base Corrosive Resistant Alloy . . . . .	2-58
2.9.81	Hastelloy Alloy R-235 Nickel Base Corrosion Resistant Alloy . . . . .	2-59
2.9.82	Inconel Alloy 718 Steel Nickel Chromium Stainless Alloy . . . . .	2-59
2.9.83	Udimet 700 Highly Alloyed Nickel Base Corrosion Resistant . . . . .	2-60



## TABLE OF CONTENTS - CONTINUED

Chapter		Page
2.9.84	Rene 41 Nickel Base Heat Treatable Stainless Alloy . . . . .	2-60
2.9.84.1	Composition Range . . . . .	2-60
2.9.85	Nicrotung Nickel Base Corrosion Resistant Alloy . . . . .	2-61
2.9.86	Nimonic 105 Nickel-Cobalt-Chromium Corrosion Resistant Alloy . . . . .	2-61
2.10	MACHINING OF STEELS (GENERAL) . . . . .	2-61
2.10.1	Machinability . . . . .	2-61
2.10.2	Cutting Tool Angles . . . . .	2-62
2.11	MACHINING CORROSION RESISTING STEEL . . . . .	2-67
2.11.1	Machining Comparison of Corrosion Resisting Steel . . . . .	2-67
2.11.2	Machining of the Corrosion Resisting Steels . . . . .	2-67
2.11.3	Cutting Tools for Machining Corrosion Resisting Steels . . . . .	2-68
2.12	TURNING OF THE CORROSION RESISTING STEELS . . . . .	2-69
2.13	MILLING CORROSION RESISTING STEEL . . . . .	2-70
2.13.1	Cutters for Milling . . . . .	2-71
2.13.2	Lubrication for Milling . . . . .	2-71
2.14	DRILLING CORROSION RESISTING STEEL . . . . .	2-71
2.14.1	Drilling Speeds for Corrosion Resisting Steel . . . . .	2-71
2.14.2	Lubrication for Drilling Stainless . . . . .	2-71
2.15	REAMING CORROSION RESISTING STEEL . . . . .	2-72
2.15.1	Hardening Characteristics of Corrosion Resisting Steel . . . . .	2-72
2.15.2	Reamers for Cutting Stainless Steel . . . . .	2-72
2.15.3	Speeds for Reaming . . . . .	2-72
2.16	TAPPING CORROSION RESISTING STEEL . . . . .	2-72
2.16.1	Tapping Quality Corrosion Resisting Steel . . . . .	2-72
2.16.2	Tapping Speeds Corrosion Resisting Steel . . . . .	2-73
2.16.3	Lubrication for Tapping . . . . .	2-73
2.17	SAWING . . . . .	2-74
2.17.1	Hack Saws (Mechanical Drive) . . . . .	2-74
2.17.2	Band Sawing . . . . .	2-74
2.18	FABRICATION OF FERROUS ALLOYS . . . . .	2-74
2.18.1	Accomplish Designs, Application and Fabrication . . . . .	2-74
2.19	BENDING (SINGLE CURVATURE) . . . . .	2-75
2.19.1	Spring back Allowance . . . . .	2-75
2.20	DRAW FORMING . . . . .	2-76
2.20.1	Surface Condition . . . . .	2-76
2.21	STRETCH FORMING . . . . .	2-77
2.21.1	Trimming of Edges, Removal of Nicks and Scratches . . . . .	2-77
2.21.2	Forming Dies/Blocks for General Production . . . . .	2-77
2.22	DROP HAMMER FORMING . . . . .	2-78
2.23	SPINNING . . . . .	2-78
2.23.1	Form Blocks for Spinning . . . . .	2-78
2.24	SHEARING AND BLANKING . . . . .	2-78
2.25	BLANKING AND PUNCHING . . . . .	2-78
2.26	GENERAL FABRICATING CHARACTERISTICS . . . . .	2-78
2.27	PLAIN CARBON AND ALLOY STEELS . . . . .	2-78
2.27.1	Plain Carbon Steel - 1006 through 1015 . . . . .	2-78
2.27.2	Plain Carbon Steels - SAE 1016 through 1030 . . . . .	2-79
2.27.3	Plain Carbon Steels - 1030 through 1050 . . . . .	2-79
2.27.4	Alloy Steels - 1055 through 1095 . . . . .	2-79
2.27.5	1100 Series Steel . . . . .	2-79
2.27.6	1300 Series Alloy Steel . . . . .	2-79
2.27.7	2300 Series Nickel Alloy Steels . . . . .	2-79
2.27.8	2500 Series Nickel Steel . . . . .	2-79
2.27.9	3100, 3200, and 3300 Series Nickel Chromium Steels . . . . .	2-79
2.27.10	4000 Series Molybdenum Steels . . . . .	2-79



## TABLE OF CONTENTS - CONTINUED

Chapter		Page
2.27.11	4100 Series Chromium - Molybdenum Steels	2-79
2.27.12	4130 Grade Steel	2-79
2.27.13	4140 Series Steel	2-79
2.27.14	4300 Series Nickel-Chromium-Molybdenum Steels	2-79
2.27.15	8000 Series Molybdenum Steels	2-80
2.27.16	8600, 8700, 9300, 9700, 9800, and 9900 Series Steels	2-80
2.28	CORROSION RESISTANT (STAINLESS) AND HEAT RESISTANT STEELS	2-80
2.28.1	Forming Sheet Stock	2-80
2.28.2	Draw Forming	2-80
2.28.3	Drop Hammer Forming	2-80
2.28.4	Spinning	2-80
2.28.5	Shearing and Blanking	2-80
2.28.6	Hot Forming	2-80
2.29	STEEL SURFACE FINISHES	2-84
2.30	DEFINITION OF DISSIMILAR METALS	2-84
2.31	TYPES OF PLATING	2-84
2.31.1	Cadmium Plating, AMS-QQ-P-416	2-85
2.31.2	Zinc Plating, QQ-Z-325	2-85
2.31.3	Nickel Plating, QQ-N-290	2-86
2.31.4	Chromium Plating, QQ-C-320	2-86
2.31.5	Tin Plating, QQ-T-425	2-87
2.31.6	Phosphate Coating, MIL-P-16232	2-87
2.31.7	Silver Plating, QQ-S-635	2-87
2.31.8	Intended Use	2-88
2.32	SURFACE TREATMENTS FOR CORROSION AND HEAT-RESISTING STEELS AND ALLOYS	2-88
2.33	PASSIVATION OF STAINLESS STEELS	2-88
2.33.1	Prior to Accomplishing the Passivation	2-89
2.34	VAPOR DEPOSITED COATING	2-89
2.35	MECHANICAL-SURFACE FINISH	2-89
2.35.1	Designation of Surface Finish	2-90
3	ALUMINUM ALLOYS	3-1
3.1	CLASSIFICATION	3-1
3.2	COMMERCIAL AND MILITARY DESIGNATIONS	3-1
3.3	MECHANICAL PROPERTIES	3-2
3.3.1	Tempers of Aluminum Alloys	3-2
3.3.2	Physical Properties	3-4
3.4	HEAT TREATMENT OF ALUMINUM ALLOYS	3-23
3.4.1	General	3-23
3.5	NEWLY FABRICATED PARTS	3-23
3.6	RECORDS	3-23
3.7	SOLUTION HEAT TREATMENT	3-24
3.7.1	Heating Temperature	3-24
3.7.2	Heating (Soak) Time	3-24
3.7.3	Interruptions	3-24
3.7.4	Oven/Part Loading	3-24
3.7.5	Oven Recovery Time	3-25
3.8	QUENCHING	3-25
3.8.1	Quench Equipment	3-25
3.8.2	Quench Delay	3-25
3.8.3	Quenchant Temperature	3-25
3.8.4	Quenchant Temperature Rise	3-25
3.8.5	Agitation	3-25



## TABLE OF CONTENTS - CONTINUED

Chapter		Page
3.8.6	Immersion Time	3-26
3.9	STRAIGHTENING OF PARTS AFTER QUENCHING	3-26
3.10	REFRIGERATION	3-26
3.11	PRECIPITATION HEAT TREATING (Artificial Aging)	3-26
3.11.1	Artificial Aging	3-26
3.11.2	Soak Time	3-27
3.11.3	Part Loading	3-27
3.11.4	Interruptions	3-27
3.11.5	Annealing	3-27
3.11.6	Cold Working	3-28
3.11.7	Re-Solution Heat Treatment	3-28
3.12	HEAT TREATMENT OF RIVETS	3-28
3.12.1	2117 (AD) Rivets	3-28
3.12.2	2017 or 2017-T4 (D) Rivets	3-29
3.12.3	2024-0 or 2024-T4 (DD) Rivets	3-29
3.12.4	1100 and 5056 Rivets	3-29
3.12.5	7050 (E) Rivets	3-29
3.12.6	D/DD Rivets	3-29
3.13	HEAT TREATING EQUIPMENT	3-37
3.13.1	Air Furnaces/Ovens	3-38
3.13.2	Salt Bath Furnace	3-38
3.13.3	Field Test Instruments	3-39
3.13.4	Controlling, Monitoring, and Recording Equipment	3-39
3.13.5	TC	3-39
3.14	TEMPERATURE CONTROL AND UNIFORMITY TESTING	3-41
3.14.1	System Accuracy Test (SAT)	3-41
3.14.1.5	Modification Offset	3-42
3.14.2	TUS	3-42
3.14.2.2	Initial TUS Requirement	3-43
3.14.2.3	Periodic TUS Requirement	3-43
3.14.2.4	Annual TUS Requirement	3-43
3.14.3	TUS Procedure	3-44
3.14.3.1	Number of Required Thermocouples	3-44
3.14.3.2	Location of TUS Sensors	3-44
3.14.3.3	Qualified Working Zone	3-44
3.14.3.4	TUS Data Collection	3-44
3.14.4	Temperature Uniformity Pass/Fail Requirements	3-45
3.14.5	TUS Data and TUS Reports	3-45
3.14.5.2	TUS Survey Report Requirements	3-45
3.14.6	Failed TUS Procedures	3-46
3.14.6.2	Modification Offset	3-46
3.15	FABRICATION	3-47
3.16	FORMING SHEET METAL	3-47
3.16.1	General	3-47
3.16.2	Bending	3-48
3.16.3	Draw Forming	3-48
3.16.4	Stretch Forming	3-49
3.16.5	Hydraulic Press Forming	3-49
3.16.6	Drop Hammer Forming	3-49
3.16.7	Joggling	3-49
3.16.8	Hot-Forming	3-49
3.16.9	Spinning	3-49
3.16.10	Blanking and Shearing	3-50
3.16.11	Blanking	3-50
3.16.12	Riveting	3-50



## TABLE OF CONTENTS - CONTINUED

Chapter		Page
3.16.12.8	Rivet Selection . . . . .	3-52
3.16.13	Machining . . . . .	3-54
3.16.14	Cutting Tools for Machining Aluminum . . . . .	3-55
3.16.15	Turning . . . . .	3-55
3.16.16	Milling - Aluminum . . . . .	3-56
3.16.17	Shaping and Planing . . . . .	3-58
3.16.18	Drilling Aluminum Alloy . . . . .	3-61
3.16.19	Tapping . . . . .	3-66
3.16.20	Filing . . . . .	3-66
3.16.21	Reaming . . . . .	3-67
3.16.22	Sawing . . . . .	3-67
3.16.22.1	Band Saws . . . . .	3-67
3.16.22.2	Hack Saws . . . . .	3-68
3.16.22.3	Lubricants and Coolants . . . . .	3-68
3.16.23	Grinding . . . . .	3-68
3.16.23.2	Lubricants and Coolants . . . . .	3-68
3.16.24	Polishing . . . . .	3-68
3.16.25	Roughing . . . . .	3-68
3.16.26	Greasing or Oiling . . . . .	3-69
3.16.27	Buffing . . . . .	3-69
3.17	HARDNESS TESTING . . . . .	3-69
3.17.1	Brinell Hardness . . . . .	3-69
3.18	NON-DESTRUCTIVE TESTING/INSPECTION . . . . .	3-69
3.18.1	Anodizing Process for Inspection of Aluminum Alloy Parts . . . . .	3-69
3.18.2	Aluminum Alloy Effects on Scratches on Clad Aluminum Alloy . . . . .	3-69
3.18.3	Allowable Defects . . . . .	3-70
3.18.4	Harmful Scratches . . . . .	3-70
3.18.5	Inspection . . . . .	3-70
3.18.6	Test for Depth of Scratches . . . . .	3-70
3.19	DISPOSITION OF SCRATCHED SHEETS/PARTS . . . . .	3-71
3.19.1	Air Weapon Parts . . . . .	3-71
3.20	CLEANING OF ALUMINUM ALLOY SHEET (STOCK) . . . . .	3-71
3.20.1	Dry Cleaning Solvent . . . . .	3-71
3.20.2	Alkali Cleaning Solution . . . . .	3-71
3.20.3	Preparation . . . . .	3-71
3.20.4	Nitric-Hydrofluoric Acid Cleaning . . . . .	3-72
3.20.5	Corrosion Removal . . . . .	3-73
3.20.6	Chromate Conversion Coating . . . . .	3-73
3.20.7	Packaging, Packing and Storage of Aluminum Alloy Sheets . . . . .	3-75
3.20.8	Anodic Coatings for Aluminum . . . . .	3-75
4	MAGNESIUM ALLOYS . . . . .	4-1
4.1	CLASSIFICATION . . . . .	4-1
4.2	DEFINITIONS . . . . .	4-1
4.2.1	Hardness . . . . .	4-1
4.2.2	Tensile Strength . . . . .	4-1
4.2.3	Temper . . . . .	4-1
4.2.4	Shear Strength . . . . .	4-1
4.2.5	Elongation . . . . .	4-1
4.2.6	Physical Properties . . . . .	4-2
4.2.7	Chemical Properties . . . . .	4-2
4.2.8	Temper Designation System . . . . .	4-2
4.3	SAFETY REQUIREMENTS FOR HANDLING AND FABRICATION OF MAGNESIUM ALLOYS . . . . .	4-2



## TABLE OF CONTENTS - CONTINUED

Chapter		Page
4.3.1	Magnesium-Thorium Alloys (HK31, HM21, HM31, HZ32, ZH42, ZH62)	4-2
4.3.2	Safety Precautions for All Alloys (Including Fire Hazards)	4-3
4.3.3	Heat Treating Safety Practices	4-4
4.3.4	Identification of Alloy	4-6
4.4	HEAT TREATING MAGNESIUM ALLOYS - GENERAL	4-6
4.4.1	Precautions During Heating	4-6
4.4.2	Heat Treating Equipment	4-6
4.4.3	Heat Treatment Solution	4-7
4.4.4	Heat Treating Procedures	4-7
4.5	ALLOY GENERAL CHARACTERISTIC INFORMATION	4-8
5	TITANIUM AND TITANIUM ALLOYS	5-1
5.1	CLASSIFICATION	5-1
5.2	GENERAL	5-1
5.2.1	Military and Commercial Designations	5-1
5.2.2	Physical Properties	5-1
5.2.3	Mechanical Properties	5-1
5.2.4	Methods of Identification	5-1
5.2.5	Hardness Testing	5-1
5.2.6	Tensile Testing	5-1
5.2.7	Non-Destructive Testing	5-1
5.2.8	Fire Damage	5-1
5.3	HEAT TREATMENT - GENERAL	5-4
5.3.1	Furnaces	5-4
5.3.2	Hydrogen Embrittlement	5-5
5.3.3	Aging and Stress Relieving	5-5
5.4	FABRICATION	5-10
5.4.1	Forming Sheet Metal-General	5-10
5.4.2	Bending	5-10
5.4.3	Draw Forming	5-10
5.4.4	Hydraulic Press Forming	5-10
5.4.5	Stretch Forming	5-10
5.4.6	Drop-Hammer Forming	5-10
5.4.7	Joggling	5-10
5.4.8	Blanking and Shearing	5-11
5.4.9	Soldering	5-11
5.4.10	Riveting	5-11
5.5	MACHINING AND GRINDING	5-12
5.5.1	Machining	5-12
5.5.2	Turning	5-12
5.5.3	Milling	5-12
5.5.4	Drilling	5-13
5.5.5	Tapping	5-13
5.5.6	Reaming	5-13
5.5.7	Grinding	5-13
6	COPPER AND COPPER BASE ALLOYS	6-1
6.1	COPPER AND COPPER BASE ALLOYS	6-1
6.2	COPPER ALLOYING ELEMENTS	6-1
6.2.1	Zinc	6-1
6.2.2	Tin	6-1
6.2.3	Lead	6-1



## TABLE OF CONTENTS - CONTINUED

Chapter		Page
6.2.4	Aluminum . . . . .	6-1
6.2.5	Iron . . . . .	6-1
6.2.6	Phosphorous . . . . .	6-1
6.2.7	Nickel . . . . .	6-1
6.2.8	Silicon . . . . .	6-1
6.2.9	Beryllium . . . . .	6-1
6.2.10	Manganese . . . . .	6-1
6.3	CHEMICAL COMPOSITION . . . . .	6-1
6.4	HEAT TREATMENT AND NOT WORKING TEMPERATURE OF COPPER ALLOYS . . . . .	6-1
6.5	STRESS RELIEF OF COPPER ALLOYS . . . . .	6-2
6.5.1	Machining Copper and Copper Alloys . . . . .	6-2
6.5.2	Wrought-Copper-Beryllium Alloys . . . . .	6-2
6.6	HEAT TREATING PROCEDURES AND EQUIPMENT REQUIREMENTS . . . . .	6-2
6.6.1	Solution Heat Treatment Copper-Beryllium . . . . .	6-2
6.6.2	Precipitation or Age Hardening . . . . .	6-2
7	TOOL STEELS . . . . .	7-1
7.1	GENERAL . . . . .	7-1
7.2	ALLOYING ELEMENTS IN TOOL STEELS . . . . .	7-1
7.2.1	Carbon . . . . .	7-1
7.2.2	Chromium . . . . .	7-1
7.2.3	Cobalt . . . . .	7-1
7.2.4	Manganese . . . . .	7-1
7.2.5	Molybdenum . . . . .	7-1
7.2.6	Nickel . . . . .	7-1
7.2.7	Silicon . . . . .	7-1
7.2.8	Tungsten . . . . .	7-1
7.2.9	Vanadium . . . . .	7-1
7.3	SPECIFICATIONS . . . . .	7-1
7.4	CLASS DESIGNATIONS . . . . .	7-6
7.5	APPLICATIONS OF TOOL STEELS . . . . .	7-6
7.6	SELECTION OF MATERIAL FOR A CUTTING TOOL . . . . .	7-6
7.6.1	High Speed Cutting Tools . . . . .	7-7
7.6.2	High Speed Drills . . . . .	7-7
7.6.3	Material for Reamers . . . . .	7-7
7.6.4	Material for Taps . . . . .	7-7
7.6.5	Milling Cutters . . . . .	7-7
7.6.6	Punch and Die Material . . . . .	7-7
7.7	HEAT TREAT DATA . . . . .	7-7
7.8	DISTORTION IN TOOL STEELS . . . . .	7-7
8	TESTING AND INSPECTION HARDNESS TESTING . . . . .	8-1
8.1	GENERAL . . . . .	8-1
8.2	METHODS OF HARDNESS TESTING . . . . .	8-1
8.2.1	Brinell Hardness Test . . . . .	8-1
8.2.2	Making The Brinell Test . . . . .	8-1
8.3	ROCKWELL HARDNESS TEST . . . . .	8-1
8.3.1	Rockwell Machine/Tester . . . . .	8-2
8.3.2	Rockwell Test Procedure . . . . .	8-2
8.4	VICKERS PYRAMID HARDNESS TEST . . . . .	8-11
8.4.1	Vickers Tester . . . . .	8-11
8.4.2	Making The Vickers Test . . . . .	8-12



## TABLE OF CONTENTS - CONTINUED

Chapter		Page
8.5	SHORE SCLEROSCOPE HARDNESS TEST .....	8-14
8.5.1	The Scleroscope Tester .....	8-14
8.6	TESTING WITH THE SCLEROSCOPE .....	8-15
8.6.1	Tensile Testing .....	8-15
8.7	DECARBURIZATION MEASUREMENT .....	8-16
8.8	HARDNESS METHOD .....	8-16
8.8.1	Taper or Step Grind .....	8-16
8.8.2	File Method .....	8-17
8.9	NONDESTRUCTIVE INSPECTION METHODS .....	8-21
8.9.1	Radiographic Inspection .....	8-21
8.9.2	Penetrant Inspection .....	8-21
8.9.3	Ultrasonic Inspection .....	8-21
8.9.4	Magnetic Particle Inspection .....	8-21
8.9.5	Eddy Current Inspection .....	8-21
8.10	CHEMICAL ANALYSIS .....	8-21
8.11	SPECTROCHEMICAL ANALYSIS .....	8-22
9	HEAT TREATMENT .....	9-1
9.1	GENERAL .....	9-1
9.1.1	Cold Oven .....	9-1
9.2	SPECIAL HEAT TREATMENT INFORMATION .....	9-1
9.2.1	Cadmium Plated Parts .....	9-1
9.3	TINT TEST FOR DETERMINING COATING REMOVAL FROM NICKEL BASE AND COBALT BASE ALLOYS .....	9-1
9.4	TITANIUM ALLOY PARTS .....	9-3
9.4.1	General .....	9-3
9.5	SOLUTION, STABILIZATION, OR PRECIPITATION HEAT TREATMENT .....	9-3
9.5.1	General .....	9-3
9.5.2	Stabilization Heat Treatment .....	9-4
9.5.3	Precipitation Heat Treatment .....	9-4
9.5.4	Sequence of Solution, Stabilization, or Precipitation Heat Treatment .....	9-4
9.5.5	Air Cool and Air Cool or Faster .....	9-4
9.5.5.1	Air Cool .....	9-4
9.5.5.2	Air Cool or Faster .....	9-4
9.6	CYCLE NUMBER, TYPE OF HEAT TREATMENT, SPOP NUMBER, AND MAXIMUM TEMPERATURE .....	9-4
9.6.1	Cycle 20 (SPOP 480) .....	9-4
9.6.2	Cycle 21 (SPOP 481) .....	9-5
9.6.3	Cycle 12 (SPOP 471) .....	9-5
9.6.4	Cycle 12A (SPOP 465) .....	9-6
9.6.5	Cycle 15 (SPOP 468) .....	9-6
9.6.6	Cycle 17 (SPOP 470) .....	9-6
9.6.7	Cycle 101 (SPOP 761) .....	9-7
9.6.8	Cycle 102 (SPOP 762) .....	9-7
9.6.9	Cycle 103 (SPOP 763) .....	9-8
9.6.10	Cycle 104 (SPOP 764) .....	9-8
9.6.11	Cycle 105 (SPOP 765) .....	9-8
9.6.12	Cycle 106 (SPOP 766) .....	9-9
9.6.13	Cycle 107 (SPOP 767) .....	9-9
9.7	STRESS-RELIEF AFTER WELDING .....	9-10
9.7.1	General .....	9-10
9.8	CYCLE NUMBER, SPOP NUMBER, AND MAXIMUM TEMPERATURE .....	9-10
9.8.1	Cycle 1 (SPOP 455-1) .....	9-10
9.8.2	Cycle 1A (SPOP 455-2) .....	9-10



## TABLE OF CONTENTS - CONTINUED

Chapter		Page
9.8.3	Cycle 2 (SPOP 456) . . . . .	9-11
9.8.4	Cycle 3 (SPOP 457) . . . . .	9-11
9.8.5	Cycle 4 (SPOP 458-1) . . . . .	9-11
9.8.6	Cycle 4A (SPOP 458-2) . . . . .	9-11
9.8.7	Cycle 5 (SPOP 459-1) . . . . .	9-11
9.8.8	Cycle 5A (SPOP 459-2) . . . . .	9-11
9.8.9	Cycle 6 (SPOP 460-1) . . . . .	9-12
9.8.10	Cycle 6A (SPOP 460-2) . . . . .	9-12
9.8.11	Cycle 7 (SPOP 461) . . . . .	9-12
9.8.12	CYCLE 8 (SPOP 455-3) . . . . .	9-12
9.8.13	Cycle 9 (SPOP 459-3) . . . . .	9-12
9.8.14	Cycle 11 (SPOP 464) . . . . .	9-13
9.8.15	Cycle 13 (SPOP 466) . . . . .	9-13
9.8.16	Cycle 14 (SPOP 467) . . . . .	9-13
9.8.17	Cycle 22 (SPOP 482) . . . . .	9-13
9.9	LOCAL STRESS-RELIEF . . . . .	9-14
9.9.1	General . . . . .	9-14
9.10	DESCRIPTION OF METHODS . . . . .	9-15
9.10.1	Resistance . . . . .	9-15
9.10.2	Induction . . . . .	9-15
9.10.3	Quartz Lamp . . . . .	9-15
9.10.4	Radiant Gas Burner . . . . .	9-15
APPENDIX A	SUPPLEMENTAL DATA . . . . .	A-1
A.1	THE FOLLOWING IS SUPPLEMENTAL DATA FOR THIS MANUAL . . . . .	A-1
GLOSSARY	. . . . .	Glossary 1



## LIST OF ILLUSTRATIONS

Number	Title	Page
2-1	Number and Distribution of Thermocouples . . . . .	2-14
2-2	Stretch Forming . . . . .	2-82
2-3	Surface Roughness . . . . .	2-91
2-4	Surface Roughness and Lay Symbols . . . . .	2-92
3-1	Head to Alloy Identification Method . . . . .	3-30
3-2	Welded Thermocouple Wire . . . . .	3-39
3-3	Twisted Thermocouple Wire . . . . .	3-40
3-4	Rivet ID Information . . . . .	3-51
3-5	Drill Designs and Recommended Cutting Angles . . . . .	3-65
4-1	Typical Dust Collectors for Magnesium . . . . .	4-10
8-1	Brinell Hardness Tester . . . . .	8-9
8-2	Rockwell Hardness Tester . . . . .	8-10
8-3	Attachments for Rockwell Tester . . . . .	8-11
8-4	Vickers Pyramid Hardness Tester . . . . .	8-13
8-5	Standard Pyramid Diamond Indentor . . . . .	8-14
8-6	Shore Scleroscope . . . . .	8-15
8-7	Test Specimens . . . . .	8-18
A-1	Bend Set Back Chart . . . . .	A-51

## LIST OF TABLES

Number	Title	Page
2-1	Soaking Periods for Hardening Normalizing and Annealing (Plain Carbon Steel) . . . . .	2-15
2-2	Specification Cross Reference . . . . .	2-17
2-3	Cutting Speeds and Feeds for SAE 1112 Using Standard High Speed Tools . . . . .	2-62
2-4	Machinability Rating of Various Metals . . . . .	2-63
2-5	Conversion of SFM to RPM (10-110) . . . . .	2-65
2-6	Conversion of SFM to RPM (120-300) . . . . .	2-66
2-7	Tool Correction Chart . . . . .	2-67
2-8	General Machining Comparison of Corrosion Resisting Steel to Free Machining Screw Stock B1112 . . . . .	2-68
2-9	Suggested Cutting Speeds and Feeds . . . . .	2-68
2-10	Tool Angles - Turning . . . . .	2-69
2-11	Suggested Milling Cutting Speeds and Feeds . . . . .	2-70
2-12	Suggested Tool Angles - Milling . . . . .	2-70
2-13	Drilling Speeds for Corrosion Resisting Steel . . . . .	2-72
2-14	Tapping Allowances (Hole Size to Screw Size) . . . . .	2-73
2-15	Cold Bend Radii (Inside) Carbon/Low Alloy Steels . . . . .	2-83
2-16	Cold Bend Radii (Inside) Corrosion Resistant Steel Alloys . . . . .	2-83
2-17	Forging Temperature Ranges For Corrosion Resistant Steel . . . . .	2-83
2-18	Galvanic Series of Metals and Alloys . . . . .	2-90
3-1	Designations for Alloy Groups . . . . .	3-1
3-2	Aluminum Alloy Designation and Conversions to 4 Digit System . . . . .	3-1
3-3	Aluminum Alloy Material Specifications . . . . .	3-4
3-4	Chemical Composition Nominal and General Use Data . . . . .	3-11
3-5	Mechanical Properties, Aluminum - Typical . . . . .	3-14
3-6	Physical Properties - Standard Aluminum Alloys . . . . .	3-17
3-7	Properties of Common Aluminum Alloys - Minimum . . . . .	3-21
3-8	Solution Heat Treating Temperatures for Wrought Aluminum Alloys . . . . .	3-30
3-9	Solution Heat Treat Soaking Times for Wrought Aluminum Alloys . . . . .	3-31



## LIST OF TABLES - CONTINUED

Number	Title	Page
3-10	Solution Heat Treating Temperatures and Soak Times for Cast Aluminum Alloys . . . . .	3-31
3-11	Maximum Quench Delay Times . . . . .	3-32
3-12	Quenching Temperature for Aluminum Forgings and Castings . . . . .	3-32
3-13	Refrigeration Requirements . . . . .	3-33
3-14	Precipitation Heat Treating (Aging) Process for Wrought Aluminum Alloys . . . . .	3-33
3-15	Precipitation Heat Treating (Aging) Process for Cast Aluminum Alloys . . . . .	3-35
3-16	Annealing - Wrought Aluminum Alloys . . . . .	3-37
3-17	Annealing - Cast Aluminum Alloys . . . . .	3-37
3-18	Re-Solution Heat Treatment of Alclad Alloys . . . . .	3-37
3-19	Temperature Uniformity Allowance for Heat Treat Operations . . . . .	3-46
3-20	Expendable Base Metal Thermocouples . . . . .	3-47
3-21	Oven/Furnace Instrumentation Type, Sensor Requirements . . . . .	3-47
3-22	Maximum Accumulative Reheat Times for Hot Forming Heat Treatable Alloys at Different Temperatures . . . . .	3-50
3-23	General Rivet (Alum) Identification Chart . . . . .	3-52
3-24	General Aluminum Rivet Selection Chart (Rivet Alloy vs Assembly Alloy) . . . . .	3-54
3-25	Shear Strength of Protruding and Flush Head Aluminum Alloy Rivets, Inch Pounds . . . . .	3-56
3-26	Bearing Properties, Typical, of Aluminum Alloy Plates and Shapes . . . . .	3-58
3-27	Standard Rivet Hole Sizes with Corresponding Shear and Bearing Areas for Cold Driven Aluminum Alloy Rivets . . . . .	3-60
3-28	Turning Speeds and Feeds . . . . .	3-62
3-29	Tool Angles - Turning . . . . .	3-62
3-30	Milling - Speeds and Feeds . . . . .	3-63
3-31	Tool Angles - Milling . . . . .	3-63
3-32	Shaping and Planing-Speeds and Feeds . . . . .	3-63
3-33	Shaping Tool Angles . . . . .	3-63
3-34	Thread Constant for Various Standard Thread Forms . . . . .	3-66
4-1	Cross-Reference, Alloy Designation to Specifications . . . . .	4-11
4-2	Alloy Designation Cross-Reference . . . . .	4-13
4-3	Chemical Properties of Magnesium Alloys . . . . .	4-14
4-4	Mechanical Properties Magnesium Extrusions and Forgings at Room Temperature - Typical . . . . .	4-16
4-5	Mechanical Properties of Magnesium Alloy Sheet and Plate at Room Temperature - Typical . . . . .	4-18
4-6	Mechanical Properties of Magnesium Alloy Castings at Room Temperatures . . . . .	4-20
4-7	Physical Properties Magnesium Alloy at 68 °F . . . . .	4-21
4-8	Solution Heat Treating Temperatures and Holding Times . . . . .	4-22
4-9	Artificial Aging (Precipitation Treatment) . . . . .	4-22
5-1	Specification Cross Reference Titanium Alloys . . . . .	5-2
5-2	Nominal Mechanical Properties at Room Temperature . . . . .	5-6
5-3	Heat Treat, Stress Relief and Annealing Temperatures and Times . . . . .	5-8
5-4	Recommended Minimum Constant Current Line Drive (CCLD) Bend Radii . . . . .	5-11
5-5	Turning Speeds for Titanium Alloys . . . . .	5-14
5-6	Tool Angles for Alloys . . . . .	5-14
5-7	Speeds and Feeds for Milling . . . . .	5-14
5-8	Angles for Tool Grinding . . . . .	5-15
6-1	Chemical Composition by Trade Name . . . . .	6-3
6-2	Hot Working and Annealing Temperatures for Copper and Wrought Copper Alloys . . . . .	6-9
6-3	Typical Stress-Relief Treatments for Certain Copper Alloys . . . . .	6-10
6-4	Standard Machinability Rating of Copper Alloys . . . . .	6-11
6-5	Typical Engineering Properties . . . . .	6-12
6-6	Age Hardening Time-Temperature Conditions and Material Temper Designations . . . . .	6-12
7-1	Tool Steel Specifications . . . . .	7-2
7-2	Chemical Composition, Tool Steel . . . . .	7-4
7-3	Tool Steel Selection . . . . .	7-6
7-4	Tool Steel Hardening and Tempering Temperatures . . . . .	7-6
7-5	Forging, Normalizing and Annealing Treatments of Tool and Die Steels . . . . .	7-8



## LIST OF TABLES - CONTINUED

Number	Title	Page
7-6	Thermal Treatment for Hardening and Tempering Tool Steel - General	7-10
7-7	Comparison of Tool Steel Properties	7-12
8-1	Hardness Conversion Chart for Hardened Steel and Hard Alloys Scale	8-3
8-2	Hardness Conversion Chart for Unhardened Steel, Steel of Soft Temper, Grey and Malleable Cast Iron and Most Non-Ferrous Metal 100-3000 Load	8-4
8-3	Hardness Conversion Chart for Unhardened Steel, Steel of Soft Temper, Grey and Malleable Cast Iron and Most Non-Ferrous Metal 100-500 Load	8-6
8-4	Rockwell Scales, Loads and Prefix Letters	8-16
8-5	Approximate Hardness - Tensile Strength Relationship of Carbon and Low Alloy Steels	8-19
9-1	Typical Heat Treatment Application	9-2
9-2	Cross-Index for Solution, Stabilization, or Precipitation Heat Treatments	9-9
9-3	Cross-Index for Stress-Relief Heat Treatments	9-14
A-1	Chemical Symbols	A-1
A-2	Decimal Equivalents	A-2
A-3	Engineering Conversion Factors	A-6
A-4	Table of Weights - Aluminum and Aluminum Alloy (Length)	A-8
A-5	Table of Weights - Aluminum and Aluminum Alloy (Area)	A-11
A-6	Table of Weights - Brass	A-11
A-7	Table of Weights - Brass (Area)	A-17
A-8	Table of Weights - Brass Shim Stock	A-18
A-9	Table of Weights - Bronze (Length)	A-18
A-10	Table of Weights - Bronze (Area)	A-19
A-11	Table of Weights - Copper	A-20
A-12	Table Of Weights - Copper (Area)	A-24
A-13	Table of Weights - Copper Wire	A-24
A-14	Table of Weights - Iron	A-25
A-15	Table of Weights - Iron (Area)	A-25
A-16	Table of Weights - Lead	A-26
A-17	Table of Weights - Magnesium and Magnesium Alloy	A-26
A-18	Table of Weights - Magnesium and Magnesium Alloy (Area)	A-27
A-19	Table of Weights - Nickel Chromium Iron Alloy (Inconel)	A-28
A-20	Table of Weights - Nickel Chromium Iron Alloy (Inconel) (Area)	A-29
A-21	Table of Weights - Nickel Copper Alloy	A-29
A-22	Table of Weights - Nickel Copper Alloy (Area)	A-30
A-23	Table of Weights - Steel	A-30
A-24	Table of Weights - Steel (Area)	A-39
A-25	Table of Weights - Steel (Length)	A-39
A-26	Table of Weights - Zinc	A-40
A-27	Temperature Conversion Chart (-459.4 - 75)	A-41
A-28	Temperature Conversion Chart (76 - 750)	A-42
A-29	Temperature Conversion Chart (751 - 2000)	A-43
A-30	Temperature Conversion Chart (2001 - 3000)	A-45
A-31	Standard Bend Radii for 90° Cold Forming-Flat Sheet (0.008 - 0.050)	A-46
A-32	Standard Bend Radii for 90° Cold Forming-Flat Sheet (0.063 - 0.250)	A-48
A-33	Metal Bending and Bend Radii Bend Allowances Sheet Metal Bend Allowances per Degree of Bend Aluminum Alloys	A-50
A-34	Comparative Table of Standard Gages	A-52
A-35	Melting Points Approximate	A-53



## INTRODUCTION

### 1 PURPOSE.

This is one of a series of technical or engineering technical manuals prepared to assist personnel engaged in the maintenance and repair of Aerospace Weapon Systems and Supporting Equipment Aerospace Ground Equipment (AGE). Army Personnel: Wherever the text of this manual refers to other Technical Orders (TO's) for supporting information, refer to comparable Army documents.

### 2 SCOPE.

This manual consists of the following chapters:

<a href="#">Chapter 1</a>	Introduction
<a href="#">Chapter 2</a>	Ferrous (Steel) Alloys
<a href="#">Chapter 3</a>	Aluminum Alloys
<a href="#">Chapter 4</a>	Magnesium Alloys
<a href="#">Chapter 5</a>	Titanium and Titanium Alloys
<a href="#">Chapter 6</a>	Copper and Copper Base Alloys
<a href="#">Chapter 7</a>	Tool Steels
<a href="#">Chapter 8</a>	Testing and Inspection, Hardness Testing
<a href="#">Chapter 9</a>	Heat Treatment
<a href="#">Appendix A</a>	Supplemental Data

### 3 ABBREVIATIONS.

All abbreviations used in this manual are shown in the list of abbreviations below. Standard abbreviations are in accordance with ASME Y14.38, Abbreviations and Acronyms for Use in Product Definition and Related Documents.

°C	degree Celsius
°F	degree Fahrenheit
AC	Air-Cooled
ACS	Annealed Copper Standard
AEC	Atomic Energy Commission
AF	Air Force
AFTO	Air Force Technical Order
AGE	Aerospace Ground Equipment
AMS	Aeronautical Material Specification
AWS	American Welding Society
BHN	Brinell Hardness Number
BTU	British Thermal Unit
CCLD	Constant Current Line Drive
CD	Cold Drawn
CID	Commercial Item Description
DLA	Defense Logistics Agency
DoD	Department of Defense
ESDS	Electrostatic Discharge Sensitive
ETIMS	Enhanced Technical Information Management System
FPM	Foot per minute
GSE	Ground Support Equipment
HCI	Hardness Critical Items



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

IACS	International Annealed Copper Standard
KSI	Kips per Square Inch
MFTO	Metal Fabrication and Technologies Office
NCOIC	Non Commissioned Officer in Charge
NDI	Non-Destructive Inspection
No.	Number
NSN	National Stock Number
OSHA	Occupational Safety and Health Administration
PPE	Personal Protective Equipment
PRE	Precipitation
PSI	Pound-force per Square Inch
PSIG	Pound-force per Square Inch, Gauge
PWA	Printed Wiring Assembly
RAM	Random-Access Memory
RMS	Root Mean Square
RPM	Revolutions Per Minute
S/m	Siemens/meter
SAE	Society of Automotive Engineers
SAT	System Accuracy Test
SDS	Safety Data Sheet
SFM	Surface Feet per Minute
SOL	Solution
ST	Surface Temperature
STA	Stabilization
STR	Stress-Relief
TC	Thermocouple
TO	Technical Order
TOMA	Technical Order Management Agency
TUS	Temperature Uniformity Survey

**4** **RELATED PUBLICATIONS.**

**NOTE**

When searching technical order (TO) numbers in the Enhanced Technical Information Management System (ETIMS) catalog, please use the wildcard (\*) after typing in the TO number. Many TOs are not available in paper format, (i.e., digital (WA-1) or Compact Disk (CD-1)). This ensures TOs in all media formats will populate the search.

The following publications contain information in support of this technical manual.

**List of Related Publications**

Number	Title
ASME Y14.38	Abbreviations and Acronyms for Use in Product Definition and Related Documents
DoDI 5330.03	Single Manager of DoD Document Services
TO 00-5-1	AF Technical Order System
TO 00-25-195	AF Technical Order System Source, Maintenance, and Recoverability Coding of Air Force Weapons, Systems, and Equipments
TO 00-25-234	General Shop Practice Requirements for the Repair, Maintenance, and Test of Electrical Equipment
TO 00-25-252	Intermediate And Depot Level Maintenance Instructions - Aeronautical Equipment Welding



### List of Related Publications - Continued

Number	Title
TO 00-85A-23-1	Packaging, Packing, And Storage Of Aluminum Alloy Sheet And Plate
TO 1-1-2	Fiberglass Airborne Radomes, Maintenance Repair And Electrical Requirements
TO 1-1-8	Application And Removal Of Organic Coatings, Aerospace And Non-Aerospace Equipment
TO 1-1A-1	Engineering Handbook Series For Aircraft Repair General Manual For Structural Repair (Atos)
TO 1-1A-8	Aircraft And Missile Repair - Structural Hardware
TO 1-1A-9	Aerospace Metals - General Data And Usage Factors
TO 33B-1-1	Nondestructive Inspection Methods, Basic Theory (Atos)
TO 33B-1-2	Nondestructive Inspection - General Procedures And Process Controls (Atos)
TO 42C2-1-7	Metal Treatments - Electrodeposition Of Metals And Metal Surface Treatments To Meet Air Force Maintenance Requirements


### 5 RECORD OF APPLICABLE TIME COMPLIANCE TECHNICAL ORDERS (TCTOS).


#### List of Time Compliance Technical Orders

TCTO Number	TCTO Title	TCTO Date
None		


### 6 HARDNESS CRITICAL ITEMS (HCI).




The HCI symbol () establishes special requirements limiting changes and substitutions and that the specific parts listed must be used to ensure hardness is not degraded.

If included, items with nuclear survivability requirements are marked with the HCI symbol (). All changes to, or proposed substitutions of, HCIs must be approved by the acquiring activity.

### 7 ELECTROSTATIC DISCHARGE SENSITIVE (ESDS) ITEMS.



All ESDS parts shall be handled in accordance with the ESDS device handling procedures in TO 00-25-234.

If included, items containing ESDS parts are marked with the ESDS symbol ()

### 8 IMPROVEMENT REPORTS.

Recommended changes to this manual shall be submitted in accordance with TO 00-5-1.



## SAFETY SUMMARY

### 9 GENERAL SAFETY INSTRUCTIONS.

This manual describes physical and/or chemical processes which may cause injury or death to personnel, or damage to equipment, if not properly followed. This safety summary includes general safety precautions and instructions that must be understood and applied during operation and maintenance to ensure personnel safety and protection of equipment. Prior to performing any specific task, the WARNINGS, CAUTIONS, and NOTES included in that task shall be reviewed and understood.

### 10 WARNINGS, CAUTIONS, AND NOTES.

WARNINGS and CAUTIONS are used in this manual to highlight operating or maintenance procedures, practices, conditions, or statements which are considered essential to protection of personnel (WARNING) or equipment (CAUTION). WARNINGS and CAUTIONS immediately precede the step or procedure to which they apply. WARNINGS and CAUTIONS consist of four parts: heading (WARNING, CAUTION, or icon), a statement of the hazard, minimum precautions, and possible results if disregarded. NOTES are used in this manual to highlight operating or maintenance procedures, practices, conditions, or statements which are not essential to protection of personnel or equipment. NOTES may precede or follow the step or procedure, depending upon the information to be highlighted. The headings used and their definitions are as follows:

#### **WARNING**

Highlights an essential operating or maintenance procedure, practice, condition, statement, etc. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

#### **CAUTION**

Highlights an essential operating or maintenance procedure, practice, condition, statement, etc. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

#### **NOTE**

Highlights an essential operating or maintenance procedure, condition, or statement.

### 11 HAZARDOUS MATERIALS (HAZMAT) WARNINGS.

HAZMAT Warnings are provided through use of the following Hazard Symbols. Consult the HAZMAT DESCRIPTION or Safety Data Sheet (SDS) (Occupational Safety and Health Administration (OSHA) Form 20 or equivalent) for specific information on hazards, effects, and protective equipment requirements. If you do not have an SDS for the material involved, contact your supervisor, or the base Safety or Bioenvironmental Engineering Offices.

11.1 HAZMAT Icons. The following icons are used throughout this Air Force technical manual to indicate the use of hazardous materials:



The symbol of drops of liquid onto a hand shows that the material will cause burns or irritation of skin and tissue.



The symbol of a person wearing goggles shows that the material will injure eyes.



The rapidly expanding symbol shows that the material may explode if subjected to high temperature, sources of ignition, or high pressure.





The symbol of a flame shows that the material can ignite and burn.



The symbol of a skull and crossbones shows that the material is poisonous or a danger to life.



The symbol of a human figure in a cloud shows that the material gives off vapors that are a danger to life or health.



The symbol of a liquid entering the mouth shows that eating or drinking this material can cause a health hazard.



The hand symbol shows a material that can irritate the skin or enter the body through the skin and cause a health hazard.

**11.2 HAZMAT Description.** The following detailed HAZMAT warnings pertain to materials or substances used in connection with procedures called out or described in this technical manual. Use these advisory warnings and their associated precautions in conjunction with the current SDS for each material or substance. If there is conflict between this safety summary and the SDS, the SDS takes precedence.



ALKALINE WATER BASE CLEANING COMPOUND, MIL-PRF-87937

1

Liquid alkaline cleaner is an eye, skin and respiratory irritant. Ingestion may cause digestive tract irritation. Do not ingest. Appropriate skin and eye protection must be worn.



CORROSION REMOVING COMPOUND, SAE AMS-1640

2

Corrosion removing compound is corrosive to the eyes and skin. Causes irritation to the nose and throat, and is hazardous if ingested. Avoid contact with skin and eyes. Use in a well ventilated area and avoid breathing vapors. Keep container tightly closed when not in use. Appropriate skin and eye protection must be worn.



DRY CLEANING SOLVENT, MIL-PRF-680

3

Dry Cleaning Solvent is flammable and may contain the following hazardous chemicals: Naphtha (petroleum), Alkanes and/or C9 - C12 hydrocarbons which are skin and eye irritants and respiratory depressants. Exposure can occur through inhalation, ingestion, or skin and eye contact. May be fatal if swallowed. Avoid repeated and prolonged contact. Use with adequate ventilation. Do not ingest. Appropriate skin and eye protection must be worn.





IRIDITE NO. 14-2 CHEMICAL FILM, MIL-DTL-5541

4

Iridite Chemical Film is a severe eye, skin and respiratory irritant. It may be toxic if ingested. Chemical film materials are strongly oxidizing and present a potential fire and explosion hazard in contact with flammable materials. Avoid repeated or prolonged exposure. Keep off of skin, out of eyes and avoid breathing vapors. Appropriate skin, body, and eye protection must be worn. If spray applicators are used, wear a respirator to prevent inhalation of the atomized solution. Avoid contact with organic materials. Do not dispose of in same container as combustible materials. Do not eat, drink, or smoke when using this product. Wash exposed areas thoroughly with soap and water. Thoroughly wash all materials used to apply or remove the Iridite Solution before allowing them to dry or discard them. If allowed to dry without being washed, they may constitute a fire hazard.



METHYL ETHYL KETONE, ASTM D740

5

Methyl Ethyl Ketone is a highly flammable liquid and vapor. Harmful or fatal if swallowed. Harmful if inhaled or absorbed through the skin. Causes skin and eye irritation. Avoid repeated and prolonged contact. Use with adequate ventilation. Appropriate skin and eye protection must be worn. Do not ingest. Keep away from heat, spark, and flames.



BORON TRIFLUORIDE

6

Boron trifluoride is a colorless gas with a pungent odor. It is toxic by inhalation. It is soluble in water and slowly hydrolyzed by cold water to give off hydrofluoric acid, a corrosive material. Its vapors are heavier than air. Prolonged exposure of the containers to fire or heat may result in their violent rupturing and rocketing.



ZINC CHROMATE PRIMER, TT-P-1757

7

Zinc Chromate Primer is a flammable liquid and vapor. It may cause eye, skin and respiratory tract infection. Use only in well ventilated areas. Do not ingest. Appropriate skin and eye protection must be worn and respiratory protection may also be needed. Contact lenses should not be worn. Keep away from heat, spark, and flames.



SOLDER

8

Solder is toxic and a skin, eye and respiratory irritant. Harmful if swallowed. Danger of serious damage to health by prolonged exposure through inhalation. Avoid contact with eyes, skin and clothing. Do not ingest. Use only in well vented areas. Appropriate skin and eye protection must be worn. Respirator not required if ventilation is sufficient to remove smoke from soldering process. Wash thoroughly after contact, before eating, and at the end of the work period. Failure to comply could result in injury to, or death of, personnel or long term health hazards.





CADMIUM PLATING, AMS-QQ-P-416

9

Cadmium Plating is toxic and a skin, eye and respiratory irritant. Harmful if swallowed. Danger of serious damage to health by prolonged exposure through inhalation. Avoid contact with eyes, skin and clothing. Do not ingest. Use only in well vented areas. Appropriate skin and eye protection must be worn. Respirator not required if ventilation is sufficient to remove smoke from soldering process. Wash thoroughly after contact, before eating, and at the end of the work period. Failure to comply could result in injury to, or death of, personnel or long term health hazards.



ZINC PLATING, QQ-Z-325

10

Zinc Plating is toxic and a skin, eye and respiratory irritant. Harmful if swallowed. Danger of serious damage to health by prolonged exposure through inhalation. Avoid contact with eyes, skin and clothing. Do not ingest. Use only in well vented areas. Appropriate skin and eye protection must be worn. Respirator not required if ventilation is sufficient to remove smoke from soldering process. Wash thoroughly after contact, before eating, and at the end of the work period. Failure to comply could result in injury to, or death of, personnel or long term health hazards.



NICKEL PLATING, QQ-N-290

11

Nickel Plating is toxic and a skin, eye and respiratory irritant. Harmful if swallowed. Danger of serious damage to health by prolonged exposure through inhalation. Avoid contact with eyes, skin and clothing. Do not ingest. Use only in well vented areas. Appropriate skin and eye protection must be worn. Respirator not required if ventilation is sufficient to remove smoke from soldering process. Wash thoroughly after contact, before eating, and at the end of the work period. Failure to comply could result in injury to, or death of, personnel or long term health hazards.



CHROMIUM PLATING, QQ-C-320

12

Chromium Plating is toxic and a skin, eye and respiratory irritant. Harmful if swallowed. Danger of serious damage to health by prolonged exposure through inhalation. Avoid contact with eyes, skin and clothing. Do not ingest. Use only in well vented areas. Appropriate skin and eye protection must be worn. Respirator not required if ventilation is sufficient to remove smoke from soldering process. Wash thoroughly after contact, before eating, and at the end of the work period. Failure to comply could result in injury to, or death of, personnel or long term health hazards.



TIN PLATING, QQ-T-425

13

Tin Plating is toxic and a skin, eye and respiratory irritant. Harmful if swallowed. Danger of serious damage to health by prolonged exposure through inhalation. Avoid contact with eyes, skin and clothing. Do not ingest. Use only in well vented areas. Appropriate skin and eye protection must be worn. Respirator not required if ventilation is sufficient to remove smoke from soldering process. Wash thoroughly after contact, before eating, and at the end of the work period. Failure to comply could result in injury to, or death of, personnel or long term health hazards.





PHOSPHATE COATING, MIL-P-16232

14

Phosphate Coating is toxic and a skin, eye and respiratory irritant. Harmful if swallowed. Danger of serious damage to health by prolonged exposure through inhalation. Avoid contact with eyes, skin and clothing. Do not ingest. Use only in well vented areas. Appropriate skin and eye protection must be worn. Respirator not required if ventilation is sufficient to remove smoke from soldering process. Wash thoroughly after contact, before eating, and at the end of the work period. Failure to comply could result in injury to, or death of, personnel or long term health hazards.



SILVER PLATING, QQ-S-635

15

Silver Plating is toxic and a skin, eye and respiratory irritant. Harmful if swallowed. Danger of serious damage to health by prolonged exposure through inhalation. Avoid contact with eyes, skin and clothing. Do not ingest. Use only in well vented areas. Appropriate skin and eye protection must be worn. Respirator not required if ventilation is sufficient to remove smoke from soldering process. Wash thoroughly after contact, before eating, and at the end of the work period. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

## 12 SAFETY PRECAUTIONS.

The following safety precautions shall be observed while performing procedures in this manual.

- Dangerous voltages are present at system connectors. Ensure power is OFF prior to connecting or disconnecting cables.
- Do not wear metal frame glasses, rings, watches, or other metal jewelry while working on electronic equipment.
- Some cleaning materials specified herein are flammable and/or toxic. Keep away from open flame or other ignition sources. Provide adequate ventilation and avoid skin/eye exposure.
- Cleaning with compressed air can create airborne particles that may enter eyes or penetrate skin. Pressure shall not exceed 30 Pound-force per Square Inch, Gauge (PSIG). Wear goggles. Do not direct compressed air against skin.



## CHAPTER 1 INTRODUCTION

### 1.1 INTRODUCTION.

This is one of a series of technical or engineering technical manuals prepared to assist personnel engaged in the maintenance and repair of Aerospace Weapon Systems and Supporting Equipment Aerospace Ground Equipment (AGE). Army Personnel: Wherever the text of this manual refers to other Technical Orders (TOs) for supporting information, refer to comparable Army documents.

1.1.1 General Information. This technical manual provides precise data on specific metals to assist in selection, usage and processing for fabrication and repair. It includes such data as specification cross reference; approved designation system for alloys and tempers; temperatures and other controls for heat treatments; mechanical and physical properties processing instructions for basic corrosion prevention; forming characteristics; and other information required for general aerospace weapon system repair. Procedures for general foundry practice, sand control, gating and risering of both ferrous and non-ferrous castings may be obtained from available commercial handbooks and/or publications. Due to the many types, grades, diversified uses and new developments of metal products, it may not include all data required in some instances and further study and citation of this data will be required.

1.1.2 Instructions. The information/instruction contained herein are for general use. If a conflict exists between this technical manual and the specific technical manual(s) or other approved data for a particular weapon, end item, equipment, etc., the data applicable to the specific item(s) will govern in all cases.

1.1.2.1 The use of “shall”, “will”, “should” and “may” in this technical manual is as follows:

- a. Whenever the word “shall” appears, it shall be interpreted to mean that the requirements are binding.
- b. The words “will”, “should” and “may”, shall be interpreted as non-mandatory provisions.
- c. The word “will” is used to express declaration of purpose.
- d. The word “should” is used to express non-mandatory desired or preferred method of accomplishment.
- e. The word “may” is used to express an acceptable or suggested means of accomplishment.

### 1.2 WELDING.

Information on welding aerospace metals is contained in NAVAIR 01-1A-34, TO 00-25-252, TC 9-238.







## CHAPTER 2

### FERROUS (STEEL) ALLOYS

#### 2.1 CLASSIFICATION.

**2.1.1 Society of Automotive Engineers (SAE) Numbering System.** A numeral index system is used to identify the compositions of the SAE steels, which makes it possible to use numerals that are partially descriptive of the composition of material covered by such numbers. The first digit indicates the type to which the steel belongs; for example “1” indicates a carbon steel; “2” a nickel steel; and “3” a nickel chromium steel. In the case of the simple alloy steels, the second digit generally indicates the approximate percentage of the predominant alloying element. Usually the last two or three digits indicate the approximate average carbon content in “points” or hundredths of percent. Thus “2340” indicates a nickel steel of approximately 3 percent nickel (3.25 to 3.75) and 0.40 percent carbon (0.38 to 0.43). In some instances, in order to avoid confusion, it has been found necessary to depart from this system of identifying the approximate alloy composition of a steel by varying the second and third digits of the number. An instance of such departure is the steel numbers selected for several of the corrosion and heat resisting alloys.

2.1.1.1 The basic numerals for the various types of SAE steel are:

Type Of Steel	Numerals (and Digits)
Carbon Steels	1xxx
Plain Carbon	10xx
Free Cutting (Screw Stock)	11xx
Magnesium Steels	13xx
Nickel Chromium Steels	3xxx
1.25 Percent Nickel; 0.65 Percent Chromium	31xx
Corrosion and Heat Resisting	303xx
Molybdenum Steels	4xxx
0.25 Percent Molybdenum	40xx
Nickel-Chromium-Molybdenum Steels	
1.80 Percent Nickel; 0.50 and 0.80 Percent Chromium; 0.25 Percent Molybdenum	43xx
0.55 Percent Nickel; 0.50 and 0.65 Percent Chromium; 0.20 Percent Molybdenum	86xx
0.55 Percent Nickel; 0.50 Chromium 0.25 Percent Molybdenum	87xx
3.25 Percent Nickel; 1.20 Chromium 0.12 Percent Molybdenum	93xx
Nickel-Molybdenum Steels	
1.75 Percent Nickel; 0.25 Percent Molybdenum	46xx
3.50 Percent Nickel; 0.25 Percent Molybdenum	48xx
Chromium Steels	5xxx
Low Chromium	50xx
Medium Chromium	51xxx
High Chromium	52xxx
Corrosion and Heat Resisting	514xx and 515xx
Chromium-Vanadium Steel	6xxx
0.80-1.00 Percent Chromium, 0.10-0.15 Vanadium	61xx
Silicon Magnesium Steels	9xxx
A Percent Silicon	92xx
Low Alloy, High Tensile	950
Boron Intensified	xxBxx
Leaded Steels	xxLxx



## TO 1-1A-9

### NAVAIR 01-1A-9

**2.1.2 Carbon Steels.** Steel containing carbon in percentages ranging from 0.10 to 0.30 percent is classed as low carbon steel. The equivalent SAE numbers range from 1010 to 1030. Steels of this grade are used for the manufacture of articles such as safety wire, certain nuts, cable bushing, etc. This steel in sheet form is used for secondary structural parts and clamps and in tubular form for moderately stressed structural parts.

**2.1.2.1** Steel containing carbon in percentages ranging from 0.30 to 0.50 percent is classed as medium carbon steel. This steel is especially adaptable for machining, forging, and where surface hardness is important. Certain rod ends, light forgings, and parts such as Woodruff keys, are made from SAE 1035 steel.

**2.1.2.2** Steel containing carbon in percentage ranging from 0.50 to 1.05 percent is classed as high carbon steel. The addition of other elements in varying quantities adds to the hardness of this steel. In the fully heat-treated condition it is very hard and will withstand high shear and wear, but little deformation. It has limited use in aircraft construction. SAE 1095 in sheet form is used for making flat springs and in wire form for making coil springs.

**2.1.3 Nickel Steels.** The various nickel steels are produced by combining nickel with carbon steel. Some benefits derived from the use of nickel as an alloy in steel are as follows:

1. Lowers the percentage of carbon that is necessary for hardening. The lowering of the carbon content makes the steel more ductile and less susceptible to uneven stress.
2. Lowers the critical temperature ranges (heating and cooling) and permits the use of lower heating temperatures for hardening.
3. Hardening of nickel alloy steels at moderate rates of cooling has the advantage of lowering the temperature gradients, reducing internal stress/warpage and permits deeper/more uniform hardening.
4. The low heat treating temperatures required, reduces the danger of overheating, excessive grain growth and the consequent development of brittleness.
5. The characteristics depth hardening from the addition of nickel to steel as an alloy results in good mechanical properties after quenching and tempering. At a given strength (except for very thin sections/parts) the nickel steels provide greatly improve elastic properties, impact resistance and toughness.

**2.1.4 Chromium Steels.** Chromium steel is high in hardness, strength, and corrosion resistant properties. SAE 51335 steel is particularly adaptable for heat-treated forgings which require greater toughness and strength than may be obtained in plain carbon steel. It may be used for such articles as the balls and rollers of anti-friction bearings.

**2.1.5 Chromium-Nickel Steels.** Chromium and nickel in various proportions mixed with steel form the chrome-nickel steels. The general proportion is about two and one-half times as much nickel as chromium. For all ordinary steels in this group the chromium content ranges from 0.45 to 1.25 percent, while the nickel content ranges from 1-2 percent. Both nickel and chromium influence the properties of steel; nickel toughens it, while chromium hardens it. Chrome-nickel steel is used for machined and forged parts requiring strength, ductility, toughness and shock resistance. Parts such as crankshafts and connecting rods are made of SAE 3140 steel.

**2.1.5.1** Chrome-nickel steel containing approximately 18 percent chromium and 8 percent nickel is known as corrosion resistant steel. It is usually identified as AISI types 301, 302, 303, 304, 304L, 309, 316, 316L, 321, 347, 347F or Selenium, etc., however; the basic 18-8 chrome-nickel steel is Type 302. The other grades/types have been modified by changing or adding alloying elements to that contained in the basic alloy. The alloys are varied to obtain the required mechanical properties for some specific purpose such as improving corrosion resistance or forming machining, welding characteristics, etc. The following are examples of variations:

1. 301-Chromium and Nickel (approximate 0.5 Nickel) is lowered to increase response to cold working.
2. 302-Basic Type 18 Chromium 8 Nickel.
3. 303-Sulfur or Selenium added for improved machining characteristics.



4. 304-Carbon lowered to reduce susceptibility to carbide precipitation. This alloy is still subject to carbide precipitation from exposure to temperatures 800-1500 degree Fahrenheit (°F) range and this shall be considered when it is selected for a specific application.
5. 304L-Carbon lowered for welding applications.
6. 309-Chromium and Nickel higher for additional corrosion and scale resistance.
7. 316-Molybdenum added to improve corrosion resistance and strength.
8. 316L-Carbon- lowered for welding applications.
9. 321-Titanium added to reduce/avoid carbide precipitation (stabilized grade).
10. 347-Niobium, Tantalum added to reduce/avoid carbide precipitation (stabilized grade).
11. 347F Selenium-Sulfur or Selenium added to improve machinability.

2.1.5.1.1 The chrome-nickel steels are used for a variety of applications on aircraft and missiles. In plate and sheet form it is used for firewalls, surface skin, exhaust stacks, heater ducts, gun wells, ammunition chutes, clamps, heat shields/deflectors, fairing, stiffeners, brackets, shims, etc. In bar and rod it is used to fabricate various fittings, bolts, studs, screws, nuts, couplings, flanges, valve stems/seats, turn-buckles, etc. In wire form it is used for safety wire, cable, rivets, hinge pins, screens/screening and other miscellaneous items.

2.1.6 Chrome-Vanadium Steels. The vanadium content of this steel is approximately 0.18 percent and the chromium content approximately 1.00 percent. Chrome-vanadium steels when heat-treated have excellent properties such as strength, toughness, and resistance to wear and fatigue. A special grade of this steel in sheet form can be cold-formed into intricate shapes. It can be folded and flattened without signs of breaking or failure. Chrome-vanadium steel with medium high carbon content (SAE 6150) is used to make springs. Chrome-vanadium steel with high carbon content (SAE 6195) is used for ball and roller bearings.

2.1.7 Chrome Molybdenum Steels. Molybdenum in small percentage is used in combination with chromium to form chrome-molybdenum steel; this steel has important applications in aircraft. Molybdenum is a strong alloying element, only 0.15-0.25 percent being used in the chrome-molybdenum steels; the chromium content varies from 0.80-1.10 percent. Molybdenum is very similar to tungsten in its effect on steel. In some instances it is used to replace tungsten in cutting tools, however; the heat treat characteristic varies. The addition of up to 1 percent molybdenum gives steel a higher tensile strength and elastic limit with only a slight reduction in ductility. They are especially adaptable for welding and for this reason are used principally for welded structural parts and assemblies. Parts fabricated from 4130, are used extensively in the construction of aircraft, missiles, and miscellaneous Ground Support Equipment (GSE) equipment. The 4130 alloy is used for parts such as engine mounts (reciprocating), nuts, bolts, gear structures, support brackets for accessories, etc.

## 2.2 PRINCIPLES OF HEAT TREATMENT OF STEELS.

2.2.1 Hardening. At ordinary temperatures, the carbon content of steel exists in the form of particles of iron carbide scattered throughout the iron matrix; the nature of these carbide particles, i.e., their number, size, and distribution, determines the hardness and strength of the steel. At elevated temperatures, the carbon is dissolved in the iron matrix and the carbide-particles appear only after the steel has cooled through its "critical temperature" (see [Paragraph 2.2.1.1](#)). If the rate of cooling is slow, the carbide particles are relatively coarse and few; in this condition the steel is soft. If the cooling is rapid, as by quenching in oil or water, the carbon precipitates as a cloud of very fine carbide particles, which condition is associated with high hardness of the steel.

2.2.1.1 At elevated temperatures, the iron matrix exists in a form called "austenite" which is capable of dissolving carbon in solid solution. At ordinary temperatures the iron exists as "ferrite", in which carbon is relatively insoluble and precipitates; as described in the preceding paragraph, in the form of carbide particles. The temperature at which this change from austenite to ferrite begins to occur on cooling is called the "upper critical temperature" of the steel, and varies with the carbon content; up to approximately 0.85 percent carbon, the upper critical temperature is lowered with increasing carbon content; from 0.85-1.70 percent carbon the upper critical temperature is raised with increasing carbon content. Steel that has been heated to its upper critical point will harden completely if rapidly quenched; however, in practice it is necessary to exceed this tempera-



## TO 1-1A-9

### NAVAIR 01-1A-9

ture by/from approximately 28 to 56 degree Celsius (°C) (50-100 °F)) to ensure thorough heating of the inside of the piece. If the upper critical temperature is exceeded too much, an unsatisfactory coarse grain size will be developed in the hardened steel.

2.2.1.2 Successful hardening of steel will largely depend upon the following factors after steel has been selected which has harden ability desires:

- a. Control over the rate of heating, specifically to prevent cracking of thick and irregular sections.
- b. Thorough and uniform heating through sections to the correct hardening temperatures.
- c. Control of furnace atmosphere, in the case of certain steel parts, to prevent scaling and decarburization.
- d. Correct heat capacity, viscosity, and temperature of quenching medium to harden adequately and to avoid cracks.
- e. In addition to the preceding factors, the thickness of the section controls the depth of hardness for a given steel composition. Very thick sections may not harden through because of the low rate of cooling at the center.

2.2.1.3 When heating steel, the temperature should be determined by the use of accurate instruments. At times, however, such instruments are not available, and in such cases, the temperature of the steel may be judged approximately by its color. The accuracy with which temperatures may be judged by color depends on the experience of the workman, the light in which the work is being done, the character of the scale on the steel, the amount of radiated light within the furnace, and the emissivity or tendency of steel to radiate or emit light.

2.2.1.4 A number of liquids may be used for quenching steel. Both the medium and the form of the bath depend largely on the nature of the work to be cooled. It is important that a sufficient quantity of the medium be provided to allow the metal to be quenched without causing an appreciable change in the temperature of the bath. This is particularly important where many articles are to be quenched in succession.

## 2.3 QUENCHING PROCEDURE.

### NOTE

Aerators may be used in the Quench Tanks to help dissipate the vapor barrier.

The tendency of steel to warp and crack during the quenching process is difficult to overcome, and is due to the fact that certain parts of the article cool more rapidly than others. Whenever the rate of cooling is not uniform, internal stresses are set up on the metal which may result in warpage or cracking, depending on the severity of the stresses. Irregularly shaped parts are particularly susceptible to these conditions although parts of uniform section size are often affected in a similar manner. Operations such as forging and machining may set up internal stresses in steel parts and it is therefore advisable to normalize articles before attempting the hardening process. The following recommendations will greatly reduce the warping tendency and should be carefully observed:

1. An article should never be thrown into quenching media/bath. By permitting it to lie on the bottom of the bath it is apt to cool faster on the top side than on the bottom side, thus causing it to warp or crack.
2. The article should be slightly agitated in the bath to destroy the coating of vapor which might prevent it from cooling rapidly. This allows the bath to remove the heat of the article rapidly by conduction and convection.
3. An article should be quenched in such a manner that all parts will be cooled uniformly and with the least possible distortion. For example, a gear wheel or shaft should be quenched in a vertical position.
4. Irregularly shaped sections should be immersed in such a manner that the parts of the greatest section thickness enters the bath first.

2.3.1 Quenching Medium. Oil is much slower in action than water, and the tendency of heated steel to warp or crack when quenched may be greatly reduced by its use. Unfortunately, parts made from high carbon steel will not develop maximum hardness when quenched in oil unless they are quite thin in cross section. In aircraft, however, it is generally used and is recommended in all cases where it will produce the desired degree of hardness.



**NOTE**

Alloy steels should never be quenched in water.

2.3.1.1 In certain cases water is used in the quenching of steel for the hardening process. The water bath should be approximately 18 °C (65 °F) as extremely cold water is apt to warp or crack the steel and water above this temperature will not produce the required hardness.

2.3.1.2 A 10 percent salt brine (sodium chloride) solution is used when higher cooling rates are desired. A 10 percent salt brine solution is made by dissolving 0.89 pound of salt per gallon of water.

2.3.1.3 For many articles such as milling cutters and similar tools, a bath of water covered by a film of oil is occasionally used. When the steel is plunged through this oil film a thin coating will adhere to it, retarding the cooling effect of the water slightly, thus reducing the tendency to crack due to contraction.

2.3.2 **Straightening of Parts Warped in Quenching.** Warped parts must be straightened by first heating to below the tempering temperature of the article, and then applying pressure. This pressure should be continued until the piece is cooled. It is desirable to re-temper the part after straightening at the straightening temperature. No attempt should be made to straighten hardened steel without heating, regardless of the number of times it has been previously heated, as steel in its hardened condition cannot be bent or sprung cold with any degree of safety.

2.3.3 **Tempering (Drawing).** Steel that has been hardened by rapid cooling from a point slightly above its critical range is often harder than necessary and generally too brittle for most purposes. In addition, it is under severe internal stress. In order to relieve the stresses and reduce the brittleness or restore ductility the metal is always “tempered”. Tempering consists in reheating the steel to a temperature below the critical range (usually in the neighborhood of 600-1200 °F). This reheating causes a coalescence and enlargement of the fine carbide particles produced by drastic quenching, and thus tends to soften the steel. The desired strength wanted will determine the tempering temperature. This is accomplished in the same types of furnaces as are used for hardening and annealing. Less refined methods are sometimes used for tempering small tools.

2.3.3.1 As in the case of hardening, tempering temperatures may be approximately determined by color. These colors appear only on the surface and are due to a thin film of oxide which forms on the metal after the temperature reaches 232 °C (450 °F). In order to see the tempering colors, the surface must be brightened. A buff stick consisting of a piece of wood with emery cloth attached is ordinarily used for this purpose. When tempering by the color method, an open flame of heated iron plate is ordinarily used as the heating medium. Although the color method is convenient, it should not be used unless adequate facilities for determining temperature are not obtainable. Tempering temperatures can also be determined by the use of crayons of known melting point. Such crayons are commercially available for a wide range of temperatures under the trade name of “Tempilstiks”. The above method may be used where exact properties after tempering is not too important such as for blacksmith work. The most desirable method for general aeronautical use, is to determine temperatures by hardness checks, and subsequent adjustments made as necessary to obtain the properties required. For recommended tempering temperatures see heat treat data for material/composition involved.



SOLDER

8

2.3.3.2 Steel is usually subjected to the annealing process for the following purposes:

1. To increase its ductility by reducing hardness and brittleness.
2. To refine the crystalline structure and remove stresses. Steel which has been cold-worked is usually annealed so as to increase its ductility. However, a large amount of cold-drawn wire is used in its cold-worked state when very high yield point and tensile strength are desired and relatively low ductility is permissible, as in spring wire, piano wire, and wires for rope and cable. Heating to low temperatures, as in soldering, will destroy these properties. However, rapid heating will narrow the affected area.
3. To soften the material so that machining, forming, etc., can be performed.



**2.3.4 Normalizing.** Although involving a slightly different heat treatment, normalizing may be classed as a form of annealing. This process also removes stresses due to machining, forging, bending, and welding. Normalizing may be accomplished in furnaces used for annealing. The articles are put in the furnace and heated to a point approximately 150 to 225 °F above the critical temperature of the steel. After the parts have been held at this temperature for a sufficient time for the parts to be heated uniformly throughout, they must be removed from the furnace and cooled in still air. Prolonged soaking of the metal at high temperatures must be avoided, as this practice will cause the grain structure to enlarge. The length of time required for the soaking temperature will depend upon the mass of metal being treated. The optimum soaking time is roughly one-quarter hour per inch of diameter or thickness.

**2.3.5 Case Hardening.** In many instances it is desirable to produce a hard, wear-resistant surface or “case” over a strong, tough core. Treatment of this kind is known as “case hardening”. This treatment may be accomplished in several ways, the principal ways being carbonizing, cyaniding, and nitriding.

**2.3.5.1 Flame Hardening/Softening.** Surface hardening/softening by applying intense heat (such as that produced by an Oxy-Acetylene flame) can be accomplished on almost any of the medium carbon or alloys steel, i.e. 1040, 1045, 1137, 1140, etc. The parts are surface hardened, by applying a reducing flame (an Oxidizing flame should never be used) at such a rate, that the surface is rapidly heated to the proper quenching temperature for the steel being treated. Following the application of the heat, the part is quenched by a spraying of water/oil rapidly. The fast quench hardens the steel to the depth that the hardening temperature has penetrated below the surface. The actual hardness resulting will depend on the rate of cooling from the quenching temperature. In hardening by this method the shape and size/mass of the part must be considered. Most operations will require special adapted spray nozzles to apply the quenching media, which is usually water. Normally, flame hardening will produce surface hardness higher than can be obtained by routine furnace heating and quenching, because surface can be cooled at a faster rate. If a combination of high strength core and surface is required some of the medium carbon alloy steels can be heat treated and subsequently surface hardened by the flame method.

#### **NOTE**

This method is not adapted for surface hardening of parts for use in critical applications.

**2.3.5.1.1** Surface softening is accomplished by heating the surface to just below the temperature by drastic quenching, and thus tends to soften the steel. The desired strength wanted will determine the tempering temperature. This is accomplished in the same types of furnaces as are used for hardening and annealing. Less refined methods are sometimes used for tempering small tools.

**2.3.5.2 Induction Hardening/Heating.** The induction method of heating can be used to surface harden steels, in a manner similar to that used for flame hardening. The exception is that the heat for hardening is produced by placing the part in a magnetic field (electrical) specifically designed for the purpose. Parts hardened (surface) by this method will be limited to capability and size of loop/coil used to produce the magnetic field.

**2.3.5.2.1** In some instances the induction method can be used to deep harden; the extent will depend on exposure/dwell time, intensity of the magnetic field, and the size of the part to be treated.

**2.3.6 Carburizing.** At elevated temperatures iron can react with gaseous carbon compounds to form iron carbide. By heating steel, while in contact with a carbonaceous substance, carbonic gases given off by this material will penetrate the steel to an amount proportional to the time and temperature. For example, if mild or soft steel is heated to 732 °C (1,350 °F) in an atmosphere of carbonic gases, it will absorb carbon from the gas until a carbon content of approximately 0.80 percent has been attained at the surface, this being the saturation point of the steel for the particular temperature. By increasing the heat to 899 °C/(1,650 °F) the same steel will absorb carbon from the gas until a carbon content of approximately 1.1 percent has been attained, which is the saturation point for the increased temperature.

**2.3.6.1** The carburizing process may be applied to both plain carbon and alloy steels provided they are within the low carbon range. Specifically, the carburizing steels are those containing not more than 0.20 percent carbon. The lower the carbon content in the steel, the more readily it will absorb, carbon during the carburizing process.

**2.3.6.2** The amount of carbon absorbed and the thickness of the case obtained increases with time; however, the carburization progresses more slowly as the carbon content increases during the process. The length of time required to produce the desired degree of carburization material used and the temperature to which the metal is subjected. It is apparent that, in carburizing, carbon travels slowly from the outside toward the inside center, and therefore, the proportion of carbon absorbed must decrease from the outside to the inside.



2.3.6.3 Solid, liquid, and gas carburizing methods are employed.

1. The simplest method of carburizing consists of soaking the parts at an elevated temperature while in contact with solid carbonaceous material such as wood charcoal, bone charcoal and charred leather.
2. Liquid carburizing consists of immersing the parts in a liquid salt bath, heated to the proper temperature. The carbon penetrates the steel as in the solid method producing the desired case.
3. Gas carburizing consists of heating the parts in a retort and subjecting them to a carbon-aceous gas such as carbon monoxide or the common fuel gases. This process is particularly adaptable to certain engine parts.

2.3.6.4 When pack carburizing, the parts are packed with the carburizing material in a vented steel container to prevent the solid carburizing compound from burning and to retain the carbon monoxide and dioxide gases. Nichrome boxes, capped pipes of mild steel, or welded mild steel boxes may be used. Nichrome boxes are most economical for production because they withstand oxidation. Capped pipes of mild steel or welded mild steel boxes are useful only as substitutes. The container should be so placed as to allow the heat to circulate entirely around it. The furnace must be brought to the carburizing temperature as quickly as possible and held at this heat from 1 to 16 hours, depending upon the depth of case desired and the size of the work. After carburizing the container should be removed and allowed to cool in air or the parts removed from the carburizing compound and quenched in oil or water. The air cooling, although slow, reduces warpage and is advisable in many cases.

2.3.6.5 Carburized steel parts are rarely used without subsequent heat treatment, which consists of several steps to obtain optimum hardness in the case, and optimum strength and ductility in the core. Grain size of the core and case is refined.

1. Refining the core is accomplished by reheating the parts to a point just above the critical temperature of the steel. After soaking for a sufficient time to ensure uniform heating, the parts are quenched in oil.
2. The hardening temperature for the high carbon case is well below that of the core. It is, therefore, necessary to heat the parts again to the critical temperature of the case and quench them in oil to produce the required hardness. A soaking period of 10 minutes is generally sufficient.
3. A final stress relieving operation is necessary to minimize the hardening stresses produced by the previous treatment. The stress relieving temperature is generally around 350 °F. This is accomplished by heating, soaking until uniformly heated, and cooling in still air. When extreme hardness is desired, the temperature should be carefully held to the lower limit of the range.

2.3.7 Cyaniding. Steel parts may be surface hardened by heating while in contact with a cyanid salt, followed by quenching. Only a thin case is obtained by this method and it is, therefore, seldom used in connection with aircraft construction or repair. Cyaniding is, however, a rapid and economical method of case hardening, and may be used in some instances for relatively unimportant parts. The work to be hardened is immersed in a bath of molten sodium or potassium cyanide from 30 to 60 minutes. The cyanide bath should be maintained at a temperature to 760-899 °C (1,400-1,650 °F). Immediately after removal from the bath, the parts are quenched in water. The case obtained in this manner is due principally to the formation of carbides and nitrides on the surface of the steel. The use of a closed pot and ventilating hood are required for cyaniding, as cyanide vapors are extremely poisonous.

2.3.8 Nitriding. This method of case hardening is advantageous due to the fact that a harder case is obtained than by carburizing. Many engine parts such as cylinder barrels and gears may be treated in this way. Nitriding is generally applied to certain special steel alloys, one of the essential constituents of which is aluminum. The process involves the exposing of the parts to ammonia gas or other nitrogenous materials for 20 to 100 hours at 950 °F. The container in which the work and ammonia gas are brought in contact must be airtight and capable of maintaining good circulation and even temperature throughout. The depth of case obtained by nitriding is about 0.015 inch if heated for 50 hours. The nitriding process does not affect the physical state of the core if the preceding tempering temperature was 950 °F or over. When a part is to be only partially treated, tinning of any surface will prevent it from being nitrided. Nitrided surfaces can be reheated to 950 °F with out losing any of their hardness, however, if heated above that temperature, the hardness is rapidly lost and cannot be regained by retreatment. Prior to any nitriding treatment, all decarburized metal must be removed to prevent flaking of the nitrided case. When no distortion is permissible in the nitrided part, it is necessary to normalize the steel prior to nitriding to remove all strains resulting from the forging, quenching, or machining.



## 2.4 HEAT TREATING EQUIPMENT.

Equipment necessary for heat treating consists of a suitable means for bringing the metal to the required temperature measuring and controlling device and quenching medium. Heat may, in some instances, be supplied by means of a forge or welding torch; however, for the treatment required in aircraft work, a furnace is necessary. Various jigs and fixtures are sometimes needed for controlling quenching and preventing warping.

**2.4.1 Furnaces.** Heat treating furnaces are of many designs and no one size or type perfectly fills every heat treating requirement. The size and quantity of metal to be treated and the various treatments required determine the size and type of furnace most suitable for each individual case. The furnace should be of a suitable type and design for the purpose intended and should be capable of maintaining within the working zone a temperature varying not more than  $\pm 25$  °F for the desired value. Certain processes or materials may require tighter temperature control and uniformity, see [Paragraph 2.4.2.1](#). Aircraft Metals Technology shops shall refer to JEDMICS Drawing 202432237 (CAGE 98752) Equipment Qualified Product List for selections of heat treating furnaces which has been approved by the AF Metal Fabrication and Technologies Office (MFTO). Heat treating furnaces shall be procured through the use of Commercial Item Description (CID) A-A-60033. CID A-A-60033 can be viewed at <https://assistca.dla.mil>.

**2.4.2 Heat Treating Furnaces/Baths.** The acceptable heating media for heat treating of steels are air, combusted gases, protective atmosphere, inert atmosphere or vacuum furnaces, molten-fused salt baths, and molten-lead baths. The heat treating furnaces/baths are of many designs and no one size or type will perfectly fill every heat treating requirement. Furnaces and baths shall be of suitable design, type and construction for purpose intended. Protective and inert atmospheres shall be utilized and circulated as necessary to protect all surfaces of parts comprising the furnace load.

**2.4.2.1** The design and construction of the heating equipment shall be such that the furnace/bath is capable of maintaining within the qualified working zone, at any point, a temperature varying not more than  $\pm 25$  °F from the required heat treating temperature, with any charge. After the charge has been brought up to treating/soaking temperature all areas of the working zone shall be within the permissible temperature range specified for the steel/alloy being heat treated. Certain processes or materials may require tighter temperature control and uniformity. See [Table 3-19](#), [Paragraph 2.4.2.1](#), SAE-AMS-H-6875 or specific engineering data for the material involved.

## 2.5 HEAT CONTROL: TEMPERATURE MEASURING EQUIPMENT, FURNACE TEMPERATURE UNIFORMITY SURVEY, AND SYSTEM ACCURACY TESTS (SATS).

### NOTE

SAE-AMS-2750, Pyrometry, is the control document for equipment used to heat treat aerospace materials. AMS-2750 covers temperature sensors, instrumentation, system accuracy tests, and Temperature Uniformity Surveys (TUS). For a complete description of pyrometry requirements for heat treating equipment, refer to the latest issue of SAE-AMS-2750. In case of conflict with this manual, the discrepancy will be negotiated with the responsible technical/engineering activity for resolution and updating.

**2.5.1 Controlling, Monitoring, and Recording Equipment.** Instrumentation type for controlling, monitoring, and recording equipment is broken down into five categories. Each category is based on how many controlling, monitoring, and recording Thermocouple (TCs) are operational in an furnace chamber. The most common instrumentation type is Type D. Furnace controllers, monitoring, and process recording equipment shall be digital and have a calibration accuracy of  $\pm 2$  °F or 0.2 percent of the reading, whichever is greater. Field test instruments can temporarily be used as monitoring/recording equipment to monitor and record heat treatment processes when on-board furnace equipment is inoperable or non-digital, ie; paper chart recorders. See [Table 3-21](#) for furnace instrumentation types.

**2.5.2 Field Test Instruments.** Field test instruments are used in conjunction with thermocouples to measure the operating temperature inside the furnace chamber. They are used to monitor load thermocouples, perform SATs, and TUS. They range from hand held single input units to suitcase style multi-input units. Many modern units come with software to log and record data. Field test instruments used to perform SATs and monitor load thermocouples shall have a minimum of 1 input channel, a calibration accuracy of  $\pm 1$  °F or  $\pm 0.1$  percent of the reading, whichever is greater, and the ability to log/record data. Field test instruments used to perform TUSs shall have a minimum of 9 input channels, a calibration accuracy of  $\pm 1$  °F or  $\pm 0.1$  percent of the reading, whichever is greater, and the ability to log/record data. National Stock Number (NSN) 6625-01-649-1136 is an example of a multi-point field test unit that logs data and can be used for multiple heat treatment process test, measuring, and recording applications such as SATs and TUSs.

**2.5.3 TC.** See [Paragraph 3.13.5](#) through [Paragraph 3.13.5.5.2](#).



**2.5.4 Temperature Control and Uniformity Testing.** Precise temperature control is essential to produce the exact material properties and temper requirements necessary for modern aviation manufacturing and maintenance. Periodic surveys and tests of the internal chamber temperatures must be conducted, documented and compared to the set point temperatures of the furnace/furnace controller to ensure accurate equipment operation. The two methods used to ensure accurate operation of heat treating equipment are the SAT and the TUS. The SAT is a quick and simple user test to ensure the furnace temperature remains accurate in between TUSs. The TUS is a more thorough user test to ensure temperature accuracy and uniformity in the entire furnace chamber as compared to the furnace control sensor and SAT. These two tests work in conjunction with each other as a checks and balance system to ensure accurate and uniform furnace operation. If one is accurate and the other is not, that is a sign that your furnace needs troubleshooting or maintenance to correct a deficiency.

**2.5.4.1 SAT.** A SAT is performed to assess the accuracy of the heat treat furnace's resident thermocouple and controller. This is done through the use of an independently calibrated field test instrument and thermocouple. By placing the test thermocouple within 3 inches of the resident thermocouple and taking a reading with the field test instrument, the accuracy of the furnace's controller and resident thermocouple is validated. If the difference between the field test instrument and the furnace controller is greater than  $\pm 5$  °F, then that is an indication of required maintenance or adjustment of the furnace, furnace controller, and/or resident thermocouple.

**2.5.4.1.1** A SAT shall be performed and documented using a field test instrument that meets the requirements of [Paragraph 3.13.3](#) and a TC that meets the requirements of [Paragraph 3.13.5.5.2](#), on each furnace chamber used to perform heat treating on ferrous alloys, at the following intervals/situations:

- a. Initial. Upon initial furnace installation, prior to first operational use.
- b. Periodic. SAT frequency is based on frequency of heat treating operations and furnace instrumentation type. See [Table 3-21](#) for instrumentation types.
  - (1) Shops that perform daily heat treating operations, utilizing Type D instrumentation, shall perform SATs on a biweekly basis, not to exceed 14 calendar days. If utilizing Type B or C instrumentation, the SAT interval may be extended to monthly, not to exceed 31 calendar days.
  - (2) Shops performing weekly to biweekly heat treating operations, every 5 to 14 calendar days, utilizing Type D instrumentation, shall perform SATs on a monthly basis, not to exceed 31 calendar days. If utilizing Type B or C instrumentation, the SAT interval may be extended to quarterly, not to exceed 91 calendar days.
  - (3) Shops performing biweekly to monthly heat treating operations, every 15 to 30 calendar days, utilizing Type D instrumentation, shall perform SATs on a quarterly basis, not to exceed 91 calendar days. Use of Type B or C instrumentation is recommended, but the SAT interval will not be extended.
  - (4) Shops performing heat treating operations less frequent than every 30 calendar days, regardless of instrument type, will perform a SAT prior to use/heat treating operation.
  - (5) If utilizing Type A instrumentation, refer to AMS2750 for SAT interval.
- c. After any maintenance to the furnace, ie; replacement of a sensor/TC, heating element, or controlling, monitoring, or recording instrument.
- d. Recalibration of the controlling, monitoring, or recording instrument, or when parameter/rheostat adjustments have been made.

**2.5.4.1.2 SAT Procedure.** A successful SAT reading must be within  $\pm 5$  °F of furnace controller set-point.

- a. Set furnace controller to desired set point and allow to stabilize.
- b. Insert TC into furnace with tip (measuring junction) as close to practical to the controlling, monitoring, or recording sensor tip. The tip to tip distance shall not exceed 3 inches. Proper Personal Protective Equipment (PPE) must be worn when manually inserting SAT TC into furnace.
- c. Allow furnace to recover. Some alloys have specific recovery period time lines. Recovery time must not be exceeded, as applicable.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

- d. Record temperature reading.
- e. Document and file report.

**2.5.4.1.3 SAT Report Requirements.** A paper or digital copy of the completed record shall be retained for 3 years by the facility performing the SAT in accordance with Air Force Records Disposition Schedule Table 21-06 Rule 35.00. The report will contain, at a minimum:

1. Identification of furnace/sensor (if multi-zone) being tested.
2. Date and time of the test.
3. Identification of the test sensor.
4. Test sensor correction factors.
5. Identification of the test instrument.
6. Identification of test instrument correction factors.
7. Set point of furnace during the test.
8. Observed furnace controller instrument reading.
9. Observed test instrument reading.
10. Corrected test instrument reading [will be same as (i) if (d) and (f) are programmed into test unit, if not,  $(j = i + d + f)$ ].
11. Calculated system accuracy difference ( $k = h - j$ ).
12. Indication of test pass or fail.
13. Identification of technician performing test.
14. Identification of supervisor performing review.

**2.5.4.1.4** If SAT failure occurs, corrective action may include, but is not limited to replacement of the out of tolerance sensor, rheostat adjustment, recalibration of the out of tolerance instrument/controller, etc. After any corrective actions, a SAT must be performed prior to any production heat treatments in accordance with [Paragraph 2.5.4.1.2](#).

**2.5.4.1.5 Modification Offset.** Manual modification offset of the control instrument to facilitate desired chamber temperatures based on most recent SAT results are not permitted.

**2.5.4.2 TEMPERATURE UNIFORMITY SURVEY (TUS).** A TUS is performed to ensure the furnace chamber's operating temperature is accurate and uniform, within given tolerance standards, throughout the entire volume or qualified work zone in relation to the furnace set point. This is done through the use of an independently calibrated field test instrument (multi-point data logger) and multiple thermocouples all simultaneously measuring temperature from multiple points in the furnace chamber over a period of at least 30 minutes.

**2.5.4.2.1** A TUS shall be performed and documented using a field test instrument that meets the requirements of [Paragraph 3.13.3](#) and a TC that meets the requirements of [Paragraph 3.13.5.5.2](#), on each furnace chamber used to perform heat treating on ferrous alloys, at the following intervals/situations:

1. Upon initial furnace installation, prior to first operational use. See [Paragraph 2.5.4.2.2](#).
2. Quarterly. See [Paragraph 2.5.4.2.3](#).
3. Annually. See [Paragraph 2.5.4.2.4](#).



4. After any maintenance to the furnace, ie; replacement of a sensor/TC, heating element, controlling, monitoring, or recording instrument, airflow pattern/velocity, replacement of refractory material.
5. Recalibration of the controlling, monitoring, or recording instrument, or when parameter/rheostat adjustments have been made.
6. Work zone volume increase, larger than previously qualified area.
7. Work zone location change, outside of previously qualified area.

**2.5.4.2.2 Initial TUS Requirement.** Initial survey temperatures shall be the minimum and maximum temperatures of the qualified operating temperature range. Additional temperatures shall be added as required to ensure that no two adjacent survey temperatures are greater than 600 °F apart. For example, if a furnace operating range is 1200 to 2400 °F, the furnace must be surveyed at 1200, 1800, and 2400 °F.

**2.5.4.2.3 Quarterly TUS Requirement.** A quarterly TUS shall be performed, not to exceed 91 calendar days. For single operating ranges greater than 600 °F, TUS temperatures shall be selected so that one temperature is within 300 °F of the minimum and another temperature is within 300 °F of the maximum qualified operating range and there is no more than 600 °F in between. For example, if a furnace operating range is 1200-2400 °F, then the furnace must be surveyed at 1200 °F -1500 °F and again at 2100 °F -2400 °F and the selected temperatures must not be more than 600 °F apart. Temperatures of 1500 °F and 2100 °F would meet this requirement.

1. If utilizing Type D instrumentation, after 4 consecutive passing TUSs, the interval may be extended to semiannually, not to exceed 181 calendar days.
2. If utilizing Type B or C instrumentation, after 3 consecutive passing TUSs, the interval may be extended to semiannually, not to exceed 181 calendar days.
3. If utilizing Type A instrumentation, after 2 consecutive passing TUSs, the interval may be extended to annually, not to exceed 365 calendar days.
4. If at any time a TUS fails, the interval resorts back to standard and the count starts again.

**2.5.4.2.4 Annual TUS Requirement.** In addition to the periodic test requirement, at least once per year, not to exceed 365 calendar days, surveys shall also be performed at the minimum and maximum of the qualified operating temperature range. For example, if a furnace operating range is 1200-2400 °F, then the furnace must be surveyed at 1200, 1800, and 2400 °F.

**2.5.4.3 TUS Procedure.** See [Paragraph 3.14.3](#) through [Paragraph 3.14.3.4.4](#).

**2.5.4.4 Temperature Uniformity Pass/Fail Requirements.** A survey shall be considered passing if all the following requirements are met.

- a. Control or monitoring sensor readings and TUS sensor readings did not exceed applicable positive temperature tolerance at any time. See [Table 3-19](#) for Temperature Uniformity Allowances.
- b. The time required to achieve recovery, stabilization, and maintain set point temperature tolerances did not exceed the time limit specified in any applicable process specifications.
- c. All readings of control/monitor and TUS sensor readings are within the temperature tolerance requirements of [Table 3-19](#) for the process being surveyed after the official start of TUS survey time except as allowed in [Paragraph 3.14.3.4.3](#).
- d. TUS sensor data was logged for each sensor at a frequency not greater than every two minutes.
- e. TUS is run for the minimum required time of 30 minutes.

**2.5.4.5 TUS Data and TUS Reports.** TUS data must be gathered and recorded on a system that creates electronic records that cannot be altered without detection.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

2.5.4.5.1 The TUS system software and playback utilities shall provide a means of examining and/or compiling the record data, but shall not provide any means of altering the source data. The system shall be capable of providing evidence the record was reviewed, such as by recording an electronic review or a method of printing the record for a physical marking to indicate a review.

2.5.4.5.2 TUS Survey Report Requirements. A paper or digital copy of the completed record shall be retained for 3 years by the facility performing the TUS in accordance with Air Force Records Disposition Schedule Table 21-06 Rule 35.00. The report will contain, at a minimum:

- a. Furnace identification name or serial number.
- b. Survey temperature.
- c. Required temperature uniformity.
- d. Furnace chamber dimensions or qualified working zone dimensions and location in chamber.
- e. TUS sensor and location identification including a detailed diagram, description or photograph of any load or rack used.
- f. Time and temperature data from all TUS sensors.
- g. TC spool correction factor or correction factors for each TUS sensor at each calibration temperature.
- h. Corrected or uncorrected readings of all TUS sensors. Reading shall be identified as corrected or uncorrected.
- i. As found and as left TUS offsets (if used in production).
- j. Survey start date and time.
- k. Survey end date and time.
- l. Survey test instrument identification or serial number.
- m. Survey test instrument calibration agency.
- n. Survey test instrument calibration date.
- o. Survey test sensor failures, if any.
- p. Indication of test pass or fail.
- q. Identification of technician performing survey.
- r. Identification of supervisor approving survey.

2.5.4.6 Failed TUS Procedures. If the temperature uniformity is not within the tolerances of [Table 3-19](#), the cause of the deviation shall be determined, documented, and corrected. The equipment shall not be used for additional processing until the deviation has been corrected and the TUS has been performed successfully.

2.5.4.6.1 For furnaces being tested at an extended interval, failure of a TUS shall cause the extended TUS interval to revert back to the standard periodic interval as applicable in [Paragraph 2.5.4.2.3](#).

2.5.4.6.2 Modification Offset. Manual modification offset of the control instrument to facilitate the desired chamber temperature based on the most recent TUS results are permissible, provided it does not exceed  $\pm 13$  °F. Modification offsets shall be documented, approved/signed by the section supervisor or Non Commissioned Officer in Charge (NCOIC), and used in production heat treatments, i.e. controller is offset to 1810 °F to obtain accurate uniform internal chamber temperature uniformity of  $1800 \pm 25$  °F, controller is offset to 2108 °F to obtain accurate internal chamber temperature of  $2100 \pm 25$  °F etc.




The signed temperature offset chart shall be posted next to the furnace controller or a similar location where the operator will see it and not overlook it. Temperature offsets greater than  $\pm 13$  °F shall be troubleshot and corrected by a qualified technician within 90 days.


2.5.4.6.2.1 The quenching liquids authorized for use are as follows: Water, Commercial Quenching Oil, and Aqueous Polymer Solutions. Quenchant medium shall be between 60 and 160 °F at the beginning of the quenching operation, and shall not exceed 200 °F at any time during the quenching operation, unless specified or approved by the responsible engineering authority.



RECTANGULAR FURNACE  
(WORKING ZONE)

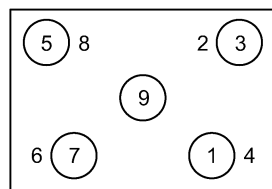


TOP VIEW

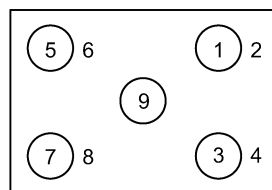


SIDE VIEW

CYLINDRICAL BATH  
(WORKING ZONE)

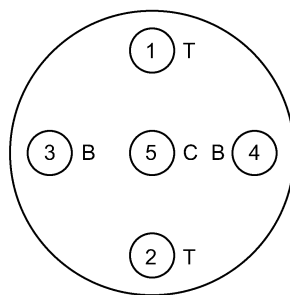


TOP VIEW

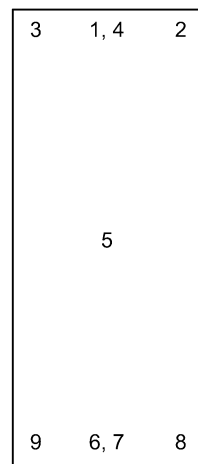

SIDE VIEW

CODE:  
B = BOTTOM  
T = TOP  
C = CENTER

CYLINDRICAL AIR FURNACE  
(WORKING ZONE)

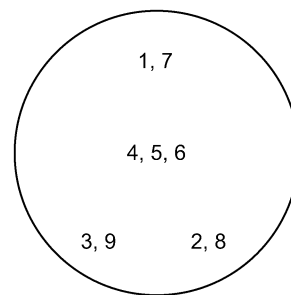

TOP VIEW

ONLY CIRCLED TEST LOCATIONS ARE REQUIRED FOR BATH - TYPE FURNACES LESS THAN 75 CUBIC FEET.

WHEN VOLUME REQUIRES ADDITIONAL TEST LOCATIONS, THEY SHALL BE SYMMETRICALLY DISTRIBUTED WITHIN THE WORKING ZONE.

TO-1-1A-9-001

**Figure 2-1. Number and Distribution of Thermocouples**



## 2.6 SALT BATH CONTROL.

The bath composition shall be adjusted as frequently as necessary to prevent objectionable attachment of the steel or alloy to be treated and to permit attainment of the desired mechanical properties of the finished product. The bath will be checked at least once a month. Temperature recording should be of the automatic controlling and recording type, preferably the potentiometer type. Thermocouples should be placed in a suitable protecting tube, unless the furnace atmosphere is such that undue deterioration of the thermocouples will not result.

**2.6.1 Quenching Tanks and Liquids.** Suitable tanks must be provided for quenching baths. The size of tanks should be sufficiently large to allow the liquids to remain approximately at room temperature. Circulating pumps and coolers may be used for maintaining approximately constant temperatures where a large amount of quenching is done. The location of these tanks is very important due to the fact that insufficiently rapid transfer from the furnace to the quenching medium may destroy the effects of the heat treatment in many instances.

**2.6.1.1** The quenching liquids authorized for use are as follows: Water, Commercial Quenching Oil, and Aqueous Polymer Solutions. Quenchant medium shall be between 60 and 160 °F at the beginning of the quenching operation, and shall not exceed 200 °F at any time during the quenching operation, unless specified or approved by the responsible engineering authority.

## 2.7 HEAT TREATING PROCEDURES.

**2.7.1 Newly Fabricated Parts.** Newly fabricated parts that require heat treatment shall be accompanied by a coupon, whenever possible. A coupon is a piece of metal that is taken from the same stock as the fabricated part. Its thickness should match that of the part with an overall size that provides adequate room for hardness testing. Coupons must be heat treated along with the fabricated part to ensure both items undergo the same metallurgical changes. After completion of heat treatment, perform required hardness testing on the coupon to prevent damage to the fabricated part. See Chapter 8 of this technical order for proper hardness testing procedures.

### NOTE

Specification SAE-AMS-H-6875, Heat Treatment of Steel Raw Materials, is the control document for heat treating steel material to be used on aerospace equipment. Where new alloys are involved, it will be necessary to review the involved specification or manufacturer's engineering or design data for the appropriate heat treat information (temperature, control, atmosphere, times, etc). In case of conflict with this manual, the discrepancy will be negotiated with the responsible technical/engineering activity for resolution and updating.

**2.7.2 Initial Furnace Temperatures.** In normalizing, annealing and hardening where parts are not preheated, the temperature in that zone of the furnace where works is introduced should be at least 149 °C (300 °F) below the working temperature at the time of insertion of parts of simple design. For parts of complicated design involving abrupt change of section or sharp corners, the temperature should be at least 260 °C (500 °F) below the working temperature. The furnace must be brought to the proper temperature gradually.

**2.7.3 Soaking Periods.** The period of soaking is governed by both the size of the section and the nature of the steel. [Table 2-1](#) indicates in a general way the effect of size on the time for soaking. This table is intended to be used as a guide only and should not be construed as being a mandatory requirement. It applies only to plain carbon and low alloy steels, and these times were taken directly from U.S. Military Standard MIL-H-6875 (Table IIA) (rescinded), and Table 2A per SAE-AMS-6875. These times are suitable for unplated parts only. In all cases, holding time shall not start until parts or material have reached specified heat-treat temperature. The holding-time intervals indicated by [Table 2-1](#) are approximately correct for heating in air. The proper tie interval will vary with the type of steel, capacity of heating elements, and size of charge, as well as with the thickness of the individual material and protective coatings.

**Table 2-1. Soaking Periods for Hardening Normalizing and Annealing (Plain Carbon Steel)**

Diameter or Thickness (Inches)	Time of Heating to Required Temperature (Approximate Hours)	Time of Holding (Approximate Hours)
1 and less	3/4	1/2
Over 1 through 2	1-1/4	1/2
Over 2 through 3	1-3/4	3/4



**Table 2-1. Soaking Periods for Hardening Normalizing and Annealing (Plain Carbon Steel) - Continued**

Diameter or Thickness (Inches)	Time of Heating to Required Temperature (Approximate Hours)	Time of Holding (Approximate Hours)
Over 3 through 4	2-1/4	1
Over 4 through 5	2-3/4	1
Over 5 through 8	3-1/2	1-1/2

**2.7.4 Hardening.** Temperatures required for hardening steel are governed by the chemical composition of the steel, previous treatment, handling equipment, size and shape of piece to be treated. Generally, parts of heavy cross section should be hardened from the high side of the given temperature range.

**2.7.5 Tempering (Drawing).** Tempering consists of heating the hardened steel to the applicable temperature holding at this temperature for approximately 1 hour per inch of the thickness of the largest section, and cooling in air or quenching in oil at approximately 27-66 °C (80-150 °F). The temperature to be used for tempering of steel depends upon the exact chemical composition, hardness, and grain structure obtained by hardening and the method of tempering. The tempering temperatures given are only approximate, and the exact temperature should be determined by hardness or tension test for individual pieces. The final tempering temperatures should not be more than 111 °C (200 °F) below the tempering temperature given. If the center of the section is more than 1/2 inch from the surface, the tensile strength at the center will in general be reduced; therefore, a lower tempering temperature should be used for sections thicker than 1 inch in order to obtain the required tensile strength.

**2.7.6 Annealing.** Annealing consists of heating to the applicable temperature, holding at this temperature for approximately the period of time given, and cooling in the furnace to a temperature not higher than 482 °C (900 °F). The steel may then be removed from the furnace and cooled in still air.

**2.7.7 Normalizing.** Normalizing consists of heating the steel to the applicable temperature, holding at this temperature for period of time, removing from furnace and cooling in still air.

**2.7.8 Carburizing.** Carburizing consists of heating the steel packed in a carburizing medium, in a closed container, to the applicable temperature and holding at this temperature for the necessary period of time to obtain the desired depth of case. 1020 steel will require 1 to 3 hours at a carburizing temperature of 899 °C (1650 °F) for each 1/64 inch of case depth, required. Parts may be cooled in the box or furnace to a temperature of approximately 482 °C (900 °F) then air cool. This treatment leaves the alloy in a relatively soft condition and it is then necessary to condition by heating and quenching, first for core refinement, followed by heating and quenching for case hardness. Alloy may be quenched directly from the carburizing furnace, thus producing a hard case and a core hardness of Rockwell B67. This treatment produces a coarse grain in some types of steel and may cause excessive distortion. Usually there is less distortion in fine grain steels. The core treatment outlined above refines the grain as well as hardens.

**2.7.9 Records.** Air Force personnel shall document heat treatment procedures performed on aircraft and missile weapon systems and support equipment by utilizing AFTO Form 8, Heat Treatment Procedure Record. On-site Air Force (AF) contractors shall also use the Air Force Technical Order (AFTO) Form 8 unless their contract specifies a different method of heat treatment documentation. Personnel performing hardness testing shall document results on AFTO Form 8, Blocks 21-25. A paper or digital copy of the completed record shall be retained for 7 years by the facility performing the heat treatment.

## **2.8 HARDNESS TESTING.**

**2.8.1 General.** Hardness testing is an important factor in the determination of the results of the heat treatment as well as the condition of the metal before heat treatment and must, therefore, be carefully considered in connection with this work. The methods of hardness testing in general use are: the Brinell, Rockwell, Vickers, and Shore Scleroscope. Each of these methods is discussed in [Chapter 8](#).

**2.8.2 Tensile Strength.** Tempering temperatures listed with the individual steels in [Table 2-3](#) are offered as a guide for obtaining desired tensile and yield strength of the entire cross section. When the physical properties are specified in terms of tensile strength, but tension tests are impractical, hardness tests may be employed using the equivalent hardness values specified in [Table 8-5](#).

**2.8.3 Hardness-Tensile Strength Relationship.** The approximate relationship between the tensile strength and hardness is indicated in [Table 8-5](#). This table is to be used as a guide. It applied only to the plain carbon and low alloy steels not to



corrosion-resistant, magnet, valve, or tool steels. When a narrow range of hardness is required, the tests to determine the relationship between hardness and strength should be made on the actual part. Hardness values should be within a range of two points Rockwell or 20 points Brinell or Vickers. The tensile strength-hardness relationship is quite uniform for parts which are sufficiently large and rigid to permit obtaining a full depression on a flat surface without deflection of the piece. For cylindrical parts of less than inch in diameter, the Rockwell reading will be lower than indicated in the table for the corresponding tensile strength. Any process which affects the surface, such as buffing and plating, or the presence of decarburized or porous areas and hard spots, will affect the corresponding relation between hardness and tensile strength. Therefore, these surfaces must be adequately removed by grinding before measurements are made.

2.8.3.1 In making hardness measurements on tubular sections, correction factors must be determined and applied to the observed readings in order to compensate for the roundness and deflection of the tubing under the pressure of the penetrator. This may be impractical because every tube size end wall thickness would have a different factor. As an alternate, the following procedure may be used: Short lengths may be cut from the tube. A mandrel long enough to extend out both ends of the tube and slightly smaller in diameter than the inner diameter of the tube is then passed through the section and the ends supported in "V" supports on the hardness tester. Hardness readings may then be taken on the tubing.

2.8.4 **Specification Cross Reference.** [Table 2-2](#) is a cross reference index listing the steel and alloy types and the corresponding Federal, Military, and Industry specifications for the different configurations. Where two or more specifications cover the same material, stock material meeting the requirements of a military specification shall be used for all aeronautical structural items.

**Table 2-2. Specification Cross Reference**

Comp/Alloy Design	Form/Commodity	Industry	Federal	Military
1005	Rod and wire (steel and cast iron welding)	AMS 5030		
1008	Steel, sheet and strip, flat, aluminum coated low carbon	AMS 5036		
1010	Bars, Billets, Blooms, Slabs  Wire  Sheet and Strip Tubing, Seamless Rivets Strip (For Small Arms, bullets) Tubes, Seamless (Marine Boiler application) Electrode, Welding Rod and Wire (Welding Low Carbon Steel)	AMS 5040 / 5042 / 5044 / 5047 AMS 5050 AMS 7225  AWS A5.5 AMS 5027 / 5028 / 6452 / 6456 / 6457 / 6458 / 6459 / 6461	QQ-S-633  QQ-W-461 QQ-W-405 QQ-S-698	DOD-F-24669 MIL-S-11310 MIL-S-16788    MIL-S-13468 MIL-T-16286  MIL-E-23765/1E /4
1015, 1016, 1017, 1018, 1019	Bars, Billets, and Tubing (Mechanical)  Wire (Carbon) Plate, Sheet, and Strip Sheet, Strip Bars, and Billets Blooms and Slabs	AMS 5060 / 5061 / 5069  QQ-W-405 / QQ-W-461	QQ-S-640	MIL-S-7809 DOD-F-24669
1020	Bars, Billets, Blooms, Slabs			DOD-F-24669



Table 2-2. Specification Cross Reference - Continued

Comp/Alloy Design	Form/Commodity	Industry	Federal	Military
	Bars Wire (Carbon)  Sheet and Strip Plate (Carbon) Blooms, Billets, Slabs Tubing (Welded) Tubing (Seamless, Mechanical and Welded)	ASTM A29 AMS 5032  AMS 5045 / 5046	QQ-S-633 QQ-W-461 QQ-W-405 QQ-S-698 QQ-S-635  QQ-T-830	MIL-S-11310   MIL-S-16788 MIL-T-20162
1022	Bars and Forgings Plates (Up to 1 inch) Wire (Carbon) Bars, Billets, Blooms, Slabs Sheet and Strip Tubing, (Seamless, Mechanical and Welded)	AMS 5070   AMS-QQ-S-700	QQ-S-691 QQ-W-405  QQ-T-830	DOD-F-24669
1025	Bars Casting Tubing, Seamless Tubing, Welded Wire Sheet and Strip Plate	ASTM A29  AMS 5075 AMS 5077  AMS 5046	QQ-S-633 QQ-S-681  QQ-W-405 QQ-S-691	MIL-S-11310 MIL-C-24707
Corten	Plate, Sheet and Strip (High Strength)			MIL-S-12505
1035	Steel, Carbon (Bars, Forgings, and Tubings) Wire (Carbon)  Plate (Carbon) Tubing, Seamless Plate (Marine Boiler) Shapes, Bar and Plate (Structural) Sheet and Strip Forging (Naval Ship Board)	AMS 5080   AMS 5082	QQ-W-461 QQ-W-405 QQ-S-635  QQ-S-691 QQ-S-741 QQ-S-640	MIL-S-19434
1040	Bars Plate (Carbon) Castings Wire (Carbon) Bars Blooms, Billets, Bars and Slabs	ASTM A29	QQ-S-633 QQ-S-635 QQ-S-681 QQ-W-405	MIL-S-11310 DOD-F-24669
1045	Tubing, Seamless and Welded Bars Wire (Carbon) Plate (Carbon) Sheets and Strip	ASTM A29	QQ-T-830 QQ-S-633 QQ-W-461 QQ-S-635 QQ-S-640	
1050	Bars Plate (Carbon)	ASTM A29	QQ-S-633 QQ-S-635	



Table 2-2. Specification Cross Reference - Continued

Comp/Alloy Design	Form/Commodity	Industry	Federal	Military
	Blooms, Billets, and Slabs (For Forgings) Bars, Billets, Slabs, Castings	AMS 5085		MIL-S-16788
1055	Forgings (For Projectile Stock) Bars Electrodes	ASTM A29	QQ-S-633	MIL-S-10520 MIL-E-23765
1060	Bars Spring Blooms, Billets, Slabs, Forgings  Sheet and Strip	ASTM A29	QQ-S-633  QQ-S-640	MIL-S-2839 MIL-S-16788 DOD-F-24669
1070-1075	Sheet and Strip Wire, Spring Tool Steel Washers Bar Steel, Strip (Spring-Time Fuse) Strip, Spring	AMS 5115  SAE 7240 ASTM A29  AMS 5120 (1074)	QQ-T-580 FF-W-84 QQ-S-633	MIL-S-8143    MIL-DTL-11713
1080, 1086, 1090	Bars  Tool Steel Blooms, Billets, Slabs, Forgings Wire, Carbon Spring	ASTM A29  AMS 5110	QQ-S-633 QQ-T-580	MIL-S-16788
1095	Bars Wire, Spring Sheet, Strip Blooms, Billets, Slabs, Forgings Wire, Carbon Spring Steel Bars, Round, Square, and Flat for Springs	AMS 5132 / 8559 AMS-QQ-W-428 AMS 5121 / 5122	QQ-S-633	MIL-DTL-11713 MIL-S-16788 MIL-S-46033
1112	Bars		QQ-S-633	
1117	Steel, Bars, Forgings, and Tubing	AMS 5022	QQ-S-633	
1137	Steel, Bars, Forgings, and Tubing Tubing, Seamless and Welded	AMS 5024	QQ-S-633 QQ-T-830	
2137, 2330, 2340, 2515	Bars Wire (Alloy)		QQ-S-624 QQ-W-405	
3115, 3140, 3310	Blooms, Billets, Slabs, Forgings Wire (Alloy)		QQ-S-624 QQ-W-405	DOD-F-24669
4037	Bars Bars and Forging Wire (Alloy)	ASTM A29 AMS 6300	QQ-S-624 QQ-W-405	
4050	Tool Steel		QQ-T-570	
4130	Bars and Forging Sheet, Strip, and Plate Blooms, Billets, Slabs, Forgings  Tubing, Seamless Tubing, Mechanical	AMS 6370 / 6758 AMS 6350 / 6351  AMS 6030 / 6361 / 6362 AMS 6371		DOD-F-24669



Table 2-2. Specification Cross Reference - Continued

Comp/Alloy Design	Form/Commodity	Industry	Federal	Military
	Plate Sheet and Strip Wire (Alloy)		QQ-S-626 QQ-S-627 QQ-W-405	
4135	Bars Blooms, Billets, Slabs, Forgings Tubing, Seamless Tubing, Mechanical	ASTM A29  AMS 6365 / AMST-6735 AMS 6372	QQ-S-624	DOD-F-24669
17-22A	Bars and Forgings	AMS 6303		
4137	Bars	ASTM A29		
4140	Bars Bars and Forgings Tubing, Mechanical Blooms, Billets, Slabs, Forgings Wire (Alloy)	ASTM A29 AMS 6382 / 6349 AMS 6381	QQ-S-624  QQ-W-405	DOD-F-24669
4150	Bars Bar (For Small Arms Weapons Barrels) Bar (Special Bar for AF Bullet Cores and Shot)	ASTM A29	QQ-S-624	MIL-S-11595 MIL-S-12504
52100	Bars, Forgings, and Tubing	AMS 6444 / 6447 / 6440		
Nitralloy 135	Bars, Forgings, and Tubing Bars and Forgings	AMS 6470 AMS 6472		
4337	Bars and Forgings Tubing, Mechanical Wire (Alloy)	AMS 6412 / 6475 AMS 6413	QQ-W-405	
4340	Sheet, Strip, and Plate Bars Bars, Forgings, and Tubing Blooms, Billets, Slabs, Forgings Wire (Alloy)	AMS 6359 ASTM A29 AMS 6414 / 6415	QQ-S-624  QQ-W-405	DOD-F-24669
4335 (Mod)	Bars, Forgings, and Tubing	AMS 6428		
Hy-Tuf	Bars, Forgings, and Tubing	AMS 6418		
4615	Bars Bars and Forgings Blooms, Billets, Slabs, Forgings Wire (Alloy)	ASTM A29 AMS 6290	QQ-S-624  QQ-W-405	DOD-F-24669
4617	Bars	AMS 6292		
4620	Bars Bars and Forgings Wire (Alloy)	ASTM A29 AMS 6294	QQ-S-624  QQ-W-405	
4640	Blooms, Billets, Slabs, Forgings Bars Bars, Forgings, and Tubing Bars and Forgings Wire (Alloy)	ASTM A29 AMS 6312 AMS 6317	QQ-S-624  QQ-W-405	DOD-F-24669



Table 2-2. Specification Cross Reference - Continued

Comp/Alloy Design	Form/Commodity	Industry	Federal	Military
6150	Bars Wire (Spring) Sheet, Strip and Plate Springs (Highly Stressed)	ASTM A29 / AMS 6448 AMS-QQ-W-428 AMS 6445 AMS 7301	QQ-S-624	
8615	Bars Bars, Forgings, and Tubing Blooms, Billets, Slabs, Forgings Wire (Alloy) Castings	ASTM A29 AMS 6270  AMS 5333	QQ-S-624  QQ-W-405	DOD-F-24669
8617	Bars Bars, Forgings, and Tubing Sheet and Strip Wire (Alloy)	ASTM A29 AMS 6272	QQ-S-624  QQ-S-627 QQ-W-405	
8620	Bars Bars, Forgings, and Tubing Plate (Alloy) Sheet and Strip Wire (Alloy) Blooms, Billets, Slabs, Forgings	ASTM A29 AMS 6274	QQ-S-624  QQ-S-626 QQ-S-627 QQ-W-405	DOD-F-24669
8630	Bars Bars, Forgings Tubing, Mechanical Blooms, Billets, Slabs, Forgings Plate (Alloy) Wire (Alloy) Sheet and Strip	ASTM A29 AMS 6280 AMS 6281	QQ-S-624  QQ-S-626 QQ-W-405 QQ-S-627	MIL-S-6050  DOD-F-24669
8640	Bars Blooms, Billets, Slabs, Forgings Plate (Alloy) Tubing, Seamless, Mechanical Wire (Alloy)	ASTM A29  ASTM A519	QQ-S-624  QQ-S-626 QQ-W-405	DOD-F-24669
8735	Tubing, Mechanical Bars, Forgings Sheet, Strip, and Plate	AMS 6282 AMS 6320 AMS 6357		
8740	Bars Bars, Forgings Sheet, Strip, and Plate Plate (Alloy) Tubing, Mechanical Wire (Alloy)	ASTM A29 AMS 6322 / 6325 / 6327 AMS 6358  AMS 6323	QQ-S-624  QQ-S-626  QQ-W-405	
9620	Bars Wire (Spring) Steel, Strip	ASTM A29 AMS-QQ-W-428	QQ-S-624  QQ-S-777	MIL-S-46049
9262	Bars Wire (Alloy)	ASTM A29 AMS-QQ-W-428	QQ-S-624	



Table 2-2. Specification Cross Reference - Continued

Comp/Alloy Design	Form/Commodity	Industry	Federal	Military
	Sheet and Strip		QQ-S-627	
9310	Bars Bars, Forgings, and Tubing Wire (Alloy)	ASTMA29 AMS 6260 / 6265	QQ-S-624  QQ-W-405	
301	Sheet, Strip and Plate (Solution Heat Treated) Sheet and Strip (1/4 Hard) Sheet and Strip (1/2 Hard) Sheet and Strip (3/4 Hard) Sheet and Strip (Full Hard)	AMS 5901  AMS 5517 AMS 5518 AMS 5902 AMS 5519		
302	Sheet, Strip, and Plate (Solution Heat Treated) Sheet and Strip (1/4 Hard) Sheet and Strip (1/2 Hard) Sheet and Strip (3/4 Hard) Sheet and Strip (Full Hard) Wire, Spring Temper Bars, Cold Drawn 100 Kips per Square Inch (KSI) Bars, Cold Drawn 125 KSI	AMS 5516  AMS 5903 AMS 5904 AMS 5905 AMS 5906 AMS 5688 AMS 5636 AMS 5637		
303	Bars Bar, Forging (Swaging) Bars, Wire, and Forgings	AMS 5738 AMS 5641 AMS 5640		
304	Sheet, Strip, and Plate (Solution Heat Treated) Sheet and Strip (1/4 Hard) Sheet and Strip (1/2 Hard) Sheet and Strip (3/4 Hard) Sheet and Strip (Full Hard) Wire Tubing, Seamless or Welded Bars, Wire, Forgings, Mechanical Tubing	AMS 5513  AMS 5910 AMS 5911 AMS 5912 AMS 5913 AMS 5697 AMS 5566 / 5567 AMS 5647		
314	Bars, Wire, Forgings, and Tubing Sheet, Strip, and Plate (Solution Heat Treated)	AMS 5652 AMS 5522		
316	Sheet, Strip, and Plate (Solution Heat Treated) Sheet and Strip, (1/4 Hard) Casting, Investment Casting, Sand, Centrifugal Tubing, Seamless Bars, Forgings, and Tubing Electrode, Welding, Coated Pipe, Seamless and Welded Bars, Billets, Reforgings	AMS 5524  AMS 5907 AMS 5360 AMS 5361 AMS 5573 AMS 5648 AMS 5691		MIL-P-1144 MIL-S-862
321	Sheet, Strip, and Plate (Solution Heat Treated)	AMS 5510 / 5645 / AMS-QQ-S-763		



Table 2-2. Specification Cross Reference - Continued

Comp/Alloy Design	Form/Commodity	Industry	Federal	Military
	Tubing, Seamless Tubing, Welded Tubing, Seamless, Welded Tubing, Welded, Thin Wall Wire Pins, Cotter	AMS 5570 AMS 5576 AMS 5557 AMS 5559 AMS 5689 AMS 7211		
347	Sheet, Strip, and Plate (Solution Heat Treated) Bars, Wires, Forgings, and Tubing Casting, Investment Casting, Sand, Centrifugal Tubing, Seamless Tubing, Welded Tubing, Seamless, Welded Tubing, Welded Tube, Seamless (Marine Boiler Application) Rods and Wire, Welding	AMS 5512 / AMS-QQ-S-763 AMS 5646 AMS 5362 AMS 5363 AMS 5571 AMS 5575 AMS 5556 AMS 5558  AWS A5.9 / A5.1	QQ-S-682	MIL-T-16286
410	Blooms, Billets, Slabs, Forgings Bars, Wire, and Forgings Bars, Wire, Forgings, and Tubing Sheet, Strip, and Plate Casting, Investment Casting, Sand Wire Tubing, Seamless Tubing, Flexible	AMS 5614 AMS 5612 / 5613 / 5609 AMS 5504 / 5505 AMS 5350 AMS 5351  AMS 5591	QQ-W-423	DOD-F-24669  MIL-T-7880
414	Blooms, Billets, Slabs, Forgings Bars and Forgings	AMS 5615		DOD-F-24669
416	Blooms, Billets, Slabs, Forgings Bars, Wires, and Forgings	AMS 5610		DOD-F-24669
420	Blooms, Billets, Slabs, Forgings Bars, Wire, and Forgings Bars, Wire, and Forgings (Free Mach) Sheet, Strip, and Plate Wire	AMS 5621 AMS 5620 AMS 5506	QQ-W-423	DOD-F-24669
431	Blooms, Billets, Slabs, Forgings Bars, Wires, and Forgings Casting, Sand Casting, Investment	AMS-QQ-S-763 AMS 5372 AMS 5353		DOD-F-24669
440 C	Bars, Wires, and Forgings	AMS 5630		
440 A	Bars, Wires, and Forgings	AMS 5631		
440 F	Bars, Wires, and Forgings	AMS 5632		
PH13-8Mo	Bars, Wire Forgings Rings, Extrusion	AMS 5629 / 5934		
14-4	Casting, Investment	AMS 5340		
	Casting, Investment	AMS 5400		



Table 2-2. Specification Cross Reference - Continued

Comp/Alloy Design	Form/Commodity	Industry	Federal	Military
15-5PH	Bar, Forging, Ring, and Extrusion Rolled and/or forged bar Sheet, Strip, and Plate	AMS 5659 AMS 5659 H1025 AMS 5682		
15-7 Molybdenum	Sheet, Strip, and Plate (Solution Heat Treated) Bars and Forgings	AMS 5520 AMS 5657		
17-4PH	Bars, Wire, Forgings, and Tubing Casting, Investment Casting, Investment 130 KSI Casting, Investment 150 KSI Casting, Investment 180 KSI Electrode, Welding	AMS 5643 AMS 5355 AMS 5342 AMS 5343 AMS 5344 AWS A5.4		
17-7PH	Sheet, Strip, and Plate (Solution Heat Treated) Bars and Forgings Tubing, Welded	AMS 5528 AMS 5644 AMS 5568		
19-9DL	Bar Bar and Forging Casting, Sand (Solution Heat Treated) Sheet, Strip, and Plate	AMS 5720 / 5721 AMS 5722 AMS 5369 AMS 5526 / 5527		
19-9DX	Bar Bar and Forging Sheet, Strip, and Plate	AMS 5724 / 5729 AMS 5723 AMS 5538 / 5539		
19-9 MOD	Electrode, Welding, Covered (Armor Applications)			MIL-E-13080
AM 350	Bars and Forgings Sheet and Strip (High Temperature Annealed) Tubing, Seamless Wire, Welding Electrode, Welding, Coated Wire	AMS 5745 AMS 5748 AMS 5554 AMS 5774 AMS 5775		MIL-S-6271
AM 355	Bars and Forgings Sheet and Strip (Solution Heat Treated) Plate (Solution Heat Treated) Plate (Equalized and Overtempered) Electrode, Coated Welding	AMS 5743 AMS 5547 AMS 5549 AMS 5594 AMS 5781		
A286	Bars, Wire, Forgings, and Tubing  Rivets, Steel (Annealed 1650 °F and partially precip treated)	AMS 5734 / 5735 / 5736 / 5737 AMS 7235		
Rene 41	Bars and Forging Sheet, Strip, and Plate	AMS 5712 / 5713 AMS 5545		
Greek Ascoloy (418)	Castings, Investment Sheet, Strip, and Plate Bars, Wire, Forgings, Tubing and Rings	AMS 5354 AMS 5508 AMS 5616		
Inconel 600	Sheet, Strip, and Plate Bar and Rod	AMS 5540 ASTM B 166		



**Table 2-2. Specification Cross Reference - Continued**

Comp/Alloy Design	Form/Commodity	Industry	Federal	Military
	Forging Tubing, Seamless	ASTM B 565 AMS 5580		
Inconel X750	Sheet, Strip and Plate Bars and Forgings Wire, Number (No.) 1 Temper Wire, Spring Temper	AMS 5542 AMS 5667 AMS 5698 AMS 5699		
Hastelloy C	Castings, Investment Casting, Sand Sheet, Strip, and Plate Bars, Forgings, and Rings	AMS 5388 AMS 5389 AMS 5530 AMS 5750		
Hastelloy W	Bars and Forgings Wire Electrode, Welding, Bare	AMS 5755 AMS 5786 AWS A5.14		
Hastelloy X	Bars and Forging Sheet and Plate	AMS 5754 AMS 5536		
Waspalloy	Sheet, Strip, and Plate	AMS 5544		
<b>MISC STANDARDS / SPECIFICATIONS – METAL PRODUCTS / PROCESSING</b>				
Steel: Chemical Composition and Hardenability Metal Test Methods			Fed Std 66 Fed Std 151	
Corrosion Resistant Steel Parts: Surface Passivation Sampling, Inspection, Testing for Surface Passivation		AMS 2700 AMS-STD-753		
Markings, Functions and Hazards Designations of Hose, Pipe, and Tube Lines for Aircraft missile, and Space Systems				MIL-STD-1247
Preparation of Test Reports				MIL-HDBK-831
Metals & Alloys in the Unified Numbering System		SAE HS-1086		
Inspection, Radiographic		ASTM E1742		
Standard Methods of Mechanical Testing of Welds		AWS B4.0		
Non-Destructive Inspection (NDI) Testing, Personnel Qualification and Testing		NAS 410		
Standard Practice for Temper Designations of Magnesium Alloys, Cast and Wrought		ASTM B296		
Tolerance for Copper and Copper Alloy: Seamless Tubing Sheet, Strip, and Plate Bars and Rods Wire		AMS 2221 AMS 2222 AMS 2223 AMS 2224		
Identification Bars, Wire, Mechanical Tubing, and Extrusions, Carbon, Alloy Steels, Corrosion & Heat Resistant Steels and Alloys		AMS 2806		
Identification Carbon and Low Alloy Steels, Corrosion and Heat Resistant Steels and Alloy Sheet, Strip, Plate, and Aircraft Tubing		AMS 2807		
<b>MISC STANDARDS / SPECIFICATIONS – METAL PRODUCTS / PROCESSING</b>				
Identification Forgings		AMS 2808		
Identification Titanium and Titanium Alloy Wrought Products		AMS 2809		



Table 2-2. Specification Cross Reference - Continued

Comp/Alloy Design	Form/Commodity	Industry	Federal	Military
Identification Marking of Aluminum and Magnesium Products		ASTM B666		
Identification Marking of Copper and Copper Base Alloy Mill Products		AMS-STD-185		
Identification of Pressed Bends, Forms, Seams, and Joints (Sheet Metal)			FED-STD-187	
Tolerances for Aluminum Alloy and Magnesium Alloy Wrought Products			FED-STD-245	
Standard Guide for Packaging, Marking, and Loading Methods for Steel Products for Shipping		ASTM A700		
Tolerances for Steel and Iron Wrought Products			FED-STD-48	

## 2.9 GENERAL HEAT TREATING TEMPERATURES, COMPOSITION (CHEMICAL) AND CHARACTERISTICS OF VARIOUS STEEL AND STEEL ALLOYS.

See supplement data for chemical symbols.

**2.9.1 1010 Low Carbon.** Low Carbon steel of this grade is used for manufacture of such articles as safety wire, certain nuts, cable bushings and threaded rod ends, and other items where cold formability is the primary requisite. Heat treatment is frequently employed to improve machinability. Welding is easily accomplished by all common welding methods.

### Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Iron Percent
0.08-0.13	0.3-0.6	0-0.04	0-0.5	Balance

Forms. See Specification [Table 2-2](#).

### Heat Treatment

Normalize: 1650 °F-1750 °F, cool in still air.

Anneal: 1650 °F

Harden: 1650 °F-1750 °F. Quench in oil (minimum hardness) Water, and Brine (maximum hardness).

**2.9.2 1015 Low Carbon.** This material is similar in content and characteristics to 1010. Of low tensile value, it should not be selected where strength is required.

### Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Iron Percent
0.13-18	0.3-0.6	0-0.04	0-0.05	Balance

Forms. See Specification [Table 2-2](#).

### Heat Treatment

Normalize: 1650-1750 °F, cool in still air.

Anneal: 1600-1650 °F

Harden: 1650-1700 °F. Quench with water, oil, brine.

**2.9.3 1020 Low Carbon.** Because of the carbon range this metal has increased strength and hardness but reduced cold formability compared with the lowest carbon group. It finds wide application where carburizing is required. It is suitable for welding and brazing.

### Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Iron Percent
----------------	-------------------	--------------------	----------------	--------------



8-0.23      0.3-0.6      0-0.04      0-0.05      Balance  
Forms-Specifications.      See Specification [Table 2-2](#).

Heat Treatment

Normalize:      1700 °F, air cool.  
Anneal:      1600 °F, furnace cool.  
Harden:      1600 °F, quench with water, oil, brine.

CARBO-NITRIDING

Temperature	Time	Case	Depth	Hardness	Cool	Draw
1560	2.5	0.019		62	OQ	350
1650	2.5	0.018		59	OQ	350

For 1560 °F, use 35NH<sub>3</sub>d 25CH<sub>4</sub> generator gas\*.

For 1650 °F, use 38NH<sub>3</sub> and 24CH<sub>4</sub>.

\*Gas - American Gas Assoc Class [302](#).

2.9.4 1022 Low Carbon. This steel is similar in content and heat treatment requirements to 1020. Typical applications are case hardened roller chains, bearing races, cam shafts, etc.

Composition Range

Carbon Percent	Magnesium Percent	Silicon Percent	Phosphorus Percent	Sulfur Percent	Iron Percent
0.18-0.23	0.7-0.10	0-0.2	0-0.04	0-0.05	Balance

Forms-Specifications.      See Specification [Table 2-2](#).

Heat Treatment

Normalize:      1700 °F, air cool.  
Anneal:      1600 °F, furnace cool.  
Carburize:      1550-1650 °F, water quench.  
Tensile:      130,000 Pound-force per Square  
Inch (PSI)  
Yield:      78,000 PSI

2.9.5 1025 Low Carbon. Typical applications are bolts, machinery, electrical equipment, automotive parts, pipe flanges, etc. With this steel no martensite is formed and tempering is not required. This material is not generally considered a carburizing type; however, it is sometimes used in this manner for larger sections, or where greater case hardness is needed.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Iron Percent
0.22-0.28	0-0.6	0-0.04	0-0.05	Balance

Forms-Specifications.      See Specification [Table 2-2](#).

Heat Treatment

Normalize:      1600-1700 °F, furnace cool.  
Hardening:      1575-1650 °F, water quench.  
Carburize:      1650-1700 °F, water or brine quench.  
Tempering:      250-400 °F is optional  
Tensile strength:      Hot rolled 67,000, cold rolled 80,000.  
Yield strength:      Hot rolled 45,000, cold rolled 68,000.  
Temper:      1150 °F for 70,000 PSI.

2.9.6 Corten, Low Carbon, Low Alloy. This steel is not heat treatable, but in the annealed or normalized condition it is stronger than plain carbon steel, is easily formed, welded and machined. In addition, this alloy is 4-6 times more resistant to atmospheric corrosion than plain carbon steel.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

Composition Range

Carbon Percent	Chromium Percent	Copper Percent	Magnesium Percent	Nickel Percent
0-0.12	0.30-1.25	0.25-0.055	0.2-0.5	0-0.65
Silicon Percent	Phosphorus Percent	Sulfur Percent	Iron Percent	
0.25-0.75	0.07-0.15	0-0.05	Balance	

Heat Treatment

Normalize: 1650 °F, air cool.  
 Anneal: 1550 °F, furnace cool.

2.9.6.1 Stress relief 1150 °F, 1 hour per inch of maximum section thickness. This alloy cannot be hardened. Tensile strength, annealed or normalized 67,000 PSI. Yield strength, annealed or normalized 47,000 PSI. This alloy is readily welded by the usual gas and arc methods with complete freedom from air hardening. ASTM A233 or E60 electrodes are recommended for shielded arc welding. For gas welding, high strength welding rods such as ASTM A251, CA-25, are recommended. This steel may be resistance welded to itself or other resistance weldable ferrous alloys, using the same methods applied to plain carbon steel.

2.9.7 NAXAC9115 Low Carbon, Low Alloy. This material is usually in the stress relieved condition. Moderate strength is maintained with high toughness up to approximately 800 °F. Weldability is excellent and it machines better than carbon steels of the same tensile strengths.

Composition Range

Carbon Percent	Chromium Percent	Copper Percent	Magnesium Percent
0.1-0.17	0.5-0.75	0-0.35	0.5-0.8
Molybdenum Percent	Nickel Percent	Silicon Percent	Zinc Percent
0.15-0.25	0-0.25	0.6-0.9	0.05-0.15
Phosphorus Percent	Sulfur Percent	Iron Percent	
0-0.04	0-0.04	Balance	

Specifications

AMS	FORM
6354	Sheet, strip, plate.
6440	Wire.

Heat Treatment

Anneal: 1625-1650 °F, furnace cool.  
 Normalize: 1650-1675 °F, air cool.

2.9.7.1 Stress relief anneal 900-1150 °F, air cool, 30 minutes to 6 hours. Typical room temperatures: tensile 76,500, yield 53,000. For arc welding, use low hydrogen electrodes E6015 (thin gauges) and E7015. For heliarc welding use drawn filler wire of MIL-R-5032. Perform spot welding by pulsation method for heavier gauges; use post heat cycle for lighter gauges.

2.9.8 1035 Medium Carbon. This steel is selected where higher mechanical properties are needed since it may be further hardened and strengthened by heat treatment or by cold work. Typical applications are gears, clutch pedals, flywheel rings, crank shafts, tools and springs.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Iron Percent
0.32-0.38	0.6-0.9	0-0.04	0-0.05	Balance

Form Specifications See Specification [Table 2-2](#).

Heat Treatment

Normalize: 1575-1650 °F, cool in still air.  
 Anneal: 1575-1650 °F, 1 hour per 1 inch of section, (Preheat) Temper at 900 °F for 100,000 PSI.



Spheroidize: 1250-1375 °F.  
Harden: 1525-1600 °F, quench in water or oil.  
(Brine or caustic may also be used for quenching.)

2.9.8.1 Weldability is very good by all common welding methods. Cold formability is poor, but hot formability is excellent. Tensile strength, hot rolled 85,000 PSI, cold rolled 92,000 PSI, yield strength, hot rolled 54,000 PSI, cold rolled 79,000 PSI, Brinill 183-201, respectively.

2.9.9 1040 Medium Carbon. Medium Carbon is selected where intermediate mechanical properties are needed and may be further hardened and strengthened by heat treatment or cold work.

Composition Range

Carbon Percent	Magnesium Percent	Silicon Percent	Phosphorus Percent	Sulfur Percent	Iron Percent
0.37-0.44	0.6-0.9	0-0.2	0-0.04	0-0.05	Balance

Form Specifications

See Specification [Table 2-2](#).

Heat Treatment

Normalize: 1575-1650 °F, air cool.  
Anneal: 1550-1650 °F, furnace cool. (Tensile 79,000 PSI, yield 48,000 PSI annealed).  
Harden: 1500-1575 °F, water or oil quench.  
Temper: 1100-1150 °F, to obtain tensile 100,000 PSI, yield 80,000 PSI. For tensile 125,000 and yield 85,000 PSI temper at 700 °F. Suitable heat treatment is required to permit machining.

2.9.10 1045 Medium Carbon. Forgings such as connecting rods, steering arms, axles, axle shafts and tractor wheels are fabricated from this steel. Not recommended for welding.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Iron Percent
0.43-0.5	0.6-0.9	0-0.04	0-0.04	Balance

Form Specifications

See Specification [Table 2-2](#).

Heat Treatment

Normalize: 1575-1675 °F, air cool.  
Anneal: 1550-1600 °F, furnace cool for maximum softness.  
Harden: 1475-1550 °F, quench, water or oil.  
Temper: 1100 °F for tensile 100,000 PSI, yield 65,000 PSI.  
Temper: 1000 °F for tensile 125,000 PSI, yield 95,000 PSI.

2.9.11 1050 Medium Carbon. This is a medium carbon type steel with high mechanical properties which may be further hardened and strengthened by heat treatment or by cold work. Application is similar to 1045. Not recommended for welding.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Iron Percent
0.46-0.55	0.6-0.9	0-0.04	0-0.05	Balance

Form Specifications

See Specification [Table 2-2](#).

Heat Treatment

Normalize: 1550-1650 °F, air cool.  
Anneal: 1450-1525 °F, furnace cool (Tensile 90,000 yield 50,000 annealed.)  
Harden: 1475-1550 °F, oil or water quench.  
Temper: 1250 °F for 125,000 PSI tensile, 90,000 for yield.  
Temper: 1025 °F for 125,000 PSI tensile, 90,000 for yield.  
Temper: 700 °F for 150,000 PSI tensile, 114,000 for yield.

2.9.12 1055 High Carbon. Steels of this Type (1060, 1070, 1080 are in same category) have similar characteristics and are primarily used where higher carbon is needed to improve wear characteristics for cutting edges, as well as for manufacture of springs, etc. Not recommended for welding.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Iron Percent
0.50-0.60	0.6-0.9	0-0.04	0-0.05	Balance

Form Specifications

See Specification [Table 2-2](#).

Heat Treatment

Normalize:	1550-1650 °F, air cool.
Anneal:	1550-1575 °F.
Harden:	1450-1550 °F, water or oil quench.
Temper:	1250 °F for 100,000 PSI tensile, 1050 °F for 125,000 tensile, 600 °F for 150,000 tensile.

**2.9.13** 1060 High Carbon. See 1055 for application and characteristics.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Iron Percent
0.55-0.65	0.6-0.09	0-0.04	0-0.05	Balance

Form Specifications

See Specification [Table 2-2](#).

Heat Treatment

Normalize:	1525-1625 °F, air cool.
Anneal:	1500-1575 °F (Tensile 104,000 PSI, yield 54,000 PSI annealed).
Harden:	1450-1550 °F, water or oil quench.
Temper:	1125 °F for 130,000 tensile, 80,000 yield.
Temper:	1025 °F for 139,000 tensile, 96,000 yield.
Temper:	925 °F for 149,000 tensile, 99,000 yield.

**2.9.14** 1070 High Carbon. See 1055 for application and characteristics. In addition this alloy is used for flat springs and wire form as coil springs.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Iron Percent
0.65-0.75	0.6-0.9	0-0.04	0-0.05	Balance

Form Specifications

See Specification [Table 2-2](#).

Heat Treatment

Normalize:	1525-1625 °F, air cool, retard cooling rate to prevent hardness.
Anneal:	1500-1575 °F, furnace cool.
Harden:	1450-1550 °F, water or oil quench (Preheat).
Hot Working Temperature:	1550-1650 °F.
Temper:	1250 °F for 100,000 PSI tensile.
Temper:	1100 °F for 125,000 PSI tensile.
Temper:	1000 °F for 150,000 PSI tensile.

**2.9.14.1** The high carbon content of this steel causes difficulties in arc or gas welding processes. Welding by the thermit process is satisfactory. Hot formability is very good at 1550-1650 °F.

**2.9.15** 1080 High Carbon. See 1055 for application and characteristics.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Iron Percent
0.75-0.88	0.6-0.9	0-0.04	0-0.05	Balance

Form Specifications

See Specification [Table 2-2](#).

Heat Treatment

Normalize:	1550-1650 °F, air cool.
------------	-------------------------



Anneal:	1475-1525 °F (Tensile 120,000, yield 66,000 PSI annealed).
Harden:	1450-1550 °F, quench oil.
Temper:	1200 °F for 129,000 tensile, 87,000 yield.
Temper:	1100 °F for 145,000 tensile, 103,000 yield.
Temper:	900 °F for 178,000 tensile, 129,000 yield.

2.9.15.1 The high carbon content of this steel causes difficulties in arc or gas welding processes. Welding by the thermit process is satisfactory. Hot formability is very good at 1550-1650 °F.

2.9.16 1095 High Carbon. See 1055 for applications. In addition these steels are used for flat spring applications and in wire form as coil springs.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Iron Percent
0.9-1.03	0.3-0.5	0-0.04	0-0.05	Balance

Form Specifications

See Specification [Table 2-2](#).

Heat Treatment

Oil Quench

Normalize:	1550-1650 °F, air cool.
Anneal:	1425-1475 °F (Tensile 98,000 PSI, yield 52,000 PSI annealed) furnace cool. To reduce annealing time, furnace cool to 900 °F and air cool. Spheroidize for maximum softness when required.
Harden:	1425-1550 °F, (oil quench.)
Temper:	1100 °F for 146,000 PSI tensile, 88,000 yield.
Temper:	800 °F for 176,000 PSI tensile, 113,000 yield.
Temper:	600 °F for 184,000 PSI tensile, 113,000 yield.

Water Quench

Normalize:	1550-1650 °F, air cool.
Anneal:	1425-1475 °F.
Harden:	1425-1500 °F, quench with water.
Temper:	1100 °F for 143,000 PSI tensile, 96,000 yield.
Temper:	800 °F for 200,000 PSI tensile, 138,000 yield.
Temper:	600 °F for 213,000 PSI tensile, 150,000 yield.

2.9.17 1112 Free Cutting. This steel is used as the standard for rating the machinability of other steels. It is easy to machine and resulting surface finish is excellent. It has good brazing characteristics but is difficult to weld except with the low hydrogen electrode E6015 American Welding Society (AWS). This and similar grades are widely used for parts for bolts, nuts, screws, but not for parts subjected to severe stresses and shock.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Iron Percent
0-0.13 maximum	0.7-0.9	0.07-0.12	0.16-0.23	Balance

Form Specifications

See Specification [Table 2-2](#).

Heat Treatment

May be surface hardened by heating in cyanide at 1500-1650 °F, followed by single or double quench and draw. Preheat and soak at 1500-1650 °F and quench in oil or water; tempering is optional.

Tensile strength hot rolled bars 65,000.

Tensile strength cold drawn 83,000.

2.9.18 1117 Carbon (Free Cutting Steel). This material is used where a combination of good machinability and uniform response to heat treatment is needed. It is suited for fabrication of small parts which are to be cyanided or carbonitrided and may be oil quenched after case hardening heat treating.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Iron Percent
----------------	-------------------	--------------------	----------------	--------------



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

0.41-0.2	1.0-1.3	0-0.04	0.08-0.13	Balance
<u>Form Specifications</u>		See Specification <a href="#">Table 2-2</a> .		
<u>Heat Treatment</u>				
Normalize:	1650 °F, air cool.			
Anneal:	1575 °F, furnace cool (Tensile 68,000 PSI annealed)			
Harden:	1450 °F, quench in water			
<u>Single Quench And Temper</u>				
Carburized 1700 °F for 8 hours.				
Pot Cool				
Reheat to 1450 °F.				
Quench in water.				
Temper at 350 °F.				
Case depth 0.045.				
Case hardness 65 RC.				

**2.9.19 1137 Carbon, Free Cutting.** This steel is intended for those uses where easy machining is the primary requirement. It is characterized by a higher sulphur content than comparable carbon steels, which result in some sacrifice of cold forming properties, weldability and forging characteristics.

<u>Composition Range</u>				
Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Iron Percent
0.32-0.39	1.35-1.65	0-0.04	0.08-0.13	Balance
<u>Form Specifications</u>		See Specification <a href="#">Table 2-2</a> .		
<u>Heat Treatment</u>				
Normalize:	1600-1700 °F, air cool.			
Anneal:	1400-1500 °F, furnace cool.			
Harden:	1525-1575 °F, oil or water quench.			
<u>Typical Strength of Oil Quenched</u>				
Temper:	1100 °F for tensile 100,000 PSI, yield 80,000 PSI.			
Temper:	825 °F for tensile 125,000 PSI, yield 100,000 PSI.			
<u>Typical Strength of Water Quenched</u>				
Temper:	1100 °F for tensile 105,000 PSI, yield 90,000 PSI.			
Temper:	975 °F for tensile 125,000 PSI, yield 100,000 PSI.			
Tensile strength:	85,000 PSI, yield 50,000 PSI in annealed condition.			

**2.9.20 2317 Nickel Alloy.** These specifications cover steel castings for valves, flanges, fittings and other pressure containing parts intended principally for low temperature parts.

Composition Range						
Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Nickel Percent	Iron Percent
15-0.2	0.4-0.6	0.04	0.04	0.2-0.35	3.25	Balance
Form Specifications		See Specification <a href="#">Table 2-2</a> .				
Heat Treatment						
Normalize:	1600-1700 °F, air cool					
Anneal:	1500-1550 °F					
Harden:	1375-1525 °F					
Carburize:	1650-1700 °F, reheat to 1450-1550 °F, temper at 250-300 °F.					
Water Quench						
Temper:	1100 °F for tensile 100,000 PSI, yield PSI 83,000.					
Temper:	875 °F for tensile 125,000 PSI, yield PSI 100,000.					
Temper:	750 °F for tensile 150,000 PSI, yield PSI 124,000.					



Oil Quenched

Temper: 1025 °F for tensile 100,000 PSI, yield PSI 83,000.  
Temper: 850 °F for tensile 125,000 PSI, yield PSI 88,000.  
Tensile strength: 650 °F for tensile 150,000 PSI, yield PSI 108,000.

This steel may be welded by common welding procedures.

2.9.21 2330 Nickel Alloy. This is a heat treatable steel which develops high strength and toughness in moderate sections. It is used in highly stressed bolts, nuts, studs, turnbuckles, etc.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Nickel Percent	Iron Percent
0.28-0.33	0.6-0.8	0-0.04	0-0.04	0.2-0.35	3.25-0.75	Balance

Form Specifications

See Specification [Table 2-2](#).

Heat Treatment

Normalize: 1600 °F, preheat, cool in air.  
Anneal: 1425-1600 °F, furnace cool.  
Harden: 1400-1500 °F. Quench with oil.  
Temper: 1200-1250 °F for tensile 100,000 PSI, yield 90,000 PSI.  
Temper: 900 °F for tensile 140,000 PSI.  
Temper: 700 °F for 178,000 PSI.

Water Quench

700 °F - 190,000 PSI  
900 °F - 150,000 PSI  
1100 °F - 124,000 PSI

2.9.22 2340 Nickel Alloy. This metal is similar to 2330, but has greater strength. It is an oil hardening steel.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Nickel Percent
0.38-0.43	0.7-0.9	0-0.04	0-0.04	0.2-0.35	3.25-3.75

Form Specifications

See Specification [Table 2-2](#).

Heat Treatment

Normalize: 1600-1700 °F.  
Anneal: 1450-1600 °F.  
Harden: 1400-1550 °F, quench in oil.  
Temper: 1100 °F for 125,000 PSI tensile, 105,000 PSI yield.  
Temper: 900 °F for 150,000 PSI tensile, 132,000 PSI yield.  
Temper: 800 °F for 182,000 PSI tensile, 164,000 PSI yield.

2.9.23 2515 Nickel Alloy. This steel is quite similar to SAE 2512 and 2517, both in composition and response to heat treatment.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Nickel Percent	Iron Percent
0.12-0.17	0.4-0.6	0-0.04	0-0.04	0.2-0.35	4.75-5.25	Balance

Form Specifications

See Specification [Table 2-2](#).

Heat Treatment

Normalize: 1650-1750 °F  
Anneal: 1500 °F



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

Harden: 1425-1525 °F, oil quench.  
 Temper: 1200 °F for tensile 104,000, yield 80,000 PSI.  
 Temper: 900 °F for tensile 125,000, yield 106,000 PSI.  
 Temper: 700 °F for tensile 152,000, yield 125,000 PSI.

Water Quench

Temper: 1100 °F for 116,000 PSI.  
 Temper: 900 °F for 138,000 PSI.  
 Temper: 700 °F for 165,000 PSI.

**2.9.24 3115 Steel Nickel Chromium Alloy.**

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Nickel Percent	Chromium Percent	Iron Percent
0.11-0.2	0.37-0.63	0-0.048	0-0.058	0.18-0.37	1.05-1.45	0.52-0.78	Balance

Form Specifications See Specification [Table 2-2](#).

Heat Treatment

Normalize: 1625-1725 °F  
 Anneal: 1550-1600 °F  
 Harden: 1425-1525 °F, with oil.  
 Temper: 300 °F for tensile, 125,000 PSI, yield 86,000 PSI.

<u>Core Properties</u>	<u>Draw Temperature</u>	<u>Tensile KSI</u>	<u>Yield KSI</u>
3115	300 °F	125	88
Box cooled 1425 °F			
3120	300 °F	155	115
3115	300 °F	125	86
Reheated 1475 °F			
3120	300 °F	155	115
3115	300 °F	125	86
Oil Quenched 1525 °F			
3120	300 °F	155	110

**2.9.25 3140 Nickel Chrome Alloy.** This is a medium deep hardening steel capable of developing good strength and toughness when oil quenched.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Nickel Percent	Chromium Percent	Iron Percent
0.37-0.45	0.6-0.95	0-0.04	0-0.04	0.2-0.35	1.0-1.5	0.5-0.8	Balance

Form Specifications See Specification [Table 2-2](#).

Heat Treatment

Normalize: 1550-1700 °F  
 Anneal: 1475-1550 °F (Tensile 94,000 PSI, yield 66,000 PSI annealed).  
 Harden: 1475-1550 °F, oil quench.  
 Temper: 1200 °F for tensile 125,000 PSI, yield 105,000 PSI.  
 Temper: 1000 °F for Tensile 14,000 PSI, yield 125,000 PSI.  
 Temper: 800 °F for Tensile 184,000 PSI, yield 178,000 PSI.  
 Temper: 700 °F for Tensile 200,000 PSI.



**2.9.26 3310 Nickel - Chromium Alloy.** This steel has exceptionally high hardenability and is well suited for heavy parts which must have high, surface hardness combined with high and uniform properties when heat treated. It is commonly used in case hardened gears, pinions, etc. It is similar to Krupp Nickel Chromium except it contains more nickel.

Composition Range

Carbon Percent	Magnesium Percent	Silicon Percent	Nickel Percent	Chromium Percent	Phosphorus Percent	Sulfur Percent	Iron Percent
0.08-0.13	0.45-0.6	0.2-0.35	3.25-3.75	1.4-1.75	0-0.025	0-0.25	Balance

Form Specifications

See Specification [Table 2-2](#).

Heat Treatment

Normalize: 1600-1700 °F, air cool.  
 Anneal: 1475-1575 °F, furnace cool to 700 °F, air cool.  
 Quench: 1500-1550 °F, Oil, Cool Slowly  
 Carburize: 1700 °F, for 8 hours, reheat to 1500 °F, oil quench, temper 300 °F, for tensile 170,000 PSI, yield 142,000 PSI. Effective case depth 0.05 inch.

**2.9.27 4037 Molydenum Alloy.** This steel is used for such parts as gears, shafts, leaf and coil springs and hand tools.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Molybdenum Percent	Iron Percent
0.35-0.4	0.7-0.9	0-0.04	0-0.04	0.2-0.35	0.2-0.3	Balance

Form Specifications

See Specification [Table 2-2](#).

Heat Treatment

Normalize: 1600 °F, cool in air.  
 Anneal: 1500-1600 °F, furnace cool.  
 Harden: 1550 °F, quench in oil.  
 Temper: 1225 °F for 100,000 PSI.  
 Temper: 1100 °F for 125,000 PSI.  
 Temper: 975 °F for 150,000 PSI.

**2.9.28 4130 Chromium - Molydenum Alloy.** Typical usages for this material is in the manufacture of gear shafts axles, machine tool parts, etc.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Chromium Percent	Molybdenum Percent	Nickel Percent	Iron Percent
0.26-0.35	0.3-0.75	0-0.04	0-0.05	0.15-0.35	0.75-1.2	0.08-0.25	0-0.25	Balance

Form Specifications

See Specification [Table 2-2](#).

Heat Treatment

Harden (austenitize): 1550-1600 °F, water quench, for oil quench 1575 °F-1625 °F.  
 Austenitize: 1600-1650 °F, 1 hour, oil quench.  
 Castings:  
 Spheroidize: 1400-1425 °F, 6-12 hours, furnace cool.  
 Temper: 1150 °F for tensile 132,000, yield 122,000.  
 Temper: 1025 °F for tensile 151,000, yield 141,000.  
 Temper: 950 °F for tensile 163,000, yield 159,000.  
 SAE Steels: 8630 and 8730 have similar characteristics.  
 Annealed: 1525-1585 °F (tensile 80,000 PSI, yield 57,000 PSI annealed), furnace cool.



## TO 1-1A-9 NAVAIR 01-1A-9

Normalize: (cast) 1900 °F, 1 hour, AC Hardening: 1550-1650 °F, quench in oil.

Normalize: (wrought) 1600-1700 °F, air cool.

### 2.9.29 4135 Chromium Molydenum Alloy.

#### Composition Range

Carbon Percent	Magnesium Percent	Silicon Percent	Chromium Percent	Molybdenum Percent	Phosphorus Percent	Sulfur Percent	Iron Percent
0.32-0.39	0.6-0.95	0.2-0.35	0.8-1.15	0.15-0.25	0-0.04	0-0.04	Balance

#### Heat Treatment

Normalize: 1600-1700 °F, air cool.

Anneal: 1525-1575 °F, furnace cool.

Harden: 1550-1625 °F, quench in oil.

Temper: 1100 °F for 125,000 tensile PSI.

Temper: 1050 °F for 150,000 tensile PSI.

Temper: 850 °F for 180,000 tensile PSI.

**2.9.30 17-22A(V) Structural (Ultra High Strength) Low Alloy.** This is a high strength, heat resistant steel with a 1000 hour rupture strength of 1100 °F (30,000 PSI tensile strength). It is used in turbine rotors, and for components of guided missiles, in which high temperatures are encountered for short periods.

#### Composition Range

Carbon Percent	Chromium Percent	Cerium Percent	Magnesium Percent	Molybdenum Percent	Nickel Percent	Silicon Percent	Vanadium Percent	Phosphorus Percent
0.25-0.3	1.0-1.5	0-0.5	0.6-0.9	0.4-0.6	0-0.5	0.55-0.75	0.75-0.95	0-0.04
Sulfur Percent	Iron Percent							
0-0.04	Balance							

Form Specifications AMS6303 Bar, forging, forging stock.

#### Heat Treatment

Normalize: 1700-1850 °F, hold for 1 hour per inch of thickness, air cool. Larger sections may be fan cooled in order to accelerate cooling. All sections should be so placed as to provide access of air to all surfaces.

Anneal: 1450 °F, hold at this temperature 1 hour for each inch of section thickness. Cool down 20 °F per hour to 1100 °F, then air cool.

Oil Quenching requires prior heating to 1750 °F, for each inch of thickness. Annealed bars, 1 inch diameter have tensile strength 87,000 yield strength, 67,800. Pancake forgings normalized at 1800 °F + tempering at 1225 °F, 6 hours have tensile strength 142,000, yield strength 126,500, hardness Brinell Hardness Number (BHN) 311-321. This alloy may be welded by any of the commercial methods in use. A welding rod corresponding to 17-22A(S) is available. When pre-heating is required depending upon size of section and type of welding procedure, a temperature of 600 °F is generally used. Post heating or stress relief is recommended.

**2.9.31 4137CO.** This ultra-high strength steel has yield strength in the 230,000-240,000 PSI range. It forms and welds readily. It was developed for use in high performances solid rocket motor cases. Alternate designations are Unimach VC X 2, MX-2, and Rocoloy. Machining characteristics are similar to 4140.

#### Composition Range

Carbon Percent	Chromium Percent	Cobalt Percent	Magnesium Percent	Molybdenum Percent	Silicon Percent	Vanadium Percent	Phosphorus Percent	Sulfur Percent
0.39-0.4	0.95-1.2	0.98-1.23	0.6-0.79	0.22-0.35	0.97-1.19	0.14-0.16	0-0.015	0-0.012
Iron Percent								
Balance								

Specifications None

Forms Sheet, strip, plate, bar, forging, wire.



### Heat Treatment

Normalize: 1750 °F, 30 minutes, air cool.

Spheroidize: Anneal: 1420-1460 °F, 2 hours, fast cool to 1235-1265 °F, hold 14 to 24 hours, air cool. Resulting hardness RB95 maximum.

Intermediate stress relieve to restore ductility of formed parts, 1250 °F for 10 minutes, air cool. Stress relieve after welding 1250 °F, 30 minutes minimum.

Austenitize: 1700 °F for sections less than 1 1/2 inch 1725 °F for sections larger than 1 1/2 inch, 20 minutes minimum to 1 hour maximum per inch thickness, oil or salt quench at 400 °F. Maximum time in salt 12 minutes.

Double temper 540-560 °F for two consecutive 2 hour periods with intermediate cooling to room temperature. Weldability characteristics are good using the Tungsten-arc-inert-gas process.

**2.9.32 4140 Medium Carbon Chromium - Molybdenum (Nitriding Grade).** This steel is widely used where the higher strength and higher hardenability of 4340 is not required. It can be nitrided.

### Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Chromium Percent	Molybdenum Percent	Silicon Percent	Iron Percent
0.38-0.43	0.75-1.0	0-0.040 maximum	0-0.040 maximum	0.80-1.1	0.15-0.25	0.2-0.35	Balance

### Specifications

Type 4140

AMS	Form	Military
5336	Precision Investment Castings	
5338	Precision Investment Castings	
6378	Bars	
6379	Bars	
6381	Heavy Wall Tubing	
6382	Bars, Forgings, Forgings, Stock	MIL-S-5626

### Heat Treatment

Normalize: 1600-1650 °F (air cool) minimum 1 hour.

Anneal: 1550-1600 °F furnace cool.

Harden: 1550-1600 °F 30 minutes, oil quench.

Spheroidize: 1400-1425 °F furnace cool.

Temper: 4 hours to obtain desired strength. See table below.

### Draw Temperatures

1300 °F - 100,000 PSI

1175 °F - 120,000 to 140,000 PSI

1075 °F - 140,000 to 160,000 PSI

950 °F - 160,000 to 180,000 PSI

850 °F - 180,000 to 200,000 PSI

725 °F - 200,000 to 220,000 PSI

**2.9.33 SAE 4330 V Mod.** This steel is 4330 improved by the addition of vanadium, and is primarily used heat treated to a tensile strength between 220 and 240 KSI. It is highly shock resistant and has better welding characteristics than higher carbon steels.

### Composition Range

Carbon Percent	Magnesium Percent	Silicon Percent	Phosphorus Percent	Silicon Percent	Chromium Percent	Nickel Percent	Molybdenum Percent
0.28-0.33	0.75-1.00	0.20-0.35	0.040	0.040	0.75-1.00	1.65-2.00	0.35-0.50
Vanadium Percent	Iron Percent						
0.05-0.10	Balance						



## TO 1-1A-9 NAVAIR 01-1A-9

### Heat Treatment

Normalize: 1600-1700 °F, air cool.

Temper: Normalized condition for machinability 1250 °F maximum.

Full anneal at 1525-1575 °F furnace cool or cool in ash or lime.

Austenitize: 1550-1600 °F 15 minutes per inch thickness, oil quench 75-140 °F.

Temper: 180 to 200 KSI, 950-110 °F, 4 hours.

Temper: 200 to 220 KSI, 750-950 °F, 4 hours.

Temper: 220 to 240 KSI, 600-750 °F, 4 hours.

**2.9.34 4150 Chromium-Molybdenum.** This metal is used for such items as gears, shafts, pistons, springs, axles, pins, connecting rods.

### Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Chromium Percent	Molybdenum Percent	Iron Percent
0.48-0.53	0.75-1.0	0-0.040	0-0.04	0.2-0.35	0.8-0.12	0.18-0.25	Balance

Forms Specifications: See Specification [Table 2-2](#).

### Heat Treatment

Normalize: 1550-1650 °F

Anneal: 1450-1525 °F

Harden: 1475-1525 °F, oil quench

Temper: 1200 °F for tensile 128,000 yield 116,000

Temper: 1100 °F for tensile 150,000 yield 135,000

Temper: 950 °F for tensile 180,000 yield 163,000

Temper: 800 °F for tensile 200,000 yield 186,000

**2.9.35 521000 High Carbon, High Chromium Alloy.** This steel is used for anti-friction bearings and other parts requiring high heat treated hardness of approximately Rockwell C60, toughness and good wear resistance qualities. It is best machined in the spheroidized annealed condition.

### Composition Range

Carbon Percent	Chromium Percent	Magnesium Percent	Silicon Percent	Sulfur Percent	Phosphorus Percent	Iron Percent
0.95-1.1	1.3-1.6	0.25-0.45	0.2-0.35	0-0.025	0-0.025	Balance

Forms Specifications: See Specification [Table 2-2](#).

### Heat Treatment

Normalize: 1650-1700 °F air cool

Anneal: 1250-1340 °F hold 5 hours. Heat to 1430-1460 °F, at 10 °F per hour, hold 8 hours. Cool to 1320 °F at 10 °F per hour. Cool to 1250 °F at furnace rate and air cool.

Spheroidize: Slow cool (about 5 °F per hour) following austenitizing by extended heating at a temperature near the ACM point or by isothermal transformation at 1275 °F following austenitizing.

Harden: Quench in water from 1425-1475 °F or quench in oil from 1550-1600 °F, then temper to desired hardness. The Rockwell hardness at various temperatures is listed below:

Temper: 400 °F, RC60

Temper: 600 °F, RC55

Temper: 800 °F, RC48

Temper: 100 °F, RC40

Temper: 1200 °F, RC28

**2.9.36 LADISH D-6-A Low Alloy High Strength.** This alloy is suitable for hot work die applications and structural material in aircraft and missiles. It may be heat treated to strength levels up to 300,000 PSI, and at 240,000 has excellent toughness. At strength levels below 220,000 PSI it is suitable for elevated temperature applications below 900 °F. It may readily be welded and cold formed in the annealed or spheroidized condition. It also can be temper straightened.



Composition Range

Carbon Percent	Chromium Percent	Magnesium Percent	Molybdenum Percent	Nickel Percent	Silicon Percent	Vanadium Percent	Iron Percent
0.46	1.0	0.75	1.0	0.55	0.22	0.05	Balance

Specifications: None.

Forms: Available in most wrought forms and forgings.

Heat Treatment

Anneal:	1500-1550 °F, cool down at 50 °F per hour to 1000 °F.
Normalize:	1600-1650 °F, 30 minutes, air cool.
Austenitize:	1550-1575 °F, 30 minutes, oil quench. Sections 1 inch or less in cross sections may be air cooled.
Temper:	300-1275 °F, time and temperature depend on hardness desired.
Stress relieve:	1000-1250 °F one to two hours, air cool.
Form:	Up To 1 inch Thick Bar
Condition:	Vacuum remelt by consumable electrode process. Normalize 1650 °F AC 1550 °F, air cool + 600 °F temper.
Tensile:	282,000 PSI
Yield:	255,000 PSI

**2.9.37 Nitralloy 135 Mod Steel Ultra High Strength (Nitriding Grade).** This alloy is well suited for case hardening by nitriding. This process produces a case of extreme hardness without appreciably changing core tensile strength or yield strength. It is also readily machined. After nitriding it may be used where high resistance to abrasion and mild corrosion resistance are required. In welding the major problem to avoid is loss of aluminum and chromium in the weld area, the loss of which would prevent subsequent nitriding.

Composition Range

Aluminum	C5	Chromium Percent	Magnesium Percent	Molybdenum Percent	Silicon Percent	Phosphorus Percent	Sulfur Percent	Iron Percent
0.95-1.3	0.38-0.43	1.4-1.8	0.5-0.7	0.3-0.4	0.2-0.4	0-0.04	0-0.04	Balance

Specifications:

AMS	Forms	Military
5470	Plates, Tubing, Rods, Bar, forgings stock.	MIL-S-6701

Heat Treatment

Anneal:	1450 °F, 6 hours, furnace cool.
Normalize:	By slowly heating to 1790-1810 °F, air cool.
Austenitize:	1700-1750 °F.
	Oil quench sections less than 2 inches thick.
Temper:	1000-1300 °F 1 hour minimum per inch of thickness.

**NOTE**

Temper 50 °F minimum above nitriding temperatures.

Nitride:	930-1050 °F.
Form:	Bar
Condition:	1725 °F, oil quench sections less than 3 inches, water quench sections greater than 3 inches temper 1200 °F, 5 hours.
Size-Dia:	Less than 1-1/2 inches    1-1/2 to 3 inches    3 to 5 inches
Tensile:	135,000 PSI    125,000 PSI    110,000 PSI
Yield:	100,000 PSI    90,000 PSI    85,000 PSI

**2.9.38 4337 and 4340 Steel Nickel - Chromium Molybdenum Alloy.** These two alloys are similar except that carbon content differs slightly. The carbon content of 4337 is minimum 0.35 percent, maximum 0.4 percent, good strength, high



## TO 1-1A-9 NAVAIR 01-1A-9

hardenability and uniformity are characteristics. It can be heat treated to strength values within a wide range. At 260,000 to 280,000 PSI tensile this steel has been found superior to other common low alloy steels as well as some of the recently developed more complex low alloy steels. It possesses fair formability when annealed and may be welded, by special processes, which require strict control. No welding shall be performed on this alloy heat treated above 200,000 PSI unless specifically approved by design engineer. This alloy is easily welded by conventional methods using low hydrogen electrode of similar composition.

### Composition Range

Carbon Percent	Magnesium Percent	Silicon Percent	Phosphorus Percent	Sulfur Percent	Chromium Percent	Nickel Percent	Molybdenum Percent	Iron Percent
0.38-0.43	0.65-0.85	0.2-0.35	0-0.04	0-0.04	0. 7-0.9	1.54-2.0	0.2-0.3	Balance

Forms Specifications: See Specification [Table 2-2](#).

### Heat Treatment

Normalize: 1600-1700 °F, 1 hour of maximum thickness, air cool. Temper, normalize condition for improved machinability 125 °F maximum.

Anneal: 1475-1575 °F, furnace cool or cool in ash or lime.

Harden: 1475-1550 °F, oil quench.

Spheroidize 1425 °F, 2 hours, then furnace cool to 1210 °F, hold 8 hours, furnace cool or air cool.

Anneal:

Stress relief parts after straightening, machining, etc.

Temper: 1100 °F for tensile 150,000 yield, 142,000.

Temper: 900 °F for tensile 190,000, yield, 176,000.

Temper: 725 °F for tensile 220,000, yield, 200,000.

Temper: 400-500 °F for tensile 260,000, 2 hours per thickness, 6 hours minimum.

Parts heat treated to 260,000-280,000 PSI tensile and subsequently subjected to grinding, machining or straightening should be tempered to 350-400 °F, 4 hours minimum. Temperature should not exceed tempering temp or reduce the tensile strength below 260,000 PSI. Austenitize 1475-1575 °F, 15 minutes for each inch of thickness. Normalize, welded or brazed parts before austenitizing. Cool after austenitizing.

To heat treat for regular machining, normalize or austenitize, then heat to 1200 °F (maximum 1250 °F) for 15-20 hours. Resulting hardness should be 229-248 BHN.

Austen- 1575-1625 °F, oil quench.  
itize:

Tempering range is limited to 400-600 °F preferably no higher than 550 °F.

Temper: 600 °F for 230,000 PSI tensile, 194,000 PSI yield.

Temper: 550 °F for 234,000 PSI tensile, 193,000 PSI yield.

Temper: 500 °F for 235,000 PSI tensile, 191,000 PSI yield.

Temper: 400 °F for 239,000 PSI tensile, 183,000 PSI yield.

**2.9.39 4615 Steel Nickel Molybdenum Alloy.** This is a high grade carburizing steel for use where reliability and uniformity are required.

### Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Nickel Percent	Molybdenum Percent	Iron Percent
0.13-0.18	0.45-0.65	0-0.04	0-0.04	0.2-0.35	1.65-2.0	0.2-0.3	Balance

Forms Specifications: See Specification [Table 2-2](#).

### Heat Treatment

Normalize: 1675-1725 °F

Anneal: 1575-1625 °F

Harden: 1425-1550 °F, oil quench.

Carburize: 1425-1550 °F

Where case hardening is paramount, reheat to 1425-1475 °F quench in oil. Tempering 250-350 °F is optional. It is generally employed for partial stress relief and improved resistance to cracking from grinding operation.



**2.9.40 4620 Steel Nickel Molybdenum Alloy.** This is a medium hardenability case steel. Its hardenability characteristics lie between that of plain carbon steel and the high alloy carburized steel. It may be used for average size case hardened automotive parts such as gears, piston pins, crankshafts, etc.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Nickel Percent	Molybdenum Percent	Iron Percent
0.17-0.24	0.45-0.65	0-0.04	0-0.04	0.2-0.35	1.65-2.0	0.2-3.0	Balance

Heat Treatment

Normalize: 1650-1750 °F  
 Anneal: 1550-1600 °F  
 Quench: (High temperature) 1550 °F  
 Quench: (Low temperature) 1425 °F  
 Carburize: 1650-1700 °F

Recommend practice for maximum case hardness:

Direct quench from pot:

1. Carburize: at 1700 °F for 8 hours.
  2. Quench: in agitated oil.
  3. Temper: at 300 °F
- Case depth: 0.075  
 Case hardness: RC62

Single Quench and Temper:

1. Carburize: 1700 °F for 8 hours.
  2. Pot cool.
  3. Reheat: 1500 °F.
  4. Quench: in agitated oil.
  5. Temper: 300 °F.
- Case depth: 0.075.  
 Case hardness: RC62

Recommended practices for maximum core toughness: Direct quench from pot.

1. Carburize: 1700 °F for 8 hours.
  2. Quench: in agitated oil.
  3. Temper: 450 °F.
- Case depth: 0.06  
 Case hardness: RC58

Single Quench and Temper:

1. Carburize: 1700 °F for 8 hours.
  2. Pot Cool.
  3. Reheat: to 1500 °F
  4. Quench: in agitated oil.
  5. Temper: 450 °F.
- Case depth: 0.065  
 Case hardness: RC59

**2.9.41 4640 Steel Nickel Molybdenum.** This steel has excellent machinability at high hardness levels, and small distortion in heat treatment. Its application is primarily gears, spline shafts, hand tools, and machine parts.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Nickel Percent	Molybdenum Percent	Iron Percent
-------------------	----------------------	-----------------------	-------------------	--------------------	-------------------	-----------------------	--------------



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

0.38-0.43	0.6-0.8	0-0.04	0-0.04	0.2-0.35	1.65-2.0	0.2-0.3	Balance
<u>Forms Specifications:</u>		See Specification <a href="#">Table 2-2</a> .					

Heat Treatment

Normalize:	1600-1750 °F
Anneal:	1450-1550 °F
Harden:	1450-1550 °F, oil quench, agitated oil.
Temper:	1200 °F for 100,000 PSI.
Temper:	1100 °F for 120 to 140,000 PSI.
Temper:	1000 °F for 140 to 160,000 PSI.
Temper:	900 °F for 160 to 180,000 PSI.
Temper:	800 °F for 180 to 200,000 PSI.
Temper:	700 °F for 200 to 220,000 PSI.

**2.9.42 6150 and 6152 Chromium Vanadium Alloy.** These two steels are essentially the same, differing only in the amount of Vanadium. Alloy 6152 contains a minimum of 0.1 percent Vanadium. Typical usages are for flat springs under 1/8 inch thick, cold formed, and 1/8 inch and over hot formed; oil quenched, and drawn at 725-900 °F to 44-48 or 48-52 RC, and for coil springs over 1/2 inch diameter with same heat treatment. It is also used for valve springs, piston rods, pump parts, spline shafts, etc.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Chromium Percent	Vanadium Percent	Iron Percent
0.48-0.53	0.7-0.9	0-0.04	0-0.04	0.2-0.35	0.8-1.1	0.15 minimum	Balance

Forms Specifications: See Specification [Table 2-2](#).

Heat Treatment

Normalize:	1625-1750 °F, furnace cool.
Anneal:	1500-1600 °F. (Tensile PSI 90,000 yield 58,000 PSI annealed.)
Harden:	1550-1600 °F, oil quench.
Temper:	1100 °F for tensile PSI 150,000 yield PSI 137,000 PSI.
Temper:	800 °F for tensile PSI 210,000 yield PSI 194,000 PSI.
Spheroidized annealed to 183-241 BHN = 45 percent	

**2.9.43 8615 Steel-Nickel-Chromium-Molybdenum Alloy.** This is a triple alloy case-hardening steel with medium hardenability. It is primarily used for differential pinions, engine pins, gears etc.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Nickel Percent	Chromium Percent	Iron Percent
0.13-0.18	0.7-0.9	0.04	0-0.04	0.2-0.3	0.4-0.6	0.4-0.6	Balance

Forms Specifications: See Specification [Table 2-2](#).

Heat Treatment

Psuedo-Carburize:	1650-1700 °F, box cool, reheat 1550 °F, oil quench.
Temper:	300 °F for tensile 100,000 PSI yield 72,500 PSI.
Normalize:	1650-1725 °F.
Anneal:	1575-1650 °F.
Harden:	1475-1575 °F.

**2.9.44 8617 Steel-Nickel-Chromium-Molybdenum Alloy.** This steel is very similar to 8615, but develops somewhat greater strength.



Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Nickel Percent	Chromium Percent	Molybdenum Percent	Iron Percent
0.15-0.2	0.7-0.9	0-0.04	0-0.04	0.2-0.35	0.4-0.7	0.4-0.6	0.15-0.25	Balance

Forms Specifications: See Specification [Table 2-2](#).

Heat Treatment

Normalize: 1650-1725 °F  
 Anneal: 1575-1650 °F  
 Harden: 1474-1575 °F  
 Carburize: 1700 °F for 8 hours, oil quench.  
 Draw at 300 °F  
 Tensile: 128,000 PSI yield 94,000 PSI.

**2.9.45 8620 Nickel-Chromium-Molybdenum-Alloy.** This steel is similar to 8615 and 8617 though stronger. It is used for ring gears, transmission gears, cam shafts and for good core properties with high surface hardness after case hardening. It is also used in the heat treated condition as chain, at about 100,000 PSI yield strength. It is classed as medium hardenable.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Nickel Percent	Chromium Percent	Molybdenum Percent	Iron Percent
0.18-0.23	0.7-0.9	0-0.04	0-0.04	0.2-0.35	0.4-0.7	0.4-0.6	0.15-0.25	Balance

Forms Specifications: See Specification [Table 2-2](#).

Heat Treatment

Normalize: 1600-1750 °F.  
 Anneal: 1575-1625 °F.

CARBURIZING:

Recommend practice for maximum case hardness:

Direct quench from pot:

1. Carburize: 1700 °F for 8 hours.
2. Quench: in agitated oil.
3. Temper: 300 °F.

Case depth: 0.075.

Case hardness: RC64.

Single Quench and Temper:

1. Carburize: 1700 °F for 8 hours.
2. Pot cooled.
3. Reheat: to 1550 °F.
4. Quench: in agitated oil.
5. Temper: 300 °F

Case depth: 0.075

Case hardness: RC64

Recommended practices for maximum core toughness:

Direct quench from pot:

1. Carburize: 1700 °F for 8 hours.
2. Quench: in agitated oil.
3. Temper: 450 °F

Case depth: 0.050

Case hardness: RC58

Single Quench and Temper:



## TO 1-1A-9 NAVAIR 01-1A-9

1. Carburize: 1700 °F for 8 hours.
2. Pot Cool.
3. Reheat: to 1500 °F.
4. Quench: in agitated oil.
5. Temper: 450 °F
- Case depth: 0.076.
- Case hardness: RC61.

**2.9.46 8630 Steel Nickel-Chromium-Molybdenum Alloy.** This steel has characteristics very similar to 4130. It is used for aircraft engine mounts, and other aircraft parts due to good properties when normalized in light sections, and its air hardening after welding.

### Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Nickel Percent	Chromium Percent	Molybdenum Percent	Iron Percent
0.28-0.33	0.7-0.9	0-0.04	0-0.04	0.2-0.35	0.4-0.7	0.4-0.6	0.15-0.25	Balance

Forms Specifications: See Specification [Table 2-2](#).

### Heat Treatment

- Normalize: 1550-1650 °F.
- Anneal: 1500-1550 °F (Tensile 90,000 PSI, tensile 60,000 annealed), furnace cool.
- Harden: 1500-1575 °F, oil or water quench.,
- Temper: 1000 °F for 150,000 PSI tensile, 140,000 PSI yield strength.
- Temper: 700 °F for 200,000 PSI tensile, 180,000 PSI yield strength.

**2.9.47 8640 Steel Nickel-Chromium-Molybdenum.** Typical uses, propeller shafts, transmission gears, spline shafts, heavy duty bolts, etc. 4140 has higher strength and ductility and slightly better machinability.

### Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Nickel Percent	Chromium Percent	Molybdenum Percent	Iron Percent
0.38-0.43	0.75-1.0	0-0.04	0-0.04	0.2-0.35	0.4-0.7	0.4-0.6	0.15-0.25	Balance

Forms Specifications: See Specification [Table 2-2](#).

### Heat Treatment

- Normalize: 1550-1650 °F.
- Anneal: 1475-1575 °F
- Harden: 1475-1575 °F, oil quench.
- Temper: 1100 °F for 145,000 PSI tensile, 130,000 PSI yield.
- Temper: 800 °F for 200,000 PSI tensile, 184,000 PSI yield.
- Temper: 700 °F for 220,000 PSI tensile, 205,000 PSI yield.

**2.9.48 8735 Steel Nickel-Chromium-Molybdenum.** This metal is used for shapes, tubing, aircraft engine studs, knuckles, etc. It is similar in characteristics to 8630 and 8640.

### Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Nickel Percent	Chromium Percent	Molybdenum Percent	Iron Percent
0.33-0.38	0.75-1.0	0-0.04	0-0.04	0.2-0.35	0.4-0.7	0.4-0.6	0.2-0.3	Balance

Forms Specifications: See Specification [Table 2-2](#).

### Heat Treatment

- Normalize: 1575-1625 °F.
- Anneal: 1525-1525 °F.
- Harden: 1525-1600 °F Oil quench.
- Temper: 1200 °F for tensile 119,000 PSI, yield 93,000 PSI.



Temper: 1100 °F for tensile 131,000 PSI, yield 107,000 PSI.  
 Temper: 900 °F for tensile 149,000 PSI, yield 127,000 PSI.  
 Temper: 800 °F for tensile 170,000 PSI.  
 Temper: 775 °F for tensile 200,000 PSI.

**2.9.49 8740 Steel Nickel-Chromium-Molybdenum.** This steel is similar to 4140. It may be satisfactorily used for axles, tool joints, bits, core drills, reamer bodies, drill collars, piston rods, aircraft engine bolts, shapes, tubing etc.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Nickel Percent	Chromium Percent	Molybdenum Percent	Iron Percent
0.38-0.43	0.75-1.0	0-0.04	0-0.04	0.2-0.35	0.4-0.7	0.4-0.6	0.2-0.3	Balance

Forms Specifications: See Specification [Table 2-2](#).

Heat Treatment

Normalize: 1575-1625 °F.  
 Anneal: 1500-1575 °F (Tensile 103,000 PSI, yield 66,000 PSI annealed)  
 Harden: 1500-1575 °F (Quench in agitated oil)  
 Temper: 1100 °F for tensile 160,000 PSI, yield 152,000 PSI.  
 Temper: 900 °F for tensile 190,000 PSI, yield 183,000 PSI.  
 Temper: 800 °F for tensile 210,000 PSI, yield 198,000 PSI.  
 Temper: 725 °F for tensile 220,000.

**2.9.50 9260, 9261 and 9262 Steel Silicon.** These are similar alloy spring steels, oil hardening type. The quantities of chromium in each, constitutes the only chemical variations in these alloys. Typical applications are coil and flat springs, axles, chisels, bolts. etc.

Composition Range

	Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Chromium Percent	Iron Percent
9260	0.55-0.65	-0.7-1.0	0-0.04	0-0.04	1.8-2.2	—	Balance
9261	0.55-0.65	0.75-1.0	0-0.04	0-0.04	1.8-2.2	0.1-0.25	Balance
9262	0.55-0.65	0.75-1.0	0-0.04	0-0.04	1.8-2.2	0.25-0.4	Balance

Forms Specifications: See Specification [Table 2-2](#).

Heat Treatment

Normalize: 1600-1650 °F.  
 Anneal: 1525-1575 °F  
 Harden: 1575-1625 °F quench in agitated oil.  
 Temper: 1100 °F for tensile 165,000 PSI, yield 144,000 PSI.  
 Temper: 900 °F for tensile 214,000 PSI, yield 192,000 PSI.  
 Temper: 600 °F for tensile 325,000 PSI, yield 280,000 PSI.

**2.9.51 9310 Steel Nickel Chromium-Molybdenum (Electric Furnace Steel).** This is a high hardenability case steel, since it is a high alloy, both the case and core have high hardenability. This type of steel is used particularly for carburized parts having thick sections such as bearing races, heavy duty gears etc.

Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Nickel Percent	Chromium Percent	Molybdenum Percent	Iron Percent
0.7-0.13	0.4-0.7	0-0.025	0-0.025	0.2-0.35	2.95-3.55	1.0-1.45	0.08-0.15	Balance



## TO 1-1A-9 NAVAIR 01-1A-9

Forms Specifications: See Specification [Table 2-2](#).

### Heat Treatment

Normalize: 1625-1725 °F, air cool.

Anneal: 1475-1575 °F, furnace cool.

Recommend practice for maximum case hardness:

Direct quench from pot:

1. Carburize: at 1700 °F for 8 hours.

2. Quench: in agitated oil.

3. Temper: 300 °F

Case depth: 0.047 inch

Case hardness: RC62

Single Quench and Temper:

1. Carburize: 1700 °F for 8 hours.

2. Pot cool.

3. Reheat: to 1450 °F.

4. Quench: in agitated oil.

5. Temper: 300 °F.

Case depth: 0.047 inch

Case hardness: RC62.

Recommended practices for maximum core toughness:

Direct quench from pot:

1. Carburize: 1700 °F for 8 hours.

2. Quench: in agitated oil.

3. Temper: 450 °F.

Case depth: 0.039 inch.

Case hardness: RC54.

Single Quench and Temper:

1. Carburize: 1700 °F for 8 hours.

2. Pot Cool.

3. Reheat: to 1450 °F.

4. Quench: in agitated oil.

5. Temper: 450 °F.

Case depth: 0.047 inch.

Case hardness: RC59.

**2.9.52 Type 301 Steel Austenitic Stainless.** This steel belongs to the sub-family of 18-8 steels, which vary only slightly in chromium and nickel and contain no other metallic alloying element. This alloy may be strengthened to an exceptional degree by cold work. For best results, cold work should be followed by stress relieving at 400-800 °F.

### Composition Range

Carbon Percent	Magnesium Percent	Silicon Percent	Phosphorus Percent	Chromium Percent	Nickel Percent	Sulfur Percent	Copper Percent	Iron Percent
0.08-0.15	0-2.0	0-1.0	0-0.04	17.0-19.0	6.0-8.0	0-0.03	0-0.05	Balance

Forms Specifications: See Specification [Table 2-2](#).

### Heat Treatment

Anneal: 1950-2050 °F, 1 hour per inch thickness, water quench.



Cool to 800 °F within 3 minutes maximum.

To relieve the elastic characteristics and increase the compressive yield strength of cold worked conditions, 400-800 °F, 36 to 8 hours maximum respectively. After forming in order to prevent stress cracking, full anneal, or alternately 600 °F, 1/2 to 2 hours. This alloy can be hardened only by cold work. Maximum tensile strength, 1/4 hard 125,000, 1/2 hard 150,000, full hard 185,000 PSI. Full anneal is mandatory when, exposed to corrosive media, such as hot chlorides, etc. which may lead to stress corrosion cracking.

**2.9.53 Type 302 Steel Austenitic Stainless.** This alloy is similar to Type 301 in composition and characteristics. It is inferior in strength to 301, however, possesses superior corrosive resistance. It is generally used in the annealed conditions.

Composition Range

Carbon Percent	Magnesium Percent	Silicon Percent	Phosphorus Percent	Sulfur Percent	Chromium Percent	Nickel Percent	Iron Percent
0.08-0.25	0-2.0	0-1.0	0-0.045	0-0.03	17.0-19.0	8.0-10.0	Balance

Forms Specifications: See Specification [Table 2-2](#).

Heat Treatment

The heat treatment and resulting strength is similar to that recommended for Type 301, except that the temperature range for annealing Type 302 ranges between 1925-2075 °F.

**2.9.54 Type 303 and Type 303Se, Steel Austenitic Stainless.** These varieties of the 18-8 austenitic stainless family contain additions of sulphur and selenium for the purpose of improving machining characteristics. However the presence of these elements tend to decrease formability and corrosion resistance. Type 303Se is superior to 303 in these respects. The cast form of 303Se is also known as CF-16F.

Alloy	Type 303 (Percent)		Type 303Se (Percent)	
	Minimum	Maximum	Minimum	Maximum
Carbon	-	0.15	-	0.15
Magnesium	-	2.0	-	2.0
Silicon	-	1.0	-	1.0
Phosphorus	-	0.04	0.12	0.17
Sulfur	0.18	0.35	-	0.04
Chromium	17.0	19.0	17.0	19.0
Nickel	8.0	10.0	8.0	10.0
Molybdenum	-	0.75	-	0.5
Copper	-	0.5	-	0.5
Selenium	-	-	0.15	0.35
Iron	Balance		Balance	

Heat Treatment

Anneal or solution treat: 1900-2050 °F, air cool or quench, depending on section thickness, cool to 800 °F maximum within 3 minutes.

Bars, forgings: 1900-1950 °F, 1/2 hour per inch of thickness, water quench.

Sheet, tubing: 1900-1950 °F, 10 minutes, air cool up to 0.064 thickness, water Quench 0.065 inch and thicker.

Castings: 2000-2100 °F, 30 minutes minimum.

This alloy may be hardened only by cold work. Welding is not generally recommended. These steels are subject to carbide precipitation when subjected to temperature over 800 °F.

**2.9.55 Type 304 and Type 304L Steel Austenitic Stainless.** This steel is produced in two grades, Type 304 with 0.08 carbon (maximum) and Type 304L with 0.03 percent maximum carbon. They have properties similar to Type 302 but the corrosion resistance is slightly higher. These metals are available as castings under the designations CF-8 and CF-3 respectively. Welding may be readily accomplished by all common methods.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

Alloy	Type 304 (Percent)		Type 304L (Percent)	
	Minimum	Maximum	Minimum	Maximum
Carbon	-	0.08	-	0.03
Magnesium	-	2.0	-	2.0
Silicon	-	1.0	0.5	1.0
Phosphorus	-	0.04	-	0.04
Sulfur	-	0.03	-	0.03
Chromium	18.0	20.0	18.0	20.0
Nickel	8.0	11.0	8.0	11.0
Molybdenum	-	0.5	-	-
Copper	-	0.5	-	-
Iron	Balance		Balance	Balance

Heat Treatment

Same as Type 303 and Type 303Se. This alloy can only be hardened by cold work.

**2.9.56 Type 314 Steel-Austenitic Stainless.** This is a non-heat-treatable stainless steel generally used in the annealed condition. It possesses high resistance to scaling and carburizing and is used for parts and welded assemblies requiring corrosion and oxidation resistance to 2000 °F. It is subject to embrittlement after long time exposure to temperature in the 1200-1600 °F range.

Composition Range

Carbon Percent	Chromium Percent	Copper Percent	Magnesium Percent	Molybdenum Percent	Nickel Percent	Silicon Percent	Phosphorus Percent	Sulfur Percent
0.12	23.0-25.0	0.50	1.0-2.0	0.50	19.0-22.0	1.7-2.3	0.04	0.03
Iron Percent								
Balance								

Forms Specifications: See Specification [Table 2-2](#).

Heat Treatment

Anneal (solution treat) 1900-2100 °F using rapid air cooling for sheet and light plate and water quench for heavier sections. Stress relief and best corrosion resistance to high temperatures properties is achieved by final annealing at 1900 °F minimum. To restore ductility after embrittlement has occurred, anneal 1900-1950 °F for 10-60 minutes. This alloy may be hardened only by cold work.

Forms Condition	Bar Annealed	Plate Annealed	Sheet Annealed	Wire Annealed	Hard Drawn
Thickness-Inch	1 Inch Diameter			0.002 to 0.010	0.002 to 0.010
Tensile	100,000	100,000	100,000	95,000-130,000	245,000-275,000
Yield	50,000	50,000	50,000	35,000-70,000	230,000-260,000
Hardness RB	89	89	89		

**2.9.57 Type 316 and Type 317 Steel Austenitic Stainless.** Wrought products are readily formable and weldable. Castings are also weldable, and the metal arc method is most often used. These alloys have better corrosion resistance than 30302 or 30304 types.

Composition Range

Carbon Percent	Magnesium Percent	Silicon Percent	Phosphorus Percent	Sulfur Percent	Chromium Percent	Nickel Percent	Molybdenum Percent	Copper Percent
0-0.08	1.25-2.0	0-1.0	0-0.04	0-0.03	16.0-19.0	11.0-14.0	2.0-2.5	0-0.5
Iron Percent								



Balance

Forms Specifications: See Specification [Table 2-2](#).

#### Heat Treatment

Anneal wrought products 1850-2150 °F, air cool or quench depending on section size. For sheet alloys, annealing temperature 1950 °F, minimum.

Castings 1950-2100 °F, water or oil quench or air cool. Low side of temperature range is used for CF 8M, (Cast Alloy) but CF 12M castings should be quenched from above 2000 °F.

Stabilize for high temperature service 1625-1675 °F, stress relieve 400-500 °F, 1/2 to 2 hours. This alloy may be hardened only by cold work. In annealed condition, tensile 90,000 PSI, yield 45,000 PSI.

**2.9.58 Type 321 Steel Austenitic Stainless.** This is one of the two stabilized 18-8 steels since titanium forms a carbide of low solid solubility, the possibility of intergranular precipitation and of the associated intergranular corrosion is reduced. Therefore, Type 321 is used primarily either for parts fabricated by welding without postweld annealing or for service at 800-1500 °F. This steel is available in all wrought forms. Welding rods and castings are not produced in this type.

#### Corrosion Range

Carbon Percent	Magnesium Percent	Silicon Percent	Phosphorus Percent	Sulfur Percent	Chromium Percent	Nickel Percent	Molybdenum Percent
0-0.08	0-2.0	0.4-1.0	0-0.04	0-0.03	17.0-20.0	8.0-13.0	0-0.5
Titanium Percent	Copper Percent	Iron Percent					
*6XC-0.7	0-0.5	Balance					

Forms Specifications: See Specification [Table 2-2](#).

\* 6 times columbian content.

#### Heat Treatment

Full anneal 1750-1850 °F, 1 hour per inch in thickness, two hours minimum for plate furnace cool or air cool. Stabilizing anneal for service 900-1500 °F, heat to 1500-1650 °F one hour per inch thickness, 2 hours minimum for plate. Stress relieve after fabrication 1300 °F.

This may be hardened only by cold work.

Full anneal or stabilizing anneal will eliminate sensitized conditions.

Tensile-Yield Form Condition Thickness Inch	Sheet Strip Anneal	Plate	All	Bar Annealed and Cold Drawn 1 Inch	Wire Soft Temper	0.062	0.50
Tensile	90000	85000	85000	95000	115000	95000	
Yield	35000	30000	35000	60000	85000	65000	

**2.9.59 Types 347 and Type 348 Steel Austenitic Stainless.** Is the second of two stabilized 18-8 steels (see Type 321 for other). Since columbian forms a carbide of very low solubility, the possibility of intergranular precipitation and of the associated intergranular corrosion are practically eliminated. Therefore, Type 347 is used principally for parts fabricated by welding without postweld annealing, or for long service between 800-1500 °F. Columbian is usually associated with the similar element tantalum which is included in the columbian analysis, specifying only the total of both elements. Corrosion resistance of this alloy is similar to Type 302, however it has a greater tendency to pitting corrosion and attacks in streaks. Intergranular corrosion is absent in this steel unless it is overheated to above 2150 °F. At this temperature columbian carbides are going in to solid solution and subsequent rapid cooling, followed by heating to 1200 °F, will cause precipitation and reduce the resistance to intergranular attack. A stabilizing anneal will restore the corrosion resistance.

#### Composition Range

Carbon Percent	Magnesium Percent	Silicon Percent	Phosphorus Percent	Sulfur Percent	Chromium Percent	Nickel Percent	Molybdenum Percent
0-0.08	0-2.0	0.5-1.0	0-0.04	0-0.03	17.0-19.0	9.0-13.0	0-0.5
Cb1 Percent	Iron Percent						
*10XC-1.1	Balance						



## TO 1-1A-9 NAVAIR 01-1A-9

\* 10 Times Columbian Content.

Forms Specifications: See Specification [Table 2-2](#).

### Heat Treatment

Full anneal wrought products 1800-1900 °F, 1 hour per inch of thickness 2 hours minimum for plate, furnace cool or air cool. Full anneal castings 1900-2000 °F 30 minutes minimum. Stabilizing anneal for service 800-1500 °F, 1500-1650 °F, 1 hour per inch thickness, 2 hours minimum for plate. Stress relieve after fabrication 1300 °F.

Alloy may be hardened only by cold work.

Welding: Fusions welding of this alloy is comparable to Type 304L. Heavy sections may crack during welding or subsequent heating. Post weld annealing is not required, although a stress relief is recommended. This steel is subject to carbide precipitation at temperatures in excess of 2150 °F.

**2.9.60 Type 414 Steel Martensitic Stainless.** This steel has good resistance to weather and water. It should be passivated. Stainless Type 416 has similar mechanical properties, workability and resistance to corrosion, however, corrosion resistance is not as good as the 300 series stainless. It has better machinability but less weldability. Type 420 has higher mechanical properties, similar workability and machinability.

### Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Chromium Percent	Nickel Percent	Iron Percent
0.08-0.15	0-1.0	0-0.04	0-0.03	0-0.10	11.5-13.5	1.25-2.5	Balance

Forms Specifications: See Specification [Table 2-2](#).

### Heat Treatment

Annealing: 1200-1300 °F.

Hardening: 1800-1900 °F, cool rapidly.

Tensile: Strength in annealed condition 117,000 yield, 98,000 PSI.

Tensile: Strength in annealed cold drawn 130,000 yield, 115,000 PSI.

**2.9.61 Type 403, Type 410, and Type 416 Steel-Martensitic Stainless.** This is a free machining type of alloy. Best performance is obtained if heat treated or cold worked to 180-240 BHN. It is magnetic in the hardened condition and is not normally used in the annealed condition.

### Composition Range

Carbon Percent	Magnesium Percent	Phosphorus Percent	Sulfur Percent	Silicon Percent	Chromium Percent	Molybdenum Percent	Silicon Percent	Iron Percent
0.15	1.25	0.06	0.15	1.0	14.0	0.6	0.6	Balance

Forms Specifications: See Specification [Table 2-2](#).

### Heat Treatment

Annealing: 1500-1650 °F, furnace cool 50 °F per hour to 1100 °F.

Harden: 1700-1850 °F, cool rapidly, oil and quench.

Tensile: Yield strength is as follows:

1. Annealed Tensile 75,000 PSI, yield 40,000 PSI.

2. Heat Treated Tensile 110,000 PSI, yield 85,000 PSI.

3. Tempered and Drawn Tensile 100,000 PSI, yield 85,000 PSI. Weldability is poor except by use of low-hydrogen electrodes.

Temper: 400-1300 °F. Avoid 700-1075 °F temper range.

Temper: 1300 °F for 100,000 PSI.

Temper: 1075 °F for 120,000 PSI.

Temper: 575-600 °F for 180,000 PSI.

**2.9.62 Type 420 Steel Martensitic Stainless.** This is a medium carbon grade of martensitic stainless which in the past has been intensively used in the cutlery industry. It has recently proved satisfactory for air weapon application where its high strength permits heat treatment for tensile strength up to 240,000 PSI. In the fully annealed condition formability of this alloy almost equals the 1/4 hard austenitic stainless steels. Shearing type operations such as blanking and punching are not recommended. It machines best in conditions having approximately 225 BHN.



Composition Range

Carbon Percent	Magnesium Percent	Silicon Percent	Phosphorus Percent	Sulfur Percent	Chromium Percent	Nickel Percent	Molybdenum Percent	Iron Percent
0.3-0.4	0-1.0	0-1.0	0-0.04	0-0.03	12.0-14.0	0-0.5	0-0.5	Balance

Forms Specifications

See Specification [Table 2-2](#).

Heat Treatment

Full anneal: 1550-1650 °F one hour per inch of thickness, furnace cool (50 °F per hour) to 1100 °F.

Subcritical anneal: 1300-1350 °F, 3 hours minimum, air cool. Austenitize 1800-1850 °F oil quench, depending on section size. Heavy sections should be preheated at 1250 °F.

Temper: 400-1500 °F, 3 hours minimum. Tempering between 600-1000 °F is not generally recommended due to reduced ductility and corrosion resistance.

2.9.63 Type 431 Steel Martensitic Stainless. This alloy is suitable for highly stressed parts in corrosive environment.

Composition Range.

Carbon Percent	Magnesium Percent	Silicon Percent	Phosphorus Percent	Sulfur Percent	Chromium Percent	Nickel Percent	Iron Percent
0.2	1.0	1.0	0.04	0.03	15.0-17.0	1.25-2.5	Balance

Forms Specifications.

See Specification [Table 2-2](#).

Heat Treatment.

Type 431 steel must be protected from contamination at furnace temperature by dry inert atmosphere (argon, helium) or vacuum in the furnace working zones, except that air or salt bath furnaces may be employed for tempering operations. Parts shall be transferred from furnace working zones to the oil bath within a 30 second interval prior to quenching. Materials in the solution treated condition (not more than 2 percent segregated ferrite or austenite in the microstructure) may be hardened by the following treat treatment.

HT-200 Condition:

Austenitize at 1850±25 °F for 30 minutes, quickly transfer from furnace to oil quenching bath at not over 100 °F followed by refrigeration at -100±10 °F for 2 hours, tempering at 550 ±25 °F for 2 hours, air cool, and final temper at 550±25 °F for 2 hours; or austenitize 1850±25 °F for 30 minutes, marquench into salt bath at 400 °F, air cool to room temperature, refrigerate at -100±10 °F for 2 hours, temper 550±25 °F for 2 hours, air cool, temper 550 °F for 2 hours.

HT-125 (125,000 Tensile):

Austenitize at 1850±25 °F for 30 minutes, quickly transfer from furnace to oil quench to bath at not over 100 °F, temper 1200±25 °F for 2 hours, air cool, temper 1200±25 °F for 2 hours.

HT-115 (115,000 Tensile and Yield 90,000 PSI):



Avoid tempering or holding within range from 700-1100 °F. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

Heat Cond A material to 1800-1900 °F for 30 minutes, oil quench from furnace, temper at a temperature not lower than 1100 °F.

HT-175 (175,000 Tensile and 135,000 Yield PSI):

Heat Cond A material to 1850-1950 °F, quench in oil from furnace temper at a temperature not higher than 700 °F.

2.9.64 PH13-8Mo Steel, Martensitic Stainless, Precipitation Hardening. This stainless steel possesses high strength and good corrosion and oxidation resistance up to 800 °F.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

Composition Range.

Carbon Percent	Magnesium Percent	Silicon Percent	Phosphorus Percent	Sulfur Percent	Chromium Percent	Nickel Percent	Molybdenum Percent
0.05	0.01	0.01	0.001	0.008	12.25-13.25	7.5-8.5	2.00-2.50
maximum	maximum	maximum	maximum	maximum			
Aluminum Percent	Nitrogen Percent						
0.90-1.35	20 ppm						

Form. Bar, forging, ring, extrusion (Vacuum Induction plus Consumable Electrode Melted)

Specifications. AMS 5629, AMS 5934, AMS 5400

Heat Treatment. To condition A - 1700±25 °F 30 minutes, air cool or oil quench below 60 °F.

- From condition A to Condition H950 (RH-C 45/49) ±10 °F, 4 hour, air cool.
- Condition H1000 (RH-C 43/48) 1000±10 °F, 4 hours, air cool.
- Condition H1025 (RH-C 41/46) 1025±10 °F, 4 hours, air cool.
- Condition H1050 (RH-C 40/42) 1050±10 °F, 4 hours, air cool.
- Condition H1100 (RH-C 34/42) 1100±10 °F, 4 hours, air cool.
- Condition H1150M (RH-C 28/36) H1150M is an intermediate soft condition that must be re-solution heat treated to obtain a different final condition. To obtain H1150M, heat at 1400±10 °F for 2 to 2-1/2 hours, air cool below 90 °F then heat at 1150 °F for 4 hours.

2.9.64.1 Normally furnished in condition A (solution-treated). Do not place into service in condition a. Machine, joining, forming typically accomplished in condition a.

2.9.65 PH15-5 Steel, Martensitic Stainless, Precipitation Hardening. This stainless steel possesses high strength and good corrosion and oxidation resistance up to 600 °F.

Composition Range.

Carbon Percent	Magnesium Percent	Silicon Percent	Phosphorus Percent	Sulfur Percent	Chromium Percent	Nickel Percent	Niobium Percent
0.07	1	1	0.030	0.015	14-15.5	3.5-5.5	5xC-0.45
maximum	maximum	maximum	maximum				
Copper Percent	Molybdenum Percent						
2.5-4.5	0.50 maximum						

Form. Bar, forging, ring, extrusion, rolled and/or forged bar, sheet, strip, plate, investment casting

Specifications. AMS 5659, AMS 5659/H1025, AMS 5682, AMS 5400

Heat Treatment. To condition A - 1900±25 °F 30 minutes, air cool or oil quench below 90 °F

- From condition A to Condition H900 (RH-C 40/47) ±10 °F, 1 hour, air cool.
- Condition H925 (RH-C 38/45) 925±10 °F, 4 hours, air cool.
- Condition H950 (RH-C 37/44) 950±10 °F, 4 hours, air cool.
- Condition H1000 (RH-C 36/43) 1000±10 °F, 4 hours, air cool.
- Condition H1025 (RH-C 34/42) 1025±10 °F, 4 hours, air cool.
- Condition H1050 (RH-C 32/38) 1050±10 °F, 4 hours, air cool.
- Condition H1075 (RH-C 31/38) 1075±10 °F, 4 hours, air cool.
- Condition H1100 (RH-C 30/37) 1100±10 °F, 4 hours, air cool.
- Condition H1150 (RH-C 28/37) 1150±10 °F, 4 hours, air cool.
- Condition H1150M (RH-C 24/30) 1150±10 °F, 4 hours, air cool. H1150M is an intermediate soft condition that must be re-solution heat treated to obtain a different final condition. To obtain H1150M, heat at 1400 °F (760 °C) for 2 to 2-1/2 hours, air cool below 90 °F (32 °C) then heat at 1150 °F (621 °C) for 4 hours.

Castings (RH-C 38/47). Castings shall be solution and precipitation heat treated.

- Solution Heat Treatment: Heat to 1900±25 °F (1038±14 °C), hold at heat for 60 minutes per inch (25.4 mm) of maximum cross-section, and cool to below 90 °F (32 °C) at a rate equivalent to an air cool or faster.



- Precipitation Heat Treatment: Heat to 935±15 °F (502±8 °C), hold at heat for 4 hours ±0.25, and cool in air.

2.9.65.1 Readily forged and welded. Do not place into service in condition A. Machine, joining, forming typically accomplished in condition A.

2.9.66 17-4PH Steel, Martensitic Stainless, Precipitation Hardening. This stainless steel possesses high strength and good corrosion and oxidation resistance up to 600 °F.

Composition Range.

Carbon Percent	Niobium Percent	Chromium Percent	Copper Percent	Magnesium Percent	Nickel Percent	Phosphorus Percent	Sulfur Percent
0.07 maxi- mum	0.15-0.45	15.5-17.5	3.0-5.0	1.0 maximum	3.0-5.0	0.04 maximum	0.03 maximum
Silicon Percent	Iron Percent						
1.0 maximum	Balance						

Specifications.

MIL-S-81506

Heat Treatment.

To condition A - 1900±25 °F 30 minutes, air cool or oil quench below 90 °F.

- From condition A to Condition H900 (RH-C 40/47) ±10 °F, 1 hour, air cool.
- Condition H925 (RH-C 38/45) 925±10 °F, 4 hours, air cool.
- Condition H950 (RH-C 37/44) 950±10 °F, 4 hours, air cool.
- Condition H975 (RH-C 36/43) 975±10 °F, 4 hours, air cool.
- Condition H1000 (RH-C 35/42) 1000±10 °F, 4 hours, air cool.
- Condition H1025 (RH-C 35/42) 1025±10 °F, 4 hours, air cool.
- Condition H1050 (RH-C 33/40) 1050±10 °F, 4 hours, air cool.
- Condition H1075 (RH-C 31/39) 1075±10 °F, 4 hours, air cool.
- Condition H1100 (RH-C 32/38) 1100±10 °F, 4 hours, air cool.
- Condition H1125 (RH-C 30/37) 1125±10 °F, 4 hours, air cool.
- Condition H1150 (RH-C 28/37) 1150±10 °F, 4 hours, air cool.

2.9.67 17-7PH Steel Martensitic Stainless (Precipitation Hardening). This stainless steel possesses good corrosion resistance, may be machined and formed in its annealed condition, and is used up to temperatures of 800 °F.

Composition Range.

Carbon Percent	Carbon Percent	Chromium Percent	Magnesium Percent	Nickel Percent	Silicon Percent	Phosphorus Percent	Sulfur Percent
0.50-1.0	0.10-0.12	16.0-18.0	1.00	6.0-8.0	1.0-5.0	0.045	0.030
Iron	Balance						

Specifications.

See MIL-S-25043.

Heat Treatment.

- Condition A - Solution anneal 1925-1975 °F, 30 minutes per inch of thickness, air cool. Age condition A to condition TH1050, 1375-1425 °F, 1-1/2 hour, air cool to 50-60 °F within 1 hour, hold at 50-60 °F 1/2 hour (condition TO) + 1040-1060 °F, 1-1/2 hour. Age condition A to condition RH950, 1735-1765 °F, 10 minutes, refrigerate (condition A 1750 °F) to -90 to -110 °F 8 hours (condition R100), +940-960 °F, 1 hour. Age condition C of cold rolled sheet or cold drawn wire to condition CH900, 890-910 °F for 1 hour.
- Condition A - 130 to 150 KSI ultimate, 55 KSI yield.
- Condition T - 125 to 145 KSI ultimate 75 to 100 KSI yield.
- Condition RH950 - 200 to 215 KSI ultimate 180 to 190 KSI yield.
- Condition RH1050 - 180 to 200 KSI ultimate 150 to 185 KSI yield.
- Condition C - 200 to 215 KSI ultimate 175 to 185 KSI yield.
- Condition CH900 - 240 to 250 KSI ultimate, 230 to 240 KSI yield.

2.9.68 Type 440A, Type 440B, Type 550C, and Type 440C Steel Martensitic Stainless. These steels are similar except for carbon range, therefore they are grouped since heat treatment requirements are the same. These steels are used for cutlery, valves, etc.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

Composition Range.

440A

Carbon Percent	Magnesium Percent	Silicon Percent	Phosphorus Percent	Sulfur Percent	Chromium Percent	Molybdenum Percent	Iron Percent
0.6-0.75 maximum	1.0 maximum	1.0 maxi- mum	0.04 maximum	0.03 maximum	16.0-18.0 maximum	0.75 maximum	Balance

Forms Specifications.

See Specification [Table 2-2](#).

Heat Treatment.

- Anneal: 1550-1650 °F.
- Temper: 300-800 °F.
- Harden: 1850-1950 °F, cool rapidly.
- 440A: tensile 270,000 PSI, yield 260,000 PSI.
- 440B: tensile 280,000 PSI, yield 270,000 PSI.
- 440C: tensile 285,000 PSI, yield 275,000 PSI.

**2.9.69 15-7-Molybdenum Steel Martensitic Stainless.** This alloy is a further development of 17-7PH alloy and due to molybdenum content it can be heat treated to high strength at room and elevated temperature (up to 1000 °F). The heat treatment is identical to 17-7PH and other properties are identical or similar to 17-7PH.

Composition Range.

Carbon Percent	Magnesium Percent	Silicon Percent	Phosphorus Percent	Sulfur Percent	Chromium Percent	Nickel Percent	Molybdenum Percent
0.09	1.0	1.0	0.4	0.03	14.0-16.0	6.50-7.75	2.0-3.0
Aluminum Percent	Iron Percent						
0.75-1.50	Balance						

Forms.

Sheet, strip, plate, bars and forgings.

Specification.

AMS 5520, AMS 5657.

Heat Treat-  
ment.

Condition A. Solution anneal sheet and strip, 1925-1975 °F, 3 minutes per 0.1 inch thickness, air cool. Bar and forgings solution anneal 1925-1975 °F, 30 minutes per inch thickness, water quench. Age condition A to condition TH1050, 1375-1425 °F, 1-1/2 hour (austenite conditioning), air cool to 50-60 °F within 1 hour, hold at 50-60 °F, 1/2 hour (condition T) + 1040-1060 °F, 1-1/2 hour, air cool. Age condition A to condition RH 950, 1735-1765 °F, 10 minutes (austenite conditioning), air cool (condition A 1750) ±90-110 °F, 8 hours (condition R100) +940-960 °F, 1 hour, air cool. Age condition C, sheet cold rolled or wire cold drawn to condition CH 900, by heating 890-910 °F for 1 hour, air cool. TH and RH conditions are also used with difference final age hardening temperatures, such as TH1150, RH1050, etc.

Typical Properties for Various Conditions.

- Condition A - 130 to 150 KSI ultimate, 55-65 KSI yield, hardness 90-100.
- Condition T - 125 to 145 KSI ultimate, 75-90 KSI yield, hardness 28-30.
- Condition TH1050 - 190 to 210 KSI ultimate, 170-200 KSI yield, hardness RC40-45.
- Condition RH950 - 225 to 240 KSI ultimate, 200-225 KSI yield, hardness RC46-48.
- Condition R100 - 180 KSI ultimate, 125 KSI yield, hardness RC40.
- Condition C - 220 KSI ultimate, 190 yield, hardness RC45.
- Condition CH900 - 265 KSI ultimate, 260 yield, hardness RC50.

**2.9.70 PH14-8 Molybdenum.** This alloy (sheet) is similar to PH15-7 Molybdenum except it has slightly lower tensile and yield strength but considerable higher toughness and superior welding characteristics. In general this alloy is unstable during exposure to temperatures exceeding 500 °F, which is a common characteristic of precipitation hardening stainless steels.

Composition Range.

Carbon Percent	Magnesium Percent	Silicon Percent	Ph Percent	Sulfur Percent	Chromium Percent	Nickel Percent	Me Percent
0.02-0.05	1.0	1.0	0.015	1.0	13.50-15.50	7.50-9.50	2.0-3.0
Aluminum Percent	Iron Percent						
0.75-1.50	Rem						



Forms and Conditions. Available - Sheet and strip. Condition A - annealed C cold worker.

Heat Treatment. Anneal to Condition A, 1800-1850 °F, 30 minutes air cool. Age condition A to SRH conditions, 1685-1715 °F, 1 hour, air cool and within 1 hour cool to -100 °F, 8 hours + age 1 hour, air cool. Aging at 940-960 °F or 1040-1060 °F is generally used with the higher temperature giving somewhat lower strength but after better toughness. Age cold worked alloy, condition C, 890-910 °F or 1040-1060 °F, 1 hour, air cool.

Typical properties for various conditions.

Condition A - 150 KSI ultimate, 65 KSI yield, hardness, RB100 max.

Condition SRH950 - 220 KSI ultimate, 190 KSI yield hardness RC40.

Condition SRH1050 - 200 KSI ultimate, 180 KSI yield, hardness RC38.

This alloy is subject to salt stress corrosion, however, early test indicate it is superior in this respect to 17-7PH and 15-7PH Molybdenum. This general welding characteristics is similar to 17-7PH. Higher toughness may be obtained by annealing after welding and then heat treating.

2.9.71 19-9DL 19-9DX. These stainless steels are not heat treatable, but can be hardened to a limited extent by cold working or hot cold working. In chemical composition 19-9DL contains columbium which was replaced by a higher molybdenum and titanium content in 19-9DX.

Composition Range.

Carbon Percent	Magnesium Percent	Silicon Percent	Ph Percent	Sulfur Percent	Chromium Percent	Nickel Percent	Molybdenum Percent
0.28-0.35	0.75-1.50	0.30-0.80	0.040	0.030	18.0-21.0	8.0-11.0	1.25-2.00
Tungsten Percent	Titanium Percent	Copper Percent	Iron Percent				
1.0-1.75	0.40-0.75	0.50	Balance				

Heat Treatment.

**NOTE**

Intergranular corrosion may occur in certain environments unless annealed at 1800 °F, followed by rapid cooling.

Bar and forgings, 1800-2150 °F (1/2 to 1 hour) rapid air cool, oil water quench. Sheet/strip, 1650-1800 °F (1/2 to 1 hour) rapid air cool. Avoid higher temperatures to prevent resolution and precipitation of carbides. Castings, 1950-2050 °F, 1/2 to 1 hour minimum, air cool. Solution Treat: Same as anneal. Stress relief: 1175-1225 °F (4 hours) air cool. This treatment is applied to hot worked or hot cold worked material for service up to 1300 °F. It is also applied to cold worked materials immediately after working to prevent stress cracking. Age: Bar and forgings, 1200-1400 °F, casting 1575-1625 °F, 8 hours minimum, air cool.

2.9.72 AM-350 Steel - Age Hardening Stainless. This alloy is one of a series of age hardening steels which combines high strength at temperatures up to 800 °F and higher with the corrosion resistance of stainless steels.

Composition Range.

Carbon Percent	Magnesium Percent	Silicon Percent	Phosphorus Percent	Sulfur Percent	Chromium Percent	Nickel Percent	Molybdenum Percent
0.08-0.12	0.5-1.25	0-0.5	0-0.04	0-0.03	16.0-17.0	4.0-5.0	2.5-3.25
Nitrogen Percent	Iron Percent						
0.07-0.13	Balance						



## TO 1-1A-9 NAVAIR 01-1A-9

### Forms and Conditions.

See Specification [Table 2-2](#).

### Heat Treatment.

Anneal to condition H - 1900-1950 °F, 3/4 hour minimum per inch of thickness, rapid air cool to 80 °F. Anneal to condition L - 1685-1735 °F, 3/4 hour minimum, per inch of thickness, rapid air cool to 80 °F. Subzero cool and age condition L to condition SCT, cool to 100 °F, hold 3 hours minimum + 850-1050 °F, 3 hours minimum. Age to condition SCT 850 °F, 825-875 °F. Age to condition SCT 1000 975-1025 °F. Double age either condition H or condition-L to condition DA, 1350-1400 °F, 2 hours, air cool to 80 °F and heat to 825-875 °F, 3 hours. Thoroughly degreased and cleaned prior to annealing to avoid harmful surface reactions and to facilitate subsequent pickling. Allowance must also be made for growth which will result from heat treating. The expansion on aging from condition H to set amounts to 0.002-0.004 inch per inch.

**2.9.73 AM-355 Steel - Age Hardening Stainless.** This alloy combines high strength at temperatures up to 850 °F with the corrosive resistance of stainless steel. This alloy differs from AM-350 by a lower chromium and a higher carbon content. It possesses good formability in the high temperature annealed condition. Corrosion resistance of this alloy is slightly lower than that of AM-350.

### Forms Specifications.

See Specification [Table 2-2](#).

### Heat Treatment.

Anneal to condition H for maximum formability and stability. Anneal to condition H: Plate and forgings at 1925-1975 °F, 1 hour minimum per inch, water quench; sheet and welded tubing, 1850-1900 °F, 3/4 hour minimum per inch, rapid air cool. Bar should not be annealed to condition H unless subsequently subjected to forgings. Anneal to Condition L: 1685-1735 °F. Sheet and strip, 3/4 hour per inch, air cool; plate 3/4 hour inch, oil or water quench. Condition H plate, if not subsequently severely cold formed, should be equalized before annealing to condition L and aging to condition SCT. Bar forgings and tubing, 1 hour minimum per inch thickness, oil or water quench. Equalize and age bar for best machineability, 1350-1400 °F, 3 hours, air cool to 80 °F maximum +1000-1050 °F, 3 hours. Resulting should be approximately RC38 Subzero cool and age condition L to condition SCT, cool to -100 °F, hold 3 hour minimum, 850-1050 °F for 3 hours minimum. Age condition SCT 850, 825-875 °F. Age to condition SCT 1000, 975-1025 °F. Double age condition L to condition DA, 1300-1450 °F 1 to 2 hours, air cool to 80 °F, 825-875 °F, 3 hours minimum. Homogenize sand and shell mold castings, 2000 °F, 2-4 hours, air cool up to 1 inch thick, oil or water quench, section above 1 inch.

**2.9.74 HNM Steel - Age Hardening Stainless.** This is a precipitation hardening austenitic steel, with high rupture and creep properties in the 1000-1400 °F and not prone to overage at these temperatures. In the solution annealed condition it has a Brinell hardness of 201 maximum. It has a low magnetic permeability, and is suitable for transformer parts, non-magnetic bolts, aircraft structural, engine components, shafts and gears. This material is very susceptible to work hardening. It is somewhat inferior to regular 18cr-8ni stainless types, however, machining requirements are similar requiring heavy positive feeds and sharp cutting tools. Welding is not recommended, however brazing may be successfully accomplished by use of orayacetylene torch and furnace methods, using an alloy conforming to specification AMS 4755.

### Composition Range.

Carbon Percent	Chromium Percent	Magnesium Percent	Nickel Percent	Phosphorus Percent	Silicon Percent	Sulfur Percent	Iron
0.30	18.5	3.5	9.5	0.25	0.5	0.025	Balance

### Forms Specifications.

None.

### Heat Treatment.

Anneal 2000-2150 °F, 30 minutes, water quench. Sections 5/8 inches thick may be air cooled. The optimum solution treatment for best properties after aging is approximately 2050 °F. Age 1300 °F, 16 hours, air cool.

**2.9.75 16-15-6 Steel - Iron - Chromium - Nickel - Alloy.** This alloy was developed as a replacement for 16-25-6 alloy and contains less nickel. However, the lower nickel content is balanced by additional manganese which allows an increase in the nitrogen content that can be retained during melting.

### Composition Range.

Carbon Percent	Chromium Percent	Magnesium Percent	Molybdenum Percent	Nickel Percent	Silicon Percent	Nitrogen Percent	Phosphorus Percent
----------------	------------------	-------------------	--------------------	----------------	-----------------	------------------	--------------------



0-0.07	15.0-17.5	6.5-8.5	5.0-7.0	14-0-17.0	0-1.0	0.30-0.40	0-0.03
Sulfur Percent	Iron						
0.03	Balance						
<u>Form.</u>	Bar, forging.						
<u>Specification.</u>	None.						
<u>Heat Treatment.</u>	Anneal 1700-2300 °F. Solution treat 2125-2175 °F, air cool, water or oil quench, depending on section size. Cold work (about 20 percent reduction) and age (bar up to 1-1/2 inch) 1200-1300 °F, 2 to 8 hours. At a temperature of 1200 °F a tensile of 145,000 and yield of 100,000 PSI is obtained.						

2.9.76 V57 Steel - Nickel Chromium Stainless (Austenitic). This alloy has a good combination of tensile and creep rupture properties up to 1500 °F at high stresses and is used for some parts of aircraft gas turbines.

Composition Range.

Aluminum Percent	Boron Percent	Carbon Percent	Chromium Percent	Magnesium Percent	Molybdenum Percent	Nickel Percent	Silicon Percent
0.25	0.008	0.06	15.0	0.25	1.25	25.5	0.55
Titanium Percent	Vanadium Percent	Sulfur Percent	Phosphorus Percent	Iron			
3.0	0.25	0.025	0.025	Balance			

Form. Bar, Forging.

Specification. None.

Heat Treatment. Anneal 1700-2300 °F. Solution treat 2125-2175 °F, air cool, water or oil quench, depending on section size. Cold work (about 20 percent reduction) and age (bar up to 1/2 inch) 1200-1300 °F 2 to 8 hours. At a temperature of 1200 °F a tensile of 145,000 and yield of 100,000 PSI is obtained.

2.9.77 V36 Steel Cobalt Base - Chromium-Nickel-Alloy. This is a solid solution - hardening alloy for service at 1300-1800 °F where strength and corrosion resistance is important. Used for guide vanes in gas turbines, after burner parts and high temperature springs. Chiefly furnished in sheet, but may be supplied in billet, bar, forging and wire.

Composition Range.

Carbon Percent	Chromium Percent	Chlorine Percent	Tantalum Percent	Iron Percent	Magnesium Percent	Molybdenum Percent	Nickel Percent
0.25-0.33	24.0-26.0	1.5	2.5	0-5.0	0-1.2	3.5-4.5	19.0-21.0
Silicon Percent	Tungsten Percent	Sulfur Percent	Phosphorus Percent	Cobalt			
0-1.0	1.5-2.5	0-0.03	0-0.03	Balance			

Specification. None.

Heat Treatment. This alloy is primarily solid solution hardened and only small strength increases can be obtained by aging. Solution treatment for thick sections 2200-2275 °F, 1 hour, water quench. Age 1400 °F for 16 hours. Stress relieve cold worked alloy 900 °F, 2 hours.

Form	Sheet		
Condition	Sol Treat 15 minutes 2250 °F+age	Sol Treat +20 percent, cool rapidly	Sol Treat +60 percent, cool rapidly
Tensile	147,000	166,000	279,000
Yield	83,000	127,000	248,000
RC	25		

2.9.78 W152 Steel Cobalt Chromium Tungsten Corrosion Resistant Alloy. This is a casting alloy generally used in the "as-cast" condition. It is used for investment cast parts requiring high stress rupture properties at elevated temperatures, has excellent castability and foundry characteristics. Primary use has been first-stage turbine vanes. Alternate Designations. Haynes Alloy No 152, Printed Wiring Assembly (PWA) 653, CF 239.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

Composition Range.

Carbon Percent	Chromium Percent	Chlorine + Tantalum Percent	Iron Percent	Magnesium Percent	Nickel Percent	Silicon Percent	Tungsten Percent
0.40-0.5	20.0-22.0	1.5-2.5	1.0-2.0	0-0.5	0-1.0	0-0.5	10.0-12.0
Phosphorus Percent	Sulfur Percent	Cobalt					
0-0.04	0-0.04	Balance					

Specification. None.

**2.9.79 Haynes Alloy No. 151 Cobalt Base Corrosion Resistant Alloy.** This alloy may be air melted or air cast. It is used as gas turbine blades and rotors within the heat range 1200-1700 °F.

Composition Range.

Boron Percent	Carbon Percent	Chromium Percent	Iron Percent	Magnesium Percent	Nickel Percent	Silicon Percent	Titanium Percent
0.03-0.08	0.4-0.5	19.0-21.0	0-2.0	0-1.0	0-1.0	0-1.0	0.05-0.5
Tungsten Percent	Phosphorus Percent	Sulfur Percent	Cobalt				
12.0-13.5	0-0.03	0-0.03	Balance				

Specification. None.

Forms. Available as castings and investment castings.

Heat Treatment. This material is generally used in the “as cast” condition. The best creep rupture properties are in the 1300-1500 °F range. Solution treat 2170-2200 °F, 1 hour minimum, rapid air cool. This treatment reduces tensile properties below 1400 °F and lowers creep rupture strength. Aging 1400 °F 4 hours air cool after solution treating, results in higher tensile properties than “as cast” material, but creep rupture properties are somewhat lower than the “as cast” alloy.

Hardenability. As-cast hardness at room temperature RC33.

**2.9.80 GMR-235 Nickel Base Corrosive Resistant Alloy.** GMR-235 and GMR-235D are nickel based alloys precipitation hardening, high temperature alloys developed for investment cast gas turbine wheels, buckets and vanes, operating above 1400 °F. They are similar to Hastelloy R-235 but contain more aluminum. The composition with maximum aluminum and titanium content is designated GMR-235D.

Composition Range				
	GMR-235 Percent		GMR-235D	
	Minimum	Maximum	Minimum	Maximum
Aluminum	2.5	3.5	3.25	4.0
Boron	0.05	0.1	0.05	0.1
Carbon	0.1	0.2	0.1	0.2
Chromium	14.0	17.0	14.0	17.0
Cobalt	0.1	0.2	0	0
Iron	8.0	12.0	3.5	5.0
Magnesium	0	0.25	0	0.1
Molybdenum	4.5	6.0	4.5	6.0
Silicon	0	0.60	0	0.3
Titanium	1.5	2.5	2.0	3.0
Nickel	Balance	Balance	Balance	Balance



<u>Specification.</u>	None.
<u>Forms.</u>	This material is available in wrought form only, except that GMR-235 is available in cast form.
<u>Heat Treatment.</u>	Solution treatment 2050 °F, 1 to 3 hours, air cool (GMR-235) Solution treatment 2100 °F, 2 hours, air cool (GMR-235D). For heavier sections (of both alloys) temperatures should be increased to 2150 °F, 2 to 4 hours, air cool. Aging at 1800 °F, 5 hours from the "as cast" condition improves the stress rupture life of the alloy. These alloys precipitation harden rapidly during air cooling and aging treatments are usually unnecessary. "As-cast" room temperatures hardness for both alloys is RC36 maximum. Tensile 115,000 PSI yield 90,000 PSI.

**2.9.81 Hastelloy Alloy R-235 Nickel Base Corrosion Resistant Alloy.** This is a nickel base aluminum-titanium precipitation hardening alloy. It possesses high strength up to 1800 °F with good resistance to oxidation and over aging in high temperature service. This alloy is readily fabricated and welded in the solution treated condition.

Composition Range.

Aluminum Percent	Boron Percent	Carbon Percent	Chromium Percent	Cobalt Percent	Iron Percent	Magnesium Percent	Molybdenum Percent
1.75-2.25	0-0.009	0-0.16	14.0-17.0	0-2.5	9.0-11.0	0-0.25	4.5-6.5
Silicon Percent	Titanium Percent	Phosphorus Percent	Sulfur Percent	Nickel Percent			
0-0.6	2.25-2.75	0-0.01	0-0.03	Balance			

Specification.

<u>Forms.</u>	Sheet, Strip, Plate, Bar and Wire.
<u>Heat Treatment.</u>	Solution treatment 1950-2000 °F 1/2 hour, water quench. Material treated at higher solution temperature (2200 °F) is subject to strain-age cracking. Final heat treatment after fabrication of sheet and bar depends upon properties desired. To obtain maximum long time stress-rupture life, solution treat at 2175-2225 °F, 15 minutes, water quench. Then heat to 2025-2075 °F, hold at temperature for 30 minutes and cool in still air. To obtain maximum room and high temperature tensile strength or short time rupture strength, solution treat at 1950-2000 °F hold at temperature for 30 minutes and air cool. Then age at 1385-1415 °F hold at temperature for 16 hours and air cool.

Form	Sheet
Condition Thickness (Inch)	Sol Treat 1975 °F Water Quench 0.021 Sol Treat 2200 °F Water Quench 0.70
Tensile, Maximum PSI	150,000
Yield, Maximum	95,000
PSI RC-Maximum	27

**2.9.82 Inconel Alloy 718 Steel Nickel Chromium Stainless Alloy.** This is a relatively new alloy and heat treatment and fabrication procedures are still under development. It has good properties up to 1300 °F, slow response to age-hardening and good ductility from 1200-1400 °F. It is readily welded in either the annealed or aged condition.

Composition Range.

Aluminum Percent	Carbon Percent	Chromium Percent	Chlorine Percent	Copper Percent	Magnesium Percent	Molybdenum Percent	Nickel Percent
0.4-1.0	0-0.1	17.0-21.0	+Tantalum Percent	0-0.75	0-0.50	2.0-4.0	50.0-55.0
Silicon Percent	Titanium Percent	Sulfur Percent	Iron				
0-0.5	0.3-1.3	0-0.03	Balance				

<u>Specification.</u>	None.
-----------------------	-------



## TO 1-1A-9 NAVAIR 01-1A-9

<u>Forms.</u>	Sheet, Strip, Bar, Investment Castings.
<u>Heat Treatment.</u>	Both single age and double age treatments may be employed, however, the latter is preferred for highest strength up to 1300 °F. Solution treat rods, bars and forgings 1800-1900 °F. Somewhat higher creep rupture properties are obtained at the higher temperatures. Solution treat sheet at 1725 °F. Single age anneal alloy at 1325 °F 16 hours, air cool. Double age anneal alloy at 1325 °F 8 hours, furnace cool, 20 °F per hour to 1150 °F air cool or 1325 °F 8 hours, furnace cool, 100 °F per hour to 1150 °F, hold 8 hours, air cool. Both of these double age treatments appear to give the same results.

Form:	Hot Rolled Bar 0.0500 Inch Diameter		
Condition	Anneal + Age		
	1800 °F 1 hour + 1325 °F		
	8 hour*	8 hour**	16 hour
Thickness - Inch	0.500		
Tensile PSI	211,000	204,000	193,000
Yield PSI	174,000	173,000	154,000

\*Furnace cool at temperature reduction of 100 °F per hour to 1150 °F hold 8 hours air cool.

\*\* Furnace cool at temperature reduction of 20 °F per hour to 1150 °F air cool.

**2.9.83 Udimet 700 Highly Alloyed Nickel Base Corrosion Resistant.** This alloy has higher elevated temperature tensile and stress-rupture strength than most wrought cobalt or nickel based alloys. It also has superior creep resistance, fatigue strength and high oxidation resistance. Welding is generally not recommended.

### Composition Range.

Aluminum Percent	Boron Percent	Carbon Percent	Chromium Percent	Cobalt Percent	Copper Percent	Iron	Magnesium Percent
3.75-4.75	0.025-0.035	0.03-0.1	14.0-16.0	17.0-20.0	0-0.1	0-4.0	0-0.15
Molybdenum Percent	Silicon Percent	Titanium Percent	Zirconium Percent	Sulfur Percent	Nickel Percent		
4.5-6.0	0-0.2	2.75-3.75	0-0.06	0-0.015	Balance		

### Specification.

<u>Forms.</u>	Bars, Billets, Castings, Forgings.
<u>Heat Treatment.</u>	Solution annealing for castings 2075-2125 °F, 2 hours air cool. Solution annealing for forgings 2125-2175 °F, 4 hours air cool. Solution treat. 1950-2000 °F, 4 to 6 hours, air cool. Intermediate aging 1535-1565 °F, 24 hours air cool. Final aging 1385-1415 °F, 16 hours air cool. Hardens by aging and cold working.

**2.9.84 Rene 41 Nickel Base Heat Treatable Stainless Alloy.** This alloy possesses exceptional mechanical properties at temperatures up to 1800 °F. It can be formed and also welded in the annealed condition. If cooled at a slower rate than specified, e.g. in less than 4 seconds from 2150-1200 °F, age hardening results and forming becomes difficult. Distortion is comparatively low if material is subsequently solution treated and water quenched. Best machinability is obtained in the fully aged condition after either oil or water quenching from solution treating temperature. This alloy may be fusion welded if copper and gas backing with a tight hold down is used. Start and finish should be made on metal tab of the same thickness using an inert gas atmosphere of 2 helium to 1 argon. Following the torch with a water spray reduces the hardness and produces maximum ductility in the weld and heat affected zones.

### **2.9.84.1 Composition Range.**

#### Composition Range.

Carbon Percent	Magnesium Percent	Silicon Percent	Chromium Percent	Titanium Percent	Aluminum Percent	Molybdenum Percent	Boron Percent
0.06-0.12	0-0.5	0-0.5	18.0-20.0	3.0-3.3	1.5-1.8	9.0-10.5	0-0.01
Cobalt Percent	Iron Percent	Nickel Percent					
10.0-12.0	0-5.0	Balance					

Specification. None.



Forms. Sheet, Strip, Plate, Bar, Wire.  
Heat Treatment. For maximum formability 1950-2150 °F, 30 minutes, water quench or cool from 2150-1200 °F in 4 seconds maximum. Solution treat 1950-2150 °F, 30 minutes, quench or air cool. Heat treatment for high short time strength: Solution treat 1950 °F, 30 minutes, cool to 1200 °F in 4 seconds maximum + 1400 °F, 16 hours. Heat treat for good ductility and high creep rupture strength, solution treat 2150 °F 30 minutes + 1650 °F 4 hours. Hardenability: Alloy must be water quenched to retain soft solution treated conditions.

Form	ALL
Condition	2150 °F air cooled
Tensile	2150 °F water quenched
Yield	130,000
Rockwell Hardness	160,000
	65,000
	RC43
	RB93

**2.9.85 Nicrotung Nickel Base Corrosion Resistant Alloy.** This is a nickel base investment casting alloy which is strengthened by addition of cobalt, aluminum and titanium. It has high creep strength and excellent oxidation resistance in the high temperature range 1500-1800 °F combined with good room temperature strength.

Composition Range.

Aluminum Percent	Boron Percent	Carbon Percent	Chromium Percent	Cobalt Percent	Titanium Percent	Tungsten Percent	Zirconium Percent
3.75-4.75	0.02-0.08	0.08-0.13	11.0-13.0	9.0-11.0	3.75-4.75	7.0-8.5	0.02-0.08
Nickel Percent							
Balance							

Specification. None.

Forms. Investment castings.

Heat Treatment. Heat treatment is not recommended for this alloy. This material has “as-cast” hardness of RC38-40.

**2.9.86 Nimonic 105 Nickel-Cobalt-Chromium Corrosion Resistant Alloy.** This alloy has excellent resistance to creep at very high temperatures. It is designed for use as turbine blades and rotors used in gas turbines. Corrosion resistance is good and resistance to oxidation under repeated heating and cooling is very good.

Composition Range.

Aluminum Percent	Carbon Percent	Chromium Percent	Cobalt Percent	Copper Percent	Iron Percent	Magnesium Percent	Molybdenum Percent
4.2-4.8	0-0.2	13.5-16.0	18.0-22.0	0-0.5	0-1.0	0-1.0	4.5-5.5
S1 Percent	Titanium Percent	Nickel Percent					
0-1.0	0.9-1.5	Balance					

Specification. None.

Forms. Sheet, Strip, Bar.

Heat Treatment. For maximum stress-rupture life in range 1560-1740 °F, fully heat treat solution treat, and double age as follows: Solution treat 2102 °F, 4 hours, air cool. Double age 1922 °F, 16 hours, air cool and 1526 °F, 8 hours, air cool. Where stress rupture strength above 1562 °F is not the important property, but tensile strength, elongation and impact strength up to 1292 °F is desired, the following heat treatment is recommended. Solution treat 2104 °F, 4 hours, air cool. Age 1562 °F, 16 hours, air cool.

## 2.10 MACHINING OF STEELS (GENERAL).

**2.10.1 Machinability.** There are five basic factors affecting machinability as related to steel:

- The capacity and rigidity of the machine tool.
- Cutting fluids.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

- Design composition and hardness of the cutting tool.
- Cutting condition with respect to feeds and speeds.
- The structure of the steel to be machined.

**2.10.2 Cutting Tool Angles.** The cutting tool angles (back rake, side clearance, front clearance, and side rake) are highly important in the machining of metals. The range of values based on general practice for the machining of steel and steel alloys, are as follows:

- Back rake angle, 8-16 degrees.
- Side rake angle, 12-22 degrees.
- Front clearance angle, 8-13 degrees.
- Side clearance angle, 10-15 degrees.

**2.10.2.1** Regardless of the material of which the cutting tool is made, the cutting action is the same. The main difference is the cutting speed. The carbon-steel tool cuts at low speed. The highspeed tool cuts at twice the speed of carbon-steel, the cast alloys at twice the speed of high-speed steel, and the sintered carbides at twice that of the cast alloys. The cutting speeds listed in [Table 2-4](#) are approximate speeds using high-speed steel tools, and are to be used only as a basis from which proper speeds for a particular part may be calculated. These speeds are based on SAE 1112 steel, which is assigned a machinability rating of 100 percent. In order to obtain an approximate starting speed for different steels, select the type of operation, the width, depth or diameter of cut and obtain the recommended cutting speed for SAE 1112 from [Table 2-3](#) then refer to [Table 2-4](#) for the percent rating of the metal to be machined, and multiply the Surface Feet per Minute (SFM) value from [Table 2-5](#) by the rating in [Table 2-4](#). The result is the recommended SFM for the cutting operation. For a known diameter and SFM be used for an operation, the corresponding Revolution Per Minute (RPM) can be obtained from [Table 2-5](#) and [Table 2-6](#).

**2.10.2.2** The term cutting feed is used to express the axial distance the tool moves in each revolution. A course feed is usually used for roughing operations, and a fine feed for finishing operations. In general, the feed remains the same for different cutting tool steels, and only the speed is changed. Approximate cutting feeds are listed in [Table 2-3](#). For tool corrections when improper machining on an operation is encountered, refer to [Table 2-7](#) for recommended checks.

**2.10.2.3** The use of a proper coolant (cutting fluid) often results in an increase of cutting speed for the same tool life, and also acts as a lubricant giving better cutting action and surface finish. Recommended cutting fluids for steels are lard oil, mineral oils, sulphurized oils, and soluble or emulsifiable oils.

**Table 2-3. Cutting Speeds and Feeds for SAE 1112 Using Standard High Speed Tools**

Tool Name	Size of Hole (Inch)	Width or Depth of Cut (Inch)	SFM	Feed (Inch/Rev)
Form Circular or Dovetail	--	Width - 0.500	165	0.0025
		Width - 1.000	160	0.0020
		Width - 1.500	160	0.0018
		Width - 2.000	155	0.0015
		Width - 2.500	150	0.0012
Twist Drills	0.250		105	0.0045
	0.500		105	0.005
	0.750		115	0.006
	1.000		115	0.007
	1.250		120	0.008
Box Tools Blade		Depth - 0.125	165	0.007
		Depth - 0.250	160	0.0065
		Depth - 0.375	155	0.0055
		Depth - 0.500	150	0.0045



**Table 2-3. Cutting Speeds and Feeds for SAE 1112 Using Standard High Speed Tools - Continued**

Tool Name	Size of Hole (Inch)	Width or Depth of Cut (Inch)	SFM	Feed (Inch/Rev)
Threading and Tapping	Over 25 Pitch		30-40	
	15 to 25 Pitch		20-30	
	Less than 15 Pitch		15-20	
Hollow Mills		0.062	150	0.010
		0.125	140	0.008
		0.187	135	0.007
		0.250	130	0.0065
Reamers	Under 1/2 inch		145	0.007
	Over 1/2 inch		145	0.010
Cut Off		Width - 0.062	165	0.002
		Width - 0.125	175	0.0025
		Width - 0.187	180	0.0025
		Width - 0.250	190	0.003

**Table 2-4. Machinability Rating of Various Metals**

SAE Designation	Rating Percent	Brinell Hardness
1010	50	131-170
1015	50	131-170
1020	65	137-174
1022	70	159-192
1025	65	116-126
1035	65	174-217
1040	60	179-229
1045	60	179-229
1050	50	179-229
1055	55	192-197
1060	60	183-201
1070	45	183-241
1080	45	192-229
1095	42	197-248
1112	100	179-229
1117	85	143-179
1137	70	187-229
2317	55	174-217
2330	50	179-229
2340	45	187-241
2515	30	179-229
3115	65	143-174
3140	55	187-229
3310	40	170-229
4037	65	170-229
4130	65	187-229
4135	64	170-229
4137	60	187-229
4140	66	179-197
4150	50	187-235



Table 2-4. Machinability Rating of Various Metals - Continued

SAE Designation	Rating Percent	Brinell Hardness
4337	50	187-241
4340	45	187-241
4615	65	174-217
4620	62	152-179
4640	55	187-235
5210	30	183-229
6150	50	197
8615	67	170-217
8617	63	170-217
8620	60	170-217
8630	65	179-229
8640	60	179-229
8735	55	179-229
8740	60	179-229
9260	45	187-255
9262	45	187-255
9310	40	207-217



Table 2-5. Conversion of SFM to RPM (10-110)

Diameter in Inches	SFM													
	10	15	20	25	30	40	50	60	70	80	90	100	110	
1/16	611	917	1222	1528	1823	2445	3056	3667	4278	4889	5500	6111	6722	
1/8	306	458	611	764	917	1222	1528	1833	2139	2445	2750	3056	3361	
3/16	204	306	407	509	611	815	1019	1222	1426	1630	1833	2037	2241	
1/4	153	229	306	383	458	611	764	917	1070	1222	1375	1528	1681	
5/16	122	183	244	306	367	489	611	733	856	978	1100	1222	1345	
3/8	102	153	204	255	306	407	509	611	713	815	917	1010	1120	
7/16	87	131	175	218	262	349	437	524	611	698	786	873	960	
1/2	76	115	153	191	229	306	382	458	535	611	688	764	840	
9/16	68	102	136	170	204	272	340	407	475	543	611	679	747	
5/8	61	92	122	153	183	244	306	267	428	489	550	611	672	
11/16	56	83	111	139	167	222	278	333	389	444	500	556	611	
3/4	51	76	102	127	153	203	255	306	357	407	458	509	560	
13/16	47	71	94	118	141	188	235	282	329	376	423	470	517	
7/8	44	65	87	109	131	175	218	262	306	349	393	436	480	
15/16	41	61	81	102	122	163	204	244	285	326	367	407	448	
1	38	57	76	96	115	153	191	229	267	306	344	382	420	
1-1/8	34	51	68	85	102	136	170	204	238	272	306	340	373	
1-1/4	31	46	61	76	92	122	153	183	214	244	275	306	336	
1-3/8	28	42	56	69	83	111	139	167	194	222	250	278	306	
1-1/2	25	38	51	64	76	102	127	153	178	204	229	255	280	
1-5/8	24	35	47	59	70	94	117	141	165	188	212	235	259	
1-3/4	22	33	44	55	65	87	109	131	153	175	196	218	240	
1-7/8	20	31	41	51	61	81	102	122	143	163	183	204	224	
2	19	29	38	48	57	76	95	115	134	153	172	191	210	
2-1/4	17	25	34	42	51	68	85	102	119	136	153	170	187	
2-1/2	15	23	31	38	46	61	76	92	107	122	137	153	168	
2-3/4	14	21	28	35	42	56	69	83	97	111	125	139	153	
3	13	19	25	32	38	51	64	76	89	102	115	127	140	



Table 2-6. Conversion of SFM to RPM (120-300)

Diameter in Inches	SFM															
	120	130	140	150	160	170	180	190	200	225	250	270	300			
1/16	7334	7945	8556	9167	9778	10390	11000	11612	12223	13751	15279	16807	18334			
1/8	3667	3973	4278	4584	4889	5195	5500	5806	6111	6875	7639	8403	9167			
3/16	2445	2648	2852	3056	3259	3463	3667	3871	4074	4584	5093	5602	6112			
1/4	1833	1986	2139	2292	2445	2597	2750	2903	3056	3438	3820	4202	4584			
5/16	1467	1589	1711	1833	1956	2078	2200	2322	2445	2750	3056	3361	3667			
3/8	1222	1324	1436	1528	1630	1732	1833	1935	2037	2292	2546	2801	3056			
7/16	1048	1135	1222	1310	1397	1484	1572	1659	1746	1964	2183	2401	2619			
1/2	917	993	1070	1146	1222	1299	1375	1451	1528	1719	1910	2101	2292			
9/16	815	883	951	1019	1086	1154	1222	1290	1358	1528	1698	1867	2037			
5/8	733	794	856	917	978	1039	1100	1161	1222	1375	1528	1681	1833			
11/16	667	722	778	833	889	945	1000	1056	1111	1250	1389	1528	1667			
3/4	611	662	713	764	815	866	917	968	1019	1146	1273	1401	1528			
13/16	564	611	658	705	752	799	846	893	940	1058	1175	1293	1410			
7/8	524	567	611	655	698	742	786	829	873	982	1091	1200	1310			
15/16	489	530	570	611	652	693	733	774	815	917	1019	1120	1222			
1	458	497	535	573	611	649	688	726	764	859	955	1050	1146			
1-1/8	407	441	475	509	543	577	611	645	679	764	849	934	1019			
1-1/4	367	397	428	458	489	519	550	581	611	688	764	840	917			
1-3/8	333	361	389	417	444	472	500	528	556	625	694	764	833			
1-1/2	306	331	357	382	407	433	458	484	509	573	637	700	764			
1-5/8	282	306	329	353	376	400	423	447	470	529	588	646	705			
1-3/4	262	284	306	327	349	371	393	415	437	491	546	600	655			
1-7/8	244	265	285	306	326	346	367	387	407	458	509	560	611			
2	229	248	267	287	306	325	344	363	382	430	477	525	573			
2-1/4	204	221	233	255	272	289	306	323	340	382	424	467	509			
2-1/2	183	199	214	229	244	260	275	290	306	344	382	420	458			
2-3/4	167	181	194	208	222	236	250	264	278	313	347	382	417			
3	153	166	178	191	204	216	229	242	255	286	318	350	382			



**Table 2-7. Tool Correction Chart**

Tool	Check:
Tool Chatter	<ol style="list-style-type: none"> <li>1. Tool overhand (reduce to minimum)</li> <li>2. Work Support (eliminate vibration)</li> <li>3. Nose radius (too large a radius may cause chatter)</li> <li>4. Tool clearance (be sure end cutting edge angle is sufficient)</li> <li>5. Feed (increase feed if too light a feed has tendency to rub rather than cut)</li> <li>6. Tool load (vary side cutting edge angle to correct improper load)</li> <li>7. Chip breaker (widen breaker if chips are too tight)</li> </ol>
Chipping of Cutting Edge	<ol style="list-style-type: none"> <li>1. Edge sharpness (Hone or chamber slightly)</li> <li>2. Chip Breaker (widen breaker if tight chip causes chipping)</li> <li>3. Speed (Increase)</li> <li>4. Coolant (Heating and cooling of tip may cause chipping)</li> </ol>
Rapid Tool Wear	<ol style="list-style-type: none"> <li>1. Feed (Increase)</li> <li>2. Speed (Low and excessive speeds cause tool wear)</li> <li>3. Relief angles (clearance may not be sufficient)</li> <li>4. Nose radius (decrease size)</li> </ol>
Unsatisfactory Finish	<ol style="list-style-type: none"> <li>1. Speed (rough finishes can be eliminated by increasing speed)</li> <li>2. Nose radius (too large a nose radius mats finish)</li> </ol>

## 2.11 MACHINING CORROSION RESISTING STEEL.

The corrosion resisting steels, especially the 18-8 grades, are more difficult to machine than the carbon steels and most other metals. Even though they are more difficult to machine, the same general methods are used with modification/compensation for the individual characteristics of each type or grade. To improve machining characteristics of some types, their chemical content is modified by adding selenium and sulfur. The modified alloys which are usually designated by a suffix to type number such as 430 F or Selenium. Exceptions are Type 416 and Type 303.

**2.11.1 Machining Comparison of Corrosion Resisting Steel.** For comparison and as a general guide to the machining characteristics of free machining screw stock Grade B1112 as an 100 percent machinable "norm." This table is only intended as a starting point and is not intended to replace any information accumulated through experience or other available data.

**2.11.2 Machining of the Corrosion Resisting Steels.** In machining of the corrosion resisting steels, difficulty will be experienced from seizing, galling and stringing. To overcome these problems requires control of speeds, cutting tools, and lubricants. The following general practices are recommended for shaping/grinding cutting tools, equipment, etc., for cutting corrosion resisting steel:

- a. Select tools of proper alloy/type and keep cutting edges sharp, smooth, free of burrs, nicks and scratches.
- b. Avoid overheating cutting tool when grinding to prevent surface and stress cracking.
- c. Grind tools with generous lip rake and with ample side and front clearance.
- d. Speeds are critical in machining stainless; select speed about 50 percent slower than those used for carbon steels as a starting point.
- e. In general, use slow speeds and heavy feed to reduce effect of work hardening. Avoid riding of tool on work and intermittent cutting when possible.
- f. Apply proper lubricant/coolant to cutting tool to prevent overheating.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

- g. Support cutting tool rigidly near work to prevent lash and other difficulty from use of heavy cutting feeds.

**2.11.3 Cutting Tools for Machining Corrosion Resisting Steels.**

**NOTE**

Some types of tool steel are available in raw stock in accordance with Federal Specifications, see [Paragraph 7.2](#). Prior to attempting local manufacture of cutting tools, facilities/equipment must be available to properly heat treat. In addition, from an economic standpoint, it is usually advisable to obtain most cutting tools pre-finished to size, etc., and heat treated.

Selection of cutting tool is important for machining stainless due to tough machining characteristics. The following is a recommended guide for selection of tools:

- For general machining and short runs use high speed tool steels such as Tungsten Type T1 (18-41) and Molybdenum-Tungsten Type M3 (6-6-3).
- For medium runs at approximately 25 percent higher speed, use Tungsten-Cobalt Type T5 (18-4-2-8) and Tungsten-Cobalt Type T4.
- For long production runs at high speed, use Tungsten Carbides. Cutting tool of these alloys can be used at approximately 100 percent faster speeds than the Tungsten-Cobalt type.

**Table 2-8. General Machining Comparison of Corrosion Resisting Steel to Free Machining Screw Stock B1112**

Grade/Type		Machinability Rating	Grade/Type		Machinability Rating
Group I	430F	80 percent	Group III	420	45 percent
	416	75 percent		431	45 percent
	420F	70 percent		440	45 percent
	303	65 percent		442	45 percent
				446	45 percent
				347	40-45 percent
Group II	403	55 percent	Group IV	302	40 percent
	410	50 percent		304	40 percent
	430	50 percent		309	40 percent
	440F	50 percent		316	40 percent

**Table 2-9. Suggested Cutting Speeds and Feeds**

Alloy Type/ Grade	Feed Inch <u>1</u> / Grade	Cutting Speed SFM	Operation	Tool Material
302, 304, 309, 310, 314, 316	0.020-0.040	20-40	Rough	High Speed Steel
	0.008-0.015	50-80	Finish	High Speed Steel
	0.020-0.040	40-60	Rough	Tungsten-Cobalt
	0.008-0.015	90-110	Finish	Tungsten-Cobalt
	0.010-0.030	150-200	Rough	Carbide
	0.008-0.018	150-300	Finish	Carbide
420, 431, 440, 442, 446, 347, 321	0.015-0.040	20-40	Rough	High Speed Steel
	0.008-0.018	55-90	Finish	High Speed Steel
	0.015-0.040	40-80	Rough	Tungsten-Cobalt
	0.008-0.018	100-130	Finish	Tungsten-Cobalt
	0.015-0.030	165-220	Rough	Carbide
	0.005-0.015	165-330	Finish	Carbide



**Table 2-9. Suggested Cutting Speeds and Feeds - Continued**

Alloy Type/ Grade	Feed Inch <u>1</u> /	Cutting Speed SFM	Operation	Tool Material
430F, 416	0.015-0.040	30-60	Rough	High Speed Steel
	0.008-0.018	75-120	Finish	High Speed Steel
	0.015-0.040	60-105	Rough	Tungsten-Cobalt
	0.005-0.015	135-180	Finish	Tungsten-Cobalt
	0.010-0.030	225-300	Rough	Carbide
	0.005-0.015	225-450	Finish	Carbide
420F 303	0.015-0.050	25-55	Rough	High Speed Steel
	0.005-0.015	65-105	Finish	High Speed Steel
	0.020-0.050	50-90	Rough	Tungsten-Cobalt
	0.005-0.015	100-155	Finish	Tungsten-Cobalt
	0.010-0.030	175-240	Rough	Carbide
	0.005-0.015	195-350	Finish	Carbide
<p style="text-align: center;"><b>NOTE</b></p> <p><u>1</u>/Feeds cited are based on turning 1 inch stock or larger. Feeds for smaller sizes should be reduced proportionally to size of material being turned.</p>				

## 2.12 TURNING OF THE CORROSION RESISTING STEELS.

### NOTE

In grinding chip breakers, allow for chip to clear work or rough finish will result.

Tools for turning the corrosion steels should be ground with a heavy side rake clearance for maximum cut freedom. The upper surface of the tool should be finished with a fine wheel or hand stoned to prevent galling. For chip disposal or breakage a chip groove is usually necessary except with the free machining grades. In addition, the chip breakage is a safety precaution to prevent difficulty and hazards in breaking the expelled cutting. Do not allow tools to become dull to prevent surface hardening from rubbing and hard spots which are difficult to remove. The softer condition of stainless is not necessarily the easiest to cut. It is generally preferable that material be moderately hardened (Brinell 200-240) for best machining. Another factor requiring consideration in machining stainless is high co-efficient of thermal expansion which will necessitate adjusting (slacking off) centers as material heats up. The recommended cutting speeds, tool angles and feeds for turning corrosion resisting steel are cited in [Table 2-9](#) and [Table 2-10](#).

**Table 2-10. Tool Angles - Turning**

Tool Angles	High Speed Tool Steel	Cobalt	Carbide
Top Rake	5-10°	5-10°	-5-8°
Back Rake (side)	4-10°	8-15°	6-12°
Side Clearance	5-8°	6-10°	6-10°
End Relief	4-10°	4-10°	4-10°
Side Cutting Lead	5-15°	4-12°	3-12°
Front Clearance	7-10°	7-10°	5-10°



Table 2-10. Tool Angles - Turning - Continued

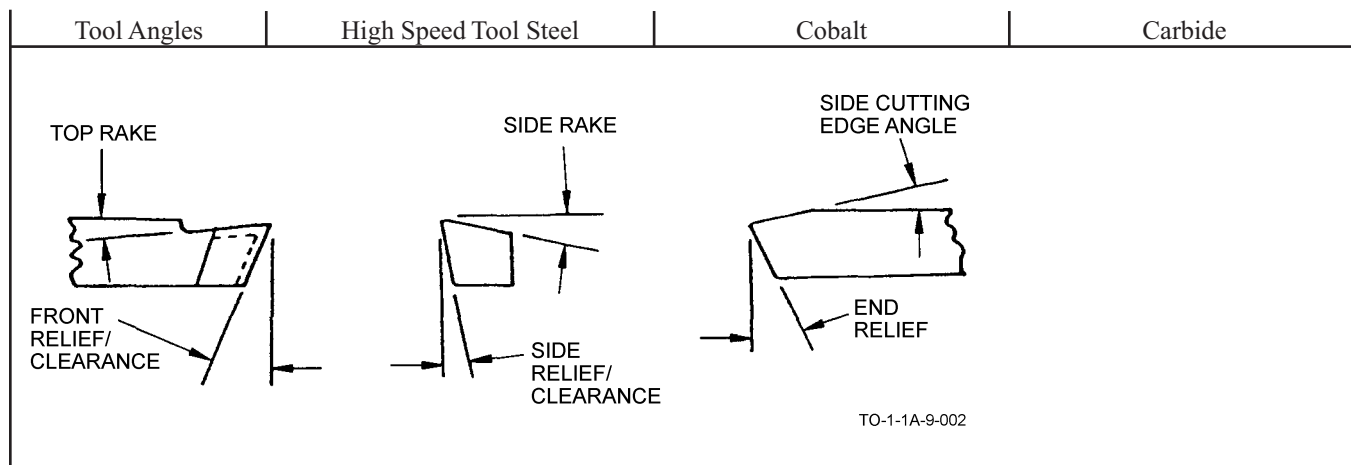


Table 2-11. Suggested Milling Cutting Speeds and Feeds

Alloy Type/Grade	Feed Inch <u>1/</u>	Speed SFM	Tool Material
301, 302, 304, 309, 310, 314, 316, 321, 347, PH13-8Mo, 15-5PH, 17-4PH, 17-7PH, 420, 431, 440, 442, 446	0.002-0.005	35-70	High Speed Steel
403-410, 430	0.002-0.007	30-95	High Speed Steel
440F	0.002-0.008	35-90	High Speed Steel
303	0.002-0.008	35-70	High Speed Steel
430F, 416	0.002-0.008	50-100	High Speed Steel
420F	0.002-0.006	50-130	High Speed Steel
	0.002-0.006	35-80	High Speed Steel

1/ Use heavy feeds for rough cuts and light feeds for finishing.

Table 2-12. Suggested Tool Angles - Milling

Tool Angles	Tool Material		
	High Speed Steel	Cemented Carbide/Carbon	Alloy
Rake Radial <u>1/</u>	10-20°	Use lower angle	
Rake Axial <u>1/</u>	30-50°	Use lower angle	
Clearance	4-8°	Approximately same	
Land Width	1/64-1/16 inches	Approximately same	

1/ Saws, form relieved cutters, and miscellaneous profile cutters, etc., are sometimes used with rake angle as low as 0 degrees.

## 2.13 MILLING CORROSION RESISTING STEEL.

The same general procedures/equipment are used in working stainless as those used with carbon steel. However more power and rigid support of tool is required to accomplish cutting due to inherent strength and toughness of the various stainless alloys. In milling the corrosion resisting steel, difficulty will be experienced from heat build-up. Heat conduction of the chromium-nickel grades is about 50 percent slower than the carbon steels. This problem can be controlled in most cases by adjusting cutting speeds, tool angles, method of grinding, and use of proper lubricants in adequate quantities. In close tolerance work, controlling of heat build-up is of utmost importance to meet dimensional requirements.



2.13.1 Cutters for Milling. High speed tool steel is used for most milling on stainless. The other grades are used under certain conditions, such as cemented carbides; however, capacity of equipment and cost of tooling for specific uses requires consideration.

2.13.1.1 All the standard cutter designs used for cutting carbon steel can be used to cut stainless but preferred design is those with helical (spiral) teeth. The use of helical cutter minimizes vibration and chatter especially when cutter/cut exceeds 1 inch. Chip removal and loading of cutter can be aided when milling slots by staggering teeth to cut successively on alternate sides and half the bottom.

2.13.1.2 Cutter lands should be ground to narrow width (0.020 to 0.025) with clearance (3 degrees - 10 degrees primary angular) behind cutting lip to reduce frictional heat resulting from rubbing. The exact amounts the land is ground will depend on diameter of cutter, material hardness, grade, etc. However, in grinding the lands, care should be taken to avoid unnecessary weakening of support for cutting edge. As a further measure against rubbing, a secondary clearance of 6 degrees - 12 degrees starting at the back of the land is recommended. On side cutter, angular clearance of 3 degrees to 10 degrees to avoid frictional heat and rubbing is recommended.

**CAUTION**

Before starting operation/equipment, carefully check for proper set up, safety, rigid support of work and cutters, running condition of equipment, and flow of coolant/lubrication. Once cutting is started, it should be carried to completion to avoid the effects of changes in metal temperature. Naturally the continuous operation will depend on satisfactory operation of equipment and other factors. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

2.13.1.3 The recommended cutting speeds, tools, angles, and feeds for milling are cited in [Table 2-11](#) and [Table 2-12](#). The information in these tables is only provided as a starting point, or as a guide.

2.13.2 Lubrication for Milling. The lubrication of milling cutter is very important to control generation of heat which is considerable in cutting all grades of stainless, and to prevent seizing of chips to cutting edges. The cutting oils used should be applied in large quantities directly on the cutter and zone of cut. The sulphurized oils diluted to desired viscosity with paraffin oil are usually satisfactory.

## 2.14 DRILLING CORROSION RESISTING STEEL.

High speed steel drills are commonly used for drilling stainless. Special types are used for drilling grades (420, 440, etc.) that are abrasive due to high carbon content. Speeds for drilling the high carbon types are usually reduced 25-50 percent in comparison to the other grades. Drills for use with the corrosion resisting steels are prepared with different cutting angles than used with carbon steel. Drill point/tips for use with the chromium-nickel grades are usually ground with 135 degrees - 140 degrees (included) angle and 8 degrees - 15 degrees lip clearance. The web support for the point should be as heavy as possible; however, thinning of the web at the point will relieve point pressure. When drilling the free machining 400 series grades the angle is reduced to 118 degrees - 130 degrees. For general illustration of point designs see [Figure 3-4](#).

2.14.1 Drilling Speeds for Corrosion Resisting Steel. Speeds used for drilling the corrosion resisting steels should be closely controlled to prevent hardening of metal and excessive drill damage from heat. For suggested drilling speed using high speed steel drill bits, see [Table 2-13](#).

2.14.2 Lubrication for Drilling Stainless.

**NOTE**

Do not let drill ride on work to prevent work hardening and heat damage to drill. On larger diameter drills use chip curling grooves to help expel and prevent chip accumulation in area of hole being drilled.

The recommended lubrication for general use and light drilling is soluble oil, and for heavy work, sulphurized mineral or fatty oils. Utilization of adequate lubrication/coolant is of utmost importance in drilling stainless due to poor heat conduction of this material.



**Table 2-13. Drilling Speeds for Corrosion Resisting Steel**

Grade Type	Speed SFM (Approximate)
301, 302, 304, 310	20-40
303	40-80
309, 316, 321, 347	30-50
403, 410	35-75
416, 420F, 430F	60-95
420 AB & C	20-40
442, 446	30-60

## 2.15 REAMING CORROSION RESISTING STEEL.

The recommended reamer for the corrosion resisting steels is the spiral fluted type which is made from high speed steel/ carbide tipped. These spiral fluted reamers are used to help alleviate chatter and chip removal that are associated with the straight fluted reamers.

**2.15.1 Hardening Characteristics of Corrosion Resisting Steel.** Due to the work hardening characteristics of the corrosion resisting steel, it is advisable to leave sufficient stock to ensure that cutting will occur behind the work hardening surface resulting from drilling. The recommended material to be left for reaming is 0.003-0.007 inch, and feed per revolution should be 0.003-0.005 for holes up to 1/2 inch and 0.005-0.010 for reamers up to 1 inch diameter.

**2.15.2 Reamers for Cutting Stainless Steel.** Reamers for cutting stainless should have a 26-30° starting chamfer with a slight lead angle behind the chamfer of 1-2° for about 1/8-3/16 inch on the land to reduce initial shock of cutting. The land should be ground with a clearance of 4-7° (and width should not be reduced below 0.010-0.012 inch) to reduce rubbing and frictional heat.

**2.15.3 Speeds for Reaming.** Speeds for reaming will vary according to type of material being cut. The recommended speed for reaming Types 301, 302, 304, 316, 321, 347, 403 and 410 is 20-75 SFM; for 430F, 420F, 416, 440F and 303 --35-100 SFM; and for 309, 310, 430, 431, 440, 442, 426-20-60 SFM. Trial should be conducted to determine best cutting for individual operations.

## 2.16 TAPPING CORROSION RESISTING STEEL.

Conventional or standard type taps are used with stainless; however, better results can sometimes be obtained by modification of taps (in shop) as required and by use of two fluted type taps for small holes. For instance modification of taps can be accomplished by grinding longitudinal grooves along the lands, omission of cutting edges on alternate threads and relieving cutting edges will reduce binding and frictional drag. These modifications will also aid in distribution of lubrication to cutting area, provide additional clearance for chips and compensate for the swelling which is encountered with the softer temper material. In addition, the tap basically should have a taper/chamfer of about 9 degrees with center line on the starting end to facilitate entry into hole. The taper should be held short (1st thread) for blind holes, and on through holes, it may extend over 3 or 4 threads. The modification is usually accomplished as follows:

- Longitudinal grooves are ground down the center of each land about 1/3 to 1/2 thread depth and 1/3 to 1/2 approximately of land width.
- Cutting edges are relieved by grinding a 2-5° radial taper on each land.
- Lands are narrowed by removing about half the threading area from each land. The portion removed should trail the foremost cutting edge. Also, cutting edge should be ground to have positive hook/rake 15-20° for softer material and 10-15° for harder material.

**2.16.1 Tapping Quality Corrosion Resisting Steel.** Due to high strength and poorer cutting quality of the stainless series steels, holes for tapping are usually made as large as possible consistent with fit specified by drawing or other data. Actually due to the higher strength of this material less thread area or engagement is required in comparison to most other metals. Due to the above and the fact that less cutting is required, 75 percent thread depth is generally used as maximum unless otherwise specified. Higher percentages of thread depth are necessary in material when stock is not thick enough to permit the required



number of thread. For tapping allowances of some size screws/bolts see [Table 2-14](#). The decreased thread depth also reduces tendency to gall and seize, power required to drive tap, tap wear, and effect of swelling in soft material.

**2.16.2 Tapping Speeds Corrosion Resisting Steel.** Tapping speeds used for stainless should be slower than those used for carbon steel. The 18-8 (300 series) are usually tapped at 10-25 SFM except for the free machining types which are tapped at 15-30 SFM. The straight-chromium 400 series generally is tapped at 15-25 SFM, except the free machining grades, which are tapped at 15-35 SFM.

**2.16.3 Lubrication for Tapping.** The lubrications recommended for tapping are sulphurized mineral oils with paraffin and lard oil. The lubricant serves to prevent overheating as well as lubrication, and if applied under pressure, aids in chip removal. Oil flow/application should be applied before tapping commences to prevent initial congestion of cuttings.

**Table 2-14. Tapping Allowances (Hole Size to Screw Size)**

Thread/Screw Size	Major Diameter	Minor Diameter	Drill Size Decimal and NR	Thread Depth (Percent)
4-40	0.1120	0.0871±0.002	0.0810-46	95
			0.827-45	90
			0.0860-44	80
			0.0890-43	71
			0.0960-41	49
6-32	0.1380	0.1100±0.004	0.0995-39	95
			0.1040-37	83
			0.1100-35	72
			0.1160-32	54
6-40	0.1380	0.1144±0.0035	0.1065-36	97
			0.1130-33	77
			0.1200-31	65
8-32	0.1640	0.1342±0.004	0.1250-1/8 inch	96
			0.1285-30	87
			0.1360-29	69
			0.1405-28	57
10-32	0.1900	0.1593±0.003	0.1520-24	93
			0.1562-5/32 inch	83
			0.1610-20	71
			0.1660-19	59
			0.1695-18	50
1/4-20	0.2500	0.2010±0.005	0.1850-13	100
			0.1875-3/16 inch	96
			0.1935-10	87
			0.1990-8	78
			0.2090-4	63
1/4-24	0.2500	0.2143±0.003	0.1960-9	100
			2031-13/64 inch	86
			0.2090-4	75
			0.2130-3	68
1/4-28	0.2500	0.2193±0.002	0.2090-4	88
			0.2130-3	80
			0.2187-7/32 inch	67
5/16-24	0.3125	0.2708±0.0032	0.2610-G	95
			0.2656-17/64 inch	86
			0.2720-1	75



**Table 2-14. Tapping Allowances (Hole Size to Screw Size) - Continued**

Thread/Screw Size	Major Diameter	Minor Diameter	Drill Size Decimal and NR	Thread Depth (Percent)
			0.2770-J	65
3/8-24	0.3750	0.3278±0.002	0.3281-2 1/64 inch	86
			0.3320-Q	70
			0.3390-R	66
1/2-24	0.5000	0.4579±0.003	0.4531-29/64 inch	86
			0.4687-15/32 inch	57

## 2.17 SAWING.

Hack saws (hand) for cutting corrosion resisting steel should be of high speed steel with approximately 32 teeth per inch for light work and approximately 24 teeth per inch for heavy work. The teeth area should be of wavy construction to increase width of cut area to prevent binding. As with cutting other metal, the blade should not be allowed to drag/ride on the return stroke, especially with the 300 series types to prevent work hardening. The hack saw blade should be lightly lubricated with lard oil/other cutting oil for best results.

**2.17.1 Hack Saws (Mechanical Drive).** Power hack saws are used for heavy cross-cutting section bars, tubing, etc. With the power hack saw, deeper cuts are made at relatively low speed. The deeper cuts are used to get under work hardened surface resulting from previous cut (stroke). The teeth per inch for saw blades average 8-12 and speed of saw travel usually ranges from 50-100 feet per minute depending on type and temper of material being cut. Coolant/lubrication is essential to prevent excess blade damage from heat. Lubrication recommended is soluble oil/water mixed about 1 part oil to 4 parts water for heavy work, and for light work, a light grade cutting oil.

**2.17.2 Band Sawing.** Band saws are well suited for low speed (straight line/contour) sawing of stainless/corrosion resisting steel within prescribed limitation. The saw manufacturer's recommendations should be followed for cutting speed, saw selection, etc. However, speeds usually vary with the physical properties, temper, etc., of type/grade being cut. As general guide, speeds range from 100-125 FPM for material under 0.062 and 60-100 FPM for thickness over 0.062 inch. Saw blades must be kept in sharp condition for effective low speed sawing.

**2.17.2.1** For faster cutting with the band saw, the friction cutting method may be employed. In utilizing the friction method, the band saw velocity ranges from 5000 FPM for cutting flat 1/32 inch material to about 10,000 FPM for 1/2 inch and 14,000 for 1 inch material; tubing material is run at slightly higher speed. Feed for this method can be considerably higher than is used for slow speed cutting, rates range from about 100 FPM for light gauge to 15-18 FPM for 1/2 inch material. Saw teeth per inch varies from 18 for material below 1/8 inch thick to 10 per inch for thicknesses over 1/2 inch.

**2.17.2.2** Heavy pressure to maintain cut is not usually necessary. Pressure should be just sufficient to create proper heating and softening at cut point without forcing the saw. Lubricants should not be used.

## 2.18 FABRICATION OF FERROUS ALLOYS.

The information furnished in this section is provided as a guide to aid personnel engaged in the use and application of the ferrous alloys. Due to varied usage of steel products, details and rules related will not fit every application. In many instances, experimentation trial and further study will be required.

**2.18.1 Accomplish Designs, Application and Fabrication.** Personnel assigned to accomplish designs, application and fabrication must be well trained in fundamentals of metal forming practices, analysis, properties, corrosion control, machining, plating, welding, heat treat, riveting, painting, blue print reading, assembly, etc., in accordance with scope of relation to fabrication process. Also, these personnel must keep constantly abreast of advancing processes for maximum efficiency/proficiency.

**2.18.1.1** The section of steel for design or application to equipment and component is usually based on the following:

- Strength and weight requirement of part/equipment to be fabricated.
- Method to be used for fabrication, i.e., welding, forming, machining, heat treat, etc.



- c. Corrosion resistance to certain chemicals/environments.
- d. Temperatures to which part will be subjected.
- e. Fatigue properties under cyclic loads, etc.


2.18.1.2 The following general rules should be employed in handling and forming:

- a. Sheet, sheared/sawed strips and blank shall be handled with care to prevent cutting and other parts of the body.
- b. Sheared or cut edges shall be sanded, filed, or polished prior to forming. The removal of rough and sharp edges is also recommended prior to accomplishing other machining operations to reduce hazards in handling.
- c. Form material across the grain when possible using correct or specified bend radii. Also provide bend relief in corner when required.



Machines rated for carbon steel shall not be used over 60 percent of rated capacity when cutting, forming or machining stainless steel unless approved by responsible engineering activity. When in doubt inquire. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

- d. Observe load capacity of equipment such as brakes, presses, rolls, drills, lathes, shears, mills, etc.
- e. Tool and equipment shall be maintained smooth, free of nicks, rust, burrs and foreign material. In addition to above, dies, ways, etc., shall be checked for alignment tolerances, etc., periodically/each set-up.
- f. Surfaces of material, especially finished sheet, shall be protected from scratching, foreign particles, etc. These surfaces can be protected using non-corrosive paper, tape, other approved material and good cleaning procedures. Polished sheet material should be protected when forming to prevent die tool marking.



Avoid handling parts, especially corrosion resistant steel, with bare hands after cleaning and subsequent to heat treating/passivation because finger prints will cause carburization and pitting of surface, when heated. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

- g. After forming/machining is completed, remove all cutting lubrication, etc., by cleaning, degreasing, pickling, prior to any heat treat, plating or painting process.

## 2.19 BENDING (SINGLE CURVATURE).

The bending of most steel sheet and thin bar stock can be readily accomplished provided that equipment with adequate bending and cutting capacity is available and if the materials are formed in the soft condition/lower temper range. The heat treatable alloys are usually formed in the annealed or normalized condition and heat treated if required/specified after forming. Some difficulty will be encountered from warping due to treat treating and precautions must be taken when forming the material to prevent sporadic or uneven stress in the work piece. Also, parts will require jigs or close control during the heating and cooling phase of heat treatment. The use of heat treated formed sheet metal parts on aerospace craft are usually an exception in part due to above and most materials are used in the normalized or annealed condition.

2.19.1 Spring back Allowance. Spring back allowance will vary according to the type and temper of material being formed. The use of sharp bend radii on parts for aeronautical application shall be avoided and other application where the parts will be subjected to flexing (cycle) or concentrated stresses, due to possible fatigue or stress corrosion failure. For recommended General Bend Radii for use on Aerospace weapon/equipment (see [Table 2-15](#) for Low Carbon/low alloy steel and [Table 2-16](#) for Corrosion Resistant Steel.)



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

2.19.1.1 In utilizing [Table 2-15](#) and [Table 2-16](#) it is recommended that in practice bend area be checked for strain, grain, or bend cracking. If parts show presence of above, increase radius by one thickness or more until difficulty does not exist. Other details, inspection requirements, etc., shall be used when specified.

**2.20 DRAW FORMING.**

Control of die design, and material from which dies are made, are essential to successfully draw form steel. For long production runs, high carbon, high chromium steel is recommended to manufacture drawing dies because of wear resistance and hardness. For medium and short production runs, Kirksite/case zinc alloy can be used with drop hammer hydraulic press if the draw is not severe. Hardwood and phenolic can be used in some cases for piece production where draws are shallow. Successful drawing of steel will depend on:

- a. Radii used for forming or bending. Use moderate radii, usually equal to 3-6 times thickness of material depending on specific requirements, and the severity of draw.
- b. Finish of die-all scratches and surface roughness should be removed.
- c. Blank hold down pressure and drawing rings. Hold down pressure should be sufficient to prevent wrinkling of material, but not to the extent that would prevent flow of the metal into the female portion of the die. Drawing rings radii should be 4-8 times metal thickness and smoothly polished.
- d. Clearance between punch and die - Generally punch clearance should be about 1-1/4 to 1-1/2 times thickness for the initial draws, and about 1-1/8 to 1-1/4 times for the following draws. If parts show signs of galling, clearance (drawing) should be increased when clearance is increased, size requirement must be considered.
- e. Temper-drawing should be started with annealed/normalized material and intermediate annealing accomplished as required. The requirement for annealing (intermediate) usually is needed after reduction exceeds 30-35 percent for stainless/20-25 percent carbon steel on the initial draw, and when reduction exceeds 8-15 percent on each following draw. Parts should be cleaned removing all lubrication and other contaminate prior to annealing and desealed after annealing. In instances where draws exceed 22-25 percent annealing is recommended after completion of the drawing operation followed by descaling and passivation (stainless). Restriking on final stage die to remove distortion after final anneal is permissible without further heat treatment.
- f. Drawing Speed - Generally a speed of 20-55 feed per minute is satisfactory. Drawing using a hydraulic powered press in lieu of a cam operated or toggle type press is usually the most satisfactory.
- g. Lubricant - Compounds used should be of heavy consistency capable of withstanding high temperature and restating pressure necessary to form material. One heavy bodied lubricant used is lard oil, sulfur (one pound of sulfur to 1 gallon of oil) to which lithopone is added in equal parts until consistency equals 600 weight engine grease, or as desired. Other compounds such as tallow, mixture of mineral oil and soft soap, powdered graphite mixed to thin paste with lightweight oil can be used.
- h. Blank size and preparation - A good practice is to use minimum size required to meet dimensional size of parts and for hold down. When trimming, consideration must be given to the fact that on rectangular parts, the majority of drawings will occur on wider portions of the rectangle away from the corners. To overcome this problem, the radius of the vertical corner should be approximately 10 percent of the width. Trial, using a very ductile material to determine blank size and stress areas prior to starting the forming operation is recommended. After size is determined by trial, etc., the blank should be filed/polished to prevent cracking in wrinkle/stress areas, handling hazard and surface friction which hinders flow of metal into die.

2.20.1 Surface Condition. The surface condition of the blank also has an effect on drawing. A slightly roughened surface, such as obtained by pickling (dull surface) improves control of metal under hold down pads and the holding lubricants. On the other hand, the roughened surface may be less desirable because of greater friction, especially where free flowing drawing methods are used (without hold down).

2.20.1.1 Where facilities are available, cold forming of some steels (primarily straight chromium stainless such as 410, 416, 430, 442, 446) can be improved by preheating dies and blanks. The preheating tends to reduce work hardening and the requirement for intermediate annealing during the drawing operation.



2.20.1.2 When forming involves more than one draw, the first operation should be a moderate draw with punch diameter equal to 60 percent of blanks diameter and reduction of 15-25 percent. The second and subsequent draws should be made with punches about 20 percent. It is recommended that part be cleaned and annealed following each draw. Excessive distortion may result from final annealing after last draw. This problem can be overcome in most instances, by reducing the severity of the last draw or restriking after final annealing on last stage die for the purpose of removing distortion.

## 2.21 STRETCH FORMING.



Parts shall be cleaned of all contaminants, lubrication, filing, other foreign material, etc., before heating or annealing and upon completion of forming or drawing operation. Failure to clean the parts will result in pitting and carburization, which will damage the surface. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

Stretch forming is a process where material, sheet or strip, is stretched beyond the elastic limit until permanent set will take with a minimum amount of spring back. The stretch forming is usually accomplished by gripping ends of material (blank) and applying force by a separate ram carrying the forming die. The ram pressure sufficient to cause the material to stretch and wrap to contour of the die form blank is applied perpendicular to the blank (see [Figure 2-4](#)). This method of forming is usually limited to parts with large radii of curvature and shallow depth, such as shallow dishing, reverse curves, and curved pan shaped parts containing flat areas.

2.21.1 Trimming of Edges, Removal of Nicks and Scratches. The trimming of edges and removal of nicks and scratches is important to prevent starting points for concentrated stress, which, under tension loads, would tear. The direction of major tension (stretch) and direction of grain is also important. It is recommended in forming that the major tension be transverse to the direction of grain. Lubrication aids in uniform distribution of stress and the lubricant shall be applied uniformly to work piece to avoid distortion which could result from unequal friction when material is sliding across the forming die during stretching.

2.21.2 Forming Dies/Blocks for General Production. Forming dies/blocks for general production are made from kirkite/zinc, alloy; for piece production from phenolic and hardwood. Some types and kinds of plastic with good hardness and high impact strengths are also used. The rubber pad hydraulic press is used to form relatively flat parts having flanges, beads, lightening holes, and for very light drawing of pan shaped parts having large radii.

2.21.2.1 Form blocks are usually manufactured from steel, phenolic (mechanical grades), kirkite/zinc cast alloy, and some types of hard molding plastic with high impact strength. The work is accomplished by setting the form block on the lower press plate or bed, and the blank is placed on the block. The blank is held in place on the block by locating pins (holes are drilled through the blank and into the form block for the insertion of the locating pins). These holes are referred to as "tooling holes," which prevent slippage of blank when pressure is applied. If tooling holes are not allowed, another method of alignment and holding of blank must be utilized. The sheet metal blank should be cut to size (allow sufficient material to form flange), deburred, and filed prior to pressing. After the block is prepared and placed on the plate, the rubber pad filled press head is lowered or closed over the block, and as the hydraulic pressure (applied by a ram to the head) increases, the rubber envelopes the form block forcing the blank to conform to the form block contour or shape. It is recommended that additional rubber be supplemented in the form of sheets (usually 1/2 - 1 inch, hardness of 70-80 durometers) over the form block and blank to prevent damaging the rubber press pad. The design of form blocks for hydropress forming requires compensation for springback. The form for forming flanges on ribs, stiffeners, etc., should be undercut approximately 2-8 degrees depending on the alloy, hardness, and radius. In some cases, it will be necessary to use a combination of hand forming shrinking/stretching using supplemental machinery and pressing to complete forming by this method.



## 2.22 DROP HAMMER FORMING.



Parts should be cleaned prior to annealing to protect finish. Care should be taken to remove all traces of zinc that may be picked up from kirksite forming dies, as failure to remove the zinc will result in penetration of the steel (stainless) when treated and will cause cracking. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

Dies for drop hammer forming are usually made by casting metals such as kirksite. These dies can be rapidly produced; are more economical than permanent dies; can be melted and recast; and can be reinforced at selected points of wear by facing with harder material, such as tool steel for long production runs. Normally, drop hammer forming is accomplished without benefit of hold down. The metal is slowly forced in shape by controlling the impact of blows. In many instances, it is necessary to use drawings, rings, 2 or 3 stage dies, supplemental equipment, and hard forming such as bumping hammer, wooden mallet to remove wrinkles, etc. To successfully complete forming operations, another aid that may be necessary is to anneal material between die stages and intermediately for single stage die forming.

## 2.23 SPINNING.

Those steels that have low yield strengths in the soft/annealed condition, and low rates of work hardening are the best grades for spinning. To overcome work hardening problems, intermediate annealing and 2-3 or more stage spinning blocks are used. Annealing of the part at intervals also aids the operator when manual spinning, because less pressure is required to form metal and springback is lower.

**2.23.1 Form Blocks for Spinning.** Form blocks for spinning are usually made of phenolic, hard wood, or carbon steel. Manual spinning is usually accomplished on a lathe specifically adapted and fitted for that purpose. The main requirements are that required speed be maintained without vibration; clamping pressure is sufficient to hold part; facilities are provided to apply pressure at a uniform rate; and tools are of proper design. Normally, spinning tools are the roller or round nose type designed in such a manner that high pressure can be applied without bending. Where local design of tools are required, raw material for manufacture is obtainable under QQ-T-570, Type D2, hardened to Rockwell C40-50.

## 2.24 SHEARING AND BLANKING.

To prevent damage to shear, and to assure clean, accurate cuts, clearance between shear blades should be approximately one-twentieth (5 percent) thickness of material to be cut. Also, blades or knives must be maintained in sharp condition, clean, and free of nicks. Where only one shear is available, a clearance of 0.005 to 0.006 could be used for general shearing of sheet stock up to 0.125 inches thick. Excessive blade clearance should be avoided to prevent work hardening of cut area which increases susceptibility to stress corrosion and burring. Lubrication such as lightweight engine oil or soap should be applied at regular intervals to prevent galling and to clean blades for prolonged shear blade life.

## 2.25 BLANKING AND PUNCHING.

Blanking and punching requires close control of die clearance, shearing action of punch/blanking die. Clearance for blanking and punching should be 5 percent of thickness and closely controlled for all gauges. In designing dies and punches, it is important that shear action be incorporated to equalize and reduce load. Double shear should be used when possible to minimize off balance condition and load. Punches and dies should be maintained in clean sharp condition and lubricated by swabbing or spraying material to be punched with lightweight lube oil to prevent galling and to aid in keeping punch/die clean.

## 2.26 GENERAL FABRICATING CHARACTERISTICS.

The fabricating characteristics for steels are listed below.

## 2.27 PLAIN CARBON AND ALLOY STEELS.

**2.27.1 Plain Carbon Steel - 1006 through 1015.** This group of steels is used where cold formability is the main requirement, and have good drawing qualities. This series is not used where great strength is required. The strength and hardness of these grades will vary according to carbon content and amount of cold work.



2.27.2 Plain Carbon Steels - SAE 1016 through 1030. This group of steels is commonly known as the carburizing or case hardening grades. The addition of manganese improves machining qualities but reduces the cold formability characteristics. This group is widely used for forged stock.

2.27.3 Plain Carbon Steels - 1030 through 1050. This group (medium carbon types) is used where higher mechanical properties are required. The lower carbon and manganese types are used for most cold formed parts. Alloys 1030-1035 are used for wire and rod for cold upsetting applications, such as bolts. The higher carbon groups, such as 1040 are often cold drawn to required physical properties for use without heat treatment.

2.27.4 Alloy Steels - 1055 through 1095. This alloy group is used where wear resistance resulting from high carbon content is needed, and is heat treated before use in particularly every application.

2.27.5 1100 Series Steel. Steels in this group are generally used where easy machining is the primary requirement. The main use of these steels is for screw stock.

2.27.6 1300 Series Alloy Steel. The basic advantages of this group is high strength coupled with fair ductility and abrasion resistance. The major use is in the manufacture of forgings.

2.27.7 2300 Series Nickel Alloy Steels. The addition of nickel has very little effect on machinability and greatly increases elasticity and strength. This material is normally machined in the forged, annealed, and normalized condition, and heat treated after fabrication.

2.27.8 2500 Series Nickel Steel.

#### NOTE

These grades not currently being produced. Listed for reference only.

This series almost without exception, is a carburizing grade with extremely high strength core. However, the case is not as hard as obtained with other carburizing steels. This steel is used for parts requiring a high strength core and good wear resistance.

2.27.9 3100, 3200, and 3300 Series Nickel Chromium Steels.

#### NOTE

These grades not currently being produced.

This series of steels is characterized by good wear resistance and tough core and surface. The 3300 series is used primarily in the form of forgings and bars which are required to meet rigid mechanical properties. This steel is more difficult to handle in fabrication and heat treatment than lower nickel - chromium alloys.

2.27.10 4000 Series Molybdenum Steels. This group of steels have good impact strength and require close control of heat treatment practices to obtain the required strength and ductility.

2.27.11 4100 Series Chromium - Molybdenum Steels. This series has good working properties, response to heat treatment, and high wear resistance. This group is easily fabricated by forging and rolling. After welding and cold forming, internal stresses produced should be relieved and loss in strength regained by normalizing.

2.27.12 4130 Grade Steel. This grade is used extensively in aircraft construction in the form of sheet, bar, rod and tubing. This grade has very good cold forming characteristics. Forming and welding operations are accomplished utilizing annealed material, and heat treated or normalized after these operations are completed. 4130 sheet (MIL-S-18729 can be cold bent in the annealed condition to an angle of 180 degrees with a radius equal to the thickness of the sheet. In the normalized condition, a radius equal to 3 times the thickness is recommended.

2.27.13 4140 Series Steel. This steel is used for structural, machined and forged parts over 1/2 inch thick. It is usually obtained in the normalized condition. Forgings are always normalized or heat treated after fabrication.

2.27.14 4300 Series Nickel-Chromium-Molybdenum Steels. These steels are used to meet conditions in which other alloy steels have insufficient strength. Preparation for machining or forming must be by a suitable annealing cycle.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

**2.27.15 8000 Series Molybdenum Steels.** These steels are characterized by their high impact strength and resistance to fatigue. They are easy to forge and machine, and are stable at high temperatures.

**2.27.16 8600, 8700, 9300, 9700, 9800, and 9900 Series Steels.** These steels have approximately the same characteristics as the 4300 series steel.

**2.28 CORROSION RESISTANT (STAINLESS) AND HEAT RESISTANT STEELS.**

The fabrication of stainless steel requires the use of modified procedures in comparison to those used for carbon steels.

**2.28.1 Forming Sheet Stock.** The corrosion resisting series, i.e., types 301, 302, 304, 305, 316, 321, 347, 410, 430, 431, etc., generally have good forming and drawing qualities. Some types (302, 304 and 305) have forming characteristics superior to plain carbon steel because of the wide spread between tensile and yield strength, and higher elongation. However, more power is required to form these types than is required for carbon steel because of higher tensile strengths and the fact that yield strength increases rapidly during forming or bending.

**2.28.1.1** The straight chromium grades such as 410, 416, 430, 442, and 446 react similar to carbon steel and are somewhat less ductile than the 300 series stainless. The tensile strength are higher than carbon steel and consequently will stand higher loads before rupture. Yield strengths are also higher which means that more power is required for bending and forming. Because of the ductility factor of this series drawing and forming should be limited to 20-25 percent reduction.

**2.28.1.2** The 301, 302, 304, 305 and 316 types can be drawn based on a reduction of 35 to 50 percent, i.e., a shape 8 inches in diameter and 4 inches in depth could be drawn in one operation, based on a 50 percent reduction.

**2.28.1.3** The strains set up by severe reductions (above 45 percent with chromium-nickel types and 20 percent with straight chromium types) should be relieved by annealing immediately after the operation is completed, especially if using Type 301. If this material is not relieved in 2-4 hours, it may crack.

**2.28.1.4** Springback allowance should be about 2 to 3 times the amount allowed for carbon steel, and naturally will vary according to the type of material being formed. The use of sharp radii shall be avoided where parts are subjected to flexing or concentrated stresses due to possible fatigue or stress corrosion failure.

**2.28.1.5** Recommended bend radii for use with stainless is shown in [Table 2-16](#).

**2.28.2 Draw Forming.** Stainless steels should be annealed for draw forming, and hardness should not exceed Rockwell B90. The best drawing grades are of the 18-8 series. In selecting the type for drawing, welding of the finished parts, if required, shall be considered.

**2.28.3 Drop Hammer Forming.** The most common types of corrosion resistant steel used for drop hammer forming are 301, 302, 304, 305, and stabilized grades 321 and 347. 301 work hardens more rapidly and is subject to strain cracking. The condition of material for best forming should be annealed. It is possible to form some Type (301 and 302) in 1/4 and 1/2 hard condition. However, the severity of the forming operation must be reduced to compensate for the pre-hardened material.

**2.28.4 Spinning.** Spinning procedures for stainless are similar to those used for other metals. Difficulty and variations depend on individual characteristics of grade to be worked, i.e., yield strength, ultimate strength, ductility, hardness and reaction to cold working. The best grades for spinning are those that have low yield strength in soft/annealed condition and low rate of work hardening such as 304, 305, 403, 410 and 416. The straight chromium grades respond to spinning similar to carbon steel. However, more power is required. Mild warming above 200 °F improves performance of the straight chromium grades.

**2.28.5 Shearing and Blanking.** Shearing and blanking of corrosion resisting steels as with other fabrication processes requires more power in comparison to shearing carbon steel and most other metals. Shears and other equipment rated for carbon steel should not be used above 50-70 percent of rated capacity when cutting stainless.

**2.28.6 Hot Forming.** Hot forming is used to form shapes in stainless that cannot be accomplished by cold forming and for forging parts economically. In using heat for forming, it is important that temperature be closely controlled. Also, finished parts should be relieved of residual stress and carbide precipitation which affects corrosion resistance. In either case, this is accomplished by fully annealing.





Difference in temper of raw material will result in variation of preheating, especially with the air hardening grades. The air hardening grades in tempers other than annealed may crack from thermal shock upon loading into a hot furnace. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

2.28.6.1 Hot forming by methods other than forging is accomplished at somewhat lower temperatures. The unstabilized chromium-nickel grades may be formed at temperatures up to 800 °F and the extra low carbon grades up to 1000 °F. The use of temperatures higher than those cited above should be avoided to prevent subjection of material to the carbide precipitation heat zone.

2.28.6.2 The straight chromium (Type 400 series) are more responsive to hot forming than the chromium-nickel grades. The reaction of these metals to hot forming is similar to carbon steels. Upon heating to 800-900 °F, their tensile strength is lowered considerably and at the same time ductility begins to increase.

2.28.6.3 Forming of the air hardening Grades Type 403 and 410 is accomplished in two temperature ranges as follows:


- a. Low temperature forming up to 1400 °F. The advantage of forming at this temperature is that parts can be stress relieved at 1350-1450 °F to restore strength uniformity, and scaling is held at a minimum.
- b. High temperature forming at 1525-1575 °F. Forming at this temperature is somewhat easier because strength is low and ductility is higher. Upon completion of forming at this temperature, parts shall be fully annealed under controlled conditions by heating to 1550 °F and holding, slowly cooling to 1100 °F (at approximately 50 °F per hour) and then cooling in air.

2.28.6.4 Grades 403 and 410 are not subject to loss of corrosion resistance due to the forming of intergranular carbides at grain boundaries.

2.28.6.5 When it is required that the non-hardening Grades 430, 442, and 446 be hot formed, the recommended temperature for forming is 1400-1500 °F. This temperature is recommended in view of the following:

- a. Heating these grades above 1600 °F promotes grain growth which can only be corrected by cold working.
- b. For types 442 and 446, the 1400-1500 °F temperature is below the scaling limit and very close to being below the scaling limit for Type 430.



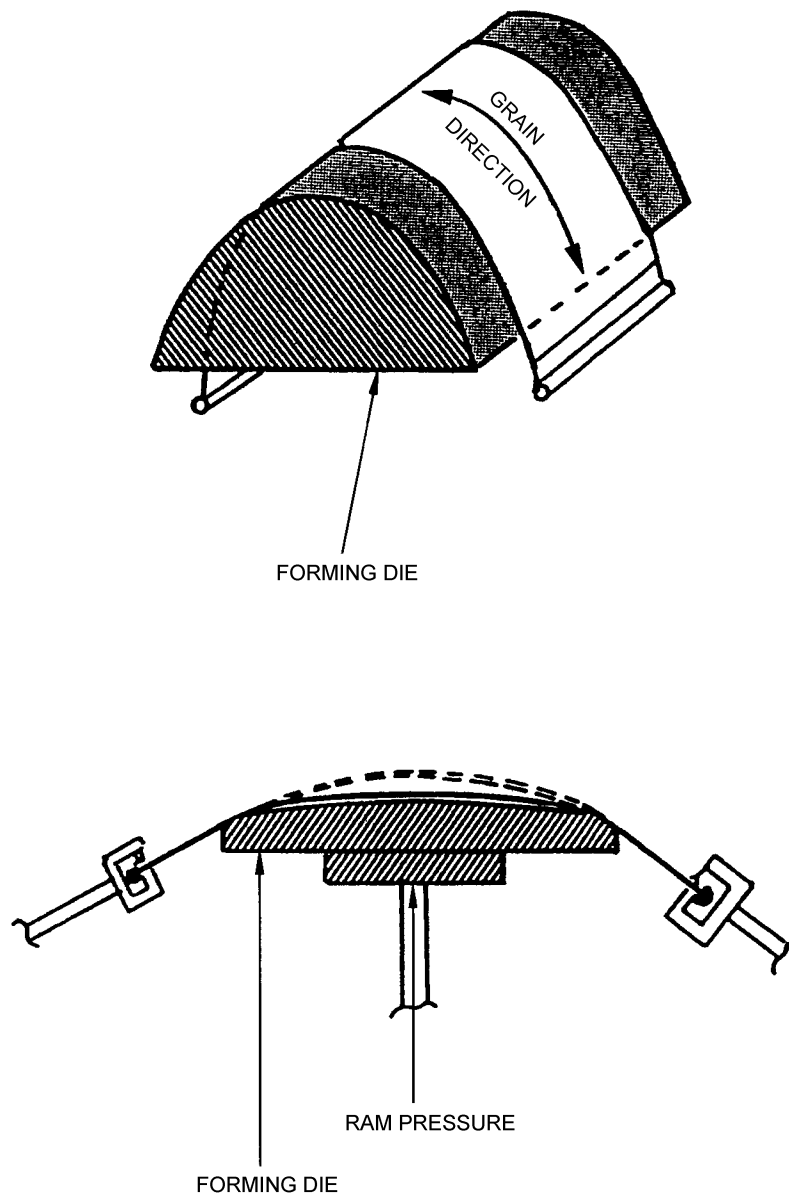

TO-1-1A-9-003

Figure 2-2. Stretch Forming



**Table 2-15. Cold Bend Radii (Inside) Carbon/Low Alloy Steels**

Temper, Sheet Thickness = T (Inches)									
Alloy Temper	0.016	0.020	0.025	0.032	0.040	0.050	0.063	0.125	0.187
1020/1025	2T	2T	2T	2T	2T	2T	2T	2T	2T
4130 Annealed	2T	3T	2-1/2T	2T	2-1/2T	2T	2T	2T	2T
4130 Normalized	2T	3T	2-1/2T	3T	3T	3T	3T	3T	3T
8630 Annealed	3T	3T	2-1/2T	3T	2-1/2T	2T	2T	2T	2T
8630 Normalized	3T	3T	2-1/2T	3T	3T	3T	3T	3T	3T

**Table 2-16. Cold Bend Radii (Inside) Corrosion Resistant Steel Alloys**

Sheet Thickness = T (Inches)				
Alloy	Temper	0.012 - 0.051	0.051 - 0.090	0.190 - 0.250
201, 202	Annealed	1-2T	1T	1-1/2T
301, 302	1/4 Hard	1-2T	1 1/2T	2T
305, 304	1/2 Hard	2T	2T	2T
309, 310	3/4 Hard	2T	3T	--
316, 321, 347	Hard	3-4T	4-5T	
405, 410, 430	Annealed	1T	1T	1-1/2T
17-7PH	Annealed	1T	1 1/2T	2T

**Table 2-17. Forging Temperature Ranges For Corrosion Resistant Steel**

Type/Grade	Preheat °F	Forging Temperature		Heat Treated
		Starting	Finishing	
301	1500-1600	2050-2200	1600-1700	See Heat Treat Data for annealing and stress relief, see <a href="#">Table 2-3</a> .
302	1500-1600	2050-2200	1600-1700	
303	1500-1600	2050-2200	1700-1800	
304	1500-1600	2050-2200	1600-1700	
305	1500-1600	2100-2200	1600-1700	
308	1500-1600	2100-2200	1600-1700	
316	1500-1600	2150-2250	1600-1700	
321	1500-1600	2100-2200	1600-1700	
374	1500-1600	2100-2200	1650-1750	
AIR HARDENING				These grades shall be promptly annealed after forging because they air harden intently if allowed to cool from forging temperatures. See Heat Treat Data <a href="#">Table 2-3</a> for temperatures.
403	1400-1500	1900-2100	1600-1700	
410	1400-1500	1900-2100	1600-1700	
414	1400-1500	2050-2200	1600-1700	
416	1400-1500	2100-2250	1600-1700	
420	1400-1500	2000-2100	1600-1700	
431	1400-1500	2050-2150	1600-1700	
440	1400-1500	1950-2100	1950-2100	



Table 2-17. Forging Temperature Ranges For Corrosion Resistant Steel - Continued

Type/Grade	Preheat °F	Forging Temperature		Heat Treated
		Starting	Finishing	
NON-HARDENING				
405	1400-1500	1900-2100	1750-1850	Post annealing required. See Heat Treat Data <a href="#">Table 2-3</a> for temperatures.
430	1400-1500	1900-2100	1350-1450	
442	1400-1500	1900-2000	1300-1400	
446	1400-1500	1800-2000	1300-1500	

## 2.29 STEEL SURFACE FINISHES.

Metal plating is a process where an item is coated with one or more thin layers of some other metal. This is the type of finishes generally used on ferrous parts, other than organic finishes. It is usually specified when there is a need for surface characteristics that the basic metal does not possess. The most commonly used types of plating are: Cadmium plate; zinc plate; nickel plate; chromium plate; copper plate; tin plate; and phosphate coatings. The thickness of the plated coating is important since its protective value is primarily dependent on its thickness. The type of plated coatings is generally dependent on the characteristics desired. For protection against corrosion when appearance is unimportant, either cadmium or zinc coatings is usually used. For appearance, nickel, chromium, and silver plating are the most commonly used. For hardness, wear resistance, and buildup of worn parts, nickel and chromium plating are used. Effectiveness of most other metallic coatings depends on their ability to provide envelope or anodic protection. Porous coatings of the more noble metals such as silver, copper, platinum and gold, tend to accelerate the corrosion of steel. For processing instructions, refer to TO 42C2-1-7. The following galvanic series table and dissimilar metal definition in accordance with MS33586 are for use as a guide in the selection of the most suitable plating for parts subject to uses where galvanic corrosion would be a prime factor.

## 2.30 DEFINITION OF DISSIMILIAR METALS.

Dissimilar metals and alloys, for the purpose of aircraft and aircraft parts construction are separated into four groups in accordance with MS33586. Metals classified in the same group are considered similar to one another and materials classified in different groups are considered dissimilar to one another. The metal/material referred to in the groups is the metal on the surface of the part; e.g., zinc includes all zinc parts such as castings as well as zinc coated parts, whether the zinc is electro deposited, applied by hot dipping, or by metal spraying over similar or dissimilar metal parts. The four groups are as follows:

- GROUP I - Magnesium and its alloys. Aluminum alloys 5052, 5056, 5356, 6061 and 6063.
- GROUP II - Cadmium, zinc, and aluminum and their alloys (including the aluminum alloys in Group I).
- GROUP III - Iron, lead, and tin and their alloys (except stainless steels).
- GROUP IV - Copper, chromium, nickel, silver, gold, platinum, titanium, cobalt, rhodium and rhodium alloys; stainless steels; and graphite.

### NOTE

The above groups do not apply to standard attaching parts such as rivets, bolts, nuts and washers which are component parts of assemblies, which will be painted prior to being placed in service unless other wise specified by specifications MIL-F-7179, or other approved data.

## 2.31 TYPES OF PLATING.



CADMIUM PLATING, AMS-QQ-P-416





## SOLDER

8

**2.31.1 Cadmium Plating, AMS-QQ-P-416 .** The primary purpose of cadmium plating is to retard or prevent surface corrosion of parts. Unless otherwise specified, the plating shall be applied after all machining, brazing, welding, forming and perforating of the item has been completed. Proper safety precautions shall be observed in the event any welding or soldering operations are required on cadmium plated parts because of danger from toxic vapors during such operations. Cadmium coatings should not be used on components for space applications, high vacuum applications, or on components subjected to temperatures of 450 °F or higher. All components shall be baked within 4 hours after plating for hydrogen embrittlement relief.

- Threaded fasteners between 150-220 KSI (33-46 HRC) shall be baked for 23 hours minimum at 375±25 °F.
- Steel components between 160-180 KSI(36-40 HRC) shall be baked for 8 hours minimum at 375±25 °F.
- Steel components with a minimum tensile strength of 220 ksi (46 HRC) shall be baked for 23 hours minimum at 375±25 °F.

**2.31.1.1** All steel parts having an ultimate tensile strength of 220,000 PSI or above shall not be plated, unless otherwise specified. When permission is granted, a low embrittlement cadmium plating bath shall be used. Federal Specifications AMS-QQ-P-416 shall be used for cadmium plate requirements. Critical parts should be magnafluxed after plating. The following alloys are not considered susceptible to hydrogen embrittlement from cadmium plating process, and therefore do not require hydrogen embrittlement relief.

- UNS S66286, UNS N07718, UNS R30159, UNS R30035, UNS N04400, UNS N06600, UNS N07750.
- 300 Series austenitic stainless steels.

## **2.31.2 Zinc Plating, QQ-Z-325.**



## ZINC PLATING, QQ-Z-325

10



Chromium and nickel electro deposits severely reduce the fatigue strength of high strength steels. All steel parts having a tensile strength of 180,000 PSI or above should be shot-peened prior to electro plating. In addition high strength steels are susceptible to detrimental hydrogen embrittlement when electro plated. All steel having an ultimate strength of 220,000 PSI or above shall not be electro plated without specific approval of the procuring service or responsible engineering activity. Failure to comply could result in damage to, or destruction of, equipment or loss of mission.

The primary purpose of zinc coatings is to retard or prevent the formation of corrosion products on exposed surfaces. Unless otherwise specified, the plating shall be applied after all machining, brazing, welding, forming and perforating have been completed. All parts having a hardness greater than Rockwell C40 and higher shall be baked at 375±25 °F for 3 hours after plating for hydrogen embrittlement relief. Zinc shall be deposited directly on the basic metal without a preliminary plating of other metal, except in the case of parts made from corrosion resisting steels on which a preliminary plating of nickel is permissible. Zinc plating (Type 1) should not be used in the following applications:

- Parts which in service are subjected to a temperature of 700 °F or higher.
- Parts in contact with structural fabric structure.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

- c. Parts in functional contact where gouging or binding may be a factor or where corrosion might interfere with normal functions.
- d. Grounding contacts where the increased electrical resistance of zinc plated surfaces would be objectional.
- e. Surfaces where free circulation of air does not exist and condensation of moisture is likely to occur. For additional information, refer to QQ-Z-325.

**2.31.3 Nickel Plating, QQ-N-290.**



**NICKEL PLATING, QQ-N-290**

11

This coating is divided into two classes. Class I, plating is intended for decorative plating, and Class II, plating is intended for wear and abrasion resistance. Unless otherwise specified, the plating shall be applied after all base metal heat treatments and mechanical operations such as machining, brazing, welding, forming and perforating on the article have been completed, all steel parts shall be given a stress relief at  $375 \pm 25$  °F ( $191 \pm 14$  °C) for 3 hours or more prior to cleaning and plating, as required, to relieve residual tensile caused by machining, grinding or cold forming. Steel parts having a hardness of Rockwell C40 and higher shall be baked at  $375 \pm 25$  °F for 3 hours or more and within eight (8) hours after plating to provide embrittlement relief. Parts shall not be reworked flexed or subjected to any form of stress loads after plating and prior to the hydrogen embrittlement relief treatment. The general requirements for nickel plating are specified in QQ-N-290. Nickel shall be used for the following application only in accordance with MIL-S-5002:

- a. Where temperatures do not exceed 1,000 °F and other coating would not be adequate or suitable.
- b. To minimize the effect of dissimilar metal contacts, such as mild steel with unplated corrosion resisting steel.
- c. As an undercoat for other functional coatings.
- d. To restore dimensions.

**2.31.4 Chromium Plating, QQ-C-320.**



**CHROMIUM PLATING, QQ-C-320**

12

This coating is of two classes; Class I, intended for use as a decorative coating; and Class II, for wear resistance and corrosion protection. Heavy chromium electro deposits (0-1-10 MILS) are often used to salvage under machine parts. Unless otherwise specified, the plating shall be applied after all basic metal heat treatments and mechanical operations such as machining, brazing, welding, forming and perforating have been completed. Hydrogen embrittlement relief shall be in accordance with blue prints and/or applicable specifications. All plated parts which are designed for unlimited life under dynamic loads shall be shot peened in accordance with military Specification MIL-S-13165 prior to plating. All parts with a hardness of Rockwell C40 (180,000 PSI), after shot peening and plating, shall be baked at  $375 \pm 25$  °F for 3 hours for hydrogen embrittlement relief. It is extensively used as an undercoating for nickel and chromium plating.



#### 2.31.5 Tin Plating, QQ-T-425.



#### TIN PLATING, QQ-T-425

13

Tin plating is used where a neat appearance, protective coating and easy solderability are of prime importance. The base metal for tinplate shall be low carbon cold steel.

#### 2.31.6 Phosphate Coating, MIL-P-16232.



#### PHOSPHATE COATING, MIL-P-16232

14

The description of phosphate coatings herein is specified as “heavy” coatings. Light phosphate coatings used as a paint base are covered by specification TT-C-490. Type “M” (Magnesium) coatings are resistant to alkaline environments and should not be exposed to temperatures in excess of 250 °F. Except for special purpose applications, phosphate coatings should be used with a suitable supplementary treatment. Type “Z” (Zinc) coatings should not be used in contact with alkaline materials or temperature in excess of 200 °F. For the different classes of coatings and required supplemental treatments, refer to MIL-P-16232. This coating should be applied after all machining, forming, welding and heat treatment have been completed. Parts having a hardness of Rockwell C40 or higher shall be given a suitable heat treat stress relief prior to plating and shall be baked subsequent to coating as follows:

- a. Type “M” shall be baked at 210-225 °F for 1 hour.
- b. Type “Z” shall be baked at 200-210 °F for 15 minutes (embrittlement relief).

#### 2.31.7 Silver Plating, QQ-S-635.



#### SILVER PLATING, QQ-S-635

15

Silver plating (electro deposits) has high chemical and oxidation resistance, high electrical conductivity and good bearing properties. Silver is often used as an antisieze and for preventing fretting corrosion at elevated temperatures. Silver plating shall be of the following types and grades:

- a. Type I, Matte. Deposits without luster, normally obtained from silver-cyanide plating solutions operated without the use of brighteners.
- b. Type II, Semi-Bright. Semi-lustrous deposits normally obtained from silver-cyanide plating solutions operated with brightener.
- c. Type M, Bright. Sometimes obtained by polishing or by use of “brighteners”.
- d. Grade A. With supplementary tarnish resistant treatment (chromate treated).
- e. Grade B. Without supplementary tarnish resistant treatment.



2.31.8 Intended Use.



SOLDER

8

The following applications of thicknesses are for information purposes only:

- a. 0.0005 - for corrosion protection of nonferrous base metal.
- b. 0.0003 - for articles such as terminals which are to be soldered.
- c. 0.0005 to 0.010 - for electrical contacts, depending on pressure, friction and electrical load.
- d. 0.0005 - for increasing the electrical conductivity of base metals.
- e. On ferrous surfaces, the total plated thickness shall not be less than 0.001 inch. After all base-metal heat treatments and mechanical operations such as machining, brazing, welding, forming and perforating of the article have been completed, if the type is not specified, any type is acceptable. All steel parts subject to constant flexure or impact having a Rockwell hardness of RC40 or greater shall be heated at  $375 \pm 25$  °F for 3 hours for stress relief prior to cleaning and plating.

2.31.8.1 Hardened parts which have been heat treated at less than 375 °F shall not be heated as noted above, but shall be treated by any method approved by the contracting agency.

2.31.8.2 For complete information pertaining to silver plating, refer to Federal Specification QQ-S-365.

2.32 SURFACE TREATMENTS FOR CORROSION AND HEAT-RESISTING STEELS AND ALLOYS.

Normally the corrosion-resisting and heat resisting alloys are unplated unless a coating is necessary to minimize the effect of dissimilar metal contacts. When a plating is required it shall be in accordance with specification MIL-S-5002A or other approved technical engineering data. Where a plating is required, steel parts plated with hard coating, such as nickel and chromium or combinations thereof, shall be processed as follows in accordance with MIL-S-5002A:

- a. Plated parts below Rockwell C40 hardness and subject to static loads or designed for limited life under dynamic loads, or combinations thereof, need not be shot peened prior to plating or baked after plating.
- b. Plated parts below Rockwell C40 hardness which are designed for unlimited life under dynamic loads shall be shot peened in accordance with specification MIL-S-13165 prior to plating. Unless otherwise specified, the shot peening shall be accomplished on all surfaces for which the coating is required and on all immediately adjacent surfaces when they contain notches, fillets or other abrupt changes of section size where stresses will be concentrated.
- c. Plated parts which have a hardness of Rockwell C40, or above, and are subject to static loads or designed for limited life under dynamic loads or combination thereof, shall be baked at  $375 \pm 25$  °F for not less than three (3) hours after plating.
- d. Plated parts which have a hardness of Rockwell C40, or above, and are designed for unlimited life under dynamic loads, shall be shot peened in accordance with specification MIL-S-13165 prior to plating. Unless otherwise specified, the shot peening shall be accomplished on all surfaces for which the coating is required and all immediately adjacent surfaces when they contain notches, fillets, or other abrupt changes of section size where stresses will be concentrated. After plating, the parts shall be baked at  $375 \pm 25$  °F for not less than 3 hours.

2.33 PASSIVATION OF STAINLESS STEELS.

The stainless steels are usually passivated after fabricating into parts to remove surface contaminates, which may cause discoloration or corrosive attack after the parts are placed in use. The process is primarily a cleaning operation which removes the contamination and speeds up the formation of the protective (invisible) oxide film which would occur naturally but slower in the presence of oxygen in a normal atmosphere. The protective film formation is inherent with the stainless steels in normal air when they are clean. The foreign materials are removed from stainless to provide for uniform surface contact with oxidizing agents (Air or Acid) which forms the protective film or passive surface. In this case after the film has formed the



material is placed in a condition approaching that of maximum corrosion resistance. Any areas to which oxygen contact is prevented by contaminants or other means tends to remain activated and subject to corrosion attack.

#### 2.33.1 Prior to Accomplishing the Passivation.



Excessive time shall not be used, as damage to parts may occur. In addition the times and temperatures shall be selected according to the alloy involved. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

Prior to accomplishing the passivation treatments the parts shall be cleaned, all grease, oil, wax, which might contaminate the passivation solution and be a detriment to the passivation treatment shall be removed. Surfaces will be considered sufficiently clean when a wetted surface is free of water breaks. After cleaning the parts will be passivated by immersing in a solution of 20-25 percent (Volume) nitric acid (Sp.gr 1.42) plus 1.5-2.5 percent (Weight) sodium dichromate with process times and temperatures as follows:

Types Of Process	Temperature	Time (Minutes Minimum)
I	70-90	30
II	120-130	20
III	145-155	10

2.33.1.1 For parts made of ferritic or austenitic stainless use process Type I, II or III. For parts made of martensitic stainless steel, use process Type II or III. Within 15 minutes after above treatment, thoroughly rinse in hot water (140-160 °F). Within 1 hour after hot water rinse, immerse in an aqueous solution containing 4-6 percent sodium dichromate (by weight) at 140-160 °F for 30 minutes, and rinse thoroughly with water and dry.

#### NOTE

After the parts are passivated they shall be handled the minimum necessary consistent with packaging, assembly/ installation. Parts for installations in high temperature areas shall not be handled with bare hands because finger prints will cause carburization and pitting of surface when heated.

#### 2.34 VAPOR DEPOSITED COATING.

Vapor deposited coating's are applied by exposing the base metal to a heated vaporized metallic coating such as cadmium and aluminum in a high vacuum. The metal coating forms by condensation of the vaporized coating metal on all exposed surfaces of the base metal. Vapor-deposited coatings can be obtained by processes in which a volatile compound of the coating is reduced or thermally decomposed upon the heated surface of the base metal. Vapor deposited coatings are used to provide good corrosion resistance for steel and eliminate sources of hydrogen embrittlement. Specific requirements for coating, aluminum vacuum deposited, are cited in specification MIL-C-23217A; and for coating, cadmium vacuum deposited, in specification MIL-C-8837.

#### 2.35 MECHANICAL-SURFACE FINISH.

The following paragraphs are concerned with mechanical surface finish of the geometrical irregularities of surfaces of solid materials and established classification for various degrees of roughness and waviness. The surface roughness of a part is a measurement rating of the finely spaced irregularities, such as the surfaces produced by machining and abrading (abrasive honing, grinding, filing, sanding, etc). The roughness height ratings are specified in microinches as the arithmetic average of the absolute deviations from the mean surface. Profilometers and other instruments used to measure surface height if calibrated in RMS (Root Mean Square) average will read approximately 11 percent higher on a given surface than those calibrated for arithmetic average. Also associated with roughness high is roughness width, usually specified in inches and the maximum permissible spacing of surface irregularities. As the arithmetic average of the absolute deviations from the mean surface. Waviness height rating (when required) may be specified in inches as the vertical distance from peaks to valleys of the waves, whereas waviness width is the distance in inches from peak to peak of the waves. [Figure 2-3](#) shows the meaning of each symbol defined. The symbol used to designate surface irregularities is the check mark as shown below.


- \*When waviness width value is required, the value may be placed to the right of the waviness height value.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

- \*\*Roughness width cutoff value, when required, is placed immediately below the right-hand extension.

**2.35.1 Designation of Surface Finish.** Surface finish should be specified for production parts only on those surfaces which must be under functional control. For all other surfaces the finish resulting from the machining method required to obtain dimensional accuracy is generally satisfactory. The surface chosen (unless already designated) for a specific application will be determined by its required function. [Figure 2-4](#) gives the typical normal ranges of surface roughness of functional parts. The values cited are microinches, for example  $\sqrt{63} = 63$  Microinches or 0.000063 inches average deviation from mean.

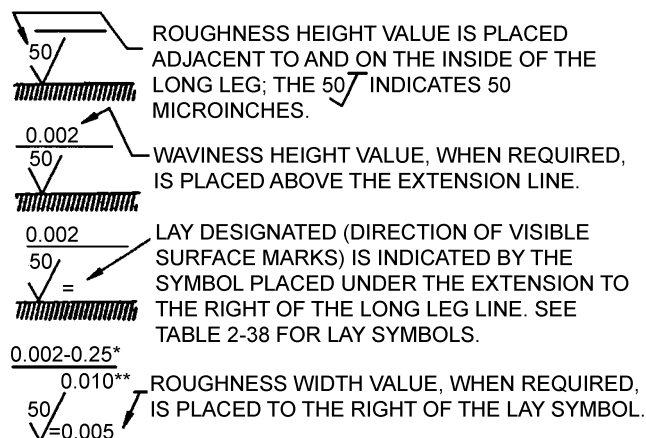


TO-1-1A-9-005

**Table 2-18. Galvanic Series of Metals and Alloys**

Corroded End - Anodic (Least Noble)	
Magnesium	Tin
Magnesium Alloys	Nickel (active)
Zinc	Inconel (active)
Aluminum - 7075 Clad	Brass
Aluminum - 6061 Clad	Copper
Aluminum - 5052	Bronze
Aluminum - 2024 Clad	Titanium
Aluminum - 3003	Monel
Aluminum - 6061 - T6	Silver
Aluminum - 7075 - T6	Nickel (Passive)
Aluminum - 7178	Inconel (Passive)
Cadmium	Silver
Aluminum - 2017 - T4	Graphite
Aluminum - 2024 - T6	Gold
Aluminum - 2014 - T6	Platinum
Steel or Iron	Protected End - Cathodic
Lead	(Most Noble)












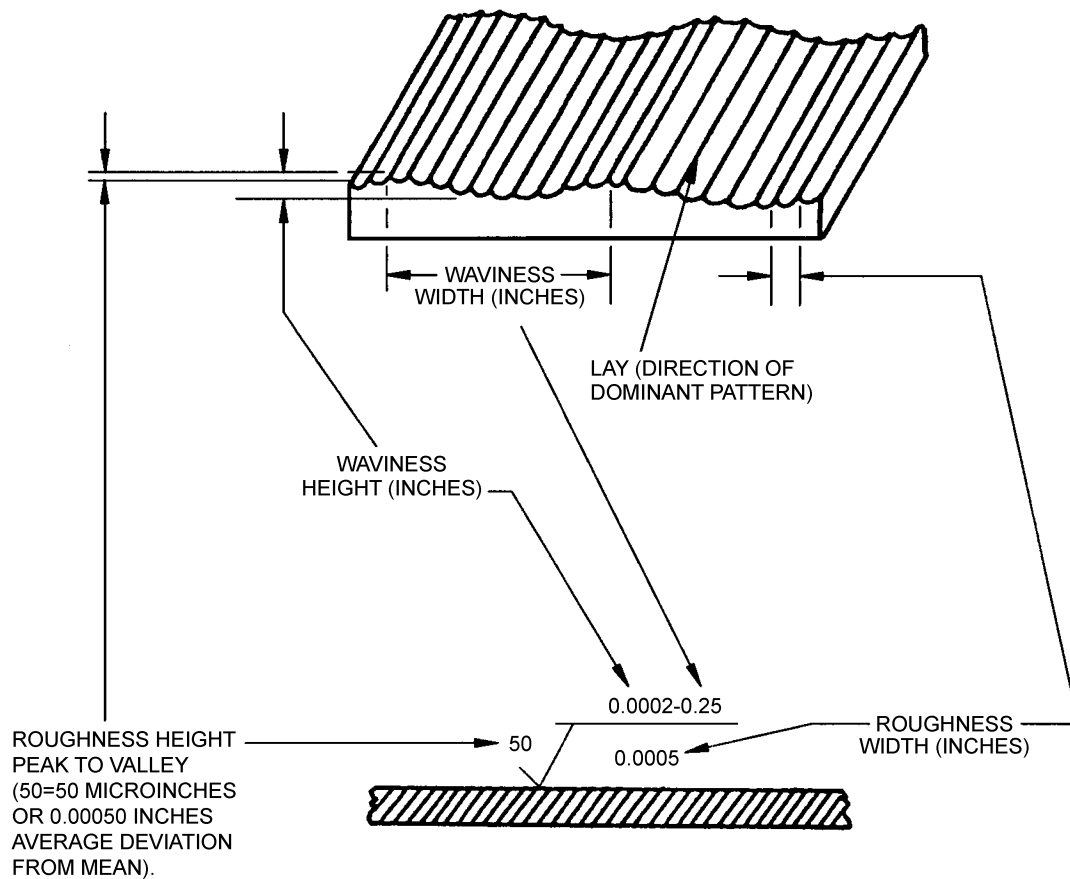















**NOTE:**

A ROUGH SURFACE SHOULD NOT EXCEED 65 MICROINCHES (MUINCHES) 0.00065 INCHES AND A POLISHED SURFACE WOULD CORRESPOND TO 10-20 MICROINCHES.

**Figure 2-3. Surface Roughness**



	MICROMETER ANVILS, MIRRORS, GAGES		MATING SURFACES, NO MOTION
	SHOP GAGE FACES COMPARATOR ANVILS		CLEARANCE SURFACES, ROUGH MACHINE PARTS
	VERNIES, CALIPERS FACES, WRIST PINS, HYDRAULIC PISTON RODS, PRECISION TOOLS, HONED ROLLER AND BALL BEARINGS (SURFACE PRODUCED BY SPECIAL HONING, LAPPING, BUFFING, ETC)		
	CRANKSHAFT JOURNALS VALVE STEMS CAM FACES HYDRAULIC CYLINDER BORES (VERY FINE SURFACE FINISH PRODUCED BY LAPPING, HONING OR BUFFING)		
	PISTON OUTSIDE DIAMETERS, CYLINDER BORES	LAY SYMBOLS	
	SPLINE SHAFTS MOTOR SHAFT BEARINGS		
	BRAKE DRUMS BROACHED HOLES PRECISION PARTS GEAR TEETH GROUND BALL AND ROLLER BEARING		
	GEAR LOCATING FACES GEAR SHAFTS AND BORES CYLINDER HEAD FACES PISTON CROWNS		

SYMBOL		EXAMPLE
	LAY PARRALLED TO SURFACE TO WHICH SYMBOL APPLIES	 DIRECT. OF TOOL MARKS
	LAY PERPENDICULAR TO SURFACE TO WHICH SYMBOL APPLIES	 DIRECT. OF TOOL MARKS
	LAY IN BOTH DIRECTIONS TO SURFACE TO WHICH SYMBOL APPLIES	 DIRECT. OF TOOL MARKS
	LAY MULTIDIRECTIONAL TO SURFACE TO WHICH SYMBOL APPLIES	
	LAY CIRCULAR TO SURFACE TO WHICH SYMBOL APPLIES	 
	LAY RADIAL RELATIVE TO SURFACE TO WHICH SYMBOL APPLIES	 

TO-1-1A-9-007

Figure 2-4. Surface Roughness and Lay Symbols



## CHAPTER 3 ALUMINUM ALLOYS

### 3.1 CLASSIFICATION.

Aluminum alloys are produced and used in many shapes and forms. The common forms are casting, sheet, plate, bar, rod (round, hex, etc.), angles (extruded and rolled or drawn), channels and forgings. The inherent advantages of this material are lightweight, corrosion resistance to the atmosphere and many varieties of chemicals, thermal and electrical conductivity, reflectivity for radiant energy of all wave lengths and ease of fabrication. The above factors plus the fact that some alloys of this material can be formed in a soft condition and heat treated to a temper comparable to structural steel make it very adaptable for fabricating various aircraft and missile parts.

### 3.2 COMMERCIAL AND MILITARY DESIGNATIONS.

#### NOTE

Cladding which is a sacrificial aluminum coating applied to an aluminum alloy core for the purpose of increasing corrosion resistance is designated as alclad 2024, alclad 2014, alclad 7075, etc.

The present system utilized to identify aluminum alloys is the 4 digit designation system. The major alloy element for each type is indicated by the first digit (see [Table 3-1](#)) i.e., 1XXX indicates aluminum of 99.00 percent minimum, 2XXX indicates an aluminum alloy in which copper is the main alloying element, etc. Although most aluminum alloys contain several alloying elements only one group the 6XXX designate more than one alloying element. See [Table 3-1](#) for complete listing. The second digit of the designation indicates modification in impurity limits. If the second digit is 0 it indicates that there is no special control on the impurities, while numbers 1-9 which are assigned consecutively as needed indicates special control of one individual impurity. Thus 1040 indicates 99.40 percent minimum aluminum without special control on individual impurities and 1140, 1240 etc. indicate same purity with special control on one or more impurities. The last two of the four digits in alloy groups 2XXX through 8XXX have no special significance except that they serve to designate the alloy by its former number, i.e., 243, 525, 758, etc. Experimental alloys are, also, designated by this system except that the 4 digit number is prefixed by an X. Aluminum alloys for military use are identified by military and federal specifications which are comparable to commercial specifications and designations. The following table is a general list of the commonly used military and federal specifications according to the commercial designation and forms of material.

**Table 3-1. Designations for Alloy Groups**

Type	Alloy
1XXX - - -	Aluminum 99.00 percent of minimum and greater
2XXX - - -	Copper
3XXX - - -	Mangenes
4XXX - - -	Silicon
5XXX - - -	Magnesium
6XXX - - -	Magnesium and Silicon
7XXX - - -	Zinc
8XXX - - -	Other element
9XXX - - -	Unused series

**Table 3-2. Aluminum Alloy Designation and Conversions to 4 Digit System**

Old	New	Major Alloying Element
2S	1100	None (Aluminum 99.00X)
3S	3003	Magnesium
4S	3004	Magnesium



Table 3-2. Aluminum Alloy Designation and Conversions to 4 Digit System - Continued

Old	New	Major Alloying Element
11S	2011	Copper
14S R301 Core	2014	Copper
17S	2017	Copper
A17S	2117	Copper (Special control of impurities)
18S	2018	Copper
24S	2024	Copper
19S	2219	Copper
32S	4032	Silicon
50S	5050	Magnesium
52S	5052	Magnesium
56S	5056	Magnesium
61S	6061	Magnesium and Silicon
62S	6062	Magnesium and Silicon
63S	6063	Magnesium and Silicon
MA15	7050	Zinc
- -	7475	Zinc
72S	7072	Zinc
75S	7075	Zinc
78S	7178	Zinc
79S	7079	Zinc

### 3.3 MECHANICAL PROPERTIES.

Prior to presenting factual data on mechanical properties the tempers (hardness) and methods of designation should be explained. For nominal mechanical properties see [Table 3-4](#).

**3.3.1 Tempers of Aluminum Alloys.** The tempers of aluminum alloys are produced essentially by three methods. These methods are cold working (strain hardening), heat treatment and a combination of the two. The various alloys of aluminum are either classed as heat-treatable or non-heat-treatable. Alloys 1100, 3003, alclad 3003, 3004, alclad 3004, 5050 and 5052 are classed as non-heat-treatable. The tempers of these alloys are designated by symbols H1, H2, H3, H4, F and O.

**3.3.1.1** A second number added to the above indicates the degree of strain hardening-actual temper.

Example: 2 = 1/4 hard (2/8) - H12, H22, H32  
4 = 1/2 hard (4/8) - H14, H24, H34  
6 = 3/4 hard (6/8) - H16, H26, H36  
8 = full hard (8/8) - H18, H28, H38

#### NOTE

Attempt should not be made to alter the temper characteristics of the "H" series of aluminum alloys other than in emergencies. This shall be limited to annealing operation only.

**3.3.1.2** As previously pointed out the above tempers designation symbols are hyphen (-dash) suffixed to the 4 digit alloy designation. Example: 1000-H12, 5052-H24, 3004-H34 etc. The general symbols used for the non-heat-treatable alloys are as follows:

- -F As fabricated
- -O Annealed
- -H21 Strain hardened only



- -H2 Strain hardened then partial annealed
- -H3 Strain hardened then stabilized

3.3.1.3 Alloys 2014-Alclad, 2024, 2024-Alclad, 6061, 7075, 7075-Alclad and 7178 are classed as heat treatable. The mechanical properties of these alloys are improved by heat treatment or by a combination of heat treatment and strain hardening. The tempers for these alloys are designated by symbols, F, O, W, AQ, T1, T2, T3, T4, T5, T6, T7, T8, T9, and T10. Following is a summary of these symbols:

- F As fabricated.
- O Annealed.
- W Solution Heat Treated, unstable temper.
- AQ As Quenched, unstable temper of parts immediately after quenching.
- T1 Cooled from an elevated temperature manufacturing/shaping process and naturally aged to a stable condition.
- T2 Cooled from an elevated temperature manufacturing/shaping process, cold worked, and naturally aged to a stable condition.
- T3 Solution heat treated, cold worked, and naturally aged to a stable condition.
- T4 Solution heat treated and naturally aged to a stable condition.
- T5 Cooled from an elevated temperature manufacturing/shaping process and artificially aged to a stable condition.
- T6 Solution heat treated then artificially aged.
- T7 Solution heat treated then artificially overaged/stabilized.
- T8 Solution heat treated, cold worked, and then artificially aged.
- T9 Solution heat treated, artificially aged, and then cold worked.
- T10 Cooled from an elevated temperature manufacturing/shaping process, cold worked, and then artificially aged to a stable condition.

3.3.1.4 Additional digits may be added to the basic designations T1 through T10 to indicate a variation in treatment that significantly alters the characteristics of the product with respect to the basic treatment or temper. For example, 2024-T36, the numeral 6 following the T3 indicates an additional amount of cold work than used in the basic T3 temper. Following is a summary of some common additional digit temper designators:

- T31 Solution heat treated, cold worked by flattening or stretching, then naturally aged.
- T351 Solution heat treated, stress relieved by stretching, then naturally aged.
- T352 Solution heat treated, stress relieved by compression, then naturally aged.
- T361 Solution heat treated, cold worked approximately 6 percent then naturally aged.
- T37 Solution heat treated, cold worked approximately 8 percent, then naturally aged.
- T42 Solution heat treated from the O, F, or mill furnished temper, and naturally aged by the user to a stable condition.
- T51 Cooled from an elevated temperature manufacturing/shaping process, stress-relieved by stretching, then artificially aged.
- T571 Cooled from an elevated temperature manufacturing/shaping process, stress-relieved by stretching, then artificially aged.
- T61 Solution heat treated (quenched in boiling water), then artificially aged.
- T62 Solution heat treated from the O, F, or mill furnished temper, and then artificially aged by the user. Applies to any temper which has been heat treated and artificially aged by user which attains mechanical properties different from those of the -T6 condition.
- T65 Solution heat treated, stress relieved by stretching, then artificially aged.
- T71 Solution heat treated (quenched in boiling water), then artificially overaged.
- T72 Solution heat treated from the O, F, or mill furnished temper, and artificially overaged by the user to meet the mechanical properties and corrosion resistance limits of the applicable T7 temper.
- T73 Solution heat treated, then artificially overaged.
- T74 Solution heat treated, then artificially overaged (slightly less than T73).
- T76 Solution heat treated, then artificially overaged.
- T761 Solution heat treated, then artificially overaged.
- T81 Solution heat treated, cold worked, then artificially aged. Applies to 2024-T3 artificially aged to T81.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

- T851 Solution heat treated, stress-relieved by stretching, then artificially aged. Applies to 2024-T351 artificially aged to T851.
- T852 Solution heat treated, stress-relieved by compression, then artificially aged. Applies to 2024-T352 artificially aged to T852.
- T861 Solution heat treated, cold worked approximately 6 percent, then artificially aged. Applies to 2024-T361 artificially aged to T861.
- T87 Solution heat treated, cold worked approximately 8 percent, then artificially aged. Applies to 2024-T37 artificially aged to T87.

3.3.1.5 For additional information on aluminum alloy tempers and to locate numerous others not listed in this Technical Order (TO), see SAE-AS-1990.

3.3.1.6 For additional information on heat treating aluminum alloys, see [Paragraph 3.4](#).

3.3.1.7 Chemical composition nominal plus general use data are given in [Table 3-4](#) and nominal mechanical properties at room temperature are given in [Table 3-5](#). The values cited are general and intended for use as comparisons values. For specific values the specification for the alloy should be utilized.

3.3.2 Physical Properties. Commercially pure aluminum weights 0.098 pounds per cubic inch, corresponding to a specific gravity of 271. Data for standard alloys are shown in [Table 3-6](#). The approximate weight for aluminum, including its alloys, is one-tenth of a pound per cubic inch (see [Table 3-6](#)).

**Table 3-3. Aluminum Alloy Material Specifications**

Alloy	Form	SAE Aeronautical Material Specification (AMS)	ASTM	Federal/Military	Superseded/Rescinded
1060	Pipe and Tubing		B210, B241		
	Extrusions		B221		
	Plate and Sheet		B209		
1100	Pipe and Tubing		B210, B241		AMS 4102, AMS 4062
	Extrusions		B221		QQ-A-411, QQ-A-561, MIL-A-12545
	Forgings				AMS-QQ-A-225/1, AMS-QQ-A-250/1
	Rolled or Drawn		B211		WW-T-783, WW-T-700/1
	Plate and Sheet	QQ-A-250	B209	QQ-A-1876	AMS 4001, AMS 4003
1230	Plate and Sheet		B209		
2004	Plate and Sheet	4208, 4209			
2011	Rolled or Drawn		B211		QQ-A-365, AMS-QQ-A-225/3
2014	Pipe and Tubing		B210, B241		QQ-A-261, QQ-A-266,
	Extrusions	QQ-A-200/2, 4153	B221		MIL-A-12545
	Forgings	QQ-A-367, 4133, 4134			AMS 4135
	Rolled or Drawn	QQ-A-225/4, 4121	B211		
	Plate and Sheet	QQ-A-250/3	B209		QQ-A-255
2017	Rolled or Drawn	QQ-A-225/5, 4118	B211	QQ-A-430	QQ-A-351, MIL-W-7986
2018	Forgings	QQ-A-367, 4140			
2020	Plate and Sheet				QQ-A-250/16, MIL-A-8882



Table 3-3. Aluminum Alloy Material Specifications - Continued

Alloy	Form	SAE Aeronautical Material Specification (AMS)	ASTM	Federal/Military	Superseded/Rescinded
2024 (Bare)	Pipe and Tubing	4086, 4087, 4088	B210, B241		WW-T-785, WW-T-700/3
	Extrusions	QQ-A-200/3, 4152	B221		QQ-A-267
	Rolled or Drawn	QQ-A-225/6, 4120	B211		QQ-A-268
	Plate and Sheet	QQ-A-250/4, 4035, 4037, 4477, 4268, 4269, 4193	B209		QQ-A-355
2024 (Alclad)	Plate and Sheet	QQ-A-250/5, 4040, 4041, 4461, 4462, 4475, 4478, 4466, 4193	B209		QQ-A-362, AMS 4042
2025	Forgings	QQ-A-367, 4130			
2098	Plate and Sheet	4327, 4457			
2117	Rivets	*SAE AS7222			
2124	Plate and Sheet	QQ-A-250/29, 4101, 4221	B209		
2218	Forgings	QQ-A-367			AMS 4142
2219	Pipe and Tubing	4066, 4068	B241		
	Extrusions	4162, 4163	B221		
	Forgings	QQ-A-367		MIL-DTL-46118	
	Rolled or Drawn		B211	MIL-DTL-46118	
	Plate and Sheet	QQ-A-250/30, 4031, 4094, 4095, 4096, 4295, 4599, 4600, 4601, 4613	B209		MIL-A-8720
2618	Forgings	QQ-A-367, 4132			AMS 4006, AMS 4008
3003	Pipe and Tubing		B210, B241		AMS 4065, AMS 4067, WW-T-700/2
	Extrusions		B221		AMS-QQ-A-200/1, QQ-A-357
	Rolled or Drawn		B211		AMS-QQ-A-225/2, QQ-A-356
	Plate and Sheet		B209, B632		AMS-QQ-A-250/2, QQ-A-359
3004	Extrusions		B221		
	Sheet and Plate		B209		
3005	Sheet and Plate		B209		
3102	Tubing		B210		
	Extrusions		B221		
3105	Sheet and Plate		B209		
4032	Forgings	QQ-A-367			AMS 4145
	Rolled or Drawn	4319	B211		AMS 4318
5005	Tubing		B210		
	Sheet and Plate		B209		
5010	Sheet and Plate		B209		
5050	Tubing		B210		
	Sheet and Plate		B209		



Table 3-3. Aluminum Alloy Material Specifications - Continued

Alloy	Form	SAE Aeronautical Material Specification (AMS)	ASTM	Federal/Military	Superseded/Rescinded
5052	Pipe and Tubing	WW-T-700/4, 4069, 4070, 4071	B210, B241		WW-T-787
	Extrusions		B221		
	Rolled or Drawn		B211		AMS-QQ-A-225/7, QQ-A-315, AMS 4114
	Plate and Sheet	QQ-A-250/8, 4015, 4016, 4017	B209		QQ-A-318
5056	Rolled or Drawn	4182	B211		
5059	Sheet and Plate		B209	MIL-DTL-46027	
5083	Pipe and Tubing		B210, B241	MIL-T-52234	
	Extrusions	QQ-A-200/4	B221		MIL-A-19005
	Forgings	QQ-A-367			
	Plate and Sheet	4056	B209	MIL-DTL-46027, MIL-A-17358	AMS-QQ-A-250/6, MIL-A-8701
5086	Pipe and Tubing	WW-T-700/5	B210, B241	MIL-T-52234	
	Extrusions	QQ-A-200/5	B221		
	Plate and Sheet		B209		AMS-QQ-A-250/7, AMS-QQ-A-250/19, MIL-A-19070
5154	Pipe and Tubing		B210		
	Extrusions		B221		
	Rolled or Drawn		B211		
	Plate and Sheet		B209	MIL-A-17357	AMS 4018, AMS 4019
5252	Plate and Sheet		B209		
5254	Plate and Sheet		B209		
5454	Pipe and Tubing		B241		
	Extrusions	QQ-A-200/6	B221		
	Plate and Sheet	QQ-A-250/10	B209		
5456	Pipe and Tubing		B210, B241		
	Extrusions	QQ-A-200/7	B221		
	Plate and Sheet		B209	MIL-DTL-46027	AMS-QQ-A-250/9, AMS-QQ-A-250/20
5457	Plate and Sheet		B209		
5657	Plate and Sheet		B209		
5754	Plate and Sheet		B209		
6003	Plate and Sheet		B209		
6005	Pipe and Tubing		B241		
	Extrusions		B221		
6013	Pipe and Tubing		B241		
	Extrusions		B221		
	Rolled or Drawn		B211		
	Plate and Sheet	4216, 4347	B209		
6020	Extrusions		B221		
	Rolled or Drawn		B211		
6041	Pipe and Tubing		B241		
	Extrusions		B221		
6042	Pipe and Tubing		B241		
	Extrusions		B221		



Table 3-3. Aluminum Alloy Material Specifications - Continued

Alloy	Form	SAE Aeronautical Material Specification (AMS)	ASTM	Federal/Military	Superseded/Rescinded
6060	Extrusions		B221		
6061 (Bare)	Pipe and Tubing	WW-T-700/6, 4079, 4080, 4081, 4082, 4083, 4480	B210, B241		MIL-T-7081, AMS-T-7081, WW-T-789
	Extrusions	QQ-A-200/8, 4113, 4150, 4160, 4161, 4172, 4173	B221, B308		AMS-QQ-A-200/16, QQ-A-270
	Forgings	QQ-A-367, 4127, 4146, 4248			
	Rolled or Drawn	4115, 4116, 4117, 4128	B211		AMS-QQ-A-225/8, QQ-A-325
	Plate and Sheet	4025, 4026, 4027	B209, B632	MIL-DTL-32262	AMS-QQ-A-250/11, QQ-A-327
6061 (Alclad)	Plate and Sheet	4021, 4023	B209		AMS 4022
6063	Pipe and Tubing		B210, B241		
	Extrusions	4156	B221		AMS-QQ-A-200/9, QQ-A-274
6064	Pipe and Tubing		B241		
	Extrusions		B221		
6066	Pipe and Tubing		B241		
	Extrusions		B221	MIL-A-25493	AMS-QQ-A-200/10
	Forgings	QQ-A-367			
6070	Pipe and Tubing		B241		
	Extrusions		B221		
6082	Pipe and Tubing		B241		
	Extrusions		B221		
6105	Pipe and Tubing		B241		
	Extrusions		B221		
6110	Rolled or Drawn		B211		
6151	Forgings	QQ-A-367, 4125			
6162	Pipe and Tubing		B241		
	Extrusions		B221		AMS-QQ-A-200/17
6262	Pipe and Tubing		B210, B241		
	Extrusions		B221		
	Rolled or Drawn		B211		AMS-QQ-A-225/10
6351	Pipe and Tubing		B241		
	Extrusions		B221		
6360	Extrusions		B221		
6463	Extrusions		B221		
6560	Extrusions		B221		
7005	Extrusions		B221		
7011	Plate and Sheet	QQ-A-250/28	B209		QQ-A-250/26
7049	Forgings	QQ-A-367			
7050	Extrusions	4340, 4341, 4342			
	Forgings	4107, 4108, 4333			
	Plate and Sheet	4050, 4201			
7050 (Alclad)	Plate and Sheet	4243			



Table 3-3. Aluminum Alloy Material Specifications - Continued

Alloy	Form	SAE Aeronautical Material Specification (AMS)	ASTM	Federal/Military	Superseded/Rescinded
7072	Pipe and Tubing		B241		
	Extrusions		B221		
	Plate and Sheet		B209		
7075 (Bare)	Pipe and Tubing	WW-T-700/7	B210, B241		
	Extrusions	QQ-A-200/11, QQ-A-200/15, 4154, 4317, 4476, 4617	B221		QQ-A-277, AMS 4170
	Forgings	QQ-A-367, 4126, 4131, 4141, 4147, 4323			AMS 4139, MIL-A-12545
	Rolled or Drawn	QQ-A-225/9, 4122, 4123, 4124, 4186, 4310, 4311	B211		QQ-A-282
	Plate and Sheet	QQ-A-250/12, 4044, 4045, 4078, 4277, 4278, 4315	B209		QQ-A-252/24, QQ-A-250/26, QQ-A-283
7075 (Alclad)	Plate and Sheet	QQ-A-250/13, QQ-A-250/18, 4046, 4048, 4049, 4316	B209		QQ-A-250/25, MIL-A-8902, QQ-A-287
7076	Forgings	QQ-A-367			AMS 4137
7079	Forgings	QQ-A-367			QQ-A-250/17, AMS 4138
7116	Extrusions		B221		
7129	Extrusions		B221		
7178	Extrusions	QQ-A-200/13, QQ-A-200/14	B221		MIL-A-9186, AMS 4158
	Plate and Sheet	QQ-A-250/14, QQ-A-250/21, QQ-A-250/28			MIL-A-9180
7178 (Alclad)	Plate and Sheet	QQ-A-250/15, QQ-A-250/22			AMS 4051, AMS 4052
7149	Extrusions	4343			
	Forgings	4320			
7249	Extrusions	4293			
	Forgings	4334			
7475	Plate and Sheet	4084, 4085, 4089, 4090, 4202			MIL-A-63547
7475 (Alclad)	Plate and Sheet	4100, 4207			
201.0	Cast, Sand	A-21180, 4223, 4229, 4242	B26, B686		4228
203.0	Cast, All	4225			
204.0	Cast, Sand		B26		
	Cast, Perm Mold		B108		MIL-A-10953
206.0	Cast, Sand and Perm Mold	4235, 4236			AMS 4237
222.0*	Cast, Sand				QQ-A-601, *Inactive Alloy
	Cast, Perm Mold				QQ-A-596, MIL-A-10953



Table 3-3. Aluminum Alloy Material Specifications - Continued

Alloy	Form	SAE Aeronautical Material Specifi- cation (AMS)	ASTM	Federal/Military	Superseded/Rescinded
242.0 (Formerly 142/A142)	Cast, Sand	4222	B26		QQ-A-601
	Cast, Perm Mold		B108		QQ-A-596, MIL-A-10953
243.0*					AMS 4224, *Inactive Alloy
295.0 (Formerly 195)	Cast, Sand		B26		QQ-A-601
296.0	Cast, Perm Mold		B108		QQ-A-596, MIL-A-10953
308.0 (Formerly A108)	Cast, Perm Mold		B108		QQ-A-596, MIL-A-10953
319.0	Cast, Sand		B26		QQ-A-601
	Cast, Perm Mold		B108		QQ-A-596, MIL-A-10953
328.0	Cast, Sand		B26		QQ-A-601
332.0	Cast, Perm Mold		B108		QQ-A-596, MIL-A-10953
333.0	Cast, Perm Mold		B108		QQ-A-596, MIL-A-10953
336.0	Cast, Perm Mold		B108		QQ-A-596, MIL-A-10953
354.0	Cast, Perm Mold	A-21180	B108, B686		MIL-A-10953
355.0	Cast, Sand	A-21180, 4210, 4212, 4214, 4215	B26, B686		QQ-A-601
	Cast, Perm Mold	A-21180, 4215, 4280, 4281	B108, B686		QQ-A-596, MIL-A-10953
356.0	Cast, Sand	4217, 4218	B26, B686		QQ-A-601
	Cast, Perm Mold	4218, 4284, 4286	B108, B686		QQ-A-596, MIL-A-10953
357.0	Cast, Perm Mold	A-21180, 4219, 4241, 4249, 4288, 4289	B108, B686		QQ-A-596, MIL-A-10953
358.0*	Cast, Sand				MIL-C-47140, *Inactive Alloy
359.0	Cast, Perm Mold	A-21180	B108		MIL-A-10953
360.0	Cast, Die	QQ-A-591, 4290	B85		MIL-A-15153
380.0	Cast, Die	QQ-A-591, 4291	B85		MIL-A-15153
383.0	Cast, Die	QQ-A-591	B85		MIL-A-15153
384.0	Cast, Die	QQ-A-591	B85		MIL-A-15153
390.0	Cast, Die		B85		MIL-A-15153
392.0	Cast, Die		B85		MIL-A-15153
413.0	Cast, Die	QQ-A-591	B85		MIL-A-15153
443.0 (Formerly 43)	Cast, Sand		B26		QQ-A-601
	Cast, Perm Mold		B108		QQ-A-596, MIL-A-10953
	Cast, Die	QQ-A-591	B85		MIL-A-15153
444.0	Cast, Perm Mold		B108		MIL-A-10953
512.0	Cast, Sand		B26		QQ-A-601
513.0	Cast, Perm Mold		B108		QQ-A-596, MIL-A-10953
514.0 (Formerly 214)	Cast, Sand		B26		QQ-A-601
518.0	Cast, Die	QQ-A-591	B85		MIL-A-15153



Table 3-3. Aluminum Alloy Material Specifications - Continued

Alloy	Form	SAE Aeronautical Material Specifi- cation (AMS)	ASTM	Federal/Military	Superseded/Rescinded
520.0 (Formerly 220)	Cast, Sand		B26		QQ-A-601
535.0	Cast, Sand		B26		QQ-A-601, AMS 4238, AMS 4239
	Cast, Perm Mold		B108		MIL-A-10953
705.0	Cast, Sand		B26		QQ-A-601
	Cast, Perm Mold		B108		QQ-A-596, MIL-A-10953
707.0	Cast, Sand		B26		QQ-A-601
	Cast, Perm Mold		B108		QQ-A-596, MIL-A-10953
710.0	Cast, Sand		B26		QQ-A-601
711.0	Cast, Perm Mold		B108		MIL-A-10953
712.0	Cast, Sand		B26		QQ-A-601
713.0	Cast, Sand		B26		QQ-A-601
	Cast, Perm Mold		B108		QQ-A-596, MIL-A-10953
771.0	Cast, Sand		B26		QQ-A-601
850.0 (Formerly 750)	Cast, Sand		B26		QQ-A-601
	Cast, Perm Mold		B108		QQ-A-596, MIL-A-10953
851.0	Cast, Sand		B26		QQ-A-601
	Cast, Perm Mold		B108		QQ-A-596, MIL-A-10953
852.0	Cast, Sand		B26		QQ-A-601
	Cast, Perm Mold		B108		QQ-A-596, MIL-A-10953



Table 3-4. Chemical Composition Nominal and General Use Data

Alloy	1 Nominal Composition - percent						Flat and Coiled Sheet	Plate	Shapes Rods and Bars	Tube	Pipe	Characteristics
	Sili-con	Cop-per	Man-ga-nese	Mag-ne-sium	Chro-mium	Zinc	Alumi-num					
EC	--	--	--	--	--	--	99.45	X				Electrical conductor
1060	0.25	0.05	0.03	0.03	--	0.05	99.60	X				Good corrosion resistance, electrical conductivity, formability and weldability.
1100	1.0	0.20	0.05	--	0.10	0.10	99.0	X	X	X		Excellent formability, readily welded and brazed, corrosion resistant.
1145	0.55	0.05	0.05	--	--	--	99.45	X				Excellent formability combined with high electrical and thermal conductivity and corrosion resistant.
2014	0.8	4.5	0.8	0.4	0.10	0.25	REM	X	X	X		High strength alloy. Electric resistance weldability excellent fusion weldability limited.
2024	0.5	4.5	0.6	1.5	0.10	0.25	REM	X	X	X		Popular sheet alloy for aircraft similar to 2014.
2219	0.1	6.2	0.3	0.01	-	0.05	REM	X	X	X		Structural uses requiring high strength up to 600 degrees Fahrenheit (°F); high strength weldments.
3003	0.6	0.20	1.2	--	--	0.10	REM	X	X	X		Stronger than 1100 with good weldability and formability, high resistance to corrosion.
3004	0.30	0.25	1.2	1.0	--	0.25	REM	X	X			Stronger than 1100 and 3003 with fair workability and good corrosion resistance.
5005	0.40	0.20	0.20	0.8	0.10	0.25	REM	X	X			Similar to 3003 in strength. Good anodizing characteristics, formability and resistance to corrosion.
5050	0.40	0.20	0.10	1.4	0.10	0.25	REM	X	X			Good anodizing strength, formability, weldability, and corrosion resistance.
5052	0.45	0.10	0.10	2.5	0.25	0.10	REM	X				Highest strength of non-heat-treatable alloys. Good corrosion resistance and finishing characteristics.
5083	0.40	0.10	0.8	4.5	0.15	0.25	REM	X	X			High weld joint efficiency with basic good strength and resistance combined with good formability.
5154	0.45	0.10	0.10	3.5	0.25	0.20	REM	X	X			Good strength and excellent weldability.



Table 3-4. Chemical Composition Nominal and General Use Data - Continued

Alloy	1 Nominal Composition - percent						Flat and Coiled Sheet	Plate	Shapes Rods and Bars	Tube	Pipe	Characteristics
	Sili-con	Cop-per	Man-ga-nese	Mag-ne-sium	Chro-mium	Zinc	Alumi-num					
5254	0.45	0.05	0.01	3.5	0.25	0.20	REM	X				Good strength, weldability and corrosion resistance.
5357	0.12	0.07	0.3	1.0	--	--	REM					Excellent bright finishing characteristics.
5454	0.40	0.10	0.8	2.7	0.2	0.25	REM	X	X	X		Excellent strength at elevated temperature (150-300 °F) plus weldability.
5456	0.40	0.20	0.8	5.3	--	--	REM	X	X			High strength and corrosion resistance, weldable.
5457	0.08	0.20	0.3	1.0	--	--	REM	X				Superior bright finish when anodized.
5557			0.25	0.6			REM	X				Good bright finishing characteristics. Good weldability and formability.
5652				2.5	0.25		REM		X			Excellent strength with good finishing characteristics and corrosion resistance.
6013	0.8	0.85	0.5	1.0	0.1	0.25	REM	X				Excellent strength and good weldability with formability better than 6061.
6061	0.6	0.25	0.15	1.0	0.25	0.25	REM	X	X	X	X	Best weldability of heat treatable alloys, good formability and corrosion resistance.
6062	0.6	0.25	0.15	1.0	0.06	0.25	REM		X	X		Good weldability with formability better than 6061.
6063	0.4	0.10	0.10	0.7	0.10	0.25	REM		X	X	X	Good finishing characteristics and resistance to corrosion. Good workability with moderate strength.
7050	-	2.3	-	2.25	-	6.2	REM	X	X	X		High tensile properties, good exfoliation corrosion resistance good stress-corrosion cracking resistance.
7075	0.50	1.6	0.30	2.5	0.3	5.6	REM	X	X	X		2/ Extra high strength and hardness. Electric resistance weldability but limited fusion weldability.
7079	0.30	0.6	0.2	3.3	0.2	4.3	REM		X			Similar to 7075 but maximum strength in thick sections.
7178		2.0	0.30	2.7	0.3	6.8	REM	X	X			High strength alloy for Air Cooled (AC) applications, however it is notch sensitive.



Table 3-4. Chemical Composition Nominal and General Use Data - Continued

Alloy	1 Nominal Composition - percent						Flat and Coiled Sheet	Plate	Shapes Rods and Bars	Tube	Pipe	Characteristics
	Sili-con	Cop-per	Man-ga-nese	Mag-ne-sium	Chro-mium	Zinc	Alumi-num					
7475	0.05	1.5	0.03	2.25	2.1	5.7	REM	X				Aerospace applications requiring high strength, toughness up to 300 °F resistance to stress-corrosion cracking.
SI = Silicon MN = Magnesium CR = Chromium AL = Aluminum CU = Copper Magnesium = Magnesium ZN = Zinc 1/ Nominal Composition Does Not Include All Alloying Elements That May Pertain, Specification Should Be Utilized When Specific Data Required. 2/ 7075 - T73 Is Completely Resistant To Stress Corrosion Cracking.												



**Table 3-5. Mechanical Properties, Aluminum - Typical**

Alloy and Temper	Tensile Strength, Pound-force per Square Inch (PSI), minimum	Yield Strength, PSI (Offset = 0.2 percent) mini- mum	Elongation, Percent in 2 inch Sheet Specimen (1/16 inch Thick) minimum	Hardness 500 kilogram Load 10 millimeter Ball	Shearing Strength, PSI, minimum
1100-0	13000	5000	35	23	9000
1100-1-112	16000	15000	12	28	10000
1100-H14	18000	17000	9	32	11000
1100-H16	21000	20000	6	38	12000
1100-H18	24000	22000	5	44	13000
Alclad 2014-0	25000	10000	21		18000
Alclad 2014-T3	63000	40000	20		37000
Alclad 2014-T4	61000	37000	22		37000
Alclad 2014-T6	68000	60000	10	120	41000
2024-0	27000	11000	20	47	18000
2024-T3	70000	50000	18	100	41000
2024-T36	72000	57000	13	130	42000
2024-T4	68000	47000	20	100	41000
2024-T6	69000	57000	10	114	41000
2024-T8	70000	65000	7	118	41000
Alclad 2024-0	26000	11000	20		18000
Alclad 2024-T3	65000	45000	18	100	40000
Alclad 2024-T36	67000	53000	11	100	41000
Alclad 2024-T4	64000	42000	19	100	40000
Alclad 2024-T6	65000	52000		100	
Alclad 2024-T81	65000	60000	6	100	40000
Alclad 2024-T86	70000	66000	6	135	42000
2219-0	25000	11000	18		
2219-T42	52000	27000	20	100	
2219-T31, T351	52000	36000	17	96	33000
2219-T37	57000	46000	11	110	37000
2219-T62	60000	42000	10	113	37000
2219-T81, T851	66000	51000		123	41000
2219-T87	69000	57000	10	128	40000
3003-0	16000	6000	30	28	11000
3003-H12	19000	18000	10	35	12000
3003-H14	22000	21000	8	40	14000
3003-H16	26000	25000	5	47	15000
3003-H18	29000	27000	4	55	16000
3004-0	26000	10000	20	45	16000
3004-H32	31000	25000	10	52	17000
3004-H34	35000	29000	9	63	18000
3004-H36	38000	33000	5	70	20000
3004-H38	41000	36000	5	77	21000
5005-0	18000	6000	30	28	11000
5005-H32	20000	17000	11	36	14000
5005-H34	23000	20000	8	41	14000
5005-H36	26000	24000	6	46	15000
5005-H38	29000	27000	5	51	16



Table 3-5. Mechanical Properties, Aluminum - Typical - Continued

Alloy and Temper	Tensile Strength, Pound-force per Square Inch (PSI), minimum	Yield Strength, PSI (Offset = 0.2 percent) mini- mum	Elongation, Percent in 2 inch Sheet Specimen (1/16 inch Thick) minimum	Hardness 500 kilogram Load 10 millimeter Ball	Shearing Strength, PSI, minimum
5050-0	21000	8000	24	36	15000
5050-H32	25000	21000	9	46	17000
5050-H34	28000	24000	8	53	18000
5050-H36	30000	26000	7	58	19000
5050-H38	32000	29000	6	63	20000
5052-0	28000	13000	25	47	18000
5052-H32	33000	28000	12	60	20000
5052-H34	38000	31000	10	68	21000
5052-H36	40000	35000	8	73	23000
5052-H38	42000	37000	7	77	24000
5154-0	35000	17000	27	58	22000
5154-H112	35000	17000	25	63	
5154-H32	39000	30000	15	67	22000
5154-H34	42000	33000	13	78	24000
5154-H36	45000	36000	12	83	26000
5154-H38	48000	39000	10	87	28000
5357-0	19000	7000	25	32	12000
5357-H32	22000	19000	9	40	13000
5357-H34	25000	22000	8	45	15000
5357-H36	28000	26000	7	51	17000
5357-H38	32000	30000	6	55	18000
6013-T4	47000	27000	24		
6013-T6	59000	54000	9		
6061-0	18000	8000	25	30	12000
6061-T4	35000	21000	22	65	24000
6061-T6	45000	35000	12	95	30000
7050-T74, T7451, T7452	74000	65000	13	142	
7075-0	33000	15000	17	60	22000
7075-T6	83000	73000	11	150	48000
Alclad 7075-0	32000	14000	17		22000
Alclad 7075-T6	76000	67000	11	125	46000
Alclad 7079-T6	70000	60000			
7178-0	40000	21000	10		
7178-T6	83000	72000	6	145	
7079-T6	72000	62000			
7475-T7351	73000	63000	14		
201.0-T6	60000	50000	5	115-145	
201.0-T7	60000	50000	3	115-145	
206.0-T4	40000	24000	8		
222.0-T6 (Sand)	30000			100-130	
222.0-T65 (Perm Mold)	40000			125-155	
242.0-T571	29000			90-120	
242.0-T61 (Sand)	32000	20000		90-120	
242.0-T61 (Perm Mold)	40000			95-125	



Table 3-5. Mechanical Properties, Aluminum - Typical - Continued

Alloy and Temper	Tensile Strength, Pound-force per Square Inch (PSI), minimum	Yield Strength, PSI (Offset = 0.2 percent) mini- mum	Elongation, Percent in 2 inch Sheet Specimen (1/16 inch Thick) minimum	Hardness 500 kilogram Load 10 millimeter Ball	Shearing Strength, PSI, minimum
295.0-T4	29000	13000	6	45-75	
295.0-T6	32000	20000	3	60-90	
295.0-T62	36000	28000		80-110	
295.0-T7	29000	16000	3	55-85	
296.0-T4	33000	15000	4.5	60-90	
296.0-T6	35000		2	75-105	
296.0-T7 (Perm Mold)	33000	16000	3	65-95	
319.0-F (Sand)	23000	13000	1.5	55-85	
319.0-T6 (Sand)	31000	20000	1.5	65-95	
319.0-F (Perm Mold)	28000	14000	1.5	70-100	
319.0-T6 (Perm Mold)	34000		2	75-105	
319.0-T61 (Perm Mold)	40000	24000	1	80-110	
328.0-F	25000	14000	1	45-75	
328.0-T6	34000	21000	1	65-95	
333.0-F	28000			65-100	
333.0-T5	30000			70-105	
333.0-T6	35000			85-115	
333.0-T7	31000			75-105	
336.0-T65	40000			115-130	
354.0-T61	48000	37000	3		
354.0-T62	52000	42000	2		
355.0-T51 (Sand)	25000	18000	2	50-80	
355.0-T6 (Sand)	32000	20000	2	65-95	
355.0-T7 (Sand)	35000				
355.0-T71 (Sand)	30000	22000		60-90	
355.0-T51 (Perm Mold)	27000			60-90	
355.0-T6 (Perm Mold)	37000		1.5	75-105	
355.0-T62 (Perm Mold)	42000			90-120	
355.0-T7 (Perm Mold)	36000			70-100	
355.0-T71 (Perm Mold)	34000	27000		65-95	
C355.0-T6	36000	25000	2.5		
C355.0-T61 (Sand)	36000	30000	1	70-100	
C355.0-T61 (Perm Mold)	40000	30000	3	75-105	
356.0-F (Sand)	19000		2	40-70	
356.0-T51 (Sand)	23000	16000		45-75	
356.0-T6 (Sand)	30000	20000	3	55-85	
356.0-T7 (Sand)	31000	29000		60-90	
356.0-T71 (Sand)	25000	18000	3	45-75	
356.0-F (Perm Mold)	21000		3	40-70	
356.0-T51 (Perm Mold)	25000	22000	3	55-85	
356.0-T6 (Perm Mold)	33000	22000	3	65-95	
356.0-T7 (Perm Mold)	25000		3	60-90	
356.0-T71 (Perm Mold)	25000		3	60-90	
A356.0-T6 (Sand)	34000	24000	3.5	55-85	



**Table 3-5. Mechanical Properties, Aluminum - Typical - Continued**

Alloy and Temper	Tensile Strength, Pound-force per Square Inch (PSI), minimum	Yield Strength, PSI (Offset = 0.2 percent) mini- mum	Elongation, Percent in 2 inch Sheet Specimen (1/16 inch Thick) minimum	Hardness 500 kilogram Load 10 millimeter Ball	Shearing Strength, PSI, minimum
A356.0-T61 (Sand)	35000	26000	1		
A356.0-T71 (Sand)	26000	19000	4		
A356.0-T6 (Perm Mold)	33000	22000	5	65-95	
A356.0-T61 (Perm Mold)	37000	26000	5	70-100	
A357.0-T6, D357.0-T6	45000	36000	3	80-110	
A357.0-T61	45000	36000	3	85-115	
359.0-T61	45000	34000	4	75-105	
359.0-T62	47000	38000	3	80-100	
520.0-T4	42000	22000	12	60-90	
705.0-T5 (Sand)	42000	17000	5	50-80	
705.0-T5 (Perm)	42000	17000	10	55-85	
707.0-T5 (Sand)	42000	22000	2	60-90	
707.0-T7 (Sand)	42000	30000	1	65-95	
707.0-T5 (Perm Mold)	42000	25000	4	80-110	
707.0-T7 (Perm Mold)	42000	35000	3	80-110	
712.0-T5 (Sand)	42000	25000	4	60-90	
713.0-T5 (Sand)	42000	22000	3	60-90	
850.0-T5	42000		5	45	
851.0-T5	42000		3	45	
852.0-T5	42000	18000	3	60	
<p style="text-align: center;"><b>NOTE</b></p> <p>To convert hardness readings between scales, see ASTM E140-07: Standard Hardness Conversion Tables. For aluminum alloys with no hardness value provided in this technical order, refer to AMS 2658: Hardness and Conductivity Inspection of Wrought Aluminum Alloy Parts.</p>					

**Table 3-6. Physical Properties - Standard Aluminum Alloys**

Alloy	Specific Gravity	Weights Per Cubic Inch.	Approximate Melting Range - °F	Electrical Conductivity Percentage of the International Annealed Copper Standard
1100-0	2.71	0.098	1,190-1,215	57-62
1100-H18				57
2014-0	2.8	0.101	950-1,180	43.5-51.5
2014-T3				31.5-35
2014-T4				31.5-35.0
2014-T6				35-41.5
Alclad 2014-T6				35.5-44
2024-0	2.77	0.1	935-1,180	46-51
2024-T3				27.5-32.5
2024-T4				27.5-34
2024-T6				34-44
2024-T8				35-42.5
Alclad 2024-T3				28.5-35



Table 3-6. Physical Properties - Standard Aluminum Alloys - Continued

Alloy	Specific Gravity	Weights Per Cubic Inch.	Approximate Melting Range - °F	Electrical Conductivity Percentage of the International Annealed Copper Standard
Alclad 2024-T4	2.84	0.102	1010-1190	28.5-35
Alclad 2024-T6				35-45
Alclad 2024-T8				35-45
2048-T8				35-42.5
2124-T3				27.5-32.5
2124-T8				35-42.5
2219-0				44-49
2219-T3				26-31
2219-T37				27-31
2219-T4				28-32
2219-T6				32-36
2219-T8				31-35
2219-T87				31-35
Alclad 2219-T6				32-37
Alclad 2219-T8				31-37
3003-0	2.73	0.099	1,190-1,210	44.5-50.5
3003-H12				37.8-51.5
3003-H14				37.8-51.5
3003-H18	2.72	0.098	1,165-1,205	40
3004-0				42
3004-H38				42
5050-0	2.69	0.097	1,160-1,205	50
5050-H38				50
5052-0			2.68	0.097
5052-H38	35			
5357-0	2.7	0.098	1,165-1,210	43
5357-H38				43
6013-T4				0.098
6013-T6	40-43			
6061-0	42-49			
6061-T4	35.5-43			
6061-T6	40-47			
Alclad 6061-T6	40-53			
6063-0	57-65			
6063-T1	48-58			
6063-T4	48-58			
6063-T5	50-60			
6063-T6	50-60			
6066-0	42-47			
6066-T4	34-41			
6066-T6	38-50			
7049-0	44-50			
7049-T73	38-44			
7049-T76	38-44			
7050-0	2.83	0.102	890-1175	44-50
7050-T73				41-44



Table 3-6. Physical Properties - Standard Aluminum Alloys - Continued

Alloy	Specific Gravity	Weights Per Cubic Inch.	Approximate Melting Range - °F	Electrical Conductivity Percentage of the International Annealed Copper Standard
7050-T736	2.8	0.101	890-1180	40-44
7050-T76				39-44
7075-0				44-48
7075-T6				30.5-36
7075-T73				38-43
7075-T76				38-42
Alclad 7075-T6				30.5-36
Alclad 7075-T76				38-42
7178-0				43-47
7178-T6				29-34
7178-T76				38-42
Alclad 7178-T6				29-34
7475-0	2.8	0.101	890-1175	46
7475-T651				36
7475-T761				40
201.0-T6			995-1200	29-31
201.0-T7				29-31
206.0-T4			1010-1200	
222.0-T61				32-34
242.0-T571			990-1175	34
242.0-T61				32-34
295.0-T62			970-1190	36-38
296.0-T4, T6				33-36
319.0-T6			960-1120	27-28
328.0-T4				29-31
328.0-T6			960-1085	
333.0-F				25-27
333.0-T5				28-30
333.0-T6				28-30
333.0-T7				34-36
336.0-T551				29
336.0-T65			1000-1050	28-30
354.0-T61				31-33
355.0-T6			1015-1150	35-37
355.0-T61				35-37
355.0-T7				41-43
355.0-T71				38-40
C355.0-T6			1015-1150	35-37
C355.0-T61				36-38
356.0-T51			1035-1135	42-44
356.0-T6				38-40
356.0-T7				39-41
356.0-T71				40-41
A356.0-T6				
A356.0-T61				38-40
A356.0-T71				



Table 3-6. Physical Properties - Standard Aluminum Alloys - Continued

Alloy	Specific Gravity	Weights Per Cubic Inch.	Approximate Melting Range - °F	Electrical Conductivity Percentage of the International Annealed Copper Standard
A357.0-T6				38-40
A357.0-T61				38-40
D357.0-T6				38-40
359.0-T61			1045-1115	34-36
359.0-T62				34-36
520.0-T4			840-1120	20-22
705.0-T5			1105-1180	24-26
707.0-T5			1085-1165	24-26
707.0-T7				
712.0-T5			1135-1200	34-36
713.0-T5			1110-1180	29-31
850.0-T5			440-1200	46-48
Other Base Alloys				
Brass	8.4-8.8	0.304-0.319		26-43
Copper	8.94	0.322	1981	100
Monel	8.8	0.318		4
Nickel	8.84	0.319	2645	16
Steel (low alloy)	7.6-7.8	0.276-0.282	2800	3-15
Steel (18.8 stainless)	7.92	0.283	2500-2650	2-4
Tin	7.3	0.265	449	15
Zinc	7.1	0.258	787	30
<p style="text-align: center;"><b>NOTE</b></p> <p>To convert hardness readings between scales, see ASTM E140-07: Standard Hardness Conversion Tables. For aluminum alloys with no hardness value provided in this technical order, refer to AMS 2658: Hardness and Conductivity Inspection of Wrought Aluminum Alloy Parts.</p>				



Table 3-7. Properties of Common Aluminum Alloys - Minimum

Alloy	Temper	Product Form	Tensile Strength, Kips per Square Inch (KSI)		Yield Strength @2 Percent Offset		Rockwell B Scale		Rockwell E Scale		Percentage of the International Annealed Copper Standard	
			Minimum	Maximum	Minimum	Maximum	Minimum	Maximum	Minimum	Maximum	Minimum	Maximum
2024	O			32		14		22		70	46	51
	T3		63		52		63			94	27.5	32.5
	T4, T42		62		38		63			94	27.5	34
	T6		64		50		72			98	34	44
	T72		60		46		72			98	38	45
	T8		67		58		74			99	35	42.5
	T86		71		66		83				37	41
	O			32		14		22			46	51
Alclad 2024	T3	≤0.063	59		39		57			91	28.5	35
		≥0.063	61		40		60			93	28.5	35
	T4, T42	≤0.063	58		36		57			91	28.5	35
		≥0.063	61		38		60			93	28.5	35
	T6	≤0.063	60		47		60			93	35	45
		≥0.063	62		49		62			94	35	45
	T8		65		56		65			97	35	45
	T86		69		64		83				37	41
6061	O			22		12						
	T4		30		16					60		
	T6		42		35		47			85		
	T6		38		32					84		
Alclad 6061												
7050	O							22			44	50
	T73						81				41	44
	T74	<0.501					82	88			38	44
	T76						84				39	44
7075	O			40		21		22			44	48
	T6		78		68		84				30.5	36
	T73		67		56		78				38	43
	T76		73		62		82				38	42



Table 3-7. Properties of Common Aluminum Alloys - Minimum - Continued

Alloy	Temper	Product Form	Tensile Strength, Kips per Square Inch (KSI)		Yield Strength @2 Percent Offset		Rockwell B Scale		Rockwell E Scale		Percentage of the International Annealed Copper Standard	
			Minimum	Maximum	Minimum	Maximum	Minimum	Maximum	Minimum	Maximum	Minimum	Maximum
Alclad 7075	O			38		20				70	44	48
	T6		74		64		76				30.5	36
NOTE												
For aluminum alloys not provided in this technical order, refer to AMS 2658, Hardness and Conductivity Inspection of Wrought Aluminum Alloy Parts, and ASTM E 140, Standard Hardness Conversion Tables.												



### 3.4 HEAT TREATMENT OF ALUMINUM ALLOYS.

#### NOTE

Society of Automotive Engineers (SAE) SAE-AMS-2770, Heat Treatment of wrought aluminum alloy parts, and SAE-AMS-2771, Heat Treatment of aluminum alloy castings, are the control documents for heat treatment of aluminum alloys used on aerospace equipment. For complete description of aluminum alloy heat treat requirements, refer to the latest issues of SAE-AMS-2770 and SAE-AMS-2771. In case of conflict with this manual, the discrepancy will be negotiated with the responsible technical/engineering activity for resolution and updating.

**3.4.1 General.** There are two types of heat treatment applicable to aluminum alloys. They are known as solution and precipitation heat treatment. Some alloys such as 2024 and 6061 will naturally develop stronger mechanical properties as a result of solution heat treatment and quenching, followed by 96 hours (natural aging) at room temperature. Yet, those same alloys and others, such as 7050 and 7075 require solution heat treatment, quenching, and precipitation heat treatment (artificial aging) for specific lengths of time at elevated temperatures to develop even stronger mechanical properties.

**3.4.1.1** Parts requiring heat treatment to produce a final “T” temper shall be solution heat treated, immediately quenched, refrigerated if necessary to delay aging, and aged (natural or artificial) as required. Heat treatment shall be performed only on entire parts, never on a portion or section of a part.

**3.4.1.2** For the purposes of this manual, the term “wrought” aluminum alloys will consist of sheet, plate, rod, bar, extrusions, and forgings or parts made from these materials. The term “cast” aluminum alloys will consist of sand castings, permanent mold castings, and parts machined from castings. If an exact nomenclature or specification is required, it will be called out in applicable paragraphs, tables, or figures.

#### NOTE

Additional Heat Treatment information is discussed in Chapter 9.

### 3.5 NEWLY FABRICATED PARTS.

#### NOTE

Results of conductivity testing on 6061, 6063, 6066, and 6951 aluminum alloy parts shall not be used as a basis of part acceptance or rejection. Conductivity testing on these aluminum alloys shall be for reference use only.

Newly fabricated parts that require heat treatment shall be accompanied by a coupon, whenever possible. Coupons must be heat treated along with the manufactured part to ensure both pieces undergo the same metallurgical changes. A coupon is a piece of metal that is taken from the same stock as the fabricated part. Its thickness should match that of the part with an overall size that provides adequate room for hardness and conductivity testing. After completion of heat treatment, all heat treated aluminum alloy parts and coupons shall be conductivity tested. In addition, perform required hardness testing on the coupon to prevent damage to the fabricated part. See Chapter 8 of this technical order for proper hardness testing procedures. When batch processing, simultaneously heat treating multiple parts of the same material and thickness, the parts with the lowest and highest conductivity readings shall also be hardness tested to validate metallurgical changes of the batch. Parts that fail to meet hardness or conductivity standards shall be rejected and reworked as appropriate.

### 3.6 RECORDS.

Air Force (AF) and government personnel shall document heat treatment procedures performed on aluminum alloy aircraft and missile weapon systems and support equipment by utilizing AFTO Form 8, Heat Treatment Procedure Record. On-site AF contractors shall also use the Air Force Technical Order (AFTO) Form 8 unless their contract specifies a different method of heat treatment documentation. The results of heat treatment performed on aluminum alloys shall be verified through hardness and conductivity testing. Minimum hardness conductivity readings for commonly used aluminum alloys are specified in [Table 3-7](#). Additional conductivity data can be found in [Table 3-6](#). Personnel performing hardness testing shall document results on AFTO Form 8, Blocks 21-25. Conductivity shall be tested by qualified Non-Destructive Inspection (NDI) personnel using TO 33B-1-2, WP 407 00, or qualified heat treat personnel, using direct reading instruments in accordance with MIL-STD-1537, “Electrical Conductivity Test for Verification of Heat Treatment of Aluminum Alloys, Eddy Current Method.” Results shall be documented on AFTO Form 8, Blocks 27 - 32 and signed by performing personnel. A paper or digital copy of the completed record shall be retained for 7 years by the facility performing the heat treatment process.



### 3.7 SOLUTION HEAT TREATMENT.

Solution heat treatment is a process where the alloying elements enter into a solid solution in the aluminum at critical temperatures. It has been found that those alloying elements, which increase the strength and hardness of the material, are more soluble in solid aluminum at high temperature than at low. To manipulate the alloy into a solid solution, the metal is held at high temperatures for sufficient time; it is then quenched rapidly in water to retain this condition. Immediately after quenching, the alloy is in an unstable condition because it consists of a supersaturated solid solution of the hardening agent. Upon standing at room temperature the hardening constituent in excess of that which is soluble at room temperature begins to precipitate. This precipitation is in effect a natural method where the molecules of the aluminum and alloying elements are realigned to increase the strength and hardness of some aluminum alloys. The precipitate is in the form of extremely fine particles, which due to their “keying” action, greatly increases their strength.

**3.7.1 Heating Temperature.** It is necessary that solution heat treatment of aluminum alloys be accomplished within specific limits in reference to temperature control and quenching. The temperature for heat treating is usually chosen as high as possible without danger of exceeding the melting point of any element of the alloy. This is necessary to obtain the maximum improvement in mechanical properties. If the maximum specified temperature is exceeded, eutectic melting will occur. The consequence will be inferior physical properties, and usually a severely blistered surface. If the temperature of heat treatment is low, maximum strength will not be obtained.

**3.7.1.1** Obtaining the designated solution heat treating temperature is required to put all of the soluble elements into a solid solution. The required solution heat treating temperatures for various wrought and cast aluminum alloys can be found in [Table 3-8](#) and [Table 3-10](#).

**3.7.2 Heating (Soak) Time.**

#### NOTE

With Alclad materials, strict conformance is required with regards to the maximum soak time. Prolonged heating will defeat the purpose of the cladding by allowing the copper and other soluble elements to diffuse into the cladding.

The heating time, commonly called the “soak time”, required to establish a solid solution increases with the thickness of the section or part to be heat treated. Solution heat treatment should be held to the minimum time required to obtain the desired physical properties. In some instances the above will require sample testing to determine the exact solution time.

**3.7.2.1** The mandatory soaking times for air furnace solution heat treatment of wrought and cast alloys are based on using furnace/oven control sensors (thermocouples) reflecting furnace air temperature. They include an allowance for the lag between air temperature and metal temperature. Therefore, basing the soak start time on a load sensor (thermocouple attached to part) temperature and soaking for the times listed in [Table 3-9](#) and [Table 3-10](#) will result in excess soak time. In the case of solution heat treatment, it will increase clad diffusion. In the case of aging, this may result in reduced properties or parts not meeting required specifications. Use of load sensors should be limited to confirming that parts reached the required temperature range, i.e., the range defined by applying the furnace temperature uniformity tolerance to the specified temperature, and remained within the allowable range until the parts were quenched. See [Table 3-9](#) and [Table 3-10](#) for the minimum required solution heat treat soaking time for wrought and cast aluminum alloys. Although required soak time is stated as a minimum time, the time stated should be adhered to as closely as possible to prevent over soaking.

**3.7.2.2** The soak time (time at temperature) starts after a successful recovery time; when all temperature control, recording, and monitoring sensors, measuring furnace air temperature, reach the minimum of the uniformity tolerance range for the operation being performed. Load sensors should not be used to determine the start of soaking time. See [Table 3-19](#) for temperature uniformity tolerance ranges of applicable heat treat processes.

**3.7.3 Interruptions.** During solution heat treatment, soaking shall be performed without interruption.

**3.7.4 Oven/Part Loading.** Ovens used to heat treat all aluminum alloys shall be stabilized at the set point temperature before loading parts. Aluminum parts and raw materials shall not be loaded into a cold oven and brought to temperature with the oven. In the case where temperature ramping is required for a specific material, the oven shall be stabilized at the initial temperature prior to part loading and soaking. Upon completion of the initial soak, the part and oven shall be ramped together to the next temperature set point, as required.



3.7.4.1 When necessary, batch materials or parts should be racked to allow adequate heat transfer and airflow. Nesting is not permitted. To prevent distortion it is necessary, in some cases, to provide jig or fixture support for complex contoured (formed) parts. However, the jig used shall be constructed so that it will not restrict the contact required (airflow) with the heating medium of the part being treated. The jig should also permit unobstructed access to the part to enable a rapid quench.

3.7.4.2 Parts having a minimum thickness of the heaviest section equal to 0.250 inch or less shall be separated by no less than 1 inch. Parts having a minimum thickness of the heaviest section larger than 0.250 inch will be separated by no less than 1 inch plus the thickness of the part. Complex parts or parts that have a large surface area, sheet or plate, may require greater separation to facilitate even and complete heating.

3.7.4.3 Load thermocouples/sensors, if used, shall be placed on or as close to the part as possible to measure ambient air temperature immediately around the part/load. They shall also be placed in such a way that they will not interfere with rapid part quenching.

3.7.4.4 Expendable base metal thermocouples may be used up to 90 calendar days after first use and for no more than 30 uses when used at or below 1200 °F. For the life cycle requirements of non-expendable base metal thermocouples, see AMS2750.

3.7.5 Oven Recovery Time. Recovery time is the time required for the oven to return to the set temperature within the uniformity allowance of the process being performed, after loading parts, but prior to the start of soak time. Recovery time for all non-alclad aluminum parts shall not exceed 40 minutes. Recovery time for parts made from alclad material under 0.125 inch thick, shall not exceed 30 minutes. Parts made from alclad material thicker than 0.125 shall not exceed 60 minutes.

### 3.8 QUENCHING.

To obtain optimum physical properties of aluminum alloys, rapid quenching is required. The basic purpose of quenching is to prevent the immediate re-precipitation of the soluble constituents after heating the material to a solid solution. Allowing the metal to cool before quenching promotes intergranular corrosion and negatively affects the hardness. This is caused by re-precipitation along grain boundaries and in certain slip planes. After quenching, wrought parts are in the AQ (as quenched) or W (unstable) temper condition. After quenching, cast parts are in the AQ condition. After 45 minutes at room temperature or after the maximum refrigerated storage time has elapsed, cast parts are in the W temper condition.

3.8.1 Quench Equipment. Equipment shall be provided for quenching in water and for measuring quenchant temperature. Provisions shall be made for mechanical or hydraulic agitation of the quenching medium and/or parts. Air agitation shall not be used. Quench tanks shall be located in close proximity to solution heat treating furnaces so the quench delay requirements of [Table 3-11](#) can be met. The quenchant volume shall be sufficient enough to prevent the quenchant temperature from rising more than permitted in [Paragraph 3.8.4](#) during quenching of a maximum load.

3.8.2 Quench Delay. Following completion of the required soak period, wrought parts shall be quenched by complete immersion in water. Castings shall be quenched by complete immersion in water or oil, as required. All parts shall be quenched within the maximum quench delay time, based on part thickness. For maximum quench delay times, see [Table 3-11](#).

3.8.3 Quenchant Temperature. At the start of the quench, quenchant temperature shall not exceed 90 °F, except when quenching parts made from forgings or castings. When quenching parts made from forgings or castings, the starting temperature of quenchant shall conform to [Table 3-12](#). Provisions shall be provided to maintain quenchant temperature, as required.

3.8.4 Quenchant Temperature Rise. The quenchant temperature shall not exceed the maximum start-of-quench temperature specified in [Paragraph 3.8.3](#) by more than 10 °F at any time during quenching. Additionally, for forgings and castings, the quenchant temperature shall not increase more than 25 °F from the starting temperature as a result of quenching any single load.

### NOTE

Small parts heated and soaked in baskets such as rivets, fasteners, washers, spacers, etc., should be quenched by dumping when the basket load is too heavy/thick to allow adequate quenchant contact and rapid cooling of parts in the center of the load, provided the parts will not be damaged by dumping.

3.8.5 Agitation. Parts and/or quenchant shall be agitated during quenching. For thin parts, under 0.105 inch, movement into the quenchant during immersion is sufficient. Agitation shall continue until all evidence of boiling ceases, or upon completion of the required immersion time stated in [Paragraph 3.8.6](#).



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

**3.8.6 Immersion Time.** Wrought parts 0.125 inch thick, or less, may be removed from the quenchant as soon as boiling ceases. Wrought parts thicker than 0.125 inch, parts that have been racked, or parts in baskets shall be kept immersed in the quenchant for not less than 1 minute per inch of maximum thickness, or for not less than 1 minute after all evidence of boiling ceases, whichever is longer. Cast parts shall be kept immersed for not less than 2 minutes per inch of thickness, or fraction thereof of the thickest section, or for not less than 2 minutes after all evidence of boiling ceases, whichever is longer. Castings quenched in boiling water shall remain immersed for not less than 2 minutes.

**3.9 STRAIGHTENING OF PARTS AFTER QUENCHING.**

**NOTE**

Formed parts that have been unavoidably distorted should be reformed immediately after quenching.

Prior to aging, it may be necessary to straighten some parts due to warping produced by the quenching process. Warped parts can be straightened by hand manipulation, restriking, or reforming. If straightening cannot be immediately performed after quenching, it is necessary to place the parts in refrigeration immediately after quenching to retard natural aging until such time straightening is accomplished.

**3.10 REFRIGERATION.**

Refrigeration is defined as the act of cooling or freezing. A temperature of 10 °F or below will delay or retard natural aging for approximately 24 hours. Lower temperatures will delay natural aging longer. See [Table 3-13](#) for refrigeration requirements and aging delays.

**3.11 PRECIPITATION HEAT TREATING (ARTIFICIAL AGING).**

Precipitation heat treating is the process of soaking previously solution heat treated parts at a moderately elevated temperature for a specific period of time, to enhance strength and corrosion resistance properties, and allowing to air cool. The strengthening of the material is due to the uniform alignment or formation of the molecular structure of the aluminum and alloying elements. Aging a material at an elevated temperature is known as artificial aging. During precipitation heat treating/artificial aging, the alloying constituents suspended in a solid solution begin to precipitate out. As the precipitation progresses, the material strength increases until the maximum is reached. Further aging (over-aging) causes the strength to decline until a stable condition is obtained. Aging material at room temperature, although not technically a heat treating process but does produce similar results, is known as natural aging. The alloying constituents naturally precipitate out and the material gains strength as a result, but material properties of natural aging are limited. To obtain higher material properties, precipitation heat treatment or artificial aging must occur.

**3.11.1 Artificial Aging.** Artificial aging of many aluminum alloys is necessary to refine the material and obtain the required properties. Heating most aluminum alloys, bare, clad or cast, at an elevated temperature, usually between 225-450 °F, following solution heat treatment will result in tensile and yield strengths well above those obtained by natural aging. However, this process will reduce the elongation factor of the material and increase resistance to forming. Therefore, most forming or straightening operations should be performed prior to this stage of treatment.

**NOTE**

Straightening or forming of parts in the following natural and artificially aged tempers is prohibited unless approved by the responsible technical/engineering authority: T4 and T4X (which have sufficiently aged at room temperature to meet the hardness or conductivity minimum), T6, T6X, T7, T7X, and T8X.

**3.11.1.1** If a T8XX condition is desired, material in a T3XX condition must be selected, formed if necessary, and precipitation heat treated (artificially aged) to achieve the desired final temper. The tempers listed in [Paragraph 3.11.1.2](#) are normally furnished by mills/producers and cannot be produced by field users. Consequently, if parts or material in one of these tempers is specified, it should not be user solution heat treated or annealed to the O condition as you will not be able to achieve a T3XX or T8XXX temper again.

**3.11.1.2** Typical mill furnished tempers: T3, T31, T351, T3510, T3511, T36, T361, T37, T451, T4510, T4511, T651, T6510, T6511, T652, T654, T7351, T73510, T73511, T7352, T7354, T73651, T736510, T7365111, T73652, T73654, T7451, T74510, T74511, T7452, T7454, T7651, T76510, T81, T851, T8510, T8511, T86, T861, T87.



3.11.1.3 Artificially aged alloys are usually slightly “over-aged” to increase their resistance to corrosion and increase chances of reaching a stabilized condition. Soak times for precipitation heat treating/artificial aging are not difficult to control due to the broad tolerances for the specified times. The greatest hazard to proper aging is under soaking. Under soaking is primarily due to not properly accounting for heavy loads, improperly racked or nested parts, and excessive interruptions. To properly age parts, ensure they are soaked for the specific amount of time listed in the precipitation heat treating process tables for wrought and cast aluminum alloys and follow the procedures of [Paragraph 3.11.2](#) through [Paragraph 3.11.4.1](#).

3.11.2 Soak Time. Soak time starts when all temperature control, recording, and monitoring sensors, measuring furnace air temperature, reach the minimum of the uniformity tolerance range for the process being performed. Load sensors should not be used to determine the start of soaking time. See [Table 3-19](#) for temperature uniformity tolerance ranges of applicable heat treat processes. See [Paragraph 3.7.5](#) for recovery time requirements.

3.11.3 Part Loading. Entrapped water shall be prevented from entering the furnace. The loading of wet parts directly after being water/liquid quenched, into a furnace is prohibited. To allow adequate contact with the heating medium/air flow, parts shall be properly racked or spaced. Parts 0.500 inch or thicker shall be separated by not less than 1 inch. Thin parts, less than 0.500, may be nested providing thickness of nested stacks does not exceed 0.500 inch and stacks are at least 1 inch apart. Furnaces shall be stabilized at the set temperature before loading parts.

3.11.3.1 Load thermocouples/sensors, if used, shall be placed on or as close to the part as possible to measure ambient air temperature immediately around the part/load.

3.11.3.2 For the life cycle requirements of load thermocouples, see [Paragraph 3.7.4.4](#).

3.11.4 Interruptions. During aging and annealing, a maximum of four interruptions, with doors not open for more than 2 minutes during each, is permissible for the loading and removing of parts. Door opening durations greater than 2 minutes are permitted provided the time between the door opening and the recovery of the furnace temperature is not included in the total soak time.

3.11.4.1 For precipitation heat treatment (artificial aging) temperature and times of wrought and cast aluminum alloys, see [Table 3-14](#) and [Table 3-15](#).

3.11.5 Annealing.



Annealed aluminum parts shall not be used for parts or fittings on aircraft or missiles unless specified by drawings or other approved engineering data. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

Annealing is a thermal treatment used to soften metal. A full anneal will soften aluminum alloys to develop maximum formability and ductility. Aluminum alloys are annealed to remove the effects of previous heat treatments and strain hardening, and make the material easier to form without cracking.

3.11.5.1 Annealing and subsequent forming of material previously heat treated should be avoided. The recommended method for aircraft parts is to repeat the solution heat treatment and immediately perform the forming or drawing operation.

3.11.5.2 When annealing, a full anneal shall be used unless a partial anneal or stress relief is specified in manufacture blueprints or approved by the responsible technical/engineering authority. Wrought and cast parts requiring annealing shall be heated, soaked, and cooled as specified in [Table 3-16](#) or [Table 3-17](#). Subsequent solution and precipitation heat treatments of annealed material will result in T-6 condition, provided the material is not worked outside of the W condition prior to aging.

3.11.5.3 For annealing oven temperature uniformity, part loading, recovery time, start of soak time, and interruptions, see [Paragraph 3.11.2](#) through [Paragraph 3.11.4](#).



3.11.6 Cold Working.

**NOTE**

Field accomplishment of the cold work required to produce the higher strength conditions is considered impractical. This is due to the amount of control and types of equipment necessary to stretch or roll the material in order to produce these conditions.

During prolonged forming or stamping operations metal becomes strain hardened, commonly called “work hardened”, and upon the performance of additional work it will split or crack. Parts work hardened during fabrication are annealed at various stages of the forming operation so that complicated shapes can be formed. Annealing will remove any properties developed as a result of strain hardening, cold working, or other induced stresses as a result of forming the material.

3.11.6.1 Mechanical properties obtained from precipitation heat treating (artificial aging) of cold worked materials are dependent on the amount of cold work present in the material at the time of aging. Conditions T-81 or T-86 would necessitate a cold work percentage of approximately 1 percent for T-81 and 6 percent for T-86 after solution heat treatment but prior to aging. The selection of material for various uses will therefore be governed by the severity of the cold work to be performed or strength and condition of the material required. The higher strength conditions can only be obtained by a controlled amount of cold work by a material producer prior to aging.

3.11.6.2 Tempers identified as cold worked and not producible at field level are T3, T8 (with the exception of artificially aging, without solution heat treating, T3XX to T8XX), T9 and T10. See [Paragraph 3.11.1.1](#) and [Paragraph 3.11.1.2](#).

3.11.7 Re-Solution Heat Treatment. Sometimes parts need to be re-solution heat treated in order to remove work induced hardening/stress, return a part back to the W condition for additional forming or bending, post-annealing heat treatment, or simply to make a second attempt at a previous heat treatment process that did not meet hardness and conductivity specifications. When re-solution heat treatment is necessary, follow the steps as detailed for solution and precipitation heat treatment, as necessary, to obtain the desired final properties of the material. There are some exceptions for re-solution heat treatment as detailed in the paragraphs below.

3.11.7.1 Bare heat treatable wrought and cast aluminum alloys can be solution heat treated repeatedly without harmful effects other than high temperature oxidation. The oxidation can be retarded by ensuring that no water/fluids enter the heat treating chamber. If oxidation is occurring, ammonium fluoborate, or equivalent, should be used in air furnaces, as necessary, to absorb moisture. However, purging the furnace with fresh air may be necessary to prevent discoloration of subsequent loads of parts made from alclad product.

3.11.7.2 For alclad product, the number of solution heat treatments is limited due to the increased diffusion of the core and cladding. Parts made from alclad product over 0.125 inch in nominal thickness shall be limited to two solution heat treatments in addition to any by the material producer. Parts made from product 0.020 inch to 0.125 inch in nominal thickness, shall be limited to one additional solution heat treatment in addition to any performed by the raw material producer. For parts made from product under 0.020 inch in nominal thickness, additional solution heat treatments are prohibited. See [Table 3-18](#) for the maximum re-solution heat treatments for alclad parts.

3.11.7.3 Example for multiple solution heat treatments of alclad parts; a 0.062 inch thick part made from alclad 2024-T3, formed, solution heat treated, quenched, and artificially aged to -T6 would not be allowed any further solution heat treatments if the material properties did not meet specs. If that same part was over 0.125 inch thick, it would be able to be solution heat treated one more time.

3.12 HEAT TREATMENT OF RIVETS.

The heat-treatable alloys commonly used for rivets are 2117, 2017, and 2024.

3.12.1 2117 (AD) Rivets. Supplied in the T-4 temper and used in the condition received. No further treatment is required. The rivet is identified by a dimple in the center of the head (see [Figure 3-1](#), item AD for head identification).



3.12.2 2017 or 2017-T4 (D) Rivets.

- (DD) rivets (by specification), ONLY have a clear/gray anodize finish; these rivets are ready to undergo the solution heat treat/quench/refrigeration process. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- (D) rivets (by specification) can have an alodine, tinted-anodize, or a clear/gray anodize finish. ONLY tinted-anodized or clear/gray anodized finished (D) rivets are acceptable to undergo the solution heat treat/quench/refrigeration process. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- (D) rivets with an alodine finish MUST NOT be subjected to the solution heat treat/quench/refrigeration process: this finish will “burn-off” leaving the surface bare. If finish on (D) rivets cannot be positively identified as an anodized finish (part number or by close examination by a finish expert), then do not subject parts to the solution heat treat/quench/refrigeration process. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

If required, solution heat treat prior to installation by heating to the temperatures and times indicated in [Table 3-8](#) and [Table 3-9](#). When utilizing a basket for heat treating rivets, maximum material layer is 2 inches. These rivets must be driven within 20 minutes after quenching or refrigerate at 10 F or lower within 15 minutes which will delay the aging time 24 hours. If either time is exceeded reheat treatment is required. It is noted the D rivets may also be used in the natural age hardened condition, T4, if allowed to sit out at room temperature after solution heat treatment without being driven. Natural aging to the T4 condition is usually achieved after 96 hours have elapsed. See [Figure 3-1](#), item D for head identification.

3.12.3 2024-0 or 2024-T4 (DD) Rivets. The same conditions apply for these rivets as for the 2017 (D), except the required soak temperature is different based on the alloy. See [Table 3-8](#) and [Table 3-9](#) for soak temperature and time. See [Figure 3-1](#), item DD for head identification.

3.12.4 1100 and 5056 Rivets. These do not require heat treatment, install as received. See [Figure 3-1](#), item A and [Figure 3-1](#), item B for identification.

3.12.5 7050 (E) Rivets.


Rivets which have been anodically oxide coated should not be re-heat treated in direct contact with molten salts more than 5 times. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

These do not require heat treatment, install as received. See [Figure 3-1](#), item E for head identification.

3.12.6 D/DD Rivets. To retard natural aging, these may be stored in refrigerator/freezers that ensure the rivet temperature does not rise above 10, 0, or -10 °F, depending on desired length of storage. Rivets held at 10 °F, or below, will retard aging (maintain W condition) and may be stored for 24 hours. Rivets held at 0 °F or below may be stored for up to 30 days. Rivets held at -10 °F or below may be stored for up to 90 days. When the rivets are transported, their temperature will be maintained at -10 °F or below by being carried in refrigerated boxes. See [Table 3-13](#) for refrigeration requirements.

- a. Quality control shall be responsible for periodically checking the temperature of each refrigerator/freezer and for prohibiting the use of rivets in any box when the temperature becomes excessive.
- b. Each refrigerator/freezer shall have the rivets removed and be thoroughly cleaned at least once every six months. A tag or placard that denotes the next cleaning date shall be attached to each refrigerator/freezer.
- c. Rivets which remain out of refrigeration for 30 minutes or more shall be reheat treated. These rivets can be reheat treated a maximum of three times.



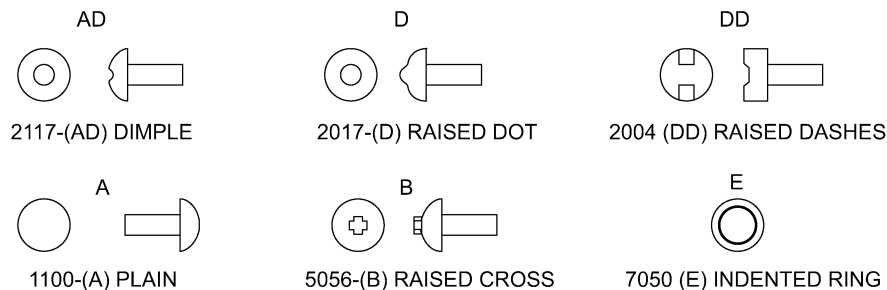

TO-1-1A-9-008

**Figure 3-1. Head to Alloy Identification Method**

**Table 3-8. Solution Heat Treating Temperatures for Wrought Aluminum Alloys**

Alloy	Form	Set Temperature °F	Notes
2004	Sheet	985	
2014, 2017, 2117	All	935	
2024, 2124, 2224	All	920	
2098	All	970	
2219	All	995	
6013	Sheet	1000	7
	Rod/Bar	985	
6061	All	985	5
6063	All	985	
6066	All	985	
6951	All	985	9
7049, 7149, 7249	All	875	1, 2
	Forgings	880	2, 4, 8
7050	All Other	890	2, 4, 8
7075	All	870	6
7178	All	870	
7475	Sheet, Plate under 0.500 inch	880	3
	Plate, 0.500 inch and over	890	3

**NOTES:**

1. The aging treatment for 7049, 7149, and 7249 alloys shall not be initiated until at least 48 hours at room temperature have elapsed after quenching.
2. To avoid stress corrosion cracking of thick 7049, 7149, 7249, and 7050 parts, delay between quenching and start of aging should not exceed 72 hours.
3. After normal soaking, increase temperature to 920 °F for alclad and 955 °F for non-clad; minimum soaking time at higher temperature, 15 minutes and 60 minutes, respectively.
4. Solution heat treat temperatures as low as 870 °F may be used to control recrystallization and surface cracking problems.
5. For 6061, an alternate solution heat treating temperature of 995 °F may be used.
6. Rivets, which are to be aged to the T73 temper may be solution heat treated at 875 °F.
7. Should not be solution heat treated after forming because it has a tendency to develop a large grain structure due to recrystallization.
8. Eutectic melting may occur at the specified temperature if the raw material was not properly homogenized or worked.
9. Applies to clad brazing sheet Number (No.) 21 and No. 22 - core is 6951 alloy.



**Table 3-9. Solution Heat Treat Soaking Times for Wrought Aluminum Alloys**

Thickness, Inches (1)	Minimum Soaking Time (2)(3)(4) (Hours:Minutes)	
	Salt/Fluidized Bed	Air Furnace
Up to 0.020, incl	0:10	0:20
Over 0.020 to 0.032	0:15	0:25
Over 0.032 to 0.063	0:20	0:30
Over 0.063 to 0.090	0:25	0:35
Over 0.090 to 0.125	0:30	0:40
Over 0.125 to 0.250	0:35	0:50
Over 0.250 to 0.500	0:45	1:00
Over 0.500 to 1.0	1:00	1:30
Over 1.0 to 1.5	1:30	2:00
Over 1.5 to 2.0	1:45	2:30
Over 2.0 to 2.5	2:00	3:00
Over 2.5 to 3.0	2:15	3:30
Over 3.0 to 3.5	2:30	4:00
Over 3.5 to 4.0	2:45	4:30
Over 4.0	Add 0:15 per 0.500 inch	Add 0:30 per 0.500 inch

Notes:

1. The thickness is the minimum dimension of the heaviest section at the time of heat treatment.
2. For alclad product, the maximum soaking time is 10 minutes longer than the minimum.
3. Minimum soaking times for the second step of 7475 solution heat treatment are 15 minutes for alclad and 60 minutes for non-clad.
4. Soak time for rivets and other small parts in baskets or on moving belts shall either be based on the full thickness of the layer or the heat treater may determine the time required to heat the parts to the soak temperature range by test with load sensors and establish a soak time based on the part thickness using the determined heat up time to soak.

**Table 3-10. Solution Heat Treating Temperatures and Soak Times for Cast Aluminum Alloys**

Alloy	Temperature °F (1)	Minimum Soak Time, Hours (5)	Temper After Solution Heat Treatment	
			After 45 Minimum At Room Temperature	After Appropriate Delay At Room Temperature (6)
201.0	980 (2)	14	W	T4
A201.0	985 (2)	14	W	T4
203.0	1010 (2)	5	W	T4
A206.0	980 (2)	12	W	T4
222.0	945	6	W	T4
242.0	970	2	W	T41
243.0	965	2	W	T41
295.0	955	6	W	T4
296.0	950	4	W	T4
319.0	935	6	W	T4
328.0	960	12	W	T4
333.0	940	2	W	T4
336.0	955	6	W	T45
354.0 (3)	980	10	W	T41
355.0	980	6	W	T4
C355	985	6	W	T4



Table 3-10. Solution Heat Treating Temperatures and Soak Times for Cast Aluminum Alloys - Continued

Alloy	Temperature °F (1)	Minimum Soak Time, Hours (5)	Temper After Solution Heat Treatment	
			After 45 Minimum At Room Temperature	After Appropriate Delay At Room Temperature (6)
356.0	1000 (4)	6	W	T4
A356	1000 (4)	6	W	T4
A357	1010 (4)	8	W	T4
D357	1010 (4)	8	W	T4
358.0 (3)	1005	20	W	T4
359.0	1000	10	W	T4
520.0	810	12	W	T4
712.0	990	2	W	T4

NOTES:

1. Unless otherwise noted, the same temperature and time apply to the other alloy modifications.
2. A step solution treatment at 955 °F, for not less than 2 hours prior to the noted solution treatment, is recommended.
3. For a final temper of T60 (see [Table 3-15](#)) the delay between solution treatment and aging shall be 4 to 6 hours.
4. Final solution heat treatment above 1010 °F may require an intermediate solution heat treatment of 1 hour, minimum, at 1000-1010 °F to prevent eutectic melting of magnesium-rich phases during final solution heat treatment.
5. Once castings have been solution treated for the required time, re-solution treatment time may be shortened to 3 hours, minimum, unless a shorter solution heat treat time is specified above.
6. Appropriate delay at room temperature is determined by hardness and conductivity testing to verify T4 temper. If higher final temper is desired, artificial aging may take place after material is in the W condition.

Table 3-11. Maximum Quench Delay Times

Minimum Thickness, Inches (1)	Maximum Time, Seconds (2)
Up 0.016, Wrought	5
Over 0.016 to 0.031, Wrought	7
Over 0.031 to 0.090, Wrought	10
Over 0.090, Wrought	15
Castings, All	15

NOTES:

1. Minimum thickness is the minimum dimension of the thinnest section of any part in the load.
2. The delay time is measured from the time the furnace door of an air furnace starts to open, or the first portion of the load emerges from a fluidized bed or salt bath or the heating zone of a continuous furnace, to complete immersion of the load in the quenchant.

Table 3-12. Quenching Temperature for Aluminum Forgings and Castings

Forging	Casting	Quenchant	Temperature
2014		Water	150-180 °F
2024, 2219, 6061, 7075		Water	140-160 °F
7049, 7149, 7249, 7050		Water	130-160 °F
	All (1)	Water or Oil	150-212 °F
	520	Oil	300 °F

Notes:

1. Unless otherwise specified.



Table 3-13. Refrigeration Requirements

Alloy	Maximum Delay Time Between Quench And Refrigeration (Minutes)	Maximum Storage Temperature		
		10 °F	0 °F	-10 °F
		Maximum Storage Days		
2XXX	15	1	30	90
All Others	30	7	30	90

Table 3-14. Precipitation Heat Treating (Aging) Process for Wrought Aluminum Alloys

Alloy	Form	Starting Temper (4) (5)	Final Temper (2)	Mand, Pref, or Alternate (1)	1st Step		2nd Step (14) (15)		Notes
					Tem-perature	Time (12)	Tem-perature	Time (12)	
					°F	Hours	°F	Hours	
2XXX	Sheet	AQ, W	T4	M	Room	96			10
	Other	AQ, W	T42	M	Room	96			10
2004	Sheet	T4	T6	M	320	17 to 19			5
2014	Sheet	T3	T6	M	320	18 to 20			5
	All	T4	T6	M	350	8 to 9			5
		T42	T62						
2024	All	AQ, W	T42	M	Room	96			10
2024	Sheet, Plate, Drawn Tube	T3	T81	M	375	12 to 13			
		T351	T851						
		T361	T861	M	375	8 to 9			
		T42	T62	M	375	9 to 12			5
		T42	T72	M	375	16 to 18			5
	Forgings	T4	T62	M	375	12 to 13			5
		T352	T852						
	Wire, Rolled Bar	T351	T851	M	375	12 to 13			
		T4	T6						
	Extruded Bar and Shapes	T351X	T851X	M	375	12 to 13			5
		T4	T6						
		T42	T62						
2098	All	T351X	T851	M	320	17 to 19			
		T42	T62	M	320	17 to 19			5
2124	Plate	T351	T851	M	375	12 to 13			
2219	Alclad Sheet	T42	T62	M	375	17 to 19			5
	Forgings	T42	T62	M	375	25 to 27			5
		T42	T62	M	375	35 to 37			5
	Sheet	T31	T81	M	350	17 to 19			
		T37	T87	M	325	23 to 25			
	Forgings	T352	T852	M	350	17 to 19			
		T4	T6	M	375	25 to 27			5
	Plate	T351	T851	M	350	17 to 19			
		T37	T87	M	325	17 to 19			
	Rivets	T31	T81	M	350	17 to 19			
	Extruded Bar and Shapes	T31	T81	M	375	17 to 19			
		T351X	T851X						
6013	Sheet	AQ, W	T4, T42	M	Room	96			10
		T4, T42	T6, T62	M	375	4 to 5			5



Table 3-14. Precipitation Heat Treating (Aging) Process for Wrought Aluminum Alloys - Continued

Alloy	Form	Starting Temper (4) (5)	Final Temper (2)	Mand, Pref, or Alternate (1)	1st Step		2nd Step (14) (15)		Notes
					Temperature	Time (12)	Temperature	Time (12)	
					°F	Hours	°F	Hours	
6061	All	AQ, W	T4, T42	M	Room	96			10
6063		T4	T6	P	350	8 to 10			5
6066		T42	T62	A	320	18 to 34			5
6951	Sheet (11)	AQ, W	T4, T42	M	Room	96			10
		T4, T42	T6, T62	M	320	17 to 19			5
7049	Extruded Bar and Shapes	W	T73	M	250	23 to 25	330	21 to 22	6, 7, 8
		W	T76	M	250	23 to 25	330	14 to 15	6, 8
7149	Forgings	W	T73	M	250	23 to 25	330	13 to 14	6, 8
7050	Rivets	AQ, W	T73	M	250	4 minimum	355	8 minimum	
	Plate, Extruded Bar and Shapes	AQ, W	T73	M	250	6 to 8	350	11.5 to 12.5	6, 8
	Plate	AQ, W	T76	M	250	6 to 8	350	6.5 to 7	6, 8
	All Except Plate	AQ, W	T76	M	250	6 to 8	350	3.5 to 4.5	6, 8
	All	AQ, W	T74 (9)	M	250	6 to 8	350	6 to 8	6, 8
7075	All	AQ, W	T6, T62	M	250	23 to 25			
	Sheet, Plate	AQ, W	T73	P	225	6 to 7	325	26 to 28	3, 8
				A	250	4 to 5	350	8 to 10	3, 8
			T76	P	225	6 to 7	325	16 to 18	8
				A	250	4 to 6	350	5 to 7	8
	Wire, Rolled Bar, and Forgings	AQ, W	T73	P	225	6 to 7	350	8 to 10	8, 15
				A	250	4 to 5	350	8 to 10	8, 15
			T76	P	250	3 to 4	325	16 to 18	8
				A	225	6 to 7	325	16 to 18	8
	Extruded Bar and Shapes	AQ, W	T73	P	225	6 to 7	350	6 to 8	8
				A	250	4 to 5	350	6 to 8	8
			T76	P	250	3 to 4	320	19 to 21	8
				A	225	6 to 7	320	19 to 21	8
7178	All	AQ, W	T62	M	250	23 to 25			
	Sheet, Plate	AQ, W	T76	P	250	23 to 25	325	16 to 18	8
				A	250	4 to 6	325	16 to 18	8
	Extruded Bar and Shapes	AQ, W	T76	P	250	23 to 25	320	18 to 20	8
				A	250	4 to 6	320	18 to 20	8
7249	Forgings	W	T73	M	250	10 to 12	325	6.5 to 7.5	6, 8
	Extrusions	W	T76	M	250	4 to 28	325	4 to 10	6, 8
7475	Sheet	AQ, W	T61	M	250	3 to 5	315	3 to 3.25	8
		AQ, W	T761	M	250	3 to 5	325	10 to 12	8
	Plate	AQ, W	T6	M	250	23 to 25			
		AQ, W	T76	M	250	3 to 5	325	12 to 18	8
		AQ, W	T73	M	250	3 to 5	325	24 to 30	8

NOTES:

1. (M) Mandatory, (P) Preferred, or (A) Alternate Aging Treatment
2. Digits added to these basic temper designations to denote stress relief treatments, etc. should appear identical before and after aging. T42 and T62 are the technical designations for aging treatment performed by entities other than the original material producer; previously T4 and T6 were sometimes used to designate these final tempers.
3. Either second step age may be used with either first step age interchangeably.



**Table 3-14. Precipitation Heat Treating (Aging) Process for Wrought Aluminum Alloys - Continued**

Alloy	Form	Starting Temper (4) (5)	Final Temper (2)	Mand, Pref, or Alternate (1)	1st Step		2nd Step (14) (15)		Notes
					Tem- perature	Time (12)	Tem- perature	Time (12)	
					°F	Hours	°F	Hours	
<p>4. For all T7XX tempers, the first step of the T7XX age may be omitted if parts (material) are (is) in the T6 temper. <a href="#">Table 3-14</a>. Precipitation Heat Treating (Aging) Process for Wrought Aluminum Alloys (NOTES continued)</p> <p>5. When temper before furnace aging is AQ, W, T4, or T42, the furnace aging treatment may be started immediately after quenching or at any time thereafter. With the exception of 7049, 7149, 7249, and 7249 alloys, natural aging is not necessary before initiating a T6XX or the first step of the T7XX age.</p> <p>6. The aging treatment for 7049, 7149, and 7249 parts shall not be initiated until at least 48 hours after quenching. To avoid stress corrosion cracking of thick 7049, 7149, 7249, and 7050 parts, the elapsed time between quenching and start of aging should not exceed 72 hours.</p> <p>7. 14 to 15 hours if thicker than 2 inches.</p> <p>8. Aging times at the specified second step temperature are permissible to reduce hardness and/or raise conductivity of T7XX parts in order to meet AMS2658 requirements. Additional aging times allowed are as follows:</p> <p>8.1. Additional aging (re-aging) is permitted only for parts which exceed the specified minimum hardness for the alloy and temper by two points HRB or equivalent.</p> <p>8.2. Additional aging (re-aging) shall be performed in cycles of 2 hours minimum plus 0.5 hours for each inch of thickness or fraction thereof in excess of 2 inches. Total re-aging time shall not exceed a total of 4 additional hours except that 6 additional hours for 7050 forgings thinner than 0.260 inches are allowed.</p> <p>8.3. Additional aging (re-aging) cycles shall meet all applicable specification requirements and shall be documented as part of the production records. Applicable hardness and conductivity tests shall be performed to verify compliance with AMS2770, Paragraph 4.4. Parts Control, after each aging cycle.</p> <p>8.4. Additional aging (re-aging) temperatures for specific alloys shall conform to the second step age requirements of <a href="#">Table 3-14</a>.</p> <p>8.5. Uninterrupted aging time may be used when additional aging time has been previously demonstrated. Total aging time shall not exceed aging time from <a href="#">Table 3-14</a> plus additional aging time in note 8.2.</p> <p>9. Formerly designated T736.</p> <p>10. T4 and T42 are achieved when hardness and conductivity values are met. Typically, this is achieved within 96 hours at room temperature.</p> <p>11. Applies to clad brazing sheet No. 21 and No. 22 - core is 6951 alloy.</p> <p>12. All soaking times, except those for 7050 alloy and those referencing note 7, are for product or nested stacks up to 0.5 inch thickness (minimum dimension at heaviest section). Add 0.5 hours to times for each additional 0.5 inch or fraction thereof. Soaking times shown are applicable to all thicknesses of 7050 alloy. When using load Thermocouples (TCs) to measure aging time, the soaking times for the 0.5 inch product shall apply.</p> <p>13. Aging temperatures and times for stress relieved tempers TX5, TX51, TX51X, and TX52 shall be the same as the basic temperatures.</p> <p>14. The second step aging process may be conducted in a continuous operation after the first step or the parts may be cooled to room temperature and then perform the second step.</p> <p>15. For forgings over 3.0 inch thick second step aging time is 6-10 hours.</p>									

**Table 3-15. Precipitation Heat Treating (Aging) Process for Cast Aluminum Alloys**

Alloy	Starting Temper	Final Temper	Set Temperature °F (1)	Soak Time, Hours (1)(2)
201.0	W or T4	T7	370	5 minimum
A201.0				
203.0	W or T4	T6	425	16 minimum
A206.0				
222.0	W or T4	T61	390	4 minimum
242.0				
242.0	F (as cast)	T571	335	22-26
242.0 (Sand)	W or T4	T61	450	2-3



Table 3-15. Precipitation Heat Treating (Aging) Process for Cast Aluminum Alloys - Continued

Alloy	Starting Temper	Final Temper	Set Temperature °F (1)	Soak Time, Hours (1)(2)
242.0 (Perm Mold)	W or T4	T61	400	3-5
243.0	W or T41	T61	425	2-3
295.0	W or T4	T62	310	12-20
296.0	W or T4	T6	310	2-8
319.0	W or T4	T6	310	2-6
328.0	W or T4	T6	310	2-5
333.0	F (as cast)	T5	400	7-9
333.0	W or T4	T6	310	2-5
333.0	W or T4	T7	500	4-6
336.0	W or T45	T65	340	14-18
354.0	W or T41	T61	310	10-12
354.0	W or T41	T62	340	6-10
355.0	W or T4	T6	310	2-6
355.0	W or T4	T61	310	6-10
355.0	W or T4	T7	440	3-5
355.0	W or T4	T71	475	3-6
C355.0	W or T4	T6	310	3-6
C355.0	W or T4	T61	310	10-12
356.0	F (as cast)	T51	440	6-12
356.0	W or T4	T6	310	1-6
356.0	W or T4	T7	400	3-6
356.0	W or T4	T71	475	3 minimum
A356.0	W or T4	T6	310	2-6
A356.0	W or T4	T61	310	6-10
A356.0	W or T4	T71	475	3-6
A357.0	W or T4	T61	320	6-10
A357.0	W or T4	T6	320	2-12
D357.0	W or T4	T6	320	2-12
358.0	W or T4	T6	325	2-8
358.0	W	T60 (3)	330	2-4
359.0	W or T4	T61	310	8-12
359.0	W or T4	T62	340	6-10
705.0	F (as cast)	T5	210	10 minimum
707.0	F (as cast)	T5	310	3-5
712.0	F (as cast)	T5	355	9-11
713.0	F (as cast)	T5	250	16 minimum
850.0				5 minimum
851.0	F (as cast)	T5	430	7-9
852.0				

NOTES:

1. Unless otherwise noted, the same temperature and time may be used for the aother alloy modifications to arrive at the same temper. Ex., A357.0, B357.0, C357.0, D357.0, etc.
2. Soak times are recommendations that produce the desired temper with a high rate of accuracy. Other times may be required depending upon casting configuration and property requirements.
3. See [Table 3-10](#) for delay between solution heat treating and aging.



**Table 3-16. Annealing - Wrought Aluminum Alloys**

Alloy	Full Anneal			Partial Anneal (Stress Relief ) (5)		
	Temperature °F (1)	Soak Time, Hours (2)	Cooling Medium	Temperature °F (1)	Soak Time, Hours (2)	Cooling Medium
1100	630-660	0.5	Air			
5052						
3003	720-770	0.5	Air	630-660	0.5	Air
2XXX	750-800	1	Furnace (3) or			
6XXX			(4)			
7XXX	750-800	2	Furnace (4)			

**NOTES:**

- Any temperature within the set temperature range may be used.
- Soak times listed are for up to 0.5 inch maximum thickness. Add 0.5 hour for each additional 0.5 inch of product or nested stack thickness of fraction thereof over 0.5 inch.
- Furnace cool at 50 °F per hour, maximum, to 500 °F. Air cool to room temperature.
- Furnace cool at 50 °F per hour, maximum, to 450 °F. Hold at 450 °F for 6 hours. Furnace or air cool to room temperature.
- Prior to solution heat treatment, in-process parts needing additional forming operations or needing control of grain size may receive an interim stress relief treatment in a controlled temperature liquid bath per AMS2750 as an alternate to a furnace stress relief. The temperature shall not be less than 645 °F and shall not exceed the solution heat treating temperature for the alloy being processed. Immersion time shall not exceed 10 minutes.

**Table 3-17. Annealing - Cast Aluminum Alloys**

Alloy	Temperature °F	Soak Time, Hours (1)	Cooling Medium
200 Series	800	1	Air
300 Series	825	1	Air
500 Series	725	5	Air

**NOTE:**

- Soak times listed are for sections up to 0.5 inch maximum thickness. Add 0.5 hour for each additional 0.5 inch of product or nested stack thickness or fraction thereof.

**Table 3-18. Re-Solution Heat Treatment of Alclad Alloys**

Thickness, Inches (1)	Number Of Solution Heat Treats, Maximum (2)
Under 0.020	0
0.020 to 0.125	1
Over 0.125	2

**Notes:**

- The thickness is the minimum dimension of the heaviest section at the time of heat treatment.
- In addition to any performed by the raw material producer. Annealing and precipitation treatments are not considered solution heat treatments.

### 3.13 HEAT TREATING EQUIPMENT.

In order to properly heat treat aerospace metals, you will need thermal processing equipment capable of precisely and uniformly controlling temperature, and independent temperature measuring equipment to perform system checks in between PMEL calibration intervals. The thermal processing equipment used in the heat treatment of metals is divided into two distinct groups. They are liquid baths and atmosphere ovens. Both groups are heated by gas, electricity or oil, and have certain advantages over the other. It is generally advisable to weigh the advantages, disadvantages, and consider environmental impacts and safety conditions before deciding on one. Regardless of the method utilized it must be demonstrated that heat treated material is not degraded by the process and satisfactory results are obtained. Additionally, independent test instrumen-



tation/temperature measuring devices, also called field test instruments, come in many configurations and accuracy levels. A substantial amount of the difficulties encountered in heating aluminum alloys is due to improper or inadequate temperature control and circulation of the heating medium. When difficulties arise, the function of these systems should be checked prior to performing other system checks. Basic heat treatment equipment requirements are detailed below.

### 3.13.1 Air Furnaces/Ovens.

#### **NOTE**

SAE-AMS-2750, Pyrometry, is the control document for equipment used to heat treat aerospace materials. AMS-2750 covers temperature sensors, instrumentation, system accuracy tests, and Temperature Uniformity Surveys (TUS). For a complete description of pyrometry requirements for heat treating equipment, refer to the latest issue of SAE-AMS-2750. In case of conflict with this manual, the discrepancy will be negotiated with the responsible technical/engineering activity for resolution and updating.

The term furnace and oven are interchangeable terms when talking about heat treating equipment. Generally, furnaces operate at higher temperatures and ovens operate at lower temperatures. Air furnaces/ovens are ideal for precipitation (aging), thermal treatments and annealing. These furnaces are also very good for solution heat treating. The initial cost of these type furnaces is higher than for the salt bath types, but they are usually safer, cleaner, more flexible, and more economical to operate. If gas or oil fired, the products of combustion must be excluded from the furnace atmosphere to help avoid high temp oxidation and atmosphere contamination. This is not an issue with electric furnaces and ovens, however, if the atmosphere is intentionally altered or inerted, care must be taken when the operator off-gasses the chamber prior to part removal. Air furnaces also come in two forms with regards to air movement inside the heating chamber; still air and recirculating air (convection). The still air type is capable of achieving higher temperatures than the circulating air type, but it also suffers greater temperature uniformity variances. Still air furnaces are generally designed to operate above 1000 °F and are better suited for ferrous alloy heat treating operations. The circulating air furnace is ideal for aluminum heat treat operations as it is generally capable, depending on build quality and process controls, of holding very tight temperature uniformity as a result of the convection process. The primary limitation of this type of furnace is the maximum effective operating temperature of around 1200 °F.

3.13.1.1 The Air Force shall utilize convection or recirculating ovens for heat treatment of aluminum alloys used on aircraft. The Navy may use still air ovens, provided they meet the requirements outlined in [Paragraph 3.13.1.2](#). The heated air in this type furnace is recirculated at high velocities to obtain a rapid heating cycle and uniform temperatures. The ideal set up for an aerospace maintenance facility that performs solution and precipitation heat treatment is a dual chamber oven with both chambers capable of independent operation and circulating air, or two separate circulating air ovens. This set up helps reduce overall heat treat time by eliminating the wait time required for equipment to stabilize at different temperatures for various heat treat processes.

3.13.1.2 Ovens used for solution and precipitation heat treatments of aircraft parts shall be a minimum of class 2, capable of maintaining  $\pm 10$  °F temperature uniformity with Type D controlling, monitoring, and recording instrumentation. Electrical heating elements and radiant tubes must be shielded to prevent direct radiant heat exposure to parts. These ovens can also be inherently used for annealing and stress relieving. See [Table 3-19](#) and [Table 3-21](#) for other aluminum heat treat process temperature uniformity and instrumentation requirements. Aircraft Metals Technology shops shall refer to JEDMICS Drawing 202432237 (CAGE 98752) Equipment Qualified Product List for selections of heat treating furnaces which has been approved by the AF Metal Fabrication and Technologies Office (MFTO). Heat treating furnaces shall be procured through the use of Commercial Item Description (CID) A-A-60033. CID A-A-60033 can be viewed at <https://assistca.dla.mil>.

3.13.2 **Salt Bath Furnace.** The salt bath method has certain advantages over the air furnace. However, the advantages are usually confined to solution heat treatment only. Associated advantages are uniform temperature without excess danger of high temperature oxidation and more efficient heat transfer which reduces the time required to bring the load to temperature. This method is adaptable for solution heat treating varying part thickness and complex shapes. The above advantages may be completely nullified by the slower quench caused by the necessary arrangement of equipment, molten liquid burn hazards, explosion hazards, increased hazmat footprint, and decomposition of the sodium nitrate which when dissolved in quenching water forms a compound that attacks aluminum alloys.

3.13.2.1 Salt baths must be operated with caution to prevent explosions or spatter as any water on the material being treated is instantly transformed to steam upon immersion in the salt bath.

3.13.2.2 Hollow core castings or wrought machined parts where the salts are likely to be difficult or impossible to remove shall not be heat treated in a salt bath.



3.13.2.3 Nitrate charged salt baths should not be used to heat-treat aluminum alloys types 5056 and 220 due to the fact that the bath compounds will attack the alloy.


3.13.3 **Field Test Instruments.** Field test instruments are used in conjunction with TCs to measure the operating temperature inside the oven chamber. They are used to monitor load TCs, perform System Accuracy Tests (SAT), and TUS. They range from hand held single input units to suitcase style multi-input units. Many modern units come with software to log and record data. Field test instruments used to perform SATs and monitor load TC shall have a minimum of 1 input channel, a calibration accuracy of  $\pm 1$  °F or  $\pm 0.1$  percent of the reading, whichever is greater, and the ability to log/record data. Field test instruments used to perform TUSs shall have a minimum of 9 input channels, a calibration accuracy of  $\pm 1$  °F or  $\pm 0.1$  percent of the reading, whichever is greater, and the ability to log/record data. National Stock Number (NSN) 6625-01-649-1136 is an example of a multi-point field test unit that logs data and can be used for multiple heat treatment process test, measuring, and recording applications such as SATs and TUSs.

3.13.4 **Controlling, Monitoring, and Recording Equipment.** Instrumentation type for controlling, monitoring, and recording equipment is broken down into five categories. Each category is based on how many controlling, monitoring, and recording TCs are operational in an oven chamber. The most common instrumentation type is Type D. Oven controllers, monitoring, and process recording equipment shall be digital and have a calibration accuracy of  $\pm 2$  °F or 0.2 percent of the reading, whichever is greater. Field test instruments can temporarily be used as monitoring/recording equipment to monitor and record heat treatment processes when on-board oven equipment is inoperable or non-digital, ie; paper chart recorders. See [Table 3-21](#) for oven instrumentation types.

3.13.5 **TC.** A TC is a thermoelectric device used to accurately measure temperatures. TCs consist of a wire with two leads of dissimilar metal. The leads are joined at one end by welding or tightly twisting the ends together. Heating the joint produces an electric current. This current is converted to a temperature reading with a field test instrument or other TC monitoring unit.

3.13.5.1 TCs may be purchased individually or as a spool and constructed to form a measuring junction. The measuring junction, i.e. hot junction, can be formed by welding or twisting the TC wire elements together. Welded TCs ([Figure 3-2](#)) are less prone to problems and should be used when available. Twisted TCs ([Figure 3-3](#)) do not form as reliable a junction as a welded TC and their reliability decreases with repeated use. If necessary, a twisted TC may be made by overlapping the bare ends of the two TC wires 1/4 inch and at 90 degrees to each other. Tightly twist the wire four to five times and cut off the excess wire; safety wire pliers are an ideal tool for producing a tight twist. The temperature reading will be measured at the twist closest to the field test instrument.


3.13.5.2 The most common type of TC used in SATs, TUSs, and load TC monitoring is Type K base metal expendable with a high temperature insulation, such as Silica or Nextel fiber. TCs that are insulated with either fiberglass, plastic, hard fired ceramic beads, or metal over braid are classified as base metal Expendable TCs. Certain ovens such as the Delta-H brand, require the use of a Type K thermocouple that is shielded from the process atmosphere by either a closed metal or ceramic protective tube. Those type of thermocouples are classified as Base Metal Non-Expendable TCs. See [Paragraph 3.13.5.4.1](#) and [Paragraph 3.13.5.4.2](#) regarding re-use limits for Base Metal Expendable/Non-Expendable TCs. Type K TCs are nickel based. The wire color coding conforms to ANSI MC 96.1. The positive (+) lead is nickel-chromium (Nickel-Chromium) and has yellow insulation. The negative (-) lead is nickel-aluminum (Nickel-Aluminum) and has red insulation. In some cases, TCs are required to be within a specified range of length to ensure their accuracy; consult the temperature monitoring equipment owner's manual for guidance. If no guidance exists, TCs should be between 10 and 50 feet long. See [Table 3-20](#) for more information about base metal TCs.

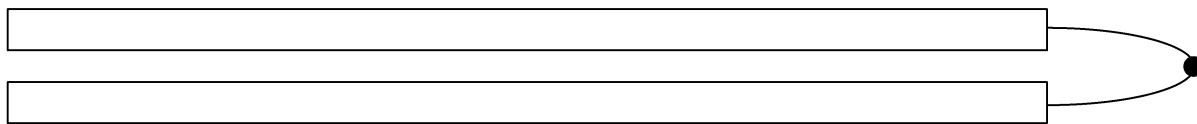

TO-1-1A-9-009

**Figure 3-2. Welded Thermocouple Wire**



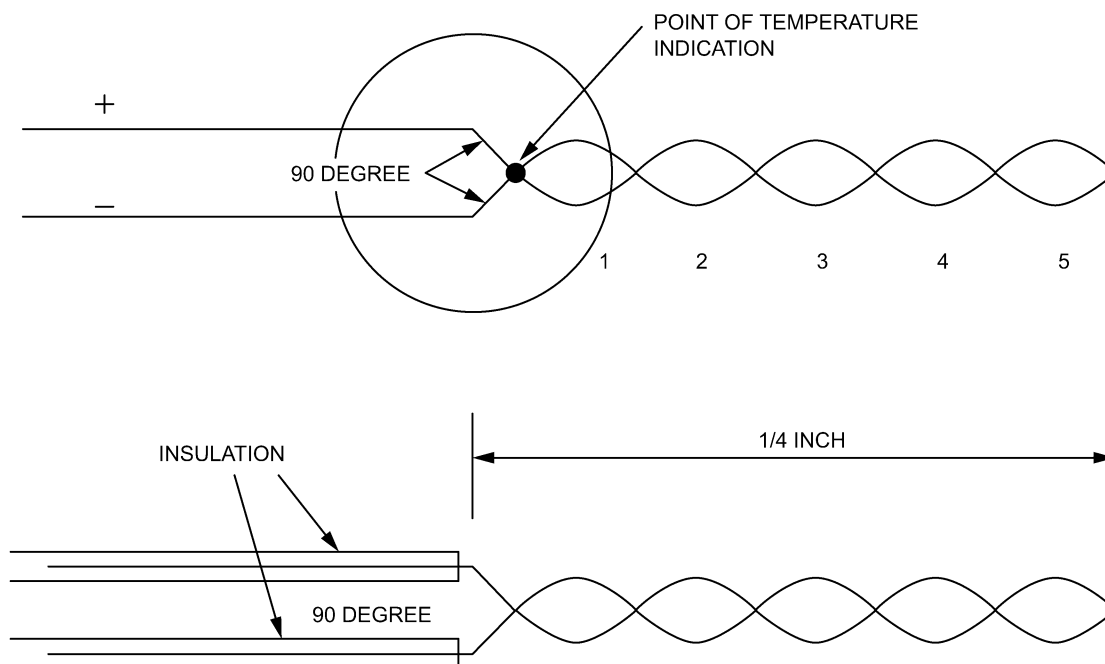

TO-1-1A-9-010

**Figure 3-3. Twisted Thermocouple Wire**

**3.13.5.3 Inspection, Prior to Use.** Perform the following inspection steps prior to each use:

- a. Inspect the junction for breaks or looseness. If the TC junction is questionable, test for continuity with a thermocouple tester or multi-meter to measure the resistance between the two ends on the connector plug or bare wire ends; if the resistance is greater than 1 ohm ( $\Omega$ ), repair or replace as necessary.
- b. Inspect insulation for tears or abrasions that expose bare wire. If bare wire is exposed, trim or replace TC as necessary.
- c. Ensure TCs are compatible with the units reading them (e.g., a Type-k thermocouple should be attached to a Type-k monitoring unit). The monitor should be as close as practical to the end of the TC. For standard 24-gauge wire, the distance shall not exceed 100 feet. Distances greater than 100 feet can produce incorrect readings.
- d. Plug the TCs into the monitor and ensure they read ambient temperature. If your hands are warmer than the ambient temperature, place each TC tip between your fingers and observe the temperature rise. If it does not respond properly, replace the TC.

**3.13.5.4 TC usage shall be tracked and documented.** A simple method is a tag attached to the TC or set of TCs, near the cold junction, that can be annotated with each use. A “use” is defined as one cycle of heating and cooling.

**3.13.5.4.1** Base metal expendable TCs used solely for SAT and TUS below 1200 °F and is not damaged can be reused up to 5 times or 3 months, whichever comes first. TC used above 1200 °F shall be limited to a single use. For base metal non-expendable TC’s, there are no reuse limits provided that the metal or ceramic protective tube is not damaged. If the protective tube is damaged, the entire non-expendable TC shall be replaced.

**3.13.5.4.2** Base metal expendable TCs used for load monitoring below 500 °F may be used for up to 90 calendar days after first use or for no more than 10 uses, whichever comes first. Load TCs used between 500-1200 °F shall be limited to 90 calendar days or five uses, whichever comes first. Load TCs used above 1200 °F are limited to one use.

**3.13.5.5** Thermocouple calibration and accuracy. TCs that are to be used with calibrated indicators do not require calibration, other than manufacture’s calibration, if they bear the designation E, J, K, R, S, or T. These designations show that the thermocouple or wire has been manufactured in accordance with one or more of the following standards for the wire type



indicated, ANSI/MC96.1, BS 1843, DIN 43714, JIS C 1610-1981 or NF C 42-323. Thermocouple wires manufactured to these specifications have been certified by the manufacturer and do not require special initial or subsequent calibration.

3.13.5.5.1 TCs must be supplied with the manufacturer's initial calibration certificate or deviation limits certification. The calibration or deviation limits supplied with each individual TC or TC spool must be entered into to the field test instrument for proper temperature offset and indication each time TCs are changed or replaced.

3.13.5.5.2 Maximum allowable error for TUS, load, and SAT TCs are  $\pm 2$  °F.

### 3.14 TEMPERATURE CONTROL AND UNIFORMITY TESTING.

Precise temperature control is essential to produce the exact material properties and temper requirements necessary for modern aviation manufacturing and maintenance. Periodic surveys and tests of the internal chamber temperatures must be conducted, documented and compared to the set point temperatures of the oven/furnace controller to ensure accurate equipment operation. The two methods used to ensure accurate operation of heat treating equipment are the SAT and the TUS. The SAT is a quick and simple user test to ensure the oven temperature remains accurate in between TUSs. The TUS is a more thorough user test to ensure temperature accuracy and uniformity in the entire oven chamber as compared to the oven control sensor and SAT. These two tests work in conjunction with each other as a checks and balance system to ensure accurate and uniform oven operation. If one is accurate and the other is not, that is a sign that your oven needs troubleshooting or maintenance to correct a deficiency.

3.14.1 System Accuracy Test (SAT). A SAT is performed to assess the accuracy of the heat treat oven's resident thermocouple and controller. This is done through the use of an independently calibrated field test instrument and thermocouple. By placing the test thermocouple within 3 inches of the resident thermocouple and taking a reading with the field test instrument, the accuracy of the oven's controller and resident thermocouple is validated. If the difference between the field test instrument and the oven controller is greater than  $\pm 3$  °F, then that is an indication of required maintenance or adjustment of the oven, oven controller, and/or resident thermocouple.

3.14.1.1 A SAT shall be performed and documented using a field test instrument that meets the requirements of [Paragraph 3.13.3](#) and a TC that meets the requirements of [Paragraph 3.13.5.5.2](#), on each oven chamber used to perform aluminum heat treating, at the following intervals/situations:

- a. Initial. Upon initial oven installation, prior to first operational use.
- b. Periodic. SAT frequency is based on frequency of aluminum heat treating operations and oven instrumentation type. See [Table 3-21](#) for instrumentation types.
  - (1) Shops that perform daily heat treating operations, utilizing Type D instrumentation, shall perform SATs on a weekly basis, not to exceed 7 calendar days. If utilizing Type B or Type C instrumentation, the SAT interval may be extended to biweekly, not to exceed 14 calendar days.
  - (2) Shops performing weekly to biweekly heat treating operations, every 5 to 14 calendar days, utilizing Type D instrumentation, shall perform SATs on a biweekly basis, not to exceed 14 calendar days. If utilizing Type B or Type C instrumentation, the SAT interval may be extended to monthly, not to exceed 31 calendar days.
  - (3) Shops performing biweekly to monthly heat treating operations, every 15 to 30 calendar days, utilizing Type D instrumentation, shall perform SATs on a monthly basis, not to exceed 31 calendar days. Use of Type B or Type C instrumentation is recommended, but the SAT interval will not be extended.
  - (4) Shops performing heat treating operations less frequent than every 30 calendar days, regardless of instrument type, will perform a SAT prior to use/heat treating operation.
  - (5) If utilizing Type A instrumentation, refer to AMS2750 for SAT interval.
- c. After any maintenance to the oven, ie; replacement of a sensor/TC, heating element, or controlling, monitoring, or recording instrument.
- d. Recalibration of the controlling, monitoring, or recording instrument, or when parameter/rheostat adjustments have been made.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

3.14.1.2 SAT Procedure: A successful SAT reading must be within  $\pm 3$  °F of oven controller set-point.

- a. Set oven controller to 300-500 °F and allow to stabilize. If oven has a dedicated SAT port, higher temperatures can be tested.
- b. Insert TC into oven with tip (measuring junction) as close to practical to the controlling, monitoring, or recording sensor tip. The tip to tip distance shall not exceed 3 inches.
- c. Allow oven to recover, not to exceed 20 minutes.
- d. Record temperature reading.
- e. Document and file report.

3.14.1.3 SAT Report Requirements: A paper or digital copy of the completed record shall be retained for 3 years by the facility performing the SAT and disposed of in accordance with Air Force Records Disposition Schedule Table 21-06 Rule 35.00. The report will contain, at a minimum:

1. Identification of oven/sensor (if multi-zone) being tested.
2. Date and time of the test.
3. Identification of the test sensor.
4. Test sensor correction factors.
5. Identification of the test instrument.
6. Identification of test instrument correction factors.
7. Set point of oven during the test.
8. Observed oven controller instrument reading.
9. Observed test instrument reading.
10. Corrected test instrument reading [will be same as (i) if (d) and (f) are programmed into test unit, if not,  $(j = i + d + f)$ ].
11. Calculated system accuracy difference  $(k = h - j)$ .
12. Indication of test pass or fail.
13. Identification of technician performing test.
14. Identification of supervisor performing review.

3.14.1.4 If SAT failure occurs, corrective action may include, but is not limited to replacement of the out of tolerance sensor, rheostat adjustment, or recalibration of the out of tolerance instrument/controller. After any corrective actions, a SAT must be performed prior to any production heat treatments in accordance with [Paragraph 3.14.1.1](#).

3.14.1.5 Modification Offset. Manual modification offset of the control instrument to facilitate desired chamber temperatures based on most recent SAT results are not permitted.

3.14.2 TUS. A TUS is performed to ensure an oven chamber's operating temperature is accurate and uniform, within given tolerance standards, throughout the entire volume or qualified work zone in relation to the oven set point. This is done through the use of an independently calibrated field test instrument (multi-point data logger) and multiple TC all simultaneously measuring temperature from multiple points in the oven chamber over a period of at least 30 minutes.



3.14.2.1 A TUS shall be performed and documented using a field test instrument that meets the requirements of [Paragraph 3.13.3](#) and a TC that meets the requirements of [Paragraph 3.13.5.5.2](#), on each oven chamber used to perform aluminum heat treating, at the following intervals/situations:

- a. Upon initial oven installation, prior to first operational use. See [Paragraph 3.14.2.2](#).
- b. Periodically. See [Paragraph 3.14.2.3](#).
- c. Annually. See [Paragraph 3.14.2.4](#).
- d. After any maintenance to the oven, ie; replacement of a sensor/TC, heating element, controlling, monitoring, or recording instrument, airflow pattern/velocity, replacement of refractory material.
- e. Recalibration of the controlling, monitoring, or recording instrument, or when parameter/rheostat adjustments have been made.
- f. Work zone volume increase, larger than previously qualified area.
- g. Work zone location change, outside of previously qualified area.

3.14.2.2 Initial TUS Requirement. Initial survey temperatures shall be the minimum and maximum temperatures of the qualified operating temperature range. Additional temperatures shall be added as required to ensure that no two adjacent survey temperatures are greater than 600 °F apart. For example, if an oven operating range is 200-1200 °F, then survey temps of 200 °F, 700 °F, and 1200 °F would meet this requirement.

3.14.2.3 Periodic TUS Requirement. For single operating ranges greater than 600 °F, TUS temperatures shall be selected so that one temperature is within 300 °F of the minimum and another temperature is within 300 °F of the maximum qualified operating range and there is no more than 600 °F in between. For example, if an oven operating range is 200-1200 °F, then the oven must be surveyed anywhere between 200-500 °F and again between 900-1200 °F, and the selected temperatures must not be more than 600 °F apart. For example, periodic TUSs conducted at temperatures of 375 °F and 925 °F would meet this requirement. Periodic TUS frequency is based on frequency of heat treating operations.

- a. Shops performing daily heat treating operations, utilizing Type D instrumentation, shall perform TUSs on a monthly basis, not to exceed 31 calendar days. After eight consecutive passing TUSs, the interval may be extended to bimonthly, not to exceed 61 calendar days. If utilizing Type B or Type C instrumentation, after 4 consecutive passing TUSs, the interval may be extended to quarterly, not to exceed 91 calendar days.
- b. Shops performing weekly heat treating operations, every 5 to 14 calendar days, utilizing Type D instrumentation, shall perform TUSs on a bimonthly basis, not to exceed 61 calendar days. After eight consecutive passing TUSs, the interval may be extended to quarterly, not to exceed 91 calendar days. If utilizing Type B or Type C instrumentation, after 4 consecutive passing TUSs, the interval may be extended to quarterly, not to exceed 91 calendar days.
- c. Shops performing biweekly to monthly heat treating operations, every 15 to 30 calendar days or less frequently, shall perform TUSs on a quarterly basis, not to exceed 91 calendar days regardless of instrumentation type used. Use of Type B or Type C instrumentation is recommended, but the SAT interval will not be extended.
- d. If at any time a TUS fails, the interval resorts back to standard and the count starts again.
- e. If utilizing Type A instrumentation, refer to AMS2750 for TUS interval.

3.14.2.4 Annual TUS Requirement. In addition to the periodic test requirement, at least once per year, not to exceed 365 calendar days, surveys shall also be performed at the minimum and maximum of the qualified operating temperature range. Additional temperatures shall be added as required to ensure that no two adjacent survey temperatures are greater than 600 °F apart. For example, if an oven operating range is 200-1200 °F, then survey temps of 200 °F, 700 °F, and 1200 °F would meet this requirement.



**3.14.3 TUS Procedure.**

**NOTE**

If, for any reason, a TUS cannot be performed, load thermocouple monitoring shall be used for all aircraft heat treating operations, not to exceed two periodic TUS cycles. If a TUS still cannot be performed after two periodic TUS cycles have elapsed, consult the responsible technical/engineering activity for aircraft heat treating process authorization.

During each TUS, the survey parameters shall reflect the normal operation of the equipment used in production. That is, if normal procedure is to load parts into a temperature stabilized oven, then the survey shall be initiated by placing the rack with TCs into an oven stabilized at the survey temperature. Common TUS procedure would be to bring the oven to desired set point, allow to stabilize, load survey rack with TCs into chamber, begin capturing data on data logger, allow oven to recover, mark official start TUS, allow TUS to run for at least 30 minutes, terminate TUS and data capture, interpret results, generate and file report.

**3.14.3.1 Number of Required Thermocouples.** The number of required sensors varies based on volume of the oven chamber to be surveyed. If the oven chamber volume is less than:

- a. 3 cubic feet, 5 sensors are required.
- b. 225 cubic feet, 9 sensors are required.
- c. 300 cubic feet, 14 sensors are required.
- d. 400 cubic feet, 16 sensors are required.
- e. 600 cubic feet, 19 sensors are required.
- f. Chamber volumes 600 cubic feet or more, refer to AMS2750.

**3.14.3.2 Location of TUS Sensors.** Sensor location varies based on the volume of the chamber.

- a. Volumes less than 3 cubic feet, four sensors shall be located at the lower four corners and the fifth sensor shall be placed in the center. TUS sensors shall be placed to best represent the qualified work zone.
- b. Volumes of 3 to 225 cubic feet shall have a sensor placed at each of the eight corners and the ninth sensor shall be placed in the center. TUS sensors shall be placed to best represent the qualified work zone.
- c. Volumes greater than 225 cubic feet, sensor placement shall be the same as indicated in [Step b](#) with the additional required sensors in [Paragraph 3.14.3.1](#) uniformly distributed to best represent the qualified working zone.

**3.14.3.3 Qualified Working Zone.** A qualified work zone is the defined portion of the oven/furnace volume where temperature variation conforms to the required uniformity tolerance. If an entire oven chamber cannot meet TUS standards, then it is acceptable to perform a TUS and qualify a working zone. The qualified work zone can be any location in the oven/furnace the operator chooses. The qualified work zone location and volume tested shall be such that no heat treated material extends beyond the defined/qualified work zone boundaries. If the qualified work zone changes, for example if a part or material to be heat treated will not fit inside the currently qualified work zone boundaries, a TUS of the new required zone/volume shall be performed prior to material heat treatment.

**3.14.3.4 TUS Data Collection.** Data collection begins once the rack is inserted into the oven chamber and the door is closed. TUS sensors shall record temperature data from all sensors at a frequency of at least once every two minutes for the duration of the survey.

**3.14.3.4.1** Secure all TCs to the rack in the specified location based on chamber volume. Connect all TCs to the data logger. Ensure data logger is on and ready to capture data.

**3.14.3.4.2** Insert TUS rack into oven chamber and begin logging the recovery process. Oven recovery time is defined as the amount of time required from the time the door is closed for all test TCs to report within  $\pm 10$  °F, or as applicable for the



process being performed, of the temperature set point. At no time shall any test, control, or recording sensor exceed the upper temperature uniformity tolerance. Oven recovery time for aluminum solution heat treating and aging TUSs shall not exceed the following:

- a. Ovens tested without a load, 20 minutes.
- b. Ovens tested with a load, 40 minutes.

3.14.3.4.3 Upon successful oven recovery, mark official TUS start time and run survey for a minimum of 30 minutes. For TUSs with 9 or less TCs, sensor or recording instrument failures are not permitted. A temporary condition such as a short or loose connection where normal temperature readout is restored shall not be considered a failed sensor. Surveys with 10 or more sensors are permitted sensor failures provided they are not in any corner and meet the following conditions:

- a. Survey with 10 to 16 sensors: 1 failure
- b. Survey with 17 to 23 sensors: 2 failures
- c. No adjacent sensor failures
- d. Surveys with 24 or more sensors, see AMS2750

3.14.3.4.4 After a minimum of 30 minutes have elapsed, conclude the TUS and remove the rack/sensors. Interpret the data, and generate/file the report.

3.14.4 Temperature Uniformity Pass/Fail Requirements. A survey shall be considered passing if all the following requirements are met.

- a. Control or monitoring sensor readings and TUS sensor readings did not exceed applicable positive temperature tolerance at any time. See [Table 3-19](#) for Temperature Uniformity Allowances.
- b. The time required to achieve recovery, stabilization, and maintain set point temperature tolerances did not exceed the time limit specified in [Paragraph 3.14.3.4.2](#).
- c. All readings of control/monitor and TUS sensor readings are within the temperature tolerance requirements of [Table 3-19](#) for the process being surveyed after the official start of TUS survey time except as allowed in [Paragraph 3.14.3.4.3](#).
- d. TUS sensor data was logged for each sensor at a frequency not greater than every two minutes.
- e. TUS is run for the minimum required time of 30 minutes.

3.14.5 TUS Data and TUS Reports. TUS data must be gathered and recorded on a system that creates electronic records that cannot be altered without detection.

3.14.5.1 The TUS system software and playback utilities shall provide a means of examining and/or compiling the record data, but shall not provide any means of altering the source data. The system shall be capable of providing evidence the record was reviewed, such as by recording an electronic review or a method of printing the record for a physical marking to indicate a review.

3.14.5.2 TUS Survey Report Requirements. A paper or digital copy of the completed record shall be retained for 3 years by the facility performing the TUS and disposed of in accordance with Air Force Records Disposition Schedule Table 21-06 Rule 35.00. The report will contain, at a minimum:

- a. Oven identification name or serial number.
- b. Survey temperature.
- c. Required temperature uniformity.
- d. Oven chamber dimensions or qualified working zone dimensions and location in chamber.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

- e. TUS sensor and location identification including a detailed diagram, description or photograph of any load or rack used.
- f. Time and temperature data from all TUS sensors.
- g. TC spool correction factor or correction factors for each TUS sensor at each calibration temperature.
- h. Corrected or uncorrected readings of all TUS sensors. Reading shall be identified as corrected or uncorrected.
- i. As found and as left TUS offsets (if used in production).
- j. Survey start date and time.
- k. Survey end date and time.
- l. Survey test instrument identification or serial number.
- m. Survey test instrument calibration agency.
- n. Survey test instrument calibration date.
- o. Survey test sensor failures, if any.
- p. Indication of test pass or fail.
- q. Identification of technician performing survey.
- r. Identification of supervisor approving survey.

**3.14.6 Failed TUS Procedures.** If the temperature uniformity is not within the tolerances of [Table 3-19](#), the cause of the deviation shall be determined, documented, and corrected. The equipment shall not be used for additional processing until the deviation has been corrected and the TUS has been performed successfully.

**3.14.6.1** For ovens being tested at an extended interval, failure of a TUS shall cause the extended TUS interval to revert back to the standard periodic interval as applicable in [Paragraph 3.14.2.3](#).

**3.14.6.2 Modification Offset.** Manual modification offset of the control instrument to facilitate the desired chamber temperature based on the most recent TUS results are permissible, provided it does not exceed  $\pm 5$  °F. Temperature offsets shall be documented, approved/signed by the section supervisor or Non Commissioned Officer in Charge (NCOIC), and used in production heat treatments, i.e. controller is offset to 380 °F to obtain accurate uniform internal chamber temperature uniformity of  $375 \pm 10$  °F, controller is offset to 916 °F to obtain accurate uniform internal chamber temperature uniformity of  $920 \pm 10$  °F, etc. The signed temperature offset chart shall be posted next to the furnace controller or a similar location where the operator will see it and not overlook it. Temperature offsets greater than  $\pm 5$  °F shall be troubleshoot and corrected by a qualified technician within 90 days.

**Table 3-19. Temperature Uniformity Allowance for Heat Treat Operations**

Process	Alloy	Uniformity Allowance	Notes
Solution Heat Treating	Aluminum, All	Class 2 ( $\pm 10$ °F)	1
Aging	Aluminum, All	Class 2 ( $\pm 10$ °F)	
Annealing	Aluminum, All	Class 5 ( $\pm 25$ °F)	
Stress Relieving	Aluminum, All	Class 5 ( $\pm 25$ °F)	
Hardening/Solution Heat Treating	Steel, All	Class 5 ( $\pm 25$ °F)	
Tempering/Aging	Steel, All	Class 2 ( $\pm 10$ °F)	2
		Class 3 ( $\pm 15$ °F)	3
Annealing	Steel, All	Class 5 ( $\pm 25$ °F)	
All Other Processes	Steel, All	Class 5 ( $\pm 25$ °F)	



**Table 3-19. Temperature Uniformity Allowance for Heat Treat Operations - Continued**

Process	Alloy	Uniformity Allowance	Notes
NOTES: 1. For alloys 7049, 7149, 7249, and 7050, aging ovens operating above 300 °F shall be a minimum of Class 1 ( $\pm 5$ °F) 2. Temperatures below 1300 °F. 3. Temperatures 1300 °F and above.			

**Table 3-20. Expendable Base Metal Thermocouples**

Type	Alloy Combination		Color Code ( $\pm$ )	Calibrated Temperature Range °F
	Positive (+)	Negative (-)		
E	Nickel/Chromium	Copper/Nickel	Purple/Red	-328 to 1652
J	Iron	Copper/Nickel	White/Red	32 to 1382
K	Nickel/Chromium	Nickel/Aluminum	Yellow/Red	-328 to 2282
N	Nicrosil	Nisil	Orange/Red	-454 to 2372
T	Copper	Copper/Nickel	Blue/Red	-328 to 662
Insulation Material			Temperature Rating °F	
Teflon, Extruded			up to 500	
Fiberglass, Braided			up to 900	
Silica, Braided			up to 1990	
Nextel, Braided			up to 2200	

**Table 3-21. Oven/Furnace Instrumentation Type, Sensor Requirements**

Required Sensors By Instrumentation Type	Instrumentation Type				
	A	B	C	D	E
One control sensor per zone that controls and displays temperature.	X	X	X	X	X
Each control zone shall have over-temperature protection.	X	X	X	X	
The temperature indicated by the control sensor in each control zone shall be recorded by a recording instrument.	X	X	X	X	
At least 1 load thermocouple/sensor in each zone that logs/records temperature.	X	X			
At least two additional recording sensors in each control zone shall be located to best represent the coldest and hottest temperatures based on the results from the most recent TUS.	X		X		

### 3.15 FABRICATION.

This portion is intended to provide some of the information required to fabricate the various aluminum products into parts and assemblies. Aluminum is one of the most workable of all the common metals. It can be fabricated into a variety of shapes by conventional methods. The formability varies considerably with alloy and temper. Specific application usually depends on the shape, strength and temper of the alloy. The preceeding will necessitate that the mechanic be well trained to cope with the variables associated with this material especially when the end use of the item is an aircraft or a missile.

### 3.16 FORMING SHEET METAL.

**3.16.1 General.** The forming of aluminum (1100) is relatively easy, using approximately the same procedures as those used for common steel except that care must be taken to prevent scratching. Do not mark on any metal surface to be used as a structural component with a graphite pencil or any type of sharp pointed instrument. Use pencil, Aircraft Marking, Specification MIL-P-83953, NSN 7510-00-537-6928 (Black), 7510-00-537-6930 (Yellow), and 7510-00-537-6935 (Red). All shop equipment, tools and work area should be kept smooth, clean and free of rust and other foreign matter.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

3.16.1.1 Alloyed aluminum (2024, 7075, 7178, etc.) are more difficult to form, and extensive control is required to prevent scratching and radii cracking. Scratching will make forming more difficult plus it provides an easy path for corrosion attack, especially on clad materials. The clad coating referenced is usually a sacrificial corrosion resisting aluminum alloy coating sandwiched metalurgically to an alloyed core material. The thickness of the coating will depend on the thickness of the sheet or plate. The nominal cladding thickness is 4 percent of composite thickness for material under 0.063 inch; 2.5 percent for material in the range of 0.063-0.187 inch and 1.5 percent for material 0.188 inch and thicker.

3.16.1.2 The following general rules should be employed in the handling and forming operation:

- a. Provide clean area; free of chips, grit and dirt and other foreign material.
- b. Provide clean smooth (rust free) and adaptable forming equipment.
- c. Sheared or cut edges shall be sanded and filed or polished, prior to bending or forming.
- d. Use only straight and smooth forming dies or brake leafs of the correct radius which are free of nicks, burrs and sharp edges.
- e. Form material across the direction of grain flow when possible.
- f. Material should be of the correct temper, thickness and alloy in the range of "formable" material.

3.16.1.3 For intricate forming operations it is necessary to use annealed (Condition "O") material and final strength developed by heat treating after the forming has been accomplished. Heat-treated alloys can also be formed at room temperature immediately after quenching ("W" temper), which is much more formable than the fully heat-treated temper. The part is then aged to develop full strength. The forming operation should be performed as soon after quenching as possible, in view of the natural aging that occurs at room temperature on all the heat treatable alloys. The natural aging can be delayed to a certain extent by placing the part in a cold storage area of 32 °F or lower. The lower the temperature the longer the delay to a point where maximum delay is obtained.

3.16.2 **Bending.** Bending is classified as single curvature forming. Upon bending sheet metal, bar or rod, the material at the bends flows or deforms i.e., the material adjacent to the other surface of the bend is under tension and the length is increased due to stretching and the material adjacent to and on the inner surface is under compression and the length is decreased.

3.16.2.1 The most common problems encountered in practice are springback and cracking within the bend area. Problems associated with bend cracking are usually a result of improper bend radii, rough edges of material being formed or forming equipment and bending parallel to direction of grain flow. Actual practice may reveal that a larger or a smaller radius may be used in some instances. Consult TO 1-1A-1 for minimum bend radii.

3.16.2.2 Difficulties encountered with springback are most commonly associated with bending of the stronger alloys, especially those having high yield strength. Springback problem associated with this material can be overcome to a certain degree by overforming. The amount of overforming utilized will depend on the temper and the alloy; the softer the material the less springback compensation required. Other means of reducing springback is to bend the material in the soft condition (Condition "O") or immediately after quenching and reducing the thickness or the radius if allowed. Avoid reducing radii to the point that grain separation or bend cracking results.

3.16.3 **Draw Forming.** Draw forming is defined as a method where a male die (punch) and a female die is used to form a sheet blank into a hollow shell. Draw forming is accomplished by forcing the male die and the metal blank into the female die. Generally mechanical press either single or double action and hydraulic presses are used to perform the drawing operation. Results will depend on die design, radii of die forming surfaces, finish of die, surface clearance between punch and female die, blank hold down pressure, shape of blank, material allowance on blank, elongation factor of material, temper, shape of part being formed, drawing speed, and lubricant. Optimum results usually requires experimentation and adjustment of one or more of these factors. Drawing of very deep shells require more experimentation and the utilization of a succession of limit draws. Because of the work hardening resulting from each draw, reduction in successive draws must be less. In severe conditions an intermediate anneal is sometimes used. Condition "O" material of the heat treatable alloys can be heat treated after drawing to obtain higher strength and to relieve the effect of work hardening. However, the non-heat treatable alloys can only be annealed to relieve the effect of work hardening. This material should not be annealed if high strength is the major requirement.



3.16.3.1 The recommended material to manufacture drawing dies is hardened tool steel for large scale production; kirksite and plastic for medium or short run production; and phenolic and hardwood for piece production.

3.16.4 **Stretch Forming.** This process involves stretching a sheet or strip to just beyond the elastic limit where permanent set will take place with a minimum amount of springback. Stretch forming is usually accomplished by gripping two opposite edges fixed vises and stretching by moving a ram carrying the form block against the sheet. The ram pressure being sufficient to cause the material to stretch and wrap to the contour of the form block.

3.16.4.1 Stretch forming is normally restricted to relatively large parts with large radii of curvature and shallow depth, such as contoured skin. The advantage is uniform contoured parts at faster speed than can be obtained by hand forming with a yoder hammer or other means. Also, the condition of the material is more uniform than that obtained by hand forming. The disadvantage is high cost of initial equipment, which is limited to Automatic Message Accounting level repair facilities.

3.16.4.2 Material used for stretch forming should be limited to alloys with fairly high elongation and good spread between yield and tensile strength. Most of the common alloys are formed in the annealed condition. It is possible to stretch form the heat treatable alloys in tempers T4 or T6, where the shape is not too deep or where narrow width material is used. For the deeper curved shapes, the material is formed in the annealed "O" temper, heat treated and reformed, to eliminate distortion resulting from heat treatment. As previously stated the material should be reformed as fast as possible after heat treatment. In some instances the material is formed immediately after heat treating and quenching. Selection of a system or condition of material to be utilized will require experimentation and the subsequent utilization of the system that gives the best results.

3.16.5 **Hydraulic Press Forming.** The rubber pad hydropress can be utilized to form many varieties of parts from aluminum and its alloys with relative ease. Phenolic, masonite, kirksite and some types of hard setting molding plastic have been used successfully as form blocks to press sheet metal parts such as ribs, spars, fans, etc. The press forming operations are usually accomplished by setting the form block (normally male) on the lower press platen and placing a prepared sheet metal blank on the block. The blank is located on the block with locating pins, to prevent shifting of blank when the pressure is applied (the sheet metal blank should be cut to size and edges deburred prior to pressing). The rubber pad filled press head is then lowered or closed over the form block and the rubber envelope, the form block forcing the blank to conform to the form blocks contour. This type forming is usually limited to relatively flat parts having flanges, beads and lightening holes. However, some types of large radii contoured parts can be formed with a combination of hand forming and pressing operations. It is recommended that additional rubber be supplemented in the form of sheets when performing the above to prevent damage to the rubber press pad. The rubber sheet used should have a shore hardness of 50-80 durometers. The design of foam block for hydropress forming require compensation for springback even though the material normally used is Condition "O" or annealed. Normal practice is to under cut the form block 2-7 degrees depending on the alloy and radii of the form block.

3.16.6 **Drop Hammer Forming.** The drop hammer can be used to form deep pan shaped and beaded type parts. Kirksite with a plastic surface insert is satisfactory for male and female dies. The surface of kirksite dies used without plastic insert should be smooth to prevent galling and scratching of the aluminum surface. When forming deep pans and complicated shaped parts it is often necessary to use drawings rings, pads or 2-3 stage dies. An intermediate anneal is sometimes used to relieve the hardened condition (cold work) resulting from the forming operation.

3.16.7 **Joggling.** A joggle is an offset formed to provide for an overlap of a sheet or angle which is projecting in the same plain. The inside joggle radii should be approximately the same as used for straight bending. Joggle run out or length as a normal rule should be three times the depth of the joggle for the medium strength alloys (2024, 2014, etc.) and approximately four times the depth for the higher strength alloys (7075, 7178, 7079 etc). Where deep and tight joggles are required, annealed material should be used with heat treatment to follow.

3.16.8 **Hot-Forming.** Hot forming is not generally recommended, however, it is sometimes used where it is not possible to form an article by other methods. Accomplishment shall not be attempted unless adequate facilities are available to control temperature requirements. Actual formability will depend on the temperature that various alloys are heated. The higher the temperature the easier formed. Excessively high temperature shall not be used, as considerable loss in strength and corrosion resistance will occur. Frequent checks should be made using an accurate contact pyrometer. [Table 3-19](#) cites the recommended times and temperature (accumulative) for the various alloys. The losses in strength as a result of re-heating at the temperature cited by this table will not exceed 5 percent. Equal formability will be obtained with shorter periods of heating in most cases and the minimum times should be used. It should be understood that this table cited the maximum accumulative times at cited temperature.

3.16.9 **Spinning.** Spinning is an art and makes exacting demands upon the skill and experience of the mechanic performing the operation. For this reason mass production of parts is impractical. However, it can be used to advantages where only a few parts are required and to assist in the removal of buckles and wrinkles in drawn shell shaped objects.



## TO 1-1A-9

### NAVAIR 01-1A-9

3.16.9.1 Forming by spinning is a fairly simple process, an aluminum disc (circle) is placed in a lathe in conjunction with a form block usually made of hardwood; as the disc and form block are revolved, the disc is molded to the form block by applying pressure with a spinning stick or tool. Aluminum soap, tallow or ordinary soap can be used as a lubricant.

3.16.9.2 The best adapted materials for spinning are the softer alloys i.e., 1100, 3003, 5052, 6061, etc. Other alloys can be used where the shape to be spun is not excessively deep or where the spinning is done in stages and intermediate annealing is utilized to remove the effect of strain hardening (work hardening) resulting from the spinning operation. Hot forming is used in some instances when spinning the heavier gauge materials and harder alloys.

3.16.10 **Blanking and Shearing.** Accurate shearing will be affected by the thickness of material, type of shear or knife blades, condition of material, adjustment and sharpness of blades, size of cut and the relationship of the width of the cut to sheet thickness.

3.16.10.1 Normally most aluminum alloys can be sheared 1/2 inch and less in thickness except for the harder alloys i.e., 7075-T6 and 7178-T6. These alloys have a tendency to crack in the vicinity of the cut especially if the sheer blades are dull or nicked. The above will naturally require that tooling used be designed to handle the thickness of material to be cut. Correct clearance between shear blades is important for good shearing. Too little clearance will quickly dull or otherwise damage the blades or knives; too much will cause the material to be burred, or even to fold between blades. Normal clearance is from one-tenth to one-eighth the sheet thickness. Blade life will be prolonged by occasionally lubricating. When the capacity of shear is doubtful the shear manufacturer should be consulted.

3.16.11 **Blanking.** Blanking is usually accomplished utilizing a blanking die in almost any type of punch press equipment. The essential factors requiring control are die clearance, shearing edge lead, and stripping action. The shearing principle is primarily the same as that encountered with the squaring shear. However, the method of grinding punch dies will vary according to the results required and in such manner that will reduce load on equipment. Commonly two or more high points are ground on die to keep side thrust on the punch at a minimum. Lubrication is essential in blanking operations. Suitable lubricants are engine oil, kerosene and lard oil which are normally used in mixed form.

**Table 3-22. Maximum Accumulative Reheat Times for Hot Forming Heat Treatable Alloys at Different Temperatures**

Alloy	450 °F	425 °F	400 °F	375 °F	350 °F	325 °F	300 °F
2014-T6	To Temperature	To Temperature	5-15 Minimum	30-60 Minimum	2-4 Hours	8-10 Hours	20-50 H
2024-T81	5 Minimum	15 Minimum	30 Minimum	1 Hour	2-4 Hours		20-40 H
2024-T86	5 Minimum	15 Minimum	30 Minimum	1 Hour	2-4 Hours		10-20 H
6061-T6	5 Minimum	15 Minimum	30 Minimum	1-2 Hours	8-10 Hours	5-100 Hours	100-200 H
7075-T6	No	No Temperature	5-10 Minimum	30-60 Minimum	1-2 Hours	2-4 Hours	10-12 H
*2014-T4, 2014-T3 No		No	No	No	No	No	No
*2024-T4, 2024-T3 No		No	No	No	No	No	No
* These materials should not be hot formed unless subsequently artificially aged.							

3.16.12 **Riveting.** Riveting is the most common method of assembling components fabricated from aluminum. Typical advantages of this method of mechanical fastening are simplicity of application, consistent joint uniformity, easily inspected (X Ray and other type equipment no required.), low cost, and in many cases lighter weight.

3.16.12.1 The rivets used in United States Air Force Weapon System structures require that the alloys and shapes be closely controlled by specifications/standards, to assure structural integrity and uniformity. These rivets are presently classified as solid shank, hishear, blind (structural-non-structural) explosive/chemical expanded. They are available in a variety of shapes, alloys, sizes, lengths and types. The most common utilized are aluminum because the structure alloys are normally aluminum. In addition some of the aluminum rivet characteristics can be changed by heat treating which facilitates application (see [Paragraph 3.12](#)).










3.16.12.2 All of the aluminum alloys could be used to manufacture rivets; however, due to some alloys having superior properties they have been selected as standard. See [Table 3-23](#) for alloys head, identification, MS/AN standard cross references, etc., for general rivets used on AF weapons systems.



3.16.12.3 Rivets in aluminum alloys 1100(A), 5056(B), 2117(AD) are used in the condition received Alloys 2017 (D) and 2024(DD) often referred to as “Ice Box Rivets” require heat treatment prior to use (see [Paragraph 3.12](#)). Rivets in alloy 2017 and 2024 should be driven immediately after quenching with a maximum delay of 20 minutes or refrigerated to delay aging. The customary procedure (unless only a few rivets are involved) is to place the rivets under refrigeration immediately after heat treatment. The time the rivets may be used will depend on refrigeration equipment available. Cooling to 10 °F will retard natural aging to the extent that the rivets may be driven up to 24 hours. Cooling rivets 0 °F will retard natural aging and may be stored for 30 days, -10 °F enables up to 90 days of storage.

3.16.12.4 Rivets utilized with extended driving time should be closely inspected after upsetting for cracks. If inspection reveals that rivets are cracked, discontinue use, remove defective rivets and obtain reheat treated rivets prior to continuing the assembly operation.

3.16.12.5 If for some reason it is necessary to determine if a rivet has been heat treated this may be done by Rockwell Hardness testing. Test by supporting rivets in a vee block and harness reading taken with a 1/16 inch ball 60 kilogram load. A harness of over 75 will indicate a heat treated rivet.

HEAD SHAPE IDENTIFICATION				RIVET MARKING TO ALLOY IDENTIFICATION		
						
ROUND	UNIVERSAL	BRAZIER	COUNTERSUNK	PLAIN HEAD 1100 (A)	RAISED CROSS 5056B	DIMPLE 2117 (AD)
<b>NOTE:</b> RIVETS MARKED X SUPERSEDED BY UNIVERSAL HEAD.						
<b>NOTE:</b> HEAD SHAPES APPLY TO SOLID SHANK ALUMINUM RIVETS ONLY.				RAISED DOT 2017 (D)	RAISED DASHES 2024 (DD)	

TO-1-1A-9-011

Figure 3-4. Rivet ID Information



Heat treatment and most other operations requiring use of heat will be accomplished prior to installing rivets, since heating after rivets are installed will cause warping and possible corrosion if salt bath is used. The salt from the bath will contaminate cracks and crevices of the assembly and complete removal can not be assured. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

3.16.12.6 Shear strength (ultimate) of a driven rivet can be determined by the formula  $P_s = S_s A N$ .  $P_s$  = ultimate shear strength (pounds),  $S_s$  = specified shear strength of the driven rivet Pound-force per Square Inch (PSI),  $A$  = cross sectional (area of the driven rivet, normally equal to hole cross section (square inch) and  $N$  = number of shear planes. For shear strength of protruding and flush head rivets see [Table 3-25](#).

3.16.12.7 The load required to cause tensile failure of a plate in a rivet joint can be determined by the formula  $T_s = P + (D - A) T_p$ .  $T_s$  = ultimate tensile strength (pounds),  $P$  = specified ultimate tensile strength of the plate PSI,  $D$  = pitch of the rivets (inch) - pitch is the distance between the center of two adjacent rivets on the same gauge line,  $A$  = diameter of hole (inch) and  $T_p$  = thickness of plate.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

**3.16.12.8 Rivet Selection.** Unless otherwise specified rivets should be selected that have comparable strength and alloy as material being assembled. This is an important factor in preventing corrosion from dissimilar metal contact and to assure structurally sound assemblies. The following tables are provided as a general guide for selection of rivet alloy vs assembly alloy.

**3.16.12.9** The formula  $P_s = S_b \text{ Air-Cooled (AC)}$  can be used to determine failure in bearing strength.  $P_s$  = ultimate bearing strength of the joints pounds,  $S_b$  = specified ultimate bearing strength of the plate PSI and AC = projected crushing area (bearing area) of rivet, or diameter (square inch) see [Table 3-26](#) for typical bearing properties of aluminum alloy plates and shapes.

**3.16.12.10** Rivet hole preparation is one of the key factors in controlling successful upsetting of rivet head, material separation and buckling which weakens the structural strength of the rivet joint, and corrosion attack of rivets and material after equipment is placed in service/use. The rivet hole should be drilled, punched/reamed to size that allows the minimum clearance (approximately 0.003 for thin sheet and up to about 0.020 for 0.750-1.000 inch thick material) required to insert rivet without forcing. Theoretical rivets holes should be completed i.e., drilled, reamed to size, deburred, chips removed that may lodge or be trapped in between surface of metal and treated (anodized etc.) before starting to rivet assembly. The above cannot always be accomplished especially where the assembly is large and requires the application of a large amount of rivets due to hole tolerance and variations in holding clamping/pressures. To overcome these problems requires that holes be pilot drilled end reamed to size at time rivet is to be installed. This method has a twofold purpose: (1) allows easy insertion of rivets, (2) prevents elongation of rivet holes and resulting weakening of rivet joint.

**3.16.12.11** Rivet holes drilled/reamed after assembly is started should be treated by coating with zinc chromate primer or other approved material. Two methods for coating rivets and improving protection of hole surfaces from corrosion are:

- a. Coat holes/bare metal with primer after drilling and allow to cure. Coat rivets with primer and install while still wet.
- b. Coat holes/bare metal with primer after drilling and allow to cure. Coat rivet with sealant and install while still wet.

**3.16.12.12** For additional information on rivets (strengths, factors, etc.) see MIL-HDBK-5, TO 1-1A-8 and TO 1-1A-1.

**Table 3-23. General Rivet (Alum) Identification Chart**

Old AN/STD	Superseding MS STD	Form	Material	Head And Numerical Ident Code	Condition	Heat Treat
AN456	MS20470	Brazier Head Solid Modified	See AN470			
<p style="text-align: center;"><b>NOTE</b></p> <p>See <a href="#">Paragraph 3.12</a> for heat treat data.</p>						
USAF460	See MS20601	1000 Flush Head Blind Type II Class 2	See MS20601			
USAF461	See MS20600	Protruding Head Type II Class I Blind	See MS20601			
USAF463	See MS20600	Same	Same			
NAF1195	See MS20600	Same	Same			
AN470	MS20470	Universal Head Solid	1100	A-Plain	F	No
			5056	B-Raised Cross	F	No
			2117	AD-Dimple	T-4	No
			2017	D-Raised Dot	T-4	Yes
			2024	DD-Raised Dash	T-4	Yes



Table 3-23. General Rivet (Alum) Identification Chart - Continued

Old AN/STD	Superseding MS STD	Form	Material	Head And Numerical Ident Code	Condition	Heat Treat
	MS20600	Protruding Head-Blind Type II, Class I	5056	B	F	No
			2117	AD	T-4	No
			Monel	M		No
	MS20601	100° Flash Head Blind Type II, Class 2	5056	B	F	No
			2117	AD	T-4	No
			Monel	M		No
	MS20602	Protruding Head Blind Chemically Expanded Type I, Class I, Styles A and B	5056	B	F	No
			2017	D	T-4	No
	MS20604	Universal Head Blind Class I Non Struct	5056	B	F	No
			2117	AD	T-4	No
			Monel M or MP (MP = Monel Plated)			No
	MS20605	100° Flash Head Blind Class 2, Non Struct	5056	B	F	No
			2117	AD	T-4	No
			Monel M or MP (MP = Monel Plated)			No
	MS20606	Modified Trusshead Blind Class 3 Non-Struct	5056	B	F	No
			2117	AD	T-4	No
			Monel M or MP (MP = Monel Plated)			No
	MS20613	Universal Head Solid	1010	Recessed Triangle Annealed		No
			302	C-None	Annealed	No
	MS20615	Universal Head Solid	Copper	CW Annealed		No
			Monel	Raised Dots	Class A	No
<div>NOTE</div> <div>Copper, steel, and monel listed for information purposes only. For special rivets see manufacturing drawing, data, specification, etc. For other information on rivets see TO 1-1A-8 and TO 1-1A-1.</div>						
AN426	MS20426	Countersunk 100°	1100	A-Plain	F	No
			5056	B-Raised Cross	F	No
			2117	AD-Dimple	T-4	No
			2017	D-Raised Dot	T-4	Yes
			2024	DD-Raised Dashes	T-4	Yes
<div>NOTE</div> <div>See <a href="#">Paragraph 3.12</a> for heat treat data.</div>						



**Table 3-23. General Rivet (Alum) Identification Chart - Continued**

Old AN/STD	Superseding MS STD	Form	Material	Head And Numerical Ident Code	Condition	Heat Treat
AN427	MS20427	Countersunk 100°	1006/1010	Recessed Triangle	A	No
			Copper 302/304	C-None F-Recessed	A A	No No
			Monel M	Dash M-None		
AN430	MS20470	Round Head replaced by universal See AN470 + MS20470				
AN435	MS20435	Round Head Solid	1006	Head Ident Recessed Triangle	A	No
<b>NOTE</b>  Listed for Reference only.			Copper 302/304	C-None	A	No
				F-Head Ident None	A	No
			Monel	M-None		
AN441	Use MS20435	See AN435				
AN442	Use MS20470	See AN70 + MS20470				
AN450	MS20450	Countersunk and oval tubular	1006/1010/1015	Blank/None	A	No
<b>NOTE</b>  Listed for Reference only.			Copper	C-None	A	No
			2117	AD-None	T-4	No
			Brass	B-None	Grade B	No
			MONEL	M-None	A	No
AN455	MS20470	Brazier Head Solid Superseded by Universal.	See AN470			

**Table 3-24. General Aluminum Rivet Selection Chart (Rivet Alloy vs Assembly Alloy)**

Rivet Alloy	Assembly Alloy
1100	1100, 3003, 3004, 5052
2117-T4 (AD)	3003 -H16 and H-18, 5052 -H16 and H18, 2014, 2017, 2024, 6061, 7075, and 7178
2017-T4 (D), 2024T4 (DD)	2014, 2017, 2024, 5052, 6061, 7075 and 7178
5056-H32 (B)	5052 and magnesium alloys, AZ31B, etc.

**3.16.13 Machining.** The resistance encountered in cutting aluminum alloys is low in comparison to other metals. In fact most of the aluminum alloys will machine approximately 10 times faster than steel. This factor combined with other properties, i.e. strength, heat treatability, weight, corrosion resistance, etc. makes aluminum a preferred material in many instances for fabrication of parts by machining. Brass (free machining) is the only other material with comparable machining properties.

**3.16.13.1** Personnel accomplishing the work should be properly trained in machining aluminum as with other types of metals. Due to various circumstances personnel familiar with machining steel products are required to machine aluminum



without proper training/information on speeds, feeds, tools etc., required to effectively accomplish a specific task. The purpose of this section is to provide a general guide for selection of tools machining speeds, etc.

3.16.13.2 The tools used for machining aluminum will normally require more rake side-top and operation at higher/feeds than used for steel. The amount of rake required will depend on composition, physical form (cast or wrought) and temper. The more ductile or softer the alloy the more rake required. The following general practices are recommended for shafing, grinding and maintaining tools for cutting aluminum:

- a. Allow more space for chips to be formed and expelled from tool than allowed for steel.
- b. Design tools (grind tool) so that chips and cuttings are expelled away from the work piece.
- c. Keep cutting edges of tools sharp, smooth, free of burrs, wire edges and scratches.
- d. Use high machining speeds, moderate feeds and depths of cut.
- e. Apply lubricant/coolant in large quantities to tool when cutting.

3.16.13.3 The higher speeds utilized for machining aluminum requires:

- a. Machines be free of vibration and lost motion.
- b. Rigid support of tool near cutting edge to minimize clatter and vibration.
- c. Secure clamping of work to machine to avoid distortion or slippage.
- d. Use of proper lubricant, cutting compound or coolants to prevent overheating, warpage/distortion and to provide adequate lubrication to cutting tool.

3.16.14 Cutting Tools for Machining Aluminum. There are four general types of tool steel material that can be used to machine aluminum. They should be selected in accordance with availability and scope of job to be accomplished. The following is a suggested guide for selection of tools:

- a. High carbon tool steel is adequate for machining a small number of parts or where cutting speed required is relatively low. This material will exceed the performance of some of the other types of tools when used for fragile tools such as drills, taps, etc., because it does not break as easily as the other types. Stock material is obtainable in accordance with Federal Specification QQ-T-580 where required for local fabrication of high carbon tools etc.
- b. High speed tool steel is the most common type used for machining except on the higher silicon alloys.
  - (1) Availability, reasonable cost.
  - (2) Heat resistance (will retain cutting edge up to about 950 °F dull red).
  - (3) Permits use of large rake angle required. Federal Specification QQ-T-590 applies to stock material. All the various classes (T1, T2, T3, etc.) may be used for machining aluminum. Class T1 (18-4-1) general purpose type is the most widely used.
- c. Where long production runs are involved cemented carbide (solid or tipped) tools give better service. The carbide tools have been known to last thirty times longer than high speed tool steel. The carbide tools are also recommended for cutting high silicon content alloys. Because of the brittleness of the cemented carbide tool the cutting angle should be greater than those recommended for high carbon/high speed steels.
- d. Diamond tipped tools should only be used for light finishing cute or special finishing operations. Normal cutting of 75-90 °F are used with top rake angles of 6-10 °F. Tool projection (or set) should be slightly above center line of the work.

3.16.15 Turning. To properly perform the turning operation firmly attach the work to the machine (lathe) chuck, collet or faceplate. The work should be held in the best manner to minimize distortion from chuck or centrifugal force action during



## TO 1-1A-9

### NAVAIR 01-1A-9

the turning operation. Long rods/stock should be supported by ball or roller bearing tailstock centers which are more satisfactory than solid or fixed centers in resisting thrusts from centrifugal force and thermal expansion. Soft liners may be used between work and machine jaw faces to prevent jaw teeth from damaging/marring work piece. When it is necessary that work be held by clamping from inside diameter outward the tightness of jaws should be checked frequently to be sure that work is not being released as a result of thermal expansion.

3.16.15.1 The recommended cutting fluids are the soluble oil emulsion which combine the functions of cooling and lubricating for general purpose use. For heavy cutting especially when speeds are low, lard oil such as Specification C-O-376 or mineral oil, Specification VV-O-241 is recommended. In practice it will be found that some machining operations can be performed dry.

3.16.15.2 [Table 3-28](#) and [Table 3-29](#) cite suggested turning speeds, tool angles and feeds. Tool projection in relation to work should be set at or slightly above work piece center line. Sturdy construction of tools and holders is essential to minimize vibration/chatter at the high speeds aluminum alloys are machined.

#### NOTE

Parting tools should have less top rake than turning tools. Recommend top rake angles of 12-20° and front clearances of 4 degrees-8 degrees grind face concave (slightly) and so that corner adjacent to work will lead opposite corner by 4-12° or as required for best results.

3.16.16 **Milling - Aluminum.** Milling of aluminum alloys should be accomplished at high cutter speeds. The limitations will usually depend on the machine and type cutters used. The reason for the higher cutter speeds is that at low speeds the cutters will have a tendency to load and gum. This will normally clear as the speed is increased.

3.16.16.1 The tooling for milling should be selected according to the operation and duration/size of job to be performed. The cutters should have fewer teeth and should be ground with more top and side rake than those used for milling steels. Most operations can be accomplished with spiral cutters. Nick tooth cutters are used when reduction in size of chips is required. Solid-tooth cutters with large helix angles are used where free-cutting tools are required. When cutters with large helix angles are used it is often necessary that two interlocking cutters of opposite helixes be employed to alleviate axial thrust.

3.16.16.2 Tool alloys should be selected for milling aluminum as follows:

- a. For short runs high carbon steel is normally satisfactory.
- b. For production runs of extended duration high speed steel is recommended.
- c. Where climb milling/high speeds are utilized, carbide tipped tools are recommended for extended runs.

3.16.16.3 Milling cutters should be inclined to work and beveled on leading corner (least bevel for finish cuts) to minimize clatter.

3.16.16.4 The cutting fluids for milling aluminum should combine cooling and lubrication properties. Coolant lubrication should be applied under pressure (atomized spray if available) in large quantities to tool and work. The recommended cutting fluids are water base cutting fluids such as soluble oils and emulsions, mixed 1 part to 15 for high speeds and 1 part to 30 for low speed cutting.

3.16.16.5 [Table 3-30](#) and [Table 3-31](#) cite suggested speeds, contour and tool angles, for milling aluminum. The best combination of cutting speeds, feed and cut for a given job will depend on design of tool/cutter, kind of tool material, condition of machine, machine power, size, clamping method and type material being worked.

**Table 3-25. Shear Strength of Protruding and Flush Head Aluminum Alloy Rivets, Inch Pounds**

Size of Rivet (Inch Diameter)	1/16	3/32	1/8	5/32	3/16	1/4	5/16	3/8
Alloy + driven temper 5056 FSU = 28 KSI	99	203	363	556	802	1450	2290	3280
2117-T321, FSU = 30 KSI	106	217	388	596	862	1550	2460	3510
2017-T31, FSU = 34 KSI	120	297	442	675	977	1760	2970	3970
2017-T3, FSU = 38 KSI	135	275	494	755	1090	1970	3110	4450



**Table 3-25. Shear Strength of Protruding and Flush Head Aluminum Alloy Rivets, Inch Pounds - Continued**

Size of Rivet (Inch Diameter)	1/16	3/32	1/8	5/32	3/16	1/4	5/16	3/8
2024-T31, FSU = 41 KSI	145	296	531	815	1180	2120	3360	4800
FSU = Average Shear Strength of alloy in specified temper. KSI = 1000 PSI example: 34 KSI = 34,000 PSI. Single shear rivet strength correction factor (resulting from use in thin plates and shapes). Sheet thickness (inch)								
0.016	0.0964							
0.018	0.0984							
0.020	0.0996							
0.025	1.000	0.972						
0.032		1.000	0.964					
0.036			0.980					
0.040			0.996	0.964				
0.045			1.000	0.980				
0.050				0.996	0.972			
0.063				1.000	1.000	0.964		
0.071						0.980	0.964	
0.080						0.996	0.974	
0.090						1.000	0.984	
0.100							0.996	0.972
0.125							1.000	1.000
0.160								
0.190								
0.250								
Double shear rivet strength correction factor (resulting from use in thin plates and shapes)								
SIZE OF RIVETS								
Sheet Thick Inch	1/16	3/32	1/8	5/32	3/16	1/4	5/16	3/8
0.016	0.688							
0.018	0.753							
0.020	0.792							
0.025	0.870	0.714						
0.032	0.935	0.818	0.688					
0.036	0.974	0.857	0.740					
0.040	0.987	0.896	0.792	0.688				
0.045	1.000	0.922	0.831	0.740				
0.050		0.961	0.870	0.792	0.714			
0.063		1.000	0.935	0.883	0.818	0.688		
0.071			0.974	0.919	0.857	0.740		
0.080			1.000	0.948	0.896	0.792	0.688	
0.090				0.974	0.922	0.831	0.753	
0.100				1.000	0.961	0.870	0.792	0.714
0.125					1.000	0.935	0.883	0.818
0.160						0.987	0.835	0.883
0.190						1.000	0.974	0.935
0.250							1.000	1.000



Table 3-25. Shear Strength of Protruding and Flush Head Aluminum Alloy Rivets, Inch Pounds - Continued

Size of Rivet (Inch Diameter)	1/16	3/32	1/8	5/32	3/16	1/4	5/16	3/8
<p align="center"><b>NOTE</b></p> <p>Values (pounds) of shear strength should be multiplied by the correction factor whenever the D/T = rivet diameter/plates sheet or shape thickness ratio is large enough to require correction. Example: Rivet diameter 1/8 (alloy 2117 - T3) installed in 0.040 sheet, shear factor is 388 pounds correction factor 0.996 =</p> <p>388 0.996 2328 3492 3492 386.448 corrected shear pounds</p>								

Table 3-26. Bearing Properties, Typical, of Aluminum Alloy Plates and Shapes

Edge Distance = 1.5 X Rivet Diameter			Edge Distance = 2.0X X Rivet Diameter	
Alloy	Yield Strength	Ultimate Strength	Yield Strength	Ultimate Strength
1100 - 0	10,000	21,000	12,000	27,000
1100 - H12	18,000	23,000	21,000	29,000
1100 - H14	22,000	24,000	23,000	31,000
1100 - H16	23,000	16,000	26,000	34,000
1100 - H18	27,000	19,000	32,000	38,000
3003 - 0	12,000	22,000	15,000	34,000
3003 - H12	21,000	27,000	24,000	36,000
3003 - H16	28,000	34,000	33,000	42,000
3003 - H18	32,000	38,000	38,000	46,000
2014 - T4	56,000	93,000	64,000	118,000
2014 - T6	84,000	105,000	96,000	133,000
2024 - T3	64,000	102,000	74,000	129,000
Alclad 2024-T3	60,000	96,000	69,000	122,000
2024 - T36	80,000	110,000	91,000	139,000
Alclad 2024-T36	74,000	100,000	85,000	127,000
5052 - 0	25,000	46,000	30,000	61,000
5052 - H32	37,000	54,000	42,000	71,000
5052 - H34	41,000	59,000	47,000	78,000
5052 - H36	47,000	62,000	54,000	82,000
5052 - H38	50,000	66,000	58,000	86,000
6061 - T4	29,000	56,000	34,000	73,000
6061 - T6	56,000	72,000	64,000	94,000
7075 - T6	101,000	123,000	115,000	156,000
Alclad 7075-T6	94,000	114,000	107,000	144,000

**3.16.17 Shaping and Planing.** The speed at which aluminum alloys can be cut by planing and shaping is somewhat slower in comparison to other machining methods, due to equipment design and limitations. The slower cutting speeds can be overcome to some extent by securely anchoring the work to the machine and using heavy rough cutting feeds. The tools used for rough cut should be (round nose) of heavy construction and properly ground to operate efficiently. Rough cut tools should be ground with moderate amount of rake to provide maximum cutting edge support. Finish tool should have more top rake



and an extra large amount of side rake. Finishing tool shall be used with fine feeds only due to the additional side and top rake (finish cut should not exceed 0.018 inch).

3.16.17.1 Most cutting operations by shaping and planning can be accomplished without cutting fluids, however fine finishing can be improved by lubrication. Recommended cutting compounds are kerosene, mixture of 50-50 lard-oil and soluble oil.

3.16.17.2 [Table 3-32](#) and [Table 3-33](#) cite suggested turning speeds, tool angles and feeds. Secure clamping of work is re-emphasized especially when heavy cutting feeds are to be used.



**Table 3-27. Standard Rivet Hole Sizes with Corresponding Shear and Bearing Areas for Cold Driven Aluminum Alloy Rivets**

Rivet Size, Inch	1/16	3/32	1/8	5/32	3/16	1/4	5/16	3/8
Drill Size, Number	51	41	30	21	11	F	P	W
Nom hole diameter, Inch	0.067	0.096	0.1285	0.159	0.191	0.257	0.323	0.386
Single Shear Area Square Inch			0.01296	0.01986	0.02865	0.05187	0.08194	0.11170
	0.032		0.00411	0.00509				
	0.040		0.00514	0.00636	0.00764			
	0.051		0.00655	0.00811	0.00974	0.01311		
	0.064		0.00822	0.0108	0.01222	0.01645	0.0207	
	0.081		0.01041	0.01288	0.01547	0.02082	0.262	0.0313
Bearing Area	0.102		0.01311	0.01622	0.01948	0.02621	0.0369	0.0394
Square Inch for various Shear	0.125		0.01606	0.01988	0.02388	0.03213	0.0404	0.0483
Sheet and Plate Thickness	0.156		0.02480	0.02980	0.04016	0.0505	0.0603	
	0.187			0.3581	0.04819	0.0606	0.0724	
	0.2187			0.04178	0.05622	0.0707	0.0844	
	0.250				0.06425	0.0808	0.0965	
	0.3125					0.1009	0.1206	
	0.3750						0.1448	
	0.500							



**3.16.18 Drilling Aluminum Alloy.** Standard type twist drills may be used satisfactorily for many drilling operations in aluminum alloys. However, better results can be obtained with improved designed drills where soft material and drilling of thick material or deep holes are involved. These drills are usually designed having more spiral twists per inch (see [Figure 3-5](#)). The additional spiral twist gives more worm action or force to drill causing the drill to cut/feed faster and is helpful in removing chips, especially in deep hole drilling operations.

**3.16.18.1** Generally a drill for a given job should be selected according to the thickness, type alloy and machine/drill motor to be utilized. The following is a general guide for the selection of drills and recommended speeds:

**3.16.18.1.1 Drill Press.**

- Point Angle: 118-140° for general work and 90-120° for high silicon.
- Spiral Angle: 24-28° for thin stock and medium depth holes up to 6 times drill diameters, 24-48° for deep holes over 6 times drill diameter.
- Lip Clearance (lip relief): 17° for soft alloys 15° for medium and hard alloys, 12° for silicone alloys.
- Speed: 600 FPM, with high speed drills and up to 2000 FPM with carbide tipped drills.
- Feed: 0.004 - 0.012 inch per revolution for drills 3/8 inch diameter, 0.006-0.020 inch per revolution for 3/8 - 1-1/4 inch diameter and 0.016 to 0.035 inch per revolution for drills over 1-1/4 inch diameter. When using carbide tipped drill, feed should be slightly less. Feed also may be determined by the formula:  $\text{Feed} = \sqrt{\text{Drill Diameter (inches)}} \div 60 \text{ feet} = \text{Drill diameter (inches)} + 0.002$ .

**3.16.18.1.2 Lathe/Screw-Machine.**

- Point Angle: 118-140°
- Spiral Angle: 0-28°
- Lip Clearance (lip relief): 15-20°
- Speed FPM up to 1500
- Feed inches per revolution 0.004-0.016.

**3.16.18.1.3 Portable Drills Electric/Air Driven.** Due to variables involved no set factors can be given. However, factors given for drill press should be used as a guide. Feed should be adjusted in accordance with speed of motor to prevent tip heating and also to satisfy operation/operator.

**WARNING**

When operating any machinery all safety precautions must be observed, i.e., safety goggles shall be worn when grinding/drilling. Machinery shall be inspected to ensure that safety guards are in place for safe operation etc., prior to operating. Work shall be securely clamped to prevent slippage. Consult safety officer when in doubt about the safety of an operation. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

**3.16.18.2** The drilling of thin material normally does not require coolant/lubrication however adequate lubrication is essential to drill life and hole quality when drilling holes of 1/4 inch depth or more. Soluble oil emulsions and lard oil mixtures are satisfactory for general drilling. The lubrication should be applied by forced feed spray/flow where possible and the drill should be withdrawn at intervals to be sure lubricant flows to the drill tip (fill holes completely) when drill is withdrawn.



**Table 3-28. Turning Speeds and Feeds**

Alloy Type and Temper	Cut Inches	Cutting Speed Feet Per Minute (FPM)	Feed, Inches per Revolution	Operation	Tool Material
Soft Series, 1100 All temp 5052-H12, H14  2011-2024-0 5056-0-6061-0 7075-0, 113  138, 214, 212 750, 220, 122	0.250 Maximum	700 - 1600	0.050 Maximum	Rough	Plain high carbon/high speed
	0.040 Maximum	1500 - 3500	0.004 - 0.015	Finish	Plain high carbon/high speed
	0.250 Maximum	4000 - 7000	0.012 Maximum	Rough	Carbide
	0.020 Maximum	6000 - 8000	0.010 Maximum	Finish	Carbide
	0.010 Maximum	At Minimum Vibration	0.002 - 0.005	Finish only Diamond	
Hard Series  108, 319, 43  5052-H34, H36, H38 T4, 2024-T3 7075-T6, 7178- T6 6061-T4, T6, etc.	0.200 Maximum	400 - 650	0.007 - 0.020	Rough	Plain high carbon/high speed
	0.020 Maximum	600 Maximum	0.002 - 0.004	Finish	Plain high carbon/high speed
	0.200 Maximum	500 - 1300	0.010 Maximum	Rough	Carbide
	0.020 Maximum	700 - 2500	0.010 Maximum	Finish	Carbide
	Not recommended			Rough	Diamond tipped
	0.006 Maximum	At minimum vibration	0.002 - 0.004	Finish	Diamond tipped
High Silicon Series  4032, 333, A132, 132, 356 etc	0.120 Maximum	600 Maximum	0.007 - 0.020	Rough	Plain high carbon/high speed
	0.020	600 Maximum	0.002 - 0.004	Finish	Plain high carbon/high speed
	0.120 Maximum	500 - 1000	0.008 Maximum	Rough	Carbide
	0.020 Maximum	500 - 1500	0.004 Maximum	Finish	Carbide
		Not Recommended		Rough	Diamond tipped
	0.006	At minimum vibration	0.001 - 0.003	Finish	Diamond tipped

**Table 3-29. Tool Angles - Turning**

Tool Angles	Plain High Carbon/High Speed	Carbide	Diamond
Cutting Angles	30-50°	52-80°	74-88°
Top Rake	30-53°	0-32°	10-0°
Side Rake	10-20°	5-10°	0-6°
Front Clear	7-10°	6-10°	Nose Radii 0.06 - 0.10
Side Clear	7-10°	6-10°	



**Table 3-30. Milling - Speeds and Feeds**

Alloy	Cut	Cutter Speed	Feed		Operation	Tool Material
Temper	Inches	FPM	FPM	Inches per Tooth		
Soft	0.250 Maximum	700 - 2000	10 Maximum	0.005 - 0.025	Rough	High carbon/ High Speed
Soft	0.020 Maximum	5000 Maximum	10 Maximum	0.005 - 0.025	Finish	High carbon/ High Speed
Hard	0.200 Maximum	500 - 1500	10 Maximum	0.005 - 0-025	Rough	High carbon/ High Speed
Hard	0.020 Maximum	4000 Maximum	10 Maximum	0.005 - 0.025	Finish	High carbon/ High Speed
Soft	0.300 Maximum	3000 - 15000	20 Maximum	0.004 - 0.020	Rough	Carbide Tipped
Soft	0.020 Maximum	3000 - 15000	20 Maximum	0.004 - 0.020	Finish	Carbide Tipped
Hard	0.250 Maximum	3000 - 15000	20 Maximum	0.004 - 0.020	Rough	Carbide Tipped
Hard	0.020 Maximum	4000 - 15000	20 Maximum	0.004 - 0.020	Finish	Carbide Tipped

**Table 3-31. Tool Angles - Milling**

Tool Angles	High Carbon/High Speed	Carbide
Cutting Angle	48-67°	68-97°
Top Rake	20-35°	10-15°
Clearance	3-7° Primary	3-7° Primary
Helix	7-12° Secondary 10-50°	7-12° Secondary 10-20°
Tooth Spacing	Course - Sufficient for chip clearance.	Approximately 1 tooth per inch of diameter.

**Table 3-32. Shaping and Planing-Speeds and Feeds**

Method	Cut Inches	Cutting Speed	Feed (Inches)	Operation	Tool Material
Shaping	1/4 Maximum	Maximum speed of Random-Access Memory (RAM)	0.008 - 0.031	Rough	High Carbon/High Speed
Shaping	0.005 - 0.014	Maximum speed of RAM	0.094 - 0.156	Finish	High Carbon/High Speed
Planing	3/8 Maximum	Maximum speed of Table	0.020 - 0.100	Rough	High Carbon/High Speed
Planing	0.005 - 0.018	Maximum speed of Table	0.050 - 0.375	Finish	High Carbon/High Speed

**Table 3-33. Shaping Tool Angles**


	Operation Rough Finish	Tool Material
		High Carbon/High Speed
Top Rake	19-10 ° 43-52°	High Carbon/High Speed
Bottom Clear	7-9° 8-10°	High Carbon/High Speed
Side Rake	30-40° 50-60°	High Carbon/High Speed
Side Clear	7-9° 0-0°	High Carbon/High Speed



Table 3-33. Shaping Tool Angles - Continued

	Operation Rough Finish	Tool Material
		High Carbon/High Speed
Cutting Angle	64-71° 30-37°	High Carbon/High Speed



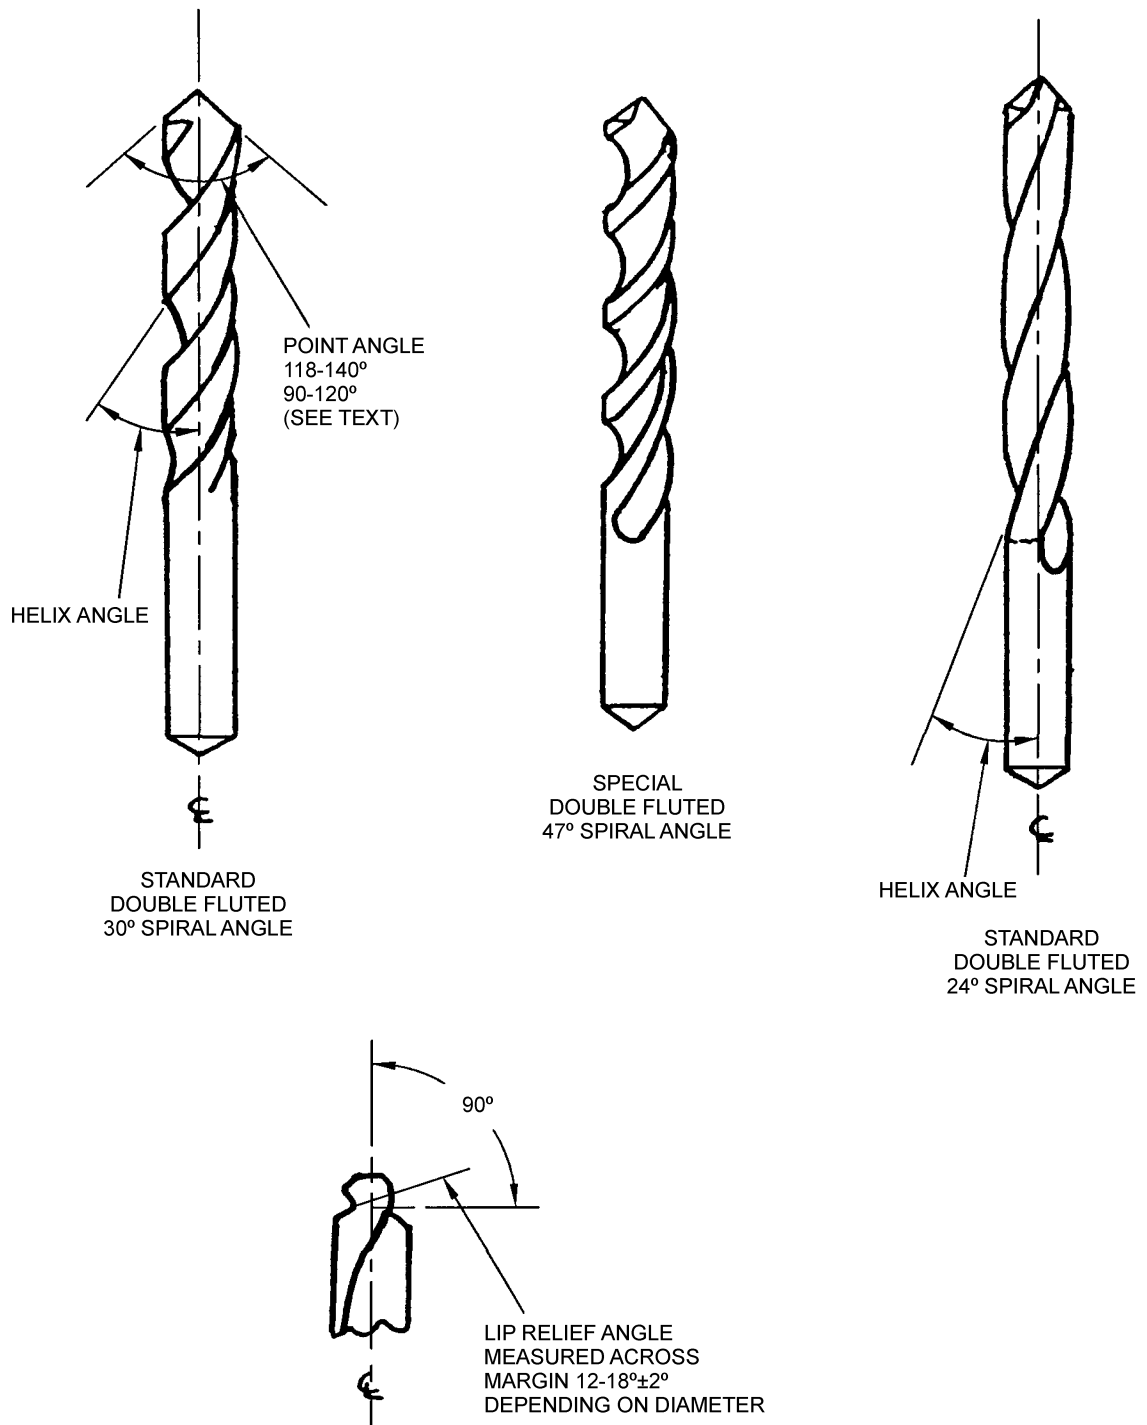

TO-1-1A-9-012

Figure 3-5. Drill Designs and Recommended Cutting Angles



Table 3-34. Thread Constant for Various Standard Thread Forms

Thread Form	Percent of Full Thread Desired			
	75 Percent	80 Percent	85 Percent	90 Percent
American Standard Course Series C =	0.9743	1.0392	1.1042	1.1691
Whitworth C =	0.9605	1.0245	1.0886	1.1526
British Association Standard C =	0.9000	0.9600	1.0200	1.0800
American Standard 60° Stub C =	0.6525	0.6960	0.7395	0.7830
American Standard Square C =	0.7500	0.8000	0.8500	0.9000
American Standard 10° modified Square Square C =	0.7500	0.8000	0.8500	0.9000

3.16.19 **Tapping.** The taps used for threading aluminum alloys should be of the spiral fluted type for best results. Straight fluted tape can be used but have a tendency to clog and tear the threads during the tapping operation. Spiral fluted taps for cutting right-handed threads should have a right-hand spiral of about 40 degree angle with a generous back off taper and highly polished flutes.

3.16.19.1 Spiral - Pointed or “Gun Taps” (straight fluted except they have a short spiral on the starting end) cut aluminum more freely than the other types. With this type tap the major portion of cutting occurs at the spiral end and curls ahead of the tap. The use of the “Gun Tap” is therefore limited to tapping holes which have room for the cuttings ahead of the tool. This spiral pointed tap should not be used for cutting tapered thread or for bottoming taps.

3.16.19.2 The following procedures and tools are recommended for tapping aluminum alloys:

- Cutting Speed: 40 to 130 FPM use lower speed for hard alloys and higher speed for soft alloys.
- Tap Type Selection: For blind holes and bottoming use spiral fluted; for semi-blind use spiral pointed (gun taps); and for hole through work use spiral pointed (gun taps).
- Thread Type: Rounded or flattened (turn coated) thread contour for general use.
- Tool Angles: Spiral flute-grind a lead spiral extending one full thread beyond chamfer on straight fluted tap. To make gun tap and spiral flute tap should be 28 degrees to 40 degrees; cutting angel 40 degrees to 45 degrees; top rake 45 degrees to 50 degrees; back rake 4 - 8 degrees; cutter area (included angles); 2 flute 36 degrees to 72 degrees and 3 flutes 24 degrees to 48 degrees.
- Tapping Allowance: Drill diameter for general tapping should be from 0.005 to 0.006 inches per inch larger than standard for the same thread in steel or in accordance with the following.

$$\text{Drill Diameter} = (1.005 \times \text{tap diameter}) - \frac{C}{\text{thread per inch}}$$

C = Thread constant for various thread forms and percentages of thread depth required as given in [Table 3-34](#).

- Lubrication: For high speed tapping use lard oil/mineral oil and for hand tapping a more viscous lubricant is recommended such as heavy grease/oil, white lead, etc.

3.16.20 **Filing.** Hand files of the single cut type having milled teeth usually give the best results for filing aluminum. The main consideration in file design/selection for aluminum is to provide ample chip space clearance. The cuttings generated are large and have a tendency to powder, pack and clog between file teeth. To overcome clogging problem chip space is increased, grooves are cut deeper and teeth are cut with generous side and top rake.

3.16.20.1 For finish filing a long angle mill file (single) (cut) with tooth spacing of 14-24 teeth per inch with side rake angle of 45-55° is recommended. In absence of the preferred file the same effect can be obtained using standard mill cut files by adjusting angle of filing incidence to the metal worked. The file is often adjusted until force or motion applied is parallel to the work piece for best results. A good general purpose file is the curved tooth type (often called “vixen”) having about ten deeply cut teeth per inch. It can be used for heavy and finish cuts. Lightly double cut files having tooth spacing of 14-20 per inch can be used for light duty rough cutting and finishing when working the harder alloys. User should be careful not to drag



file across work on back stroke as with any filing operation. Files shall be kept clean and free of rust. Clogged files can be cleaned by wire brushing. The use of chalk or talc on file will help prevent clogging.

3.16.20.2 Machine filing using rotary files (miniature milling cutters having spiralled sharp teeth with smooth deeply cut flutes) are operated at high speed. The rotary files are operated up to 10,000 Revolutions Per Minute (RPM) for small diameter and to 2,000 maximum peripheral FPM for the larger diameter. The teeth should be coarse (about 14 teeth per inch) with deep polished flute and spiral notched design.

### 3.16.21 Reaming.

#### **WARNING**

Wear goggles or face shield when filing with rotary files to protect eyes. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

Generally most of the different type reamers may be used for aluminum, but for best results the spiral fluted reamers are recommended - solid, expansion or adjustable. The spiral should be opposite to the rotation to prevent reamer from feeding and hogging into the hole. Holes to be finished by reaming should be drilled sufficiently under-size to assure positive cutting rather than scraping and swedging (indication of oversize drilled holes and improper feed is the projection of a lip around hole diameter after the reaming operation is accomplished). Finish reamers should be maintained with exceptionally keen cutting edges and highly polished flutes for smooth work.

3.16.21.1 The following procedures and tools are recommended for reaming aluminum alloys:

- Tool material: High carbon steel for general use; high speed steel/or carbide tipped for durability and continued production jobs.
- Tool type: Straight/spiral with 10 degree spiral flute and solid teeth.
- Clearance and rake angles: Top rake 5-8°; clearance angle primary 4-7°, secondary angle 15-20°; cutting angle 84-90°.
- Machine speed and hole reaming allowance: Cutting speeds up to 400 FPM for straight holes, tapered hole should be somewhat slower about 300-350. The desired feed in inches/revolution is 0.003 to 0.010. Hole to be reamed should be undersize 0.005-0.015 inch diameter (reaming allowance).
- Cutting fluids: Soluble oil/mixture of kerosene and lard oil, light weight machine oil.

3.16.22 Sawing. It should be emphasized that the same principles which govern the shape of cutting tools for aluminum should be applied, as far as practicable to saws for aluminum.

3.16.22.1 Band Saws. Band saw blades of spring temper steel having a tooth spacing from 4 to 11 teeth per inch and with amply radiused gullets are recommended for aluminum alloys. Curved or copying cuts are made with band saws. In any type of work, high blade speed are desirable with a speed range from 1,500 to 5,000 FPM. For heavy sections the saw teeth should be fairly coarse with a slight set and a slight amount of front rake, the restricted chip space requires the use of coarser tooth spacing of about four teeth per inch to avoid clogging and binding. Also the flexible back type of saw with teeth hardened to the bottom of the gullet is used for heavy work. Blades having as many as 14 teeth per inch are satisfactory for thin materials. A good and simple general rule to follow when sawing aluminum is that the spacing of the teeth on band saws for aluminum should be as coarse as is consistent with the thickness of the material being sawed. The softer alloys require appreciably more blade set than do the harder, heat treated alloys. Usually an alternate side rake of about 15 degrees and a top rake or "hook" of 10-20° proves quite satisfactory. This amount of hook, however, requires a power feed and securely clamped work. For hand feeds the top rake must be reduced considerably to avoid overfeeding.

3.16.22.1.1 The band saw blades must be well supported by side rollers and back support both immediately below the saw table and about 2 or 3 inches above the work. The top blade supports are placed slightly in advance of those below the tables and the blade should be allowed to vibrate freely to eliminate excessive saw breakage. As a general rule, a noisy band saw is cutting more efficiently than the saw that cuts quietly. Quiet smooth cutting band saws usually produce smooth burnished surfaces accompanied by excessive heat and consequently decreased blade life.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

**3.16.22.2 Hack Saws.** Hack saw blades of the wavy set type are well suited for cutting aluminum by hand. The wavy set type of blade having 5 to 15 teeth per inch has sufficient chip space to avoid clogging and binding on aluminum alloys. For extremely fine work a jewelers blade may be used.

**3.16.22.2.1** Special routing machines are available which cut varied profiles from aluminum sheet or plate rapidly and efficiently.

**3.16.22.3 Lubricants and Coolants.** Power hacksaws and hand saws require a cutting lubricant for most operations involving thick sections. Soluble oil cutting compounds and neutral mineral-base lubricating oils applied to the sides of the blade aid in minimizing friction and gullet clogging. Light applications of heavy grease or paraffin wax will provide ample lubrication for some work. A wide selection of lubricants exists, ranging from tallow or grease stick to kerosene-thinned mineral base lubricating oil. Stick type lubricants should be applied very frequently. Experience has revealed in most cases it is more convenient and adaptable to use the fluid type lubricant applied freely through a recycling system directly to the blade and work stock.

**3.16.23 Grinding.** The grinding characteristics of the various aluminum alloys vary in many instances. The harder free-cutting aluminum alloys may be ground satisfactorily with free cutting commercial silicon carbide grinding wheels, such as crystalon, carborundum and natalon. Rough grinding operations are usually performed by use of resin bonded wheels of medium hardeners and grit sizes of 24 to 30. Also the aluminum abrasives from number 14 to number 36 have been found to be satisfactory for rough grindings.

**3.16.23.1** Common alloys, particularly in their softer tempers have a tendency to clog the wheels and do not finish to as bright and smooth a surface as the harder materials.

**3.16.23.1.1** Caution should be taken in selecting the proper grade of each commercial make of wheel. Once the grinding wheel has been selected there are three variables that affect the quality of a finish; these are the wheel speed, work speed and grinding compound. Experienced operators have proven that their own good judgement is a determining factor as to the correct wheel and work speeds, however, wheel speeds of about 6,000 FPM have given good results.

**3.16.23.1.2** For finish work, a soft silicon carbide wheel of 30 to 40 grit in a vitrified bond have proven to be very satisfactory. A grinding compound of soluble cutting oil and water works well. However, the fine grindings of aluminum must be strained from the compound before reusing in order to prevent deep scratches on the finished surface.

**3.16.23.1.3** Special care should be exercised when grinding castings and wrought alloy products that have been heat treated, since their greater resistance to cutting or grinding generates a considerable amount of heat which may cause warping and damage to the material.

**3.16.23.2 Lubricants and Coolants.** Generous applications of stick grease are recommended to prevent clogging of the grinding wheels during rough grinding, while copious quantities of a low viscosity coolant type grinding compound are essential and recommended for finish grinding. Soluble oil emulsions of the proportions of 30 or 40 to 1 are most suitable.

**3.16.24 Polishing.** Polishing or finishing aluminum and most of its alloys, by the application of proper machining procedures, gives it a smooth lustrous finish. Aluminum and its alloys are polished in the same manner as other metals, but a lower wheel-to-metal pressure is used for aluminum.

**3.16.24.1** Polishing is the act of removing marks, scratches or abrasion on the metal resulting from previous handling and operations; it must be understood that a more gentle cutting action or finer abrasives are used for polishing aluminum than used for steel. The various operations covered under the polishing category include roughing, greasing or oiling, buffing and coloring. These operations are briefly described in the following paragraph.

**3.16.25 Roughing.** This is a term used to describe the preliminary finishing operation or process, used to prepare aluminum surfaces having deep scratches gouges or unusually rough surfaces, for subsequent polishing procedures. Roughing is not required on smooth undented or unscratched surfaces. The preliminary finishing or roughing process usually employs a flexible aluminum oxide paper disc, a semi flexible bonded muslin or canvas wheel, faced with suitable abrasives. Usually 50-100 grit abrasives are for this process and are set in an adhesive in accordance with standard practice. The peripheral speed of these discs runs around 6,000 FPM; faster wheel speeds would cause heating or ridging of the soft metal surface. Heating is also reduced by small applications of tallow or a tallow oil mixture.



3.16.26 Greasing or Oiling. This is a refined or gentle roughing procedure for finishing aluminum surfaces. Application is visually employed by a soft wheel faced with 100 to 200 grit aluminum oxide emery, plus a light coat of tallow or beeswax lubricant to prevent excessive heating. Here again, peripheral speeds of about 6,000 FPM are used.

3.16.26.1 Greasing or oiling is a necessary operation in finishing coatings and other fabricated work which has been marred by previous operations. Excess aluminum pick-up on the wheels as results from overheating will cause deep scratches in the metal.

3.16.27 Buffing. This is a term used to describe a finishing procedure employed to obtain a smooth high luster on an aluminum surface. This high luster finish is obtained by use of a fine abrasive, such as tripole powder mixed with a grease binder, which is applied to the face of the wheel. These wheels usually consist of muslin discs sewed together, turned at a peripheral speed of 7,000 FPM.

3.16.27.1 Many factors, such as, the thread count of the buff, the pressure applied to the buff against the work, the buffing compound used, the speed of the buff or wheel and the skill and experience of the operator must be considered in obtaining a satisfactory and quality type finish.

### 3.17 HARDNESS TESTING.

Hardness is the resistance of a metal to deformation by scratching penetration or indentation, and is usually a good indication of strength. Metal hardness can be measured accurately by the Brinell, Rockwell or Vickers Process.

3.17.1 Brinell Hardness. The Brinell technique is usually used to obtain the hardness of aluminum and aluminum alloys. This hardness value is obtained by applying a load through a ball indenter and measuring the permanent impression in the material. To obtain the hardness value of a material, divide the applied load in kilograms by the spherical area of the impression in square millimeters. Hardness value of aluminum alloy is tested by applying a load of 500 kilograms to a ball ten millimeters in diameter for 30 seconds.

### 3.18 NON-DESTRUCTIVE TESTING/INSPECTION.

Aluminum and aluminum alloys are susceptible to stress risers resulting from notching, nicking or scratching. A very close visual inspection is required of all raw material prior to any forming or machining operations. Before any fabrication commences it is necessary that all scratches, nicks and notches be removed by sanding, polishing and filing.

3.18.1 Anodizing Process for Inspection of Aluminum Alloy Parts. Parts for which anodic coating is applicable in accordance with MIL-A-8625 Type I, can be anodized for the inspection of defects as cited in Specification MIL-1-8474.

3.18.1.1 The parts are examined visually for indications of cracks, forging laps or other defects. Parts inspected by this method shall be limited to sheet stock and surface defect of forgings. This method of inspection is not acceptable for inspection of parts subject to internal defects, i.e. inclusion in castings and forging or any part subject to internal stress, etc.

3.18.1.2 Defects are indicated by darkening of cracked or void areas after the anodic treatment. Insufficient rinsing in cold water after anodizing produces stains which may be confused with defects. In case of doubt strip film from part and reanodize. If the indications do not reappear the defects shall be considered absent and part should not be rejected for that reason.

#### NOTE

For additional general information on inspection and testing see Chapter 8 of this TO.

3.18.2 Aluminum Alloy Effects on Scratches on Clad Aluminum Alloy. The purpose of the following information on the effects of scratches on aluminum alloys is to assist in eliminating controversy in depots and field inspection, regarding serviceability of aluminum alloy, sheet, skin and aircraft structural parts which have been scratched, abraded or discolored from the stand point of corrosion resistance and fatigue strength.

3.18.2.1 In some instances, serviceable aluminum alloy parts and sheets, have been disposed of due to lack of knowledge by inspection personnel as to the effect of various depth scratches on the strength and corrosion resistance of the clad alloy. Also, attempts have been made to remove scratches from aircraft skin by sanding, buffing, or polishing resulting in removal of much of the cladding material and causing decrease in strength and corrosion resistance.



3.18.3 Allowable Defects. The following surface defects are those which do not affect the strength or corrosion resistance.

- Scratches which penetrate the surface layer of clad aluminum alloy sheets or parts but do not extend beneath the cladding are not serious or detrimental.
- The presence of small corroded areas will not materially affect the strength of clad unless the corroded pitted area extends through the cladding down to or into the bare metal. Clean corroded areas thoroughly by authorized methods (see [Paragraph 3.20](#)).
- Stains are not grounds for rejection since they affect neither the strength nor the corrosion resistance.

3.18.4 Harmful Scratches.



No attempt will be made to remove scratches or other surface defects by sanding or buffing since the protective layer of cladding will be removed by such operations. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

Scratches which extend through the cladding and penetrate the core material act as notches and create stress concentrations which will cause fatigue failure if the part is highly stressed or subjected to repeated small stress reversals. However, sheets so scratched may be utilized for non-stressed applications.

3.18.5 Inspection. Assemblies fabricated from clad aluminum-alloy sheets will not be rejected by inspection personnel, unless the defect is of sufficient depth to adversely affect the mechanical properties or cover sufficient area to impair the corrosion resistance of the assembly. Scratches or abrasions which penetrate the cladding will not affect corrosion resistance. Scratches resulting from the normal handling and processing of clad aluminum-alloy sheet rarely extend through the cladding and penetrate the core.

3.18.6 Test for Depth of Scratches. Since it is very difficult to measure the depth of a scratch on a sheet without cross sectioning the sheet, it has been found convenient (on clad material) to use a "spot" test to determine whether or not a scratch extends through the cladding.

3.18.6.1 On alloys except 7075 and 7178 the "spot" test is made by placing a drop of caustic solution (10 percent by weight of sodium hydroxide, in water) on a portion of the scratch, and allowing it to react for 5 minutes. The caustic solution will then be rinsed off the sheet with water, and the spot allowed to dry. If a black residue remains in the base of the scratch at the spot tested, it indicates that the scratch extends to the core. If no black color is visible and only a white residue remains in the base of the scratch, it indicates that the scratch does not penetrate through the cladding. For alloys 7075 and 7178 a drop of 10 percent cadmium chloride solution will produce a dark discoloration within two minutes if the scratch penetrates the clad. The cadmium chloride applied as above will not cause 2024 to discolor within two minutes.

3.18.6.2 When making the "spot" test to determine whether a scratch extends to the core, it is advisable for comparison purposes to spot test an adjacent area in which there are no scratches. It is then easier to determine whether the residue which remains is black or white.



DRY CLEANING SOLVENT, MIL-PRF-680

3

3.18.6.3 Before making the "spot" test, the sheet area will be cleaned and degreased with solvent MIL-PRF-680 (replaced Federal Specification P-D-680), or other suitable solvent, so that the caustic solution will react properly.

3.18.6.4 Caution will be exercised to make sure that all of the caustic solution is removed from the sheet by thorough rinsing, since the caustic solution is very corrosive to aluminum and aluminum alloys. Care will be taken not to use excessive amounts of the caustic solution for the same reason and it is preferable that only one drop be used for each test. The caustic solution will be prepared fresh for each series of tests to be made.



### 3.19 DISPOSITION OF SCRATCHED SHEETS/PARTS.

All scratched clad aluminum-alloy sheets will be utilized to the fullest extent. Serviceable portions of damaged sheets will be used in the manufacture of smaller parts and assemblies. Only that portion of sheet that is scratched and otherwise damaged beyond serviceability will be administratively condemned.

3.19.1 Air Weapon Parts. Parts (air weapon) shall be closely inspected as cited and if they do not meet specified requirement shall be condemned and replaced as directed.

### 3.20 CLEANING OF ALUMINUM ALLOY SHEET (STOCK).

#### 3.20.1 Dry Cleaning Solvent.



DRY CLEANING SOLVENT, MIL-PRF-680

3

Stubborn or exceptionally oily sheets may be cleaned by using solvent, MIL-PRF-680 or CID A-A-59601 or MIL-PRF-32095, before cleaning with alkali solution. The cleaning will be accomplished by brushing, soaking, scrubbing and wiping. Material or equipment that would scratch or abrade the surface shall not be used. Also material shall not be stored after solvent cleaning and prior to alkaline cleaning, unless solvent is completely removed from the surfaces of the metal.

#### 3.20.2 Alkali Cleaning Solution.



Do not use strong alkali solution because it will etch the aluminum. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

Composition of solution is 4 to 6 ounce of cleaner specification MIL-C-5543 to one gallon of water. The material is cleaned by immersing in the solution (as prepared by instructions cited in [Paragraph 3.20.3](#)) for 4-6 minutes, thoroughly rinsing in water (fresh tap) and then completely drying. Never pile/store material while damp, wet or moist. Refer to TO 00-85A-23-1 for packaging and storage.

#### 3.20.3 Preparation.



Do not use strong alkali solution because it will etch the aluminum. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

Use water heated to a temperature of 170 °F (77 degree Celsius (°C)). Add not more than one pound of cleaner at a time. Prepare the solution in the following manner:

- a. Fill the tank 1/2 to 2/3 full of water.
- b. Carefully dissolve the alkaline cleaner.
- c. Add water to operating level and stir thoroughly with a wooden paddle or other means.

##### 3.20.3.1 Maintain solution in the following manner:

- a. Add tap water to balance-up solution loss.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

- b. Make addition as required to maintain the active alkali concentration between 4 and 6 ounces alkaline cleaner for each gallon of water added and stir thoroughly.
- c. Prepare a new solution when contamination impares the cleaning ability of the solution.
- d. Clean the tank thoroughly before preparing a new solution.

**3.20.4 Nitric-Hydrofluoric Acid Cleaning.** The solution shall consist of 1 gallon technical nitric acid (58-62 percent Nitric-Hydrofluoric) (39.5° Beryllium).

- a. 1/2 pint technical hydrofluoric acid (48 °HF) (1.15 Sp), 9 gallons of water.
- b. Parts shall be immersed for 3 to 5 minutes in cold acid (50-105 °F).

**NOTE**

The sheet will stain when rinsed with sodium dichromate. The stronger the solution the darker the stain. A light detectable stain is desired on corroded areas. If the stain is dark reduce the amount of sodium dichromate added to rinse water.

**3.20.4.1** After removing from the acid, the parts shall be washed in fresh hot or cold running water for a sufficient length of time to thoroughly remove the acid. Diluted solution of sodium dichromate) 12 to 14 ounces per gallon of water, shall be added to the rinse water as a corrosion inhibitor. The rinsing time depends upon the freshness of the solution, size of the part and the amount of solution circulated. One half hour or less should be sufficient. Parts shall then be completely dried by blasting with compressed air or other approved method.

**3.20.4.2** Corrosion Removal and Treatment of Aluminum Sheets When Immersion Is Not Practical.



ALKALINE WATER BASE CLEANING COMPOUND, MIL-PRF-87937

1

**3.20.4.3** The surface shall be cleaned with water base cleaner, Specification MIL-PRF-87937.

**3.20.4.3.1 Heavily Soiled Areas.** Dissolve the contents of two 5-pound packages in 10 gallons of water. Stir with a wooden paddle until fully dissolved.

**3.20.4.3.2 Lightly Soiled Areas.** Dissolve four 5-pound packages in 50 gallons of water (a 55 gallon drum is suitable for this purpose). Agitate thoroughly with wooden paddle to ensure proper mixture.

**3.20.4.3.3 Application.** Apply the solution by spraying, or with a mop, sponge, or brush. Allow to remain on the surface for several minutes while agitating with a brush. Rinse thoroughly with a spray or stream of water. Do not allow solution to dry before rinsing as less effective cleaning will result.



### 3.20.5 Corrosion Removal.



CORROSION REMOVING COMPOUND, SAE AMS-1640

2



Metal conditioner and brightener is for use only on aluminum alloys, and it shall not be used just for the sake of improving the appearance of material. Material in storage shall not be treated with this material more than one time. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

To remove corrosion products use a metal conditioner and brightener, Specification SAE AMS-1640.

- a. Prepare the brightening solution by mixing Specification SAE AMS-1640 compound with an equal amount of water, in a rubber pail.
- b. Apply enough diluted brightener to completely cover the area being treated with a nonmetallic bristle brush.
- c. Agitate the brightener by scrubbing with a non-metallic bristle brush. Depending on the ambient temperature and amount of corrosion deposits present, allow approximately 5 to 10 minutes from application of brightener before rinsing. When using brightener at high ambient temperature (above 80 °F) leave brightener on for shorter periods of time. Do not leave brightener on the surface longer than necessary to dissolve the corrosion.
- d. Rinse the brightener from the surface (using approximately 50 gallons of water per minute. Ensure that all traces of brightener have been removed (shown by no foaming or bubbles while rinsing).

### 3.20.6 Chromate Conversion Coating.



IRIDITE NO. 14-2 CHEMICAL FILM, MIL-DTL-5541

4





CORROSION REMOVING COMPOUND, SAE AMS-1640

2

**WARNING**

- Any absorbent material used in applying or wiping up MIL-DTL-5541 material shall be rinsed in water before discarding. They are extreme fire hazards if allowed to dry otherwise. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- Do not permit Specification MIL-DTL-5541 material to contact paint thinner, acetone or other combustible materials. Fire may result. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

**CAUTION**

Avoid brushing or rubbing the newly applied chemical conversion coating, since it is soft and can be easily rubbed off the surface before completely drying. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

**NOTE**

- A light (just visible to the naked eye) evenly dispersed conversion coating is all that is required. It is recommended that a test panel be prepared and subjected to complete cleaning/treating procedure before applying material to a sheet. The test panel shall be used to determine the dwell time of MIL-DTL-5541 material. When clear material is being used, no control of discoloration is necessary.
- After the procedures cited in [Paragraph 3.20.6](#) through [Paragraph 3.20.8.1](#) have been complied with, an AF Form 50A will be attached to each sheet with a statement that, "This material has been cleaned and treated for corrosion in accordance with TO 1-1A-9 Chapter 3, date ....." If original markings are removed as a result of the cleaning and treatment process, the material shall be remarked (staggered) at each end and in the middle with the Specification, size/thickness, temper and type or grade. The marking may be applied with Black paint Specification TT-L-50, MIL-E-7729 or "Magic Marker" manufactured by Speeddry Products Inc., Richmond Hill, New York or "Equal". A felt tip pen may also be used.

Chromate Conversion Coating Specification MIL-DTL-5541, for aluminum alloys. Aluminum alloys which are treated with Specification SAE AMS-1640 shall be treated with Specification MIL-DTL-5541. Most solutions conforming to Specification MIL-DTL-5541 leave a stain. A clear Specification MIL-DTL-5541 coating is available (reference QPL 5541) and should be used when a bright metal finish is desired.

- a. Mix the solution in a stainless steel, rubber or plastic container; not in lead, copper alloy or glass.
- b. Mix in accordance with manufacturers instructions.
- c. Apply the conversion coating (light) by using a fiber bristle brush or a clean, soft cloth. Keep the surface wet with the solution until a coating is formed which may take from 1 to 5 minutes depending on the surface condition of the metal.

**NOTE**

Do not permit excess conversion coating to dry on the metal surface because the residue is difficult to flush off with water.

- d. Rinse with clear water, or sponge the area with a clean, moist cloth, frequently rinsing the cloth in clear water. Thorough rinsing is required.
- e. Allow the surface to air dry. To speed drying the surface may be blown dry with warm clean air (140 °F maximum).



### 3.20.7 Packaging, Packing and Storage of Aluminum Alloy Sheets.



IRIDITE NO. 14-2 CHEMICAL FILM, MIL-DTL-5541

4

For Packaging, Packing, and Storage of Aluminum Alloy Sheets and Plates, refer to TO 00-85A-23-1.

3.20.8 Anodic Coatings for Aluminum. Anodizing is the anodic process of treating aluminum alloys; a thin film of artificially produced oxide is formed on the surface of the metal by electrochemical reaction. Military Specification MIL-A-8625 lists the requirements of aluminum anodizing, and TO 42C2-1-7 gives the anodizing process.

3.20.8.1 Military Specification MIL-DTL-5541 lists the requirements for corrosion protection and paint base of aluminum by the use of chemical film. These chemical films are substitutes that may be used in lieu of anodic films, and may be applied by spray, brush, or immersion as specified by QPL-5541. The anodizing method is preferable to chemical films on aluminum parts where facilities are available. For process procedures applying to chemical films, refer to TO 1-1-8 and TO 1-1-2.







## CHAPTER 4

### MAGNESIUM ALLOYS

#### 4.1 CLASSIFICATION.

Magnesium alloys are produced and used in many shapes and forms, i.e.. castings, extruded bars, rods, tubing, sheets and plate and forgings. They are suitable for varied stress and non-stress aerospace applications. Their inherent strength, light-weight, shock and vibration resistance are factors which make their use advantageous. The weight for an equal volume of magnesium is approximately two-thirds of that for aluminum and one-fifth of that for steel. The current system used to identify magnesium alloys, is a two letter, two or three digit number designation in that order. The letters designate the major alloying elements, (arranged in decreasing percentage order, or in alphabetical order if the elements are of equal amounts), followed by the respective digital percentages of these elements. The percentage is rounded off to the nearest whole number or if a tolerance range of the alloy is specified, the mean of the range (rounded off to nearest whole number) is used. A suffix letter following the percentage digits, denotes the latest qualified revision of the alloy. For example: Alloy Designation AZ92A would consist of 9 percent (mean value) aluminum and 2 percent (mean value) zinc as the major alloying elements. The suffix "A" indicates this is the first qualified alloy of this type. One exception to the use of the suffix letter is that an "X" denotes that impurity content is controlled to a low limit. Some of the letters used to designate various alloying elements are:

1. A - Aluminum
2. E - Rare Earth
3. H - Thorium
4. K - Zirconium
5. M - Magnesium
6. Z - Zinc

#### 4.2 DEFINITIONS.

**4.2.1 Hardness.** Is the resistance of a metal to plastic deformation from penetration, indentation, or scratching. The degree of hardness is usually a good indication of the metals strength. The hardness of a metal can be accurately measured using the Brinell or Rockwell process of testing. [Table 4-4](#), [Table 4-5](#) and [Table 4-6](#) list the nominal hardness of various magnesium alloys. Brinell hardness testing is explained in [Chapter 8](#) of this manual.

**4.2.2 Tensile Strength.** The useful tensile strength of a metal is the maximum stress it can sustain in tension or compression without permanent deformation. The yield strength is that point of stress, measured in pounds per square inch, at which permanent deformation results from material failure. The data in [Table 4-4](#), [Table 4-5](#) and [Table 4-6](#) lists the nominal yield strengths of various alloys. The yield point in magnesium is not reached abruptly, but rather a gradual yielding when the metal is stressed above the proportional limit. Tensile and yield strengths decrease at elevated temperatures.

**4.2.3 Temper.** Is the condition produced in the alloy by mechanically or thermally treating it to alter its mechanical properties. Mechanical includes cold rolling, cold working, etc.; thermal includes annealing, solution and precipitation heat treat and stabilization treating. See [Paragraph 4.2.8](#) for temper designations.

**4.2.4 Shear Strength.** Is the maximum amount (in Pound-force per Square Inch (PSI)) in cross sectional stress that a material will sustain before permanent deformation or rupture occurs.

**4.2.5 Elongation.** Is the linear stretch of a material during tensile loading measured before and after rupture. In magnesium it is the increase in distance which occurs when stretch is applied between two gage marks placed 2 inches apart on the test specimen. After rupture the two pieces are fitted together and remeasured. The elongation is the percentile difference of the amount of stretch in ratio to the original 2 inches.



## TO 1-1A-9

### NAVAIR 01-1A-9

**4.2.6 Physical Properties.** Magnesium, in its pure state, has a specific gravity of 1.74, weighing 0.063 pounds per cubic inch. Similar data for magnesium alloys are included in [Table 4-6](#) as well as other physical property information.

**4.2.7 Chemical Properties.** Chemically bare magnesium is resistant to attack by alkalis, chromic and hydrofluoric acids and many organic chemicals including hydrocarbons, aldehydes, alcohols, phenols, amines, esters and most oils. It is susceptible to attack by salts and by galvanic corrosion from contact with dissimilar metals and other materials. Adequate protection of the metal against unfavorable conditions can be maintained generally, by using proper surface finish and assembly protection. The chemical property constituents of the various alloys are listed in [Table 4-3](#).

**4.2.8 Temper Designation System.** The hyphenated suffix symbol which follows an alloy designation denotes the condition of temper, (heat treat or strain hardening), to which the alloy has been processed. These symbols and their meanings are listed below: (Heat treating itself is discussed in subsequent paragraphs of this section of the manual). Added suffix digits 2, 4, 6, 8, to the H1, H2, H3 symbols indicate the degree of strain hardening, i.e., 2 = 1/4 hard, 4 = 1/2 hard, 6 = 3/4 hard, and 8 = full hard.

-AC	As-Cast
-F	As-fabricated
-O	Annealed
-W	Solution heat treated - unstable temper
-T	Treated to produce stable tempers other than for -O
-T2	Annealed (cast products only)
-T3	Solution heat treated and then cold worked
-T4	Solution heat treated
-T5	Artificially aged only
-T6	Solution heat treated and then artificially aged
-T7	Solution heat treated and stabilized
-T8	Solution heat treated, cold worked and then artificially aged
-T9	Solution heat treated, artificially aged and then cold worked
-T10	Artificially aged and then cold worked
-H1	Strain hardened only
-H2	Strain hardened and partially annealed
-H3	Strain hardened and stabilized

## 4.3 SAFETY REQUIREMENTS FOR HANDLING AND FABRICATION OF MAGNESIUM ALLOYS.

### WARNING

Magnesium thorium alloys shall be handled, stored and disposed of through applicable disposal procedures. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

There are two special major areas of safety precautions to observe in proceeding of magnesium alloys other than general shop safety practices. One is the fact some alloys contain thorium, a radioactive element (e.g., HK31A, HM21A, HM31A) and the other is the low melting point/rapid oxidation (fire hazard) characteristics of the metal. Where the application of heat is to be made to a thorium alloy, both of these areas must be considered.

**4.3.1 Magnesium-Thorium Alloys (HK31, HM21, HM31, HZ32, ZH42, ZH62).** Magnesium-Thorium Alloys (HK31, HM21, HM31, HZ32, ZH42, ZH62) are mildly radioactive but are within the safe limits set by the Atomic Energy Commission (AEC) and represent no hazard to personnel under normal conditions. A standard of 0.1 milligrams per cubic meter of thorium in air is a safe limit for continuous atmospheric exposure and is readily met in processing magnesium alloys containing up to 10 percent thorium. For example: Stirring alloy melt of 5 percent thorium content resulted in 0.002 milligrams per cubic meter atmospheric contamination and grinding air alloy of 3 percent thorium content gave thorium contamination in the breathing zone ranging from 0.008 to 0.035 milligrams per cubic meter. Only long exposure to fine dust or fumes need cause concern as to radioactive toxicity of magnesium-thorium. Normal dust control precautions, followed to avoid fire hazards, can be expected to control any health hazards that might result from fine dust in grinding the low thorium content alloys. In



welding these alloys without local exhaust, concentrations of thorium above the tentative limit of 0.1 milligrams per cubic meter of air were found in the breathing zone. Use of local exhaust reduced thorium concentrations to well within acceptable limits. If ventilation is such that the visible fumes flow away from the welder, it is adequate, providing such fumes are not permitted to accumulate in the immediate vicinity. An alternate practice involves use of ventilated welder's hood, if there is not sufficient room ventilation to control contamination of the general atmosphere. Thorium containing scrap and wet grinding sludge may be disposed of by burning providing an AEC amendment is secured for the basic AEC license. If burned, the ashes which will then contain the thorium, must be disposed of in accordance with AEC Standards for Protection Against Radiation 10 CFR Part 20. As an alternative the ashes or scrap may be turned over to an AEC licensed scrap dealer, through applicable disposal procedures.

4.3.1.1 For indoor storage of thorium alloy sheets and plates, the size of stacks should be limited to 1000 cubic feet with an aisle width not less than one-half the stack's height. Such storage is within the normal recommendations for fire safety.

4.3.1.2 Radiation surveys have shown that exposure of workers handling the referenced thorium alloys is well within the safe limits set by the AEC. Assuming hand contact, the body one foot away from the alloy for an entire 40 hour work week, the exposure would be 168 millirems to the hands and 72 millirems to the whole body. These are maximum values which probably would not be approached in actual practice. The corresponding AEC permissible safe limits are 1500 millirems/week for the hands and 300 millirems/week for the whole body.

4.3.1.3 Despite the relative safety present in the handling, to rage and processing of thorium containing alloys, it is mandatory that all such actions be made according to the requirements and restrictions of the 00-100 series technical orders, as applicable, and AEC regulations. As previously stated, the normal precautions taken in the shop processing of magnesium will suffice for safe handling of thorium alloys. These precautions are noted in the following paragraphs on safety precautions.

4.3.2 **Safety Precautions for All Alloys (Including Fire Hazards).** Since magnesium will ignite and burn fiercely when heated to a point near its melting temperature, certain precautions should be taken during working of it.

4.3.2.1 **Machining Safety Rules.** During machining operations, observance of the following rules will control any potential fire hazard:

- a. Keep all cutting tools sharp and ground with adequate relief and clearance angles.
- b. Use heavy feeds to produce thick chips.
- c. Machine the metal dry whenever possible, avoiding fine feeds and keeping speeds below 500 - 700 Surface Feet per Minute (SFM) during turning and boring. If a coolant is definitely required use a mineral oil.
- d. Keep work areas clean.
- e. Store magnesium chips in clean, plainly labeled, covered, non-combustible containers where they will remain dry. Do not allow chips to accumulate on machines or operator's clothing. Machinists should not wear textured or fuzzy clothing and chips and sawdust should not be allowed to accumulate in cuffs or pockets.
- f. Do not permit tools to rub on the work after a cut has been made.
- g. Keep an adequate supply of a recommended magnesium fire extinguisher within reach of the operators. If chips should become ignited, extinguish them as follows:

**WARNING**

Water or any of the common liquid or foam type extinguishers will intensify a magnesium chip fire and may cause an explosion and shall not be used. Failure to comply could result in injury to , or death of, personnel or long term health hazards.

- (1) Cover with a layer of G-1 or Met-L-X powder. Clean, dry unruined cast iron chips, graphite powder, clean dry sand, talc and pitch may also be used.



## TO 1-1A-9

### NAVAIR 01-1A-9

- (2) Actively burning fires on combustible surfaces should be covered with a 1/2 inch layer or more of extinguishing powder; then the entire mass shoveled into an iron container or onto a piece of iron plate. Alternately, a one or two inch layer of powder can be spread on the floor or surface nearby and the burning metal transferred to it, then add more powder as required.
- (3) High cutting speeds, extremely fine feeds, dull, chipped or improperly designed tools, tool dwell on work after feed is stopped, tool rub, or tool hitting a steel or iron insert increase the chances of chip ignition. Keeping the cutting speed below 700 feet per minute (FPM) will greatly reduce the fire possibilities even with a dull or poorly designed tool and fine feeds.

**4.3.2.2 Grinding and Polishing Safety Practices.** During grinding and polishing operations a proper dust collection system must be used. [Figure 4-1](#) illustrates acceptable type collectors. The dust produced during grinding and polishing of magnesium must be removed immediately from the working area with a properly designed wet type dust collection system. Proper systems precipitate the magnesium dust by a heavy spray of water and must be so designed that dust or sludge cannot accumulate and dry out to a flammable state. Small collectors as shown in [Figure 4-1](#), Detail A serving one or two grinders are the best. The grinder-to-collector ducts should be short and straight. The self opening vents illustrated prevent hydrogen collection during shut down. The grinder's power supply, air exhaust blower and liquid level controller should be electrically water connected so cessation or failure of the dust collector operation will shut the grinder off. In addition a suitable device should be installed in the system that will ensure the collector system is in full operation and has changed the air in the ducts, etc., several times before the grinder begins running. Dry type filter collectors or central collector systems which carry the dust through long dry ducts should not be used for magnesium. The collector portrayed in [Figure 4-1](#), Detail B is used with booth type portable grinding and polishing where the dust passes through the grate with the air being circulated into a liquid spray which removes the dust. Design the booth to catch all the dust possible. On individual grinders for small scale work, as shown in [Figure 4-1](#), Detail C, the hood design and the oil pan combine to afford a satisfactory dust collection. Any dust escaping the hood should be kept swept up and properly disposed of.

**4.3.2.3** The following specific safety rules pertain to the grinding and polishing of magnesium:

- a. Magnesium grinding should be done on equipment set aside and labeled for that purpose. Do not grind sparking material on these grinders unless the magnesium dust has been completely removed from the equipment system. In addition, the grinding wheel or belt must be replaced prior to grinding of any other metal.
- b. If chrome pickled magnesium is to be ground, sparks may result. Therefore, dust and air-dust mixtures must not be allowed to accumulate within spark range.
- c. Maintain adequate supplies of plainly labeled approved fire extinguishing powder and suitable dispensing tools readily available to operators. Fire control is the same as detailed in [Paragraph 4.3.2.1](#) for machine chips.
- d. Keep dust from accumulating on surrounding floors, benches, windows, etc. If such accumulation is evident the collector system is not operating properly and must be checked and repaired. Periodically and no less than once a month, completely clean the entire collector systems. Inspect and clean the grinder to collector ducts daily or move frequently if the volume of collection is high.
- e. Dispose of grinding sludge as soon as it is removed from the equipment. Do not store or allow to even partially dry since it is extremely flammable. This may be done by spreading it on a layer of fire brick or hard burned paving brick to a maximum depth of 3-4 inches, then placing a combustible material on top of it and burning the entire lot. The sludge will burn with intense heat, therefore, a safe location must be used. A method of rendering magnesium sludge chemically inactive and non-combustible by reacting it with a 5 percent solution of ferrous chloride (Fe C122H20) is detailed in the National Fire Protection Association's Bulletin Number 48, Standards for Magnesium.
- f. The clothing of operators should be smooth and fire retardant without pockets and cuffs. Caps should be worn. All clothing should be easy to remove and kept free of dust accumulations.

**4.3.3 Heat Treating Safety Practices.** Heat treating of magnesium alloys requires the exercising of certain definite rules, if safe and good quality workmanship is to result. The following rules should be closely followed:

- a. Use furnace equipment having two sets of temperature controls, operating independently of each other.
- b. Standardize checking procedures and adjustments of all equipment and of operating cycles.



- c. Load the furnace with castings of one identical alloy only. Ensure the castings are clean.
- d. Use Sulfur Dioxide atmosphere to control oxidation.
- e. Use the recommended time and temperature operating ranges at all times.
- f. Provide approved fire extinguishing equipment.

**WARNING**

Water and other extinguishers for Class A, B, and C fires shall not be used. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

4.3.3.1 If a fire should occur for any reason, as evidenced by excessive furnace temperature and omission of a light colored smoke, proceed as follows:

- a. Shut off all power, fuel and Sulfur Dioxide feed lines to the furnace.
- b. Notify fire marshal control crew at once.
- c. Begin fire extinguishing procedures using one of the following methods:
  - (1) Using G-1 Powder Method. Where it can be safely done, a small fire should be removed from the furnace, dumped into an iron container and then extinguished by covering with G-1 powder which is a graphite base powder of the Pyrene Carbon Dioxide Company. Metal Fyr Powder of the Fyr Fyter Company is the same material. In large furnaces or with fires of high intensity, the powder can be applied to the burning parts with a shovel (assuming the furnace door can be opened safely). Paper bags filled with the powder can be used if the fire is so located that such bags can be thrown in effectively. Remove parts not burning with long handled hooks. After all burning parts have been covered with the powder, the furnace load should be allowed to cool with the door open. For the handling of large quantities of G-1 powder, pumps have been constructed which can throw 75-100 pounds per minute onto the fire through a 30 foot hose and nozzle.



**BORON TRIFLUORIDE**

6

Boron trifluoride vapor or gas is toxic in the proportion of more than 1 part per million by volume of air when exposures are prolonged or frequently repeated. Five parts per million by volume of air or more are usually present in visible clouds of material resulting from the release of the gas to atmosphere. Therefore, personnel must not enter such clouds or any area where there is reason to believe the safe level is exceeded unless wearing a gas mask with an acid gas canister containing a dust filler. Analysis of atmosphere in the worker's breathing zone will be accomplished to assure personnel safety. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

- (2) Using Boron Trifluoride Gas Method. This is an effective gaseous means of extinguishing magnesium fires in heat treating furnaces. The gas is introduced into the furnace from a storage cylinder through an entry port preferably located near floor level. Connect the gas feed line to this port, open the feed line valve to provide about 2 pounds per minute (depending on furnace size and number of gas cylinders) and maintain gas flow until furnace temperature drops to 700 °F indicating the fire is out. The furnace door should be kept closed during this action and until a definite temperature drop below 700 degrees Fahrenheit (°F) is evident. Running the furnace circulating fans for about 1 minute after the gas is first introduced will assist in gas dispersal, then shut the fan off. The gas cylinder used should be fitted with a Monel needle valve and a "tee" for attaching a 0-160 PSI pressure gauge. A suitable gas transfer system uses a 5/16 inch flexible bronze hose to carry the gas to the furnace where it enters through a 1 1/4 inch steel pipe entry port. Using 10 feet of hose and feed of pipe, a gauge pressure of 15-30 PSI will deliver 1-2 pounds of Boron Trifluoride per minute. The cylinders may be permanently connected or brought to the furnace, when needed, on a suitable dolly. This gas does not require heating in order to flow. The cylinders should be weight checked for contents every 6 months.



- (3) Using Boron Trichloride Gaseous Method. This material has been successfully used to extinguish magnesium heat treat furnace fires. However, there are several factors involved with its use which makes it less preferred than boron trifluoride, these include: ten times more concentration than the 0.04 percent of boron trifluoride, the gas must be heated to flow freely; it is more expensive than trifluoride; the liquid is corrosive and the fumes irritating with a health hazard similar to hydrochloric acid fumes. Workmen should not occupy areas where noticeable vapors are present unless wearing a gas mask with an acid gas canister containing a dust filter. If this agent must be used, the liquid containing cylinders should be heated with infrared lights to provide the heat necessary to ensure adequate gas flow. The cylinder outlet should be fitted with a special valve and gauge to control gas flow. Flexible 5/8 inch inside diameter neoprene hose may be used to connect the cylinder to a steel pipe for insertion into the furnace port. Otherwise its use in extinguishing a furnace fire is similar to the procedures for boron trifluoride.

4.3.4 Identification of Alloy. Positive identification of an alloy, from a constituency standpoint, can only be determined by laboratory analysis. However, whether a light metal is magnesium or not can be generally determined by a simple test consisting of placing the test metal in contact with an 0.5 percent solution of silver nitrate, and observing the reaction for 1 minute. The solution is made by dissolving 0.5 grams of silver nitrate in 100 milliliter of water. Formation of a black deposit of metallic silver on the metal indicates magnesium or high-magnesium alloy. Then immerse the metal in a chrome pickle chemical solution, Type I Specification MIL-M-3171 (Commercially known as DOW Number 1). The solution should be freshly prepared and the test operator familiar with the colors of chemical treatment. If the metal assumes a very bright brassy coating, it indicates it is aluminum free alloy. If a greyish iridescent coating forms the alloy contains aluminum. The solution is made in the proportions of 24 ounces sodium dichromate and 24 fluid ounces concentrated nitric acid to enough water to make one gallon. Prior to the test the metal should be thoroughly cleaned down to the base metal, if necessary, by grinding or filing a clean area on the surface.

#### 4.4 HEAT TREATING MAGNESIUM ALLOYS - GENERAL

##### NOTE

- SAE-AMS-M-6857, Heat Treatment of I Magnesium Alloy Castings, will be the control for heat treatment of magnesium alloy castings used on aerospace equipment. For complete description of magnesium alloy castings heat treat requirements, refer to latest issue of SAE-AMS-M-6857.
- Additional Heat Treatment information is discussed in Chapter 9.

4.4.1 Precautions During Heating. Of first importance in the heat processing of these alloys is a clear understanding of the characteristics of the metal relative to heat. Pure magnesium will melt at approximately 1202 °F. The alloys melting points range from 830-204 °F, approximately, according to their element constituency. Therefore, during any heating of alloy items, specified temperature maximums must be closely adhered to, particularly during solution heat treating. The metal is easily burned and overheating will also cause formation of molten pools within it, either condition resulting in ruining of the metal. Certain alloys such as AZ63A Type 1, or AZ92A Type 1, are subject to eutectic melting of some of its elements if heated too rapidly. They must be brought up to heat treating temperature slowly enough to prevent this. In the case of these two examples, no less than two hours should be consumed in bringing them from 640 °F to treating temperature.

4.4.1.1 An additional and no less important characteristic of the metal relative to heat treatment, is that it is subject to excessive surface oxidation at 750 °F and higher temperatures. In an oxidizing atmosphere, this characteristic can result in ignition and fierce burning. To prevent such occurrences, a protective atmosphere containing sufficient sulphur dioxide, carbon dioxide or other satisfactory oxidation inhibitor shall be used when heating to 750 °F and over. When oxidation inhibitors are used, their concentration percentage in the furnace atmosphere should be periodically checked for correct amounts. The particular requirements for various alloys are detailed in [Paragraph 4.5](#) in this section. These requirements and those of other pertinent specifications and instructions should be consulted and strictly adhered to in processing the metal. The safety measures defined in [Paragraph 4.1](#) must be rigidly practiced.

4.4.2 Heat Treating Equipment. Furnaces used for solution heat treatment shall be of the air chamber type with forced air circulation. Heating provisions can be gas, electricity or oil. Their design must be such as to make impossible, direct heating element radiation or flame impingement on the articles being treated. The furnaces shall be installed with the necessary control, temperature measuring and recording instrument equipment to assure complete and accurate control. The temperature control shall be capable of maintaining a given temperature to within  $\pm 10$  °F at any point in the working zone, after the charge has been brought up to this temperature. Each furnace used shall be equipped with a separate manual reset safety cut-out which will turn off the heat source in the event of any malfunction or failure of the regular automatic controls. The safety cut-outs shall be set as close as practicable above the maximum solution heat treating temperature for the alloy being treated. This will be above the variation expected but shall not be more than 10 °F above the maximum heat treat temperature of the



alloy being processed. There shall also be protective devices to shut off the heat source in case of circulation air stoppage. These devices shall be interconnected with a manual reset control.

4.4.2.1 Upon initial furnace installation and after any maintenance on the furnace or its equipment which might affect its operational characteristics, a temperature survey shall be made to test its TO 1-1A-9 capability of maintaining the minimum and maximum temperatures required for the various treatments it will be used for. A minimum of 9 test locations within the furnace load area should be checked. One in each corner, one in the center and one for each 25 cubic feet of furnace volume up to the maximum of 400 cubic feet. A monthly survey should be made after the initial survey, unless separate load Thermocouples (TCs) are employed, to record actual metal temperatures. The monthly survey should consist of one test for a solution heat treat temperature and one test for a precipitation heat treat temperature, one for each 40 cubic feet of heat treating volume with a minimum, of 9 test locations required regardless of the volume. In addition, a periodic survey should be made, using the test criteria of the initial survey. For all surveys, the furnaces should be allowed to heat to a point stabilization before taking any readings. The temperature of all test locations should be determined at 5 to 10 minute intervals after insertion of the temperature sensing elements in the furnace. The maximum temperature variation of all elements shall not exceed 20 °F and shall not exceed the solution or precipitation heat treating range at any time after equilibrium is reached.

4.4.2.2 Furnace control temperature measuring instruments shall not be used as test instruments during any survey. The thermocouple and sensing elements should be replaced periodically because of the in-service incurred effects of oxidation and deterioration.

4.4.2.3 Pyrometers used with the automatic control system to indicate, maintain and record the furnace temperatures, should preferably be of the potentiometer type.

4.4.2.4 Suitable jigs, fixtures, trays, hangers, racks, ventilators and other equipment shall be used in processing the articles.

4.4.3 Heat Treatment Solution. Solution for heat treating of magnesium alloyed articles is accomplished by heating at an elevated temperature in an air furnace for a specific length of time (holding period); during which certain alloying elements enter into uniform solid solution, since the alloys tend to become plastic at high heat treat temperatures, it is mandatory that suitable support be provided for articles being processed to prevent warping. [Table 4-8](#) lists the recommended soaking and holding time for solution heat treating alloys. The holding periods given are for castings up to 2 inches thick. Items thicker than 2 inches will require longer periods.

4.4.3.1 AZ92A (Type 2), AZ91C and QE22A sand castings and AM100A permanent mold castings may be charged into the furnace which is at the heat treating temperature. Since magnesium castings are subject to excessive surface oxidation at temperatures of 750 °F and over, a protective atmosphere containing sufficient sulphur dioxide, carbon dioxide or other satisfactory oxidation inhibitor shall be used when solution heat treating at 750 °F and over. The whole casting must be heat treated, not just part of it.

4.4.3.2 Precipitation heat treatment or artificial aging of alloys is accomplished at temperature lower than those of the solution treatment. Suggested aging treatments for various alloys are as cited in [Table 4-9](#).

4.4.3.3 Stabilization heat treating an alloy increases its creep strength and retards growth at service encountered elevated temperatures. The same general procedure of heating to temperature, holding for a time and cooling to room temperature is used as in the other two types, only the temperature and time elements are different. When applied to a solution treat treated alloy, it increases the alloy's yield strength. Actually stabilization treatment is a high temperature aging treatment accomplished quickly rather than allowing an alloy to age naturally over a period of time.

4.4.3.4 Annealing of magnesium alloys is accomplished to relieve internal stresses, generally resulting from forming operations; soften the material for forming; improve the ductility; and/or refine the grain structure. The alloy is heated to the proper temperature, soaked or held at that temperature for a specified time and cooled to room temperature. The desired effects are gained by controlling the temperature, hold time and cooling medium exposure. Avoid excessive time at temperature to prevent unwanted grain growth. Conversely, no attempt should be made to shorten the time at temperature and over all annealing time by increasing the temperature, since elements of the alloy subject to melting points lower than the alloy itself can go into solution.

4.4.4 Heat Treating Procedures. Placing of articles to be treated in the furnace, (generally referred to as charging the furnace), should not be done in a haphazard fashion. Individual pieces should be racked or supported to prevent distorting without interfering with the free flow of the heated atmosphere around the article. Distortion or warping can occur due to the semi-plastic qualities of the alloys at the furnace elevated temperatures during solution heat treat. Distortion is not a particular problem during precipitation or stabilization treatment or annealing. However, it is good practice to handle magnesium alloy



## TO 1-1A-9

### NAVAIR 01-1A-9

articles with care at all times under elevated heat conditions. In the case of complicated formed parts, it may be necessary to utilize a specially contoured jig or fixture to adequately protect the design contour of the item at high temperatures.

#### 4.5 ALLOY GENERAL CHARACTERISTIC INFORMATION.


In the following paragraphs are brief summaries of the general characteristics of the various alloys.

- a. AM100-A - Used in pressure tight sand end permanent mold castings with good combination of tensile strength, yield strength and elongation. Solution heat treat in 0.5 percent Sulfur Dioxide atmosphere 20 hours at 790 °F; cool in strong air blast. Partially artificial aging -12 hours at 325 °F; cool in still air. Completely artificial age 5 hours at 450 °F; cool in still air or oven. Aging increases basic yield strength and hardness and decreases toughness and elongation.
- b. AZ31B and C - Used in low cost extruded bars, rods, shapes, structural sections and tubing with moderate mechanical properties and high elongation sheet and plate; good formability and strength, high resistance to corrosion, good weldability. Liquid temperature 1170 °F; solid 1120 °F. Hot working temperature is 450-800 °F. Annealing temperature 650 °F. Stress relief of extrusions and annealed sheet = 500 °F for 15 minutes; hard rolled sheet = 300 °F for 60 minutes. Foreign equivalents are: British DTD 120A Sheet, 1351350 forgings; German and Italian, Electron AZ31; French - SOC Gen Air Magnesium, F3 and T8.
- c. AZ61A - Use in general purpose extrusions with good properties, intermediate cost; press forgings with good mechanical properties. Rarely used in sheet form. Hot working temperature 350-750 °F; shortness temperature above 780 °F. Anneal 650 °F. Heat treat annealed sheet extrusions and forgings 15 minutes at 500 °F rolled sheet 400 °F for 15 minutes. Foreign equivalents are British BS 1351 (forgings) BS 1354 (extrusions); German AZM.
- d. AZ63A - Used in sand castings for good strength properties with best ductility and toughness. Solution heat treat at 740 °F in a 0.5 percent Sulfur Dioxide<sub>2</sub> atmosphere for 10 hours then cool in air. Aging is done at 450 °F for 5 hours and cooled in air or furnace. Stabilize at 300 °F at 4 hours and cool in air. Foreign equivalents are Elektron AZG, British DTD59A (as cast) and DTD-289 (heat treated). Good salt water anti-corrosion properties.
- e. AZ80A - Used for extruded and press forged products. Heat treatable. Hot working temperature 600-750 °F. Shortness temperature above 775 °F, annealing temperature 725 °F. Stress relief: as extruded, 500 °F for 15 minutes, extruded and artificially aged 400 °F for 60 minutes; forgings 500 °F for 15 minutes. Foreign equivalents are British 1351 (forgings); German AZ855 Helium or Argon-arc weldable using AZ92A welding rod or may be resistance welded. Stress relieve after welding.
- f. AZ81A - Used in sand or permanent mold castings for good strength, excellent ductility, pressure tightness and toughness. Readily castable with low micro-shrinkage tendency. Solution heat treat 775 °F for 18 hours, cool in air or by fan. Stabilizing treatment 500 °F, 4 hours and air cool. To prevent germination (grain growth) an alternate heat treat of 775 °F for 6 hours, 2 hours at 665 °F and 10 hours at 775 °F may be used.
- g. AZ91A, AZ91B - AZ91A - used for die castings generally.
- h. AZ91 C - AZ91B - is also die cast alloy but has higher impurity content. AZ91C is used for pressure tight sand and permanent mold castings having high tensile and weld strength. Shortness temperatures are above 750 °F. Heat treat: T-4 condition, 16 hours at 780 °F, cool in air blast and then age at 400 °F for 4 hours; T-7 condition, 5 hours at 450 °F. Foreign equivalents are Elektron AZ91 and British DTD136A. Good impact resistance in T-4 temper. T-6 has good yield strength and, ductility.
- i. AZ92A - Used in pressure tight sand and permanent mold castings. Has high tensile and yield strengths. Solution heat treat 20 hours at 760 °F in an atmosphere of 0.5 percent Sulfur Dioxide. Cool in strong air blast. Artificial aging is done at 420 °F for 14 hours. Cool in air or oven. Stabilize for 4 hours at 500 °F, then cool in air. Equal to AX63A in salt water corrosion resistance.
- j. EK30A - Used in sand casting for elevated temperature applications. Has good strength properties in temperature range 300-500 °F. Solution heat treat at 1060 °F maximum 16 hours then cool in air by fan. Age at 400 °F then air cool.
- k. EK41A - Used as pressure tight sand casting alloy. Good strength at 300 -500 °F. Solution heat treat at 1060 °F maximum 16 hours then cool in air or with fan. Age at 400 °F 16 hours, air cool.




- l. EZ33A - Used for pressure tight, good strength sand and permanent mold castings where temperatures may reach 500 °F in use. Age at 420 °F for 5 hours. Foreign equivalent British ZRE1.
- m. HK31A - Used in sand castings for elevated temperature use up to 650 °F and sheet and plate applications. Has excellent weld and forming characteristics in sheet/plate form and retains good strength up to 650 °F. Hot working temperature is 800-1050 °F. Anneal at 750 °F. Solution heat treat sand castings by loading into a 1050 °F furnace and holding for 2 hours, then fan or air cool. Age for 16 hours at 400 °F. H23 sheet may be stress relieved after welding at 650 °F for 1 hour or 675 °F for 20 minutes. Sheet may be resistance welded.
- n. HM31A - Used in extruded bars, rods, shapes and tubing for elevated temperature service. Exposure to temperatures through 600 °F for periods of 1000 hours caused practically no change in short time room and elevated temperature properties. Superior modulus of elasticity particularly at elevated temperatures. Hot work at 700-1000 °F.
- o. HZ32A - Used for sand castings. It is of properties for medium and long range exposure at temperatures above 500 °F and is pressure tight.
- p. KIQA - Casting alloy with comparatively low strength has excellent damping characteristics.
- q. MIA - Used for wrought products and provides for moderate mechanical properties with excellent weldability, corrosion resistance and hot formability. Hot work at 560-1000 °F. Anneal at 700 °F. Stress relieve annealed sheet at 500 °F, in 15 minutes; hard rolled sheet at 400 °F in 60 minutes; and extrusions at 500 °F in 15 minutes. Foreign equivalents are British BS1352 (forgings) and German AM503.
- r. QE22A - Castings have high yield strength at elevated temperatures. Solution heat treat at 970-990 °F 4 to 8 hours. Quench in 150 °F water bath.
- s. TA54A - Best hammer forging alloy.
- t. ZE10A - Used for low cost, moderate strength sheet and plate. No stress relief required after welding. Hot work at 500-900°F. Anneal 400 °F. AZ61A or EX33A rod is preferred for welding.
- u. ZE41A - A good strength, pressure tight, weldable alloy, where temperatures are below 200 °F. Age 2 hours at 625 °F, air cool; 16 hours at 350 °F air cool. Foreign equivalent - British RZ5.
- v. ZH42A - Used in sand castings for aircraft engines and airframe structures where high strength at room temperatures and moderate longtime creep resistance at temperatures up to 480 °F are required. The alloy is a precipitation hardening one from the as-cast condition and requires no solution heat treatment. Maximum hardness is developed at 480 °F in 24 hours. More ductility and better shock resistance may be obtained by over aging at temperatures such as 750 °F. For T51 condition treat at 480 °F for 24 hours; T4 condition 750 °F for 24 hours.
- w. ZH62A - Used as a high strength good ductility structural alloy at normal temperatures and has the highest yield strength of any alloy except ZK61A-T6. Heat treat at 480 °F for 12 hours. Foreign equivalent is British T26.
- x. ZK21A - An alloy of moderate strength for extrusion fabrication. Good weldability using shielded arc and AZ61A or AZ92A, rod. Resistance welding also satisfactory. ZK51A - Used for high yield strength, good ductility, sand castings. Heat treat for 12 hours at 350 °F. Foreign equivalent is British Z52.
- y. ZK60A - Used as a wrought alloy for extruded shapes and press forgings. Has high strength and good ductility characteristics. Hot work at 600-750 °F. Shortness temperature is 950 °F. Age at 300 °F for 24 hours, air cool. Foreign equivalent is German ZW6.
- z. ZK61A - Casting Alloy. Solution heat treat at 925-935 °F for 2 hours or 895-905 °F for 10 hours.




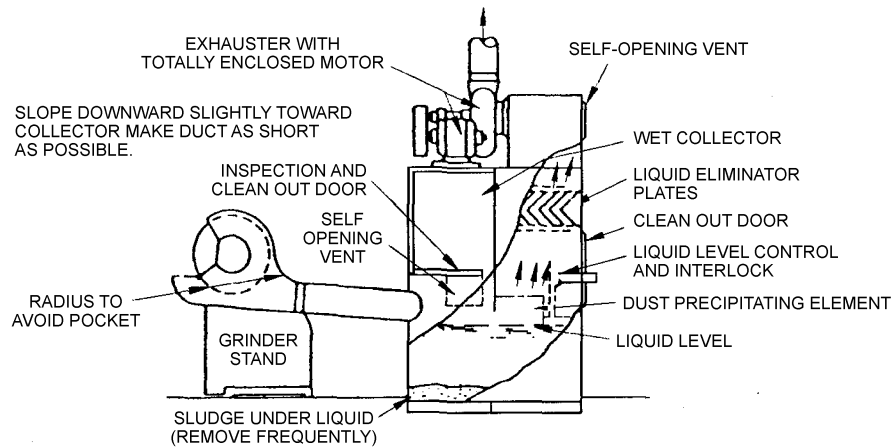

**A** TYPE OF DUST COLLECTOR FOR USE WITH GRINDING WHEEL STANDS.

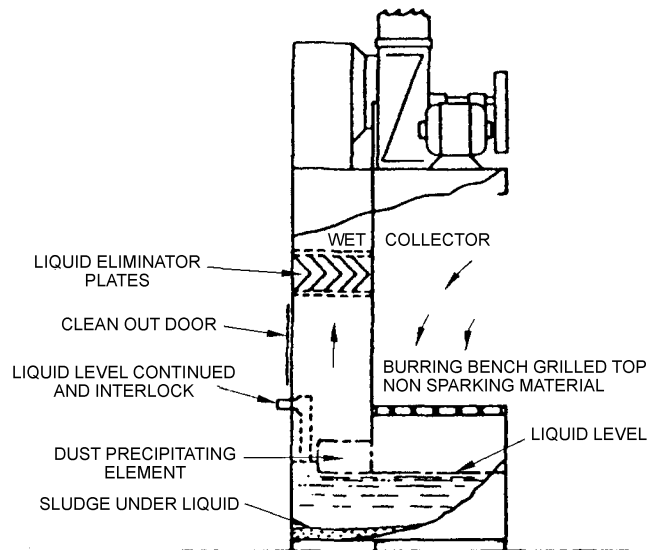

**B** BENCH TYPE DUST COLLECTOR FOR USE WITH PORTABLE GRINDING OR POLISHING TOOLS.

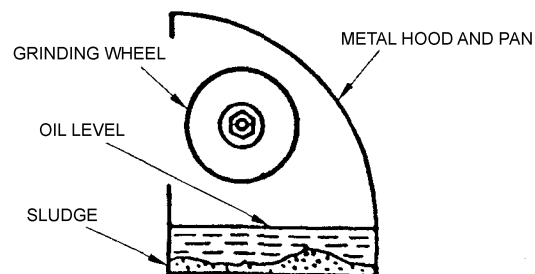

**C** TYPE OF DUST COLLECTOR FOR SMALL WHEELS USED ONLY INTERMITTENTLY AND WHEN SMALL AMOUNTS OF METAL ARE REMOVED.

TO-1-1A-9-014

**Figure 4-1. Typical Dust Collectors for Magnesium**



Table 4-1. Cross-Reference, Alloy Designation to Specifications

Alloy	Fed Spec.	Mil Spec.	Hnbk	Society of Automotive Engineers (SAE) Aeronautical Material Specification (AMS)	ASTM (ASME)	Use
AM100A	QQ-M-56 QQ-M-55		502	4483	B80 B199	Sand Casting Permanent Mold Casting
AZ31B	QQ-M-31		52		B107	Extruded Bars, Rods, Shapes
AZ31C	QQ-M-40	MIL-R-6944	510		B91	Forgings
	WW-T-825		52		B217	Extruded Tubes
	QQ-M-44		510	4375	B90	Sheet and Plate
	QQ-M-44		510	4376	B90	Sheet and Plate
	QQ-M-44		510	4377	B90	Sheet and Plate
					B260	Welding Rod
					B107	Extruded Bars, Rods, Shapes
					B217	Extruded Tubes
					B90	Sheet and Plate
AZ61A	QQ-M-31		520	4350	B107	Extruded Bars, Rods, Shapes
	QQ-M-40		530	4358	B91	Forgings
	WW-T-825		520	4350	B217	Extruded Tubes
		MIL-R-6944			B260	Welding Rod
AZ63A	QQ-M-56	MIL-C-19163	50	4420, 4422	B80	Sand Castings
	QQ-M-56	MIL-C-19163	50	4424	B80	Sand Castings
	QQ-M-55	MIL-C-19163			B199	Permanent Mold Castings
		MIL-R-6944			B260	Welding Rod
AZ80A	QQ-M-31		523		B107	Extruded Bars, Rods, Shapes
	QQ-M-40		532	4360	B91	Forgings
AZ81A	QQ-M-56		505		B80	Sand Castings
	QQ-M-40		505		B199	Permanent Mold Castings
AZ91A	QQ-M-55				B199	Permanent Mold Castings
	QQ-M-38		501	4490	B94	Die Castings
AZ91B	QQ-M-38		501		B94	Die Castings
AZ91C	QQ-M-56		504	4437	B80	Sand Castings
	QQ-M-55				B199	Permanent Mold Castings
AZ92A	QQ-M-56	MIL-C-19163	500	4434	B80	Sand Castings
	QQ-M-55	MIL-C-19163	503	4484	B199	Permanent Mold Castings
		MIL-R-6944			B260	Welding Rod
EK30A	QQ-M-56				B80	Sand Castings
EK41A	QQ-M-56			4440, 4441	B80	Sand Castings
	QQ-M-55				B199	Permanent Mold Castings
EZ33A	QQ-M-56		506	4442	B80	Sand Castings
	QQ-M-55		506		B199	Permanent Mold Castings
		MIL-R-6944			B260	Welding Rod
HK31A*	QQ-M-56		507	4445	B80	Sand Castings



Table 4-1. Cross-Reference, Alloy Designation to Specifications - Continued

Alloy	Fed Spec.	Mil Spec.	Hnbk	Society of Automotive Engineers (SAE) Aeronautical Material Specification (AMS)	ASTM (ASME)	Use
*		MIL-M-26075	507	4384	B90	Sheet and Plate
		MIL-M-26075 MIL-R-6944		4385	B260	Welding Rod
HK21A*	QQ-M-40	MIL-M-8917		4390	B90	Forgings Sheet and Plate
HM31A*		MIL-H-8916		4388	B107	Extruded Bars, Rods, Shapes
		MIL-H-8916		4389		Extruded Bars, Rods, Shapes
HZ32A*	QQ-M-56			4447	B80	Sand Castings
KIA	QQ-M-56	MIL-M-45207			B80	Sand Castings
MIA	QQ-M-31		522		B107	Extruded Bars, Rods, Shapes
	QQ-M-40		533		B217 B90 B260	Forgings
	WW-T-825		522			Extruded Tubes
	QQ-M-44		51			Sheet and Plate Welding Rod
QE22A	QQ-M-56 QQ-M-55					Sand Castings Permanent Mold Castings
TA54A	QQ-M-40		53		B91	Forgings
ZE10A			534		B90	Sheet and Plate
ZE41A	QQ-M-56					Sand Castings
ZH42*						Sand Castings
ZH62*	QQ-M-56		508	4438	B80	Sand Castings
ZK21A		MIL-M-46039		4387		Extrusions
ZK51A	QQ-M-56		509	4443	B80	Sand Castings
ZK60A	QQ-M-31		524	4352	B107	Extruded Bars, Rods, Shapes
ZK60B	QQ-M-40		524	4362	B91	Forgings
	WW-T-825			4352	B217	Extruded Tubes Extruded Bars, Rods, Shapes
ZK61A	QQ-M-56		513	4444	B80	Sand Castings
*These alloys contain radioactive thorium element. See <a href="#">Paragraph 4.3.1</a> for precautionary instructions.						
MISC SPECIFICATION MIL-M-3171 Magnesium alloy, processes for corrosion protection of SAE-AMS-M-6857 Magnesium alloy casting, heat treatment of						



Table 4-2. Alloy Designation Cross-Reference

New Designator	Former Dow Revere	Former American Magnesium	Former * Military	New Federal	Use
AZ63A	H	AM265		QQ-M-56	Castings, Sand
MIA	M	AM3S	AN-M-26	QQ-M-31	Extruded Bars, Rods, Shapes
MIB	M	AM403	AN-M-30	QQ-M-56	Castings, Sand
MIA	M	AM3S	AN-T-73	WW-T-825	Extruded Tube
MIA	M	AM3S	AN-M-22	QQ-M-40	Forgings
MIA	M	AM3S	AN-M-30	QQ-M-44	Sheet
A292A	C	AM260		QQ-M-56	Castings, Sand
AZ92A	C	AM260		QQ-M-55	Castings, Perm Mold
AM100A	G	AM240		QQ-M-55	Castings, Perm Mold
AZ91A	R	AM263	AN-M-16	QQ-M-38	Castings, Die
AZ31B	FS-1	AM52S	AN-M-27	QQ-M-31	Extruded Bar, Rod, Shape
AZ31B	FS-1	AM52S	AN-T-72	WW-T-825	Extruded Tube
AZ31B	FS-1	AM52S			Forgings
AZ31B	FS-1	AM52S	AN-M-29	QQ-M-44	Sheet
AZ61A	J-1	AMC57S	AN-M-24	QQ-M-31	Extruded Bar, Rod, Shape
AZ61A	J-1	AMC57S	AN-T-71	WW-T-825	Extruded Tubes
AZ61A	J-1	AMC57S	AN-M-20	QQ-M-40	Forgings
AZ80A	0-1	AMC58S	AN-M-25	QQ-M-31	Extruded Bar, Rod, Shape
AZ80A	0-1	AMC58S	AN-M-21	QQ-M-40	Forgings
ZK60A		AMA76S		QQ-M-31	Extruded Bar, Rod, Shape
EX41A		AMA130			Castings, Perm Mold
EZ33A		AMA131			Castings, Perm Mold
TA54A		AM65S		QQ-M-40	Forgings

**NOTE**

\* These "AN" Specifications have been superseded by the listed Federal Specifications.



Table 4-3. Chemical Properties of Magnesium Alloys

Alloy	Aluminum	Magnesium	Zinc	Zirconium	Rare Earth	Thorium	Silicon	Copper	Nickel	Magnesium	Forms
AM100A	9.3-10.7	0.10	0.30 maximum 0.6-1.4				0.30	0.10	0.01	Bal	Castings, sand, perm mold Extruded Bars, rods, shapes tubes = sheets
AZ31B(1)(2)	2.5-3.5	0.20					0.10	0.05	0.005	Bal	Same Castings, sand, and perm mold
AZ31C	2.4-3.6	0.15	0.5-1.5				0.10	0.10	0.03	Bal	Extruded Bars, rods, shapes, forgings
AZ63A(2)	5.3-6.7	0.15	2.5-3.5				0.10	0.05	0.005	Bal	Castings, sand, and perm mold
AZ80A	7.8-9.2	0.12	0.2-0.8				0.30	0.25	0.01	Bal	Extruded Bars, rods, shapes, forgings
AZ81A	7.0-8.1	0.13	0.40-1.0				0.30	0.10	0.01	Bal	Castings, sands, and perm mold
AZ91A	8.1-9.3	0.13	0.4-1.0				0.30	0.10	0.01	Bal	Castings, perm mold
AZ91A	8.1-9.7	0.13	0.4-1.0				0.50	0.10	0.03	Bal	Castings, Die
AZ91B	8.3-9.7	0.13	0.4-1.0				0.50	0.30	0.03	Bal	Castings, Die
AZ91C	8.1-9.3	0.13	0.4-1.0				0.30	0.10	0.01	Bal	Castings, sand and perm mold
AZ92A	8.3-9.7	0.10	1.6-2.4				0.30	0.25	0.01	Bal	Same
EK30A			0.3 maximum	0.20 minimum	2-3.0			0.10	0.01	Bal	Castings, sand only
EK41A			0.3	0.4-1.0	3.0-5.0			0.10	0.01	Bal	Castings, sand and perm mold
EZ33A			2.0-3.1	0.5-1.0	2.5-4.0			0.10	0.01	Bal	Castings, Sand/Sheet Plate
HK31A*		0.15 maximum	0.3	0.4-1.0		2.5-4.0		0.10	0.01	Bal	Castings, Sand/Sheet Plate
HM21A*		0.45-1.1				1.5-2.5				Bal	Forgings, Sheet/Plate
HM31A*		1.2 minimum				2.5-3.5				Bal	Extruded Bars/Rods/Shapes
HZ32A*			1. 7-2.5	0.5-1.0	0.1 maximum	2.5-4.0		0.10	0.01	Bal	Castings, Sand
K1A				0.4-1.0						Bal	Castings, Sand
M1A(l)		1.2					0.10	0.05	0.01	Bal	Extruded Bars, rods, shapes tube-sheets-forgings



Table 4-3. Chemical Properties of Magnesium Alloys - Continued

Alloy	Alumi- num	Manga- nese	Zinc	Zirconium	Rare Earth	Thorium	Silicon	Copper	Nickel	Mag- nesium	Forms
QE22A(3)				0.4-1.0	1.8-2.5			0.10	0.01	Bal	Castings, sand
TA54A(4)	3.0-4.0	0.20	0.3 maximum				0.30	0.05	0.01	Bal	Forgings
ZE10A			1.0-1.5		0.12-0.22					Bal	Sheet and Plate
ZE41A			4.25	0.5	1.25					Bal	Castings, Sand
ZH42*			3.0-4.5	0.5		1.5-2.5				Bal	Castings, Sand
ZH62A*			5.2-6.2	0.5-1.0		1.4-2.2		0.10	0.01	Bal	Castings, Sand
ZK20A			2.0-2.6	0.45 minimum						Bal	Extrusions
ZK51A			3.6-5.5	0.5-1.0				0.10	0.01	Bal	Castings, Sand
ZK60A			4.8-6.2	0.45						Bal	Extruded Bars/Rods/ Shapes Tube-Forgings
ZK60B			4.8-6.8	0.45				0.10	0.01	Bal	

NOTE

\*These alloys contain radioactive thorium. See [Paragraph 4.3.1](#)

- (1) Calcium, AZ31B, 0.04---MIA, 0.4.0.14
- (2) Iron, AZ31B, 0.005---AZ61A, 0.005---AZ63A, 0.005.
- (3) Silver, QE22A, 2.5-3.0.
- (4) Tin, TA54A, 4.6-6.0.



Table 4-4. Mechanical Properties Magnesium Extrusions and Forgings at Room Temperature - Typical

Alloy and Condition	Form	(Diameter Thickness- Inches)	Cross Sectional Area (Inches)	Minimum Tensile Str (1000 PSI)	Minimum Ten Yld Str (1000 PSI)	Minimum Elongation (2 inch Percent)	Minimum Shear Str (1000 PSI)	Hardness (Brinell)
AZ31B-F	Bars, Rods, shapes	0.249 and under	All areas	35	21	7	17	
AZ31C-F	Hollow shapes	0.250-1.499	All areas	35	22	7	17	49
		0.500-2.499	All areas	34	22	7	17	
		2.500-4.999	All areas	32	20	7		
		All dimensions	All areas	32	16	8	17	49
AZ61A-F	Bars, Rods, shapes	0.249 and under	All areas	38	21	8		
Hollow shapes	Hollow shapes	0.250-1.499	All areas	39	24	9	18	60
		0.250-4.999	All areas	40	22	7		
		All dimensions	All areas	36	16	7	18	60
AZ80A-F	Bars, Rods, shapes	0.249 and under	All areas	43	28	9	19	60
T-5	Same	0.250-1.499	All areas	43	28	8	19	60
		1.500-2.499	All areas	43	28	6	19	60
		2.500-4.999	All areas	42	27	4		60
		0.249 and under	All areas	47	30	4		82
		0.250-2.499	All areas	48	33	4	21	82
		2.500-4.999	All areas	45	30	2		82
HM31A-T5*	Bars, Rods, shapes	Not applicable	Under 4.000	37	26	4		
M1A-F	Bars, Rods, shapes	0.249 and under	All areas	30	not required	2		44
		0.250-1.499	All areas	32	not required	3	15	44
		1.500-2.499	All areas	32	not required	2	15	44
		2.500-4.999	All areas	29	not required	2		44
		All dimensions	All areas	28	not required	2	15	44
ZK60A-F	Bars, Rods, shapes	All dimensions	4.999 and under	43	31	5	22	75
			5.000-29.999	43	31	4	22	75
		All dimensions	All areas	40	28	5		
		All dimensions	4.999 and under	45	36	4	22	82



Table 4-4. Mechanical Properties Magnesium Extrusions and Forgings at Room Temperature - Typical - Continued

Alloy and Condition	Form	(Diameter Thickness; Wall Thickness-Inches)	Cross Sectional Area (Inches)	Minimum Tensile Str (1000 PSI)	Minimum Ten Yld Str (1000 PSI)	Minimum Elongation (2 inch Percent)	Minimum Shear Str (1000 PSI)	Hardness (Brinell)
	Hollow shapes	All dimensions	All areas	46	38	4	22	82
			EXTRUDED TUBES					
AZ31B-F		0.050-0.500	Not applicable	32	16	8		46
AZ31C-F								
AZ61A-F		0.050-0.500	Not applicable	28		2		42
M1A-F		0.050-0.500	Not applicable	40	28	5		75
ZK60A-F		0.050-0.250	Not applicable	46	38	5		75
ZK60A-T5		0.050-0.250	Not applicable	46	38	4		82
			DIE FORG-INGS					
AZ31B-F				34	19	6	17	55
AZ61A-F				38	22	6	19	55
AZ80A-F				42	26	5	20	69
AZ80A-T5				42	28	2	20	72
T6				50 (typical)	34 (typical)	5 (typical)		72
M1A				30	18	3	14	47
IA54A-F				36	22	7		
ZK60A-T5				42	26	7		
<p style="text-align: center;"><b>NOTE</b></p> <p>This alloy contains radioactive elements. See <a href="#">Paragraph 4.3.1</a> for precautions.</p>								



Table 4-5. Mechanical Properties of Magnesium Alloy Sheet and Plate at Room Temperature - Typical

Alloy and Condition	Dimension Thickness (Inches)	Minimum** Tensile Strength (1000 PSI)	Minimum** Tensile Yield Str (1000 PSI)	Minimum Elongation (2 inch - - Percent)	Minimum Shear Strength (1000 PSI)	Hardness (Brinell)	Use
AZ31B-F	All gauges	35 (typical)	19 (typical)	12 (typical)			Tooling Plate
AZ31B-H10	0.251-2.000	30	12	10			Standard Plate
-H11	0.016-0.250	32	12	12			Standard Plate and Sheet
-H23	0.016-0.064	39	25	4			Standard Sheet
	0.065-0.064	39	25	4			and Plate
-H24	0.016-0.063	39	29	4	18	73	Specification Sheet and Plate
	0.065-0.250	39	29	4	18	73	Same
	0.251-0.500	37	24	10			Same
	0.501-1.000	38	22	10			Same
-H26	0.501-0.750	37	25	8			Same
	0.751-1.000	37	23	8			Specification Sheet and Plate
	1.001-1.500	35	22	8			
-0	0.016-0.060	32	18	12	17	56	Specification Sheet and Plate
	0.061-0.250	32	15	12	17	56	Same
	0.251-0.500	32	15	12			Same
	0.501-2.000	30	15	10			Same
AZ31C-F	All gauges	32	15	8		52	Tread plate
HK31A-0*	0.016-0.250	30	16	12			Sheet
	0.251-0.500	30	16	12			Sheet
	0.501-1.000	30	15	12			Sheet
	1.001-3.000	29	14	12			Sheet
-H24*	0.016-0.125	34	26	4	21 (typical)	57	Sheet
	0.126-0.250	31	22	4	21 (typical)	57	Sheet
	0.251-1.000	34	25	4	20 (typical)		Sheet
	1.001-3.000	33	25	4	20 (typical)		Sheet
HM21A-T8	0.016-0.250	31	18	4			Sheet and Plate
	0.251-0.500	32	21	6			Sheet and Plate
	0.501-1.000	30	19	6			Sheet and Plate
	1.001-2.000	29	18	6			Sheet and Plate
M1A-O	All gauges	33 (typical)	18 (typical)	17 (typical)	17 (typical)	48	Sheet and Plate
H	All gauges	35 (typical)	26 (typical)	7 (typical)	7 (typical)	54	
ZE10-0	0.016-0.060	30	18	15			Sheet and Plate



**Table 4-5. Mechanical Properties of Magnesium Alloy Sheet and Plate at Room Temperature - Typical - Continued**

Alloy and Condition	Dimension Thickness (Inches)	Minimum** Tensile Strength (1000 PSI)	Minimum** Tensile Yield Str (1000 PSI)	Minimum Elongation (2 inch - - Percent)	Minimum Shear Strength (1000 PSI)	Hardness (Brinell)	Use
H24	0.061-0.250	30	15	15			Sheet and Plate
	0.251-0.500	29	12	12			
	0.016-0.125	36	25	4			
	0.126-0.188	34	22	4			
	0.189-0.250	31	20	4			
* Contains radioactive thorium element. See <a href="#">Paragraph 4.3.2</a> for precautionary data.							
** Values given are all minimum unless otherwise noted beside value.							



Table 4-6. Mechanical Properties of Magnesium Alloy Castings at Room Temperatures

Alloy and Condition	Tensile Strength (1000 PSI)		Tensile Strength Yield (1A000 PSI)		Typical Elongation Inch 2 -- Percent		Shear Strength (1000 PSI)	Hardness (Brinell)
	Type	Minimum	Type	Minimum	Type	Minimum		
AM100-F	22	20	12	10	2		18	54
-T4	40	34	13	10	10	6	20	52
-T6	40	34	16	15	4	2	21	69
-T61	40	34	22	17	1		21	69
AZ63A-F	29	24	14	10	6	4	16	50
-T4	40	34	14	10	12	7	17	55
-T5	30	24	16	10	4	2	17	55
-T6	40	34	19	16	5	3	19	73
AZ81A-T4	40	34	14	10	12	7	17	55
AZ91C-F	24	18	14	10	2.5		16	52
-T4	20	34	14	10	11	7	17	55
-T5	23	23	12	12	2			
-T6	40	34	19	16	5	3	19	73
AZ92A-F	24	20	14	10	2	1	16	65
-T4	40	34	14	10	10	6	17	63
-T5	26	20	17	11	1		16	80
-T6	40	34	21	18	2	1	20	84
EK30A-T6	23	20	16	14	3	2	18	45
EK41A-T5	23	20	16	14	1		18.7	45
-T6	25	22	18	16	3	1	19.4	50
EZ33A-T5	23	20	15	14	3	2	19.8	50
HK31A-T6*	30	27	15	13	8	4	21	55
HZ32A-T5*	29	27	14	13	7	4	20	57
K1A-F	24	24	6	6	14	14		
QE22A-T6	35	35	25	25	2	2		
ZE41A-T5	28	28	19	19	2.5	2.5	23	62
ZH42-T51 *	32.5		21.6		4.5			
ZH42-T4*	33.6	35			12			
ZH62A-T5	35.0	35	22	22	4	5	24	70
ZK51A-T5	40	34	24	20	8	5	22	65
ZK61A-T6	39	39	26	26	5	5	26	68
				DIE CAST-INGS				
AZ91A-F	33		22		3		20	67
AZ91B-F	33		22		3		20	67

**NOTE**

\*This alloy contains radioactive thorium element. See [Paragraph 4.3.2](#) precautionary instructions.



Table 4-7. Physical Properties Magnesium Alloy at 68 °F

Alloy and Condition	Specific Gravity	Density Pounds/Cubic Inch	Melting Range °F	Electrical Conductivity Percentage of the International Annealed Copper Standard
AM100A-F	1.81	0.065	867-1101	11.5
-T4	1.81	0.065	867-1101	9.9
-T6	1.81	0.065	867-1101	12.3
AZ31B and AZ31C	1.77	0.064	1116-1169	18.5
AZ61A	1.80	0.065	977-1145	11.6
AZ63A-F	1.82	0.066	850-1130	15.0
-T4	1.82	0.066	850-1130	12.3
-T6	1.82	0.066	850-1130	13.8
AZ80A	1.80	0.065	914-1130	10.6
AZ81A	1.81	0.065	914-1132	12.00
AZ91A-AZ91B	1.81	0.065	875-1105	10.1
AZ91C-F	1.81	0.065	875-1105	11.5
-T4	1.81	0.065	875-1105	9.9
-T6	1.81	0.065	875-1105	11.2
AZ92A-AC	1.83	0.066	830-1100	12.3
-T4	1.83	0.066	830-1100	10.5
-T6	1.83	0.066	830-1100	12.3
EK30A	1.79	0.065	1100-1184	27.0
EK41A-T5	1.81	0.065	1193	24.0
-T6	1.81	0.065	1193	26.0
EZ33A	1.83	0.066	1010-1189	25.0
HK31A-T6	1.79	0.065	1092-1204	22.0
HM21A	1.77	0.064	1100-1195	
HM-31A-F	1.80	0.065	1121-1202	26.0
HM32A	1.83	0.066	1026-1198	26.5
MI-A	1.76	0.064	1200	34.5
TA54A	1.87	0.067		
ZE10A	1.76	0.063	1100-1200	
ZH42	1.86	0.067	1180	23.9
ZH62A	1.86	0.067	1180	26.5
ZK21A	1.80	0.645		
ZK51A	1.81	0.066	1020-1185	28.0
ZK60A-F	1.83	0.066	968-1175	29.0
-T5	1.83	0.066	968-1175	30.0
ZK60B	1.83	0.066	968-1175	31.0
ZK61A	1.80	0.065	1145	
<p><b>NOTE</b></p> <p>Percentage conductivity of annealed copper at 68 °F (International Annealed Copper Standard (IACS)).</p>				



**Table 4-8. Solution Heat Treating Temperatures and Holding Times**

Alloy	Temperature Range	Time Period (Hours)	Maximum Temperature °F
AM100A	790-800	16-24	810
AZ63A (Type I)	720-730 (F to T4)	10-14	734
AZ63A (Type 2)*	720-740 (F to T4)	10-14	745
AZ81A	770-785	16-24	785
AZ91C	770-785	16-24	785
AZ92A (Type 1)	760-770	16-24	775
AZ92A (Type 2)	775-785	14-22	785
HK31A	1045-1055	2	1060
QE22A**	970-990	4-8	1000
ZK61A	925-935	2	935
	or		
	895-905	10	935

\* Contains calcium.

\*\* Quench in 150 °F water bath within 30 seconds after opening of furnace.

**Table 4-9. Artificial Aging (Precipitation Treatment)**

Alloy and Temper	Aging Treatment
AM100A-T6	5 hours at 450 °F or 24 hours at 400 °F
AM100A-T5*	5 hours at 450 °F
AZ63A-T6	5 hours at 425 °F or 5 hours at 450 °F
AZ63A-T5*	4 hours at 500 °F or 5 hours at 450 °F
AZ91C-T6	16 hours at 335 °F or 4 hours at 420 °F
AZ92A-T6 (Type 1)	4 hours at 500 °F or 5 hours at 425 °F
AZ92A-T6 (Type 2)	5 hours at 450 °F or 16 hours at 400 °F or 20 hours at 350 °F
AZ92A-T5* (Type 2)	5 hours at 450 °F
EZ33A-T5*	2 hours at 650 °F or 5 hours at 420 °F or 5 hours at 420 °F
HK31A-T6	16 hours at 400 °F
HZ32A-T5*	16 hours at 600 °F
QE22A-T6	8 hours at 400 °F
ZH62A-T5*	2 hours at 625 °F or 16 hours at 350 °F
ZK51A-T5*	8 hours at 424 °F or 12 hours at 350 °F
ZK61A-T5*	48 hours at 300 °F
ZK61A-T6	48 hours at 265 °F

\*T5 is aged from as-cast condition. Others are aged from T4 condition.



## CHAPTER 5

# TITANIUM AND TITANIUM ALLOYS

### 5.1 CLASSIFICATION.

Titanium is produced in pure form as well as in various alloys. Pure titanium is commonly known as unalloyed. It can be cast, formed, joined, and machined with relative ease as compared to the various alloy grades. Unalloyed titanium cannot be heat treated. Therefore, its uses are limited to end items not requiring the higher strengths obtained from the heat treatable alloys. Titanium is a very active metal, and readily dissolves carbon, oxygen, and nitrogen. The most pronounced effects are obtained from oxygen and nitrogen. For this reason, any heating process must be performed in a closely controlled atmosphere to prevent the absorption of oxygen and nitrogen to a point of brittleness.

### 5.2 GENERAL.

**5.2.1 Military and Commercial Designations.** There are presently two military specifications in existence (see [Table 5-1](#)) covering alloyed and unalloyed titanium in classes established to designate various chemical compositions. For the selection of the proper class and form of stock required for a particular purpose, reference will be made to [Table 5-1](#).

**5.2.2 Physical Properties.** Limited physical properties are available on the titanium compositions covered by existing military specifications. Compared to other materials, the melting point of titanium is higher than that of any of the other construction materials currently in use. The density of titanium is intermediate to aluminum and steel. Electrical resistivities of titanium are similar to those of corrosion-resistant steel. The modulus of elasticity is somewhat more than half that of the alloy steels and the coefficient of expansion is less than half that of austenitic stainless steels.

**5.2.3 Mechanical Properties.** As previously pointed out, titanium is a very active metal and readily dissolves carbon, oxygen and nitrogen. All three elements tend to harden the metal; oxygen and nitrogen having the most pronounced effect.

**5.2.3.1** The control of these elements causes considerable difficulty in obtaining correct mechanical properties during the fabrication of titanium. This variation in mechanical properties is the cause of difficulties encountered in the fabrication of parts, since the absorption of small amounts of oxygen or nitrogen makes vast changes in the characteristics of this metal during welding, heat treatment, or any application of heat in excess of 800 degrees Fahrenheit °F.

**5.2.3.2** Operations involving titanium requiring the application of heat in excess of 800 °F must be performed in a closely controlled atmosphere by methods explained in future paragraphs. The nominal mechanical properties are listed in [Table 5-2](#).

**5.2.4 Methods of Identification.** Methods of distinguishing titanium alloys from other metals are simple and definite. One quick method is to contact the titanium with a grinding wheel. This results in a pure white trace ending in a brilliant white burst. Also, identification can be accomplished by moistening the titanium and marking the surface with a piece of glass. This leaves a dark line similar in appearance to a pencil mark. Titanium is non-magnetic. To positively identify the various alloys, a chemical or spectrographic analysis is necessary.

**5.2.5 Hardness Testing.** Hardness is the resistance of a metal to plastic deformation by penetration, indentation, or scratching, and is usually a good indication of strength. This property can be measured accurately by the Brinell, Rockwell or Vickers Technique. The hardness to be expected from the various alloys and unalloyed titanium is listed in [Table 5-2](#).

**5.2.6 Tensile Testing.** The useful strength of a metal is the maximum load which can be applied without permanent deformation. This factor is commonly called yield strength. The tensile strength of a metal is that load, in pounds per square inch, at which complete failure occurs. In the case of titanium the yield strength is the most important factor and is therefore used by industry to designate the various types of unalloyed titanium.

**5.2.7 Non-Destructive Testing.** Titanium and titanium alloys are highly susceptible to stress risers resulting from scratching, nicking, and notching. For this reason, close visual inspection is required of all raw stock prior to any forming or machining operations. All scratches, nicks and notches must be removed, before fabrication, by sanding and polishing.

**5.2.8 Fire Damage.** Fire damage to titanium and titanium alloys becomes critical above 1000 °F due to the absorption of oxygen and nitrogen from the air which causes surface hardening to a point of brittleness. However, an over-temperatured



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

condition is indicated by the formation of an oxide coating and can be easily detected by a light green to white color. If this indication is apparent following fire damage to titanium aircraft parts, the affected parts will be removed and replaced with serviceable parts.

**Table 5-1. Specification Cross Reference Titanium Alloys**

Composition/ Alloy Designa- tion	Form/Commodity	Specification Data <sup>△</sup>		
		Aeronautical Material Specification (AMS)	Military	Other <sup>△</sup>
COMMERCIALLY PURE (UNALLOYED)				
40KS1 (A-40 55A) YIELD	Sheet, Strip Plate	4902	( MIL-T-9046 Type I, COMP. A	A-40; HA1940; MST-40; RS-40; Ti-55A
	Tubing Welded	4941		A40; 55A
	Tubing Seamless	4942		
55KS1 (A55; 65A) Yield	Sheet, Strip Plate	4900	MIL-T-9046 Type I, COMP. C	A55; HA-1950; MST 55 RS55; Ti-65A; NA2-7123B
70KS1 (A70; 75A) Yield	Forgings		MIL-F-83142 Comp. 1	
	Sheet Strip Plate	4901	MIL-T-9046 Type I, COMP. B	A70; HA-1970; MST70 RS70; Ti-75A, NA2-7126G
70KS1 (A70; 100A)	Bars, Forgings and Forging Stock	4921	MIL-T-9046 Type I, COMP. A	A70; HA-1970; MST70 RS70; Ti-75A
ALPHA TITANIUM ALLOY				
5AL-2.5Sn (A110AT)	Sheet Strip, Plate	4910	MIL-T-9046 Type II, COMP. A	A-110AT; HA5137; 0.01 014; MST 5AL-2.5Sn; RS110C; Ti-5AL-2.5Sn; NA2-71269
	Bars and Forgings	4926 4966	MIL-T-9047 Comp. 2	A-110AT; HA5137; MST 5AL-2.5Sn; RS110C; Ti-5AL- 2.5Sn; NA2-7149A
5AL-2.5Sn EL1	Sheet Strip Plate	4909	MIL-T-9046 Type II, COMP. B	
	Bars and Forgings	4924	MIL-T-9047 Comp. 3	
5AL-SZr-5Sn	Sheet, Strip Plate		MIL-T-9046 Type II, COMP. C	
7AL-12Zr	Sheet, Strip Plate		MIL-T-9046 Type II, COMP. D	
7AL-2Cb-1Ta	Sheet, Strip Plate		MIL-T-9046 Type II, COMP. E	
8AL-1MO-IV	Sheet, Strip, Plate	4915 (Single annealed)	MIL-T-9046 Type II, COMP. F	
	Bars and Forgings		MIL-T-9047 Comp. 5	
	Bars, Rings	4972		
	Forgings (Solution heat treated and stabilized)	4973		
BETA TITANIUM ALLOYS				
13V-11Cr-3AL	Forgings		MIL-F-83142 Comp. 14	
	Bars and Forgings		MIL-T-9047 Comp. 12	
13.5V-11Cr- 3AL (B120VCA)	Plate, Sheet and Strips Solution Heat Treated	4917		B-120VCA; MST 13V-11Cr- 3AL; R120B; Ti-13V-11C4- 3AL
11.5 Molybdenum- 6Zr-	Bars and Forgings		MIL-T-9047 Comp. 13	
	Bars and Wire (Solu- tion Heat Treated)	4977		



Table 5-1. Specification Cross Reference Titanium Alloys - Continued

Composition/ Alloy Designation	Form/Commodity	Specification Data <sup>△</sup>		
		Aeronautical Material Specification (AMS)	Military	Other <sup>△</sup>
8Mn (C110M)	Sheet, Strip, Plate	4908	MIL-T-9046 Type III, COMP. A	C110M, MST 8Mn; RS110A; Ti-8Mn; 0.01002
	Forgings		MIL-T-83142 Comp. 12	
4AL-3Mo-IV	Sheet, Strip, Plate	4912	MIL-T-9046 Type III COMP. B	MST 4AL-3MO-IV; RS115; Ti-3AL 3MO-IV; LB-0170-104
	Sheet, Strip, Plate (Solution and Pre-treated)	4913		
6AL-4V (C120AV)	Sheet, Strip, Plate	4911	MIL-T-9046 Type III, COMP. C	C-120AV; HA6510; MST 6AL-4V; RS120A; Ti-6AL-4V; LB0170-110
	Bars and Forgings	4928	MIL-T-9047 Comp. 6	C120AV; HA6510; MST-6AL-4V; RS120A; Ti-6AL-4V; LB0170-110; 0.01037
	Bars and Forgings (Solution and Precipitation Heat Treated)	4965		
	Extrusions	4935		C120AV; HA6510; MST-6AL-4V; RS120A; Ti-6AL-4V; LB0170-147
	Wire, Welding	4954		C120AV
	Forgings		MIL-F-83142 Comp. 6	
6AL-4VEL1	Sheet, Strip, Plate		MIL-T-9046 Type III, COMP. D	
	Bars and Forgings	4930	MIL-T-9047 Comp. 7	
	Forgings		MIL-F-83142 Comp. F	
	Wire, Welding (Extra low interstitial environment controlled)	4956		
6AL-6V-2Sn	Forgings		MIL-F-83142 Comp. 8	
	Sheet, Strip, Plate	4918	MIL-T-9046 Type III, COMP. E	
	Bars and Forgings	4973 (Annealed) 4979 (Heat Treated)	MIL-T-9046 Comp. B	
	Forgings		MIL-T-83142 Comp. 9	
7AL-4Mo (C135MO)	Sheet, Strip, Plate		MIL-T-9046 Type III, COMP. F	C135MO; HA-7146; MST 7AL-4MO; RS 135; Ti-7AL-4MO; LB0170-122
	Bars and Forgings	4970 (Heat Treated)	MIL-T-9047 Comp. 9	
	Forgings		MIL-F-83142 Comp. 13	
6AL-2SN-4Zr-2Mo	Sheet, Strip, Plate		MIL-T-9046 Type III, COMP. G	
	Bars and Forgings	4979 (Heat Treated) 4976 (Annealed)	MIL-T-9047 Comp. II	



Table 5-1. Specification Cross Reference Titanium Alloys - Continued

Composition/ Alloy Designation	Form/Commodity	Specification Data <sup>△</sup>		
		Aeronautical Material Specification (AMS)	Military	Other <sup>△</sup>
6AL-2Sn-4Zr-6Mo	Bars and Forgings		MIL-T-9047 Comp. 14	
MISCELLANEOUS SPECIFICATIONS				
Heat Treatment of Titanium and Titanium Alloys			Society of Automotive Engineers (SAE) SAE-AMS-H- 81200	
<sup>△</sup> There may be controlled requirements applicable to some specifications listed in the same alloy type or series. Validate any difference and assure that selected specification material(s) will comply with end item specification requirements before specifying or using. <sup>△</sup> The following manufactures names apply to designations listed under other: a. For designation beginning with A, B, C (example - A-40) Crucible Steel Co. b. For designation beginning with HA (example HA-1940) Harvey Aluminum Co. c. For designation beginning with MST (example MST-70) Reactive Metal Corp. d. For designation beginning with RS (example RS-40) Republic Steel Co. e. For designation beginning with T1 (example T1-8Mn) Titanium Metal Corp. f. For designation beginning with LB or NA (example LB170-110 or NA2-7123B) North American Aviation Inc. g. For designation beginning with 0.0 (example 0.01015) Convair Or General Dynamics Corp.				

### 5.3 HEAT TREATMENT - GENERAL.

#### NOTE

- SAE-AMS-H-81200, Heat Treatment of Titanium and Titanium Alloys, will be the control document for heat treatment of titanium and titanium alloys used on aerospace equipment. For complete description of titanium heat treat requirements, refer to latest issue of SAE-AMS-H-81200.
- Additional Heat Treatment information is discussed in [Chapter 9](#).

A majority of the titanium alloys can be effectively heat treated to strengthen, anneal and stress relieve. The heating media for accomplishing the heat treatment can be air, combusted gases, protective atmosphere, inert atmosphere, or vacuum furnace. However, protective, inert atmospheres or vacuum shall be used as necessary to protect all parts (titanium or titanium alloy), etc., which comprise the furnace load to prevent reaction with the elements hydrogen, carbon, nitrogen and oxygen.

#### 5.3.1 Furnaces.



Cracked ammonia or hydrogen shall not be used as a protective atmosphere for titanium and titanium alloys in any heat treating operations. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

Air-chamber furnaces are more flexible and economical for large volumes of work and for low temperature heat treatments; but at high temperatures where surface oxidation (above 1000 °F) is significant, a muffle furnace utilizing external heating gives more protection, especially if gas heated. For general use, electric furnaces are preferred since heating can be accomplished internally or externally with a minimum of contamination. Furnaces which have given satisfactory results are vacuum furnaces capable of supplying pressures of one micron or less; and inert gas furnaces which control the atmosphere to 1 percent or less of oxygen and nitrogen combined.



## NOTE

Avoid direct flame impingement to prevent severe localized oxidation and contamination. Also avoid contact with scale or dirt.

5.3.1.1 Alternately direct resistance heating may be used where extremely short heat up cycle on nearly finished parts is required to minimize surface oxidation.

5.3.1.2 The commercially pure, or unalloyed titanium, can only be hardened/strengthened by cold work. Stress relief and annealing are the only heat treatments applicable to these alloys. These processes of heat treatment are employed to remove residual stress resulting from grinding, work hardening, welding, etc. For recommended temperatures and times see [Table 5-3](#).

5.3.1.3 The soaking period for heat treatment of titanium alloys shall be the minimum necessary to develop the required mechanical properties. The minimum soaking period (when unknown) shall be determined by test samples run prior to heat treating the finished material or part. Excessive heat treat soaking periods shall be avoided to prevent diffusion of oxygen hydrogen and nitrogen. Oxygen and nitrogen diffusion will take the form of a hard brittle surface layer which is difficult to distinguish from the base metal. The brittle layer must be removed by mechanical or chemical means prior to forming or application in stressed components. For the recommended soaking periods and temperatures see [Table 5-3](#).

5.3.1.4 Scaling (oxidation) of titanium and titanium alloys starts at about 900 °F. Light scaling which forms from exposure to temperatures up to 1000 °F has little or no detrimental effect on mechanical properties. Heating to temperatures 5-8 above 1000 °F under oxidizing conditions results in severe surface scaling as well as diffusion of oxygen.

5.3.2 **Hydrogen Embrittlement.** Hydrogen embrittlement is a major problem with titanium and titanium alloys. Hydrogen is readily absorbed from pickling, cleaning and scale removal solution at room temperature and from the atmosphere at elevated temperatures. Hydrogen embrittlement in the basically pure and alpha alloys is evident by a reduction in ductility and a slight increase in strength. This is associated with a decrease in impact strength at temperatures below 200 °F and a shift in the temperature range where the change from ductile to brittle occurs. With alpha-beta alloys, embrittlement is found at slow speeds of testing and under constant or “sustained” loads as demonstrated by tests on notched specimens. This type of embrittlement, which is similar to the embrittlement of steel, only becomes evident above a certain strength level. Solution heat treating and aging the alpha-beta alloys to high strength levels increases sensitivity to hydrogen embrittlement.

5.3.2.1 Quenching from solution heat treating for temperature wrought titanium alloys, except for alloy 3AL-13V-11Cr less than 2 inches thick, which maybe air cooled, shall be by total immersion in water. The water shall be of sufficient volume or circulation or both so that the water temperature upon completion of the quenching operation will not be more than 100 °F. The quenching baths shall be located and arranged to permit rapid transfer of the load from the furnace to the bath. Maximum quench delay for immersion-type quenching shall be 4 seconds for wrought alloys up to 0.091 nominal thickness and 7 seconds for 0.091 and over. Quench delay time begins when furnace doors begin to open and ends when the last corner of the load is immersed. With extremely large loads or long lengths quench delay may be exceeded if performance test indicates that all parts comply with specification requirements.

5.3.3 **Aging and Stress Relieving.** For aging, the material shall be held within temperature range for sufficient time, depending on section size, for the necessary aging to take place and to ensure that specified properties are developed. Wrought alloys should be fully quenched by air cooling from the aging temperature. The same applies for stress relieving except the time at temperature will depend on section size plus amount of cold work hardening present in the material. The material is also quenched by air cooling from the stress relieving temperature.

## NOTE

All heat treating operations shall be performed uniformly on the whole part, etc., never on a portion thereof.



Table 5-2. Nominal Mechanical Properties at Room Temperature

Material Type	Annealed Condition			Rock- well Hard- ness	Solution Treated Condition				Solution Treated and Aged			
	Yield Str (0.2 percent Off set) 1000 Pound- force per Square Inch (PSI) Minimum	Tensile Strength (Ultimate minimum) 1000 PSI	Elong percent in 2 inch		Yield Str (0.2 percent Off set) 1000 PSI Minimum	Tensile Str (Ultimate minimum) 1000 PSI	Elong percent in 2 inch	Rockwell Hard- ness	Yield Strength	Tensile	Elong percent in 2 inch	
MIL-T-9046 1/ TYPE I, Comp A (Unalloyed 40 Kips per Square Inch (KSI))	40-65	50	20	B88								
Comp B (Unalloyed 70 KSI)	70-95	80	15	C23								
Comp C (Unalloyed 6S KSI)	55-80	65	18	B95								
TYPE II, Comp A (5AL- 2.5Sn)	110	120	10	C35								
Comp B (5AL-2.5SnE11)	95	100	8-10									
Comp C (5AL-5Zr-5Sn)	110	120	10	C35	Not recommended							
Comp D (7AL-23Zr)	120	130	10									
Comp E (7AL-2Cb-1Ta)	110	115	10	C35								
Comp F (8AL-1Mo-IV)	135	145	8-10	C38								
TYPE III, Comp A (8Mn)	110	120	10		Not recommended							
Comp B (4AL-3Mo-IV)	115	125	10		130		8		155	5.0		
Comp C (6AL-4C)	120	130	8	C36	150	160	5		145	5.0		
Comp D (6AL-4V-EL1)	120	130	10	C36								
Comp E (6AL-6V-2Sn)	140	150	10		160	170	10		160	8.0		
Comp F (7AL-4Mo)	135	145	10	C38	160		10		160	8.0		
TYPE IV, Comp A (13V- 11Cr-3Al)	120	125	10		120	125	10		160	170	10.0	
MIL-T-9047, Class 1 (Unalloyed)	70	80	15	C23								
Class 2 (5AL, 2.5Sn)	110	115-120	10	C36								
Class 3 (3AL, 5Cr)	130	140	10									
Class 4 (2Fe, 2Cr, 2Mo)	120	130	15	C36								



**Table 5-2. Nominal Mechanical Properties at Room Temperature - Continued**

Material Type	Annealed Condition			Rock- well Hard- ness	Solution Treated Condition				Solution Treated and Aged		
	Yield Str (0.2 percent Off set) 1000 Pound- force per Square Inch (PSI) Minimum	Tensile Strength (Ultimate minimum) 1000 PSI	Elong percent in 2 inch		Yield Str (0.2 percent Off set) 1000 PSI Minimum	Tensile Str (Ultimate minimum) 1000 PSI	Elong percent in 2 inch	Rockwell Hard- ness	Yield Strength	Tensile	Elong percent in 2 inch
Class 5 (6AL, 4V)	120	130	8	C36	145	160	5		150	160	5.0
Class 6 (6AL, 4V)	130	140	10	C40	150	160	5		160	175	5.0
Class 7 (5AL, 1.5Fe, 15Cr, 1.5Mo)	135	145	10	C39							
<p style="text-align: center;"><b>NOTE</b></p>											
<p>1/ Comp A, B and C are classified as commercially pure.</p>											



Table 5-3. Heat Treat, Stress Relief and Annealing Temperatures and Times

Material	Stress Relief Temperature °F	Stress Relief Time Hours	Annealing Temperature °F	Annealing Time Hours	Heat Treating Temperature °F	Heat Treated Soaking Time Minutes 14/	Aging Temperature °F	Aging Soaking Time Hours
Unalloyed Commercially Pure Comp A, B and C	1000-1100 900 800	1/2-1 2-4 8	1000-1300	1 - 1/2-2	Hardened only by cold work			
Alpha Alloys								
5A1-2.5Sn	1080-1125	1-2	1335-1550	1/4-4	Hardened only by cold work			
5A11-5Zr-5Sn	1100-1300	1/2-3/4	1335-1550	1/4-1				
7A1-12Zr	1275-1325	1/2-3/4	1630-1670	1/4-1				
7A1-2Cb-1Ta 2/	1000-1200	1/3-3/4	1630-1670	1/4-1				
8A1-1Mo-1V 1/	1285-1315	1/2	1430-1470	8				
Alpha-Beta Alloys								
8Mn 3/	950-1000	1/2-2	1250-1300	1	Not recommended			
2Fe-2Cr-2Mo 4/	800-1000	1/2-15	1175-1200	1/2	1650-1750	5-25	900-950	4-6
2.5A1-16V 5/	960-990	3-5	1360-1400	1/16-1/2	1360-1400	10-30	960-990	3-5
3A1-2.5V			1250-1350	1/2 - 1-1/2	Not recommended			
4A1-4Mn 6/	1250-1350	1/2 - 2-1/2	1250-1300	2-24	1420-1480	60-120	875-925	6-10
4A1-3Mo-1V 7/	900-1100	1/2-8	1225-1250	2-4	1620-1660	10-20	910-940	6-12
5A1-1.25Fe-2.75Cr 7/ 8/	1000-1100	1/2-2	1425-1650	1/3-2	1350-1550	10-60	900-1000	6-10
5A1-1.5Fe-4Cr-1.2Mo 9/	1100-1200	1/2-2	1180-1200	4-24	1650-1700	30-120	950-1050	4-8
6A1-4V 7/10/ 5/	900-1200	1/2-50	1275-1550	1/2-8	1670-1730	5-25	960-990	4-6
6A1-6V-2Sn 9/ 15/	1000-1100	1/2-3	1300-1500	2-3	1575-1675	30-60	875-1175	4-8
7A1-4Mo 11/	900-1300	1/2-8	1425-1450	1-8	1675-1275	30-90	975-1175	4-8
6A1-4V (low o) 10/ 5/	900-1200	1/2-50	1275-1550	1/2-8	Not recommended			
Beta Alloy								
3A1-13V-11Cr 12/	900-1000	1/4-60	1430-1470	1/4-1	1375-1425	30-90	880-920	2-60
1A1-8V-5Fe 13/	1000-1100	1/4-60	1200-1300	1/2 - 1-1/2	1375-1470	15-60	925-1000	1-3
1/ Sheet: Regular anneal furnace cool								
Duplex anneal. Mill anneal +1435 °F, 15 minutes air cool.								
Triplex anneal. Mill anneal +1850 °F, 5 minutes air cool, +1375, 15 minutes air cool.								
Bar and Forgings:								
Duplex anneal								
1650-1850, 1 hour air cool +1000-1100 °F, 8-24 hours air cool.								



**Table 5-3. Heat Treat, Stress Relief and Annealing Temperatures and Times - Continued**

Material	Stress Relief Temperature °F	Stress Relief Time Hours	Annealing Temperature °F	Annealing Time Hours	Heat Treating Temperature °F	Heat Treated Soaking Time Minutes <u>14/</u>	Aging Temperature °F	Aging Soaking Time Hours
<u>2/</u> Bar Duplex anneal: Mill anneal +1000-1200 °F, 1/2-6 hours air cool.								
<u>3/</u> Anneal furnace cool at 300 °F per hour maximum to 1000-1050 °F.								
<u>4/</u> Stress relief may be accomplished at 800 °F - 15 hours, 850 °F - 5 hours, at 900 °F - 1 hour and 950 °F - 1/2 hour.								
<u>5/</u> For 100 percent stress relief, 1000 °F - 50 hours or 1200 °F - 5 hours. For 50 percent relief, 1000 °F - 5 hours or 1100 °F - 1/2 hour.								
<u>6/</u> Furnace cool at 300 °F maximum from anneal temperature for maximum formability, also, formability may be improved by holding at annealing temperature 24 hours.								
<u>7/</u> Slow cool to 1000-1050 °F maximum from upper annealing temperature.								
<u>8/</u> Anneal sheet at temperature for 20 minutes. For bar hold at anneal temperature 2 hours.								
<u>9/</u> Air cool from annealing temperature.								
<u>10/</u> For sheet anneal, heat 1300-1350 °F, 1 hour, furnace cool at a rate of 50 °F per hour maximum to 800 °F. Air cool may be used for lower ductility requirements. For bar and forging anneal, heat at 1275-1325 °F for 2 hours, air cool. For hydrogen removal by vacuum annealing, heat at 1300-1500 °F for 1/2-2 hours, then furnace cool to 1100 °F maximum.								
<u>11/</u> Furnace cool from annealing temp (1425-1450 °F) to 1000-1050 °F maximum at 300 °F per hour (maximum) for maximum formability. For maximum creep properties (after lowering from upper annealing) temperature hold at 1050° for 24 hours.								
<u>12/</u> Solution heat treatment recommended for annealing. Stress relieve at temperature cited during aging. If aging not employed, heat treat at 1000 °F for 15 minutes. Aging time will depend on strength level required/desired.								
<u>13/</u> Furnace cool from upper annealing temperature at 300 °F per hour maximum to 900 °F.								
<u>14/</u> Longer soaking times may be necessary for specific forgings. Shorter times are satisfactory when soak time is accurately determined by thermocouples (TCs) attached to the load. Soaking time shall be measured from the time all furnace control instruments indicate recovery to the required (minimum) process range.								
<u>15/</u> Age at 1050-1150 °F air cool for best combination of mechanical properties and thermal stability.								



#### 5.4 FABRICATION.

5.4.1 Forming Sheet Metal-General. The forming of the unalloyed titanium can be accomplished at room temperature using approximately the same procedures as those established for 18-8 stainless steel. The basic difficulties encountered are sheet thickness, property variations, direction of grain flow and flatness. The above factors combined with high yield strength, high tensile strength and low uniform elongation of commercial titanium alloys makes forming difficult. The current equipment available was designed for material of uniform quality and considerable work is required for adaptation to form titanium.

5.4.2 Bending. Straight-Edge Bending of titanium using power brake on hand forming equipment can be accomplished to a limited degree using the methods developed for stainless steel. The factors which require control are the compensation for springback and the bend radii. Springback is comparable to that of hard stainless steel when formed at room temperature. The bend radii will depend on the type of material or alloy and whether forming is accomplished hot or cold. The forming of material requiring tight bends or small radii necessitates the application of heat in the range of 500 °F. The heat should be applied for only short periods of time to avoid excessive oxygen and nitrogen contamination which causes embrittlement. For approximate cold bend radii of sheet titanium see [Table 5-4](#). Actual practice may reveal that smaller bend radii can be used.

5.4.3 Draw Forming. Deep draw forming should not be attempted unless adequate equipment and facilities are available. This will require that facilities be maintained for heating and controlling temperatures of the blanks to be formed and the dies used in the forming operation.

5.4.4 Hydraulic Press Forming. Rubber pad hydropress forming can be accomplished either hot or cold depending on the type tooling employed and the press pressures used. This type of forming is used on parts that are predominately flat and have flanges, beads, and lightening holes. A male form block is set on the lower press platen and the blank held in place on the block by locating pins. A press-contained rubber pad (45 to 55 Shore Durometer hardness and about 8 inches thick) is located over the form block and blank. The press is then closed. As the ram is lowered, the rubber pad envelops the form block forcing the sheet metal blank to conform to its contour.

5.4.4.1 Many parts can be formed at room temperature on the hydropress if flange clips, wedges and hinge-type dies are used. When cold forming is employed, it is usually desirable to partially form the parts, stress-relieve at 1000 °F for 20 minutes, then finish form. Hot forming for severely contoured parts or when only low-forming pressures are available is accomplished between 600 °F and 800 °F. For this procedure, the form block is heated to the required temperature, the blank positioned and covered with powdered or shredded asbestos; then a rubber pad 70 to 80 Durometer hardness is placed on top. This extra pad of rubber serves two purposes: First, it provides additional rigidity for forming; and second, it protects the press-contained rubber from the hot form block.

5.4.4.2 Tooling for hydropress form blocks, if elevated temperature forming is to be used, requires that pressure plates and dies be made somewhat thicker than in normal practice. If long runs are anticipated, it is recommended that form blocks be made from a good grade of hot-work tool steel due to the galling action of titanium at elevated temperatures.

5.4.5 Stretch Forming. Stretch forming has been used on titanium primarily to bend angles, hat sections, Z-sections and channels and to stretch form skins so that they will fit the contour of the airplane fuselage. This type of forming is accomplished by gripping the section to be formed in knurled jaws, loading until plastic deformation begins, then wrapping the part around a female die. This operation is performed at room temperature and should be done at a very slow rate. Spring back is equivalent to that of 1/4 hard 18-8 stainless steel. All blanks for stretch-forming should have the edges polished to remove any notch effects. Approximately 0.025 inch of sheared edges should be removed.

5.4.6 Drop-Hammer Forming. Drop-hammer forming of titanium has been very successful and has been accomplished both at room and at elevated temperatures. Kirksite is satisfactory for male and female dies where only a few parts are required. If long runs are to be made, ductile iron or laminated steel dies are usually necessary. In drop-hammer forming, the best results have been obtained by warming the female die to a temperature of 200-300 °F to remove the chill and heating the blank to a temperature of 800-1000 °F for 10 to 15 minutes. The part is then struck and set in the die. Usually a stress relief operation at 1000 °F for 20 minutes is necessary, then a restrike operation. In most instances, a finished part requiring no hand work is obtained.

5.4.7 Joggling. Joggling of titanium can be accomplished without any particular difficulty provided the following rules are adhered to:

- a. The joggle die corner radius should not be less than 3T-8T.



- b. Joggle run-out should be the determining factors whether joggles are formed hot or cold. Joggles should be formed hot where a ratio of joggle run-out to joggle depth is less than 8.1.
- c. Minimum joggle run-outs should be as follows:
  - Hot joggling - four times the joggle depth.
  - Cold joggling - eight times the joggle depth.

**5.4.8 Blanking and Shearing.** These operations compare to those of 18-8 stainless steel in the 1/4 hard condition for commercially pure, and the alloys compare to 1/2 hard 18-8 stainless steel. The force required for titanium and its alloys is greater and the dies wear faster. Materials up to 0.125 inch in thickness have been sheared on 1/2 inch capacity flat bed shears designed for steel. If this capacity is to be exceeded, the shear designer should be consulted.

**5.4.8.1** Before any forming or other operations are performed 0.025 inch of the sheared, blanked, sawed, or nibbed edges should be removed to prevent stress risers that will cause a tear in the part during forming operations.

#### 5.4.9 Soldering.



#### SOLDER

8

Limited information is available on soldering. It is possible to successfully titanium where little strength is required, by precoating with a thin film of silver, copper or tin from their chloride salts. This can be accomplished by heating the chloride salts-coated titanium in an atmosphere controlled furnace as previously mentioned in [Paragraph 5.3.1.1](#). The resultant film should be made wet with either a 60 percent tin, 40 percent lead or a 50-50 percent tin and lead solder. Since the deposited film may dissolve in the liquid solder and dewet the surface, it is important that the time and temperature be held to a minimum.

**5.4.10 Riveting.** Riveting of titanium can be accomplished using conventional equipment with rivets manufactured from commercially pure material; however, the rivet holes require close tolerances to ensure good gripping. The driving time is TO 1-1A-9 increased about 65 percent over that required for high strength aluminum rivets. Better results can be obtained by using the squeeze method rather than the rivet gun and bucking bar. When it is necessary to have flush-head rivets, dimpling can be accomplished at temperatures of 500-700 °F. Other types of rivets such as high strength aluminum, stainless steel and monel are also used to join titanium.

**5.4.10.1** Due to difficulties involved, the above mentioned method will probably be replaced in most cases with rivets of the high shear series, i.e., pin rivets such as NAS1806 through NAS1816, tension rivet NAS-2006 through NAS-2010, and shear rivet NAS-2406 through NAS-2412.



#### ZINC CHROMATE PRIMER, TT-P-1757

7

**5.4.10.2** As with other metals, it is necessary to take precautions to avoid galvanic corrosion when titanium is riveted to other metals. This can be accomplished by coating the titanium with zinc chromate primer, TT-P-1757.

**Table 5-4. Recommended Minimum Constant Current Line Drive (CCLD) Bend Radii**

Type/Composition	Minimum Bend Radius (90 Degree Bend) <u>1/</u>	
	0.070 and Under Thickness	Over 0.070 to 0.187
Type I - Commercially Pure		
Comp A (unalloyed 40,000 PSI)	2T	2.5T
Comp B (unalloyed 70,000 PSI)	2.5T	3T



Table 5-4. Recommended Minimum Constant Current Line Drive (CCLD) Bend Radii - Continued

Type/Composition	Minimum Bend Radius (90 Degree Bend) <sup>1/</sup>	
	0.070 and Under Thickness	Over 0.070 to 0.187
Comp C (unalloyed 55,000 PSI)	2T	2.5T
Type II - Alpha Titanium Alloy		
Comp A (5AL02.5Sn)	4T	4.5T
Comp B (5AL-2.5Sn EL1)	4T	4.5T
Comp C (5AL-5Zr-5Sn)	4.5T	5T
Comp D (7AL-12Zr)	5T	5T
Comp E (7AL-2Cb-1Ta)		
Comp F (8AL-1Mo-1V)	4.5T	5T
Type III - Alpha-Beta		
Comp A (8Mn)	3T	3.5T
Comp B (4AL-3Mo-1V)	3.5T	4T
Comp C (6AL-4V)	4.5T	5T
Comp D (6AL-4V)	4.5T	5T
Comp E (6AL-6V-2Sn)		
Comp F (7AL-4Mo)		
Type IV - Beta		
Comp A (13V-11Cr-3AL)	3T	3-5T
1/ T = Thickness of material. Example: A piece of 0.040 MIL-T-9046, Type II, Composition A, would require a bend radii of 4 X 0.040 = 0.160 bend radii (minimum).		

## 5.5 MACHINING AND GRINDING.

5.5.1 **Machining.** Commercially pure, unalloyed titanium machines similarly to 18-8 stainless steel, but the alloy grades are somewhat harder. Variations in actual practice will depend on the type of work, equipment, and finish, so the following information is only intended as a guide.

5.5.1.1 The basic requirements are: rigid machine setups, use of a good cutting fluid that emphasizes cooling rather than lubrication, sharp and proper tools, slow speeds and heavy feeds. Since titanium has a tendency to gall and seize on other metals, the use of sharp tools is very important. Sliding contact, and riding of the tool on the work must be avoided.

5.5.2 **Turning.** Commercially pure and alloy titanium is not difficult to turn. Carbide tools such as metal carbides C91 and Carboloy 44A and other similar types give the best results for turning titanium. Cobalt-type high speed steels give the best results of the many types available. Cast alloy tools such as Stellite, Lantung, Rexalloy, etc., may be used when carbide is not available, or when the high speed steels, are not satisfactory.

5.5.2.1 The recommended cutting fluids are waterbase cutting fluids such as soluble oils or chemical type fluids.

5.5.2.2 [Table 5-5](#) and [Table 5-7](#) show suggested turning speeds, tool angles and feeds. All work should be accomplished with live centers since galling or seizing will occur on dead centers. Tool sharpness is again emphasized because a nick or a seized chip on a tool increases temperature and will cause rapid tool failures.

5.5.3 **Milling.** Considering the type of tool which is required in milling operations, it can be readily seen that this type of machining is more difficult than turning. The difficulty encountered is that chips remain tightly welded to the cutter's edge at the end of cut or during the portion of the revolution that it does not cut. As the cutter starts the next machining portion the chips are knocked off. This damages the cutting edge and the tool fails rapidly.

5.5.3.1 One method that can be utilized to relieve this difficulty to a great extent is climb milling. The cutter machines the thinnest portion of the chip as it leaves the cut. Thus, the area of contact between chip and tool is at a minimum when the chip is removed at the start of the next cutting portion of the revolution. This will reduce the danger of chipping the tool. The machine used for climb milling should be in good condition because TO 1-1A-9 if there is any lost motion in the feed mechanism of the table, the piece being cut will be pulled into the cutter. This may damage the cutter or the work piece.



5.5.3.2 For effective milling, the work feed should move in the same direction as the cutting teeth, and for face milling the teeth should emerge from the cut in the same direction that the work is fed.

5.5.3.3 To select the appropriate tool material it is advisable to try both cast alloy and carbide tools to determine the better of the two for large milling jobs. This should be done since the cutter usually fails because of chipping, and the results are not as satisfactory with carbide as they are with cast-alloy tools. The increase in cutting speeds (20 to 30 percent) possible by using carbide rather than cast (all alloy tools) does not always compensate for the additional tool grinding cost.

5.5.3.4 The same water-base cutting fluids used for turning are recommended for milling; however, carbide tools may give better results when dry.

5.5.3.5 See [Table 5-7](#) for recommended speed and feeds. For tool grinding information see [Table 5-8](#).

5.5.4 **Drilling.** Drilling of titanium can be accomplished successfully with ordinary high speed steel drills. Low speeds and heavy positive feeds are required. The unsupported portion of the drill should be as short as possible to provide maximum rigidity and to prevent drill running. All holes should be drilled without pilot holes if possible. As with other materials, chip removal is one of the principal problems and the appearance of the chip is an indication of the sharpness and correct grinding of the drill. In drilling deep holes, intermittent drilling is recommended. That is, the drill is removed from the hole at intervals to remove the chips.

5.5.4.1 The cutting fluids recommended are sulfurized and chlorinated coolants for drills with diameters of less than 1/4 inch and mixtures of mineral oil or soluble oil with water for hole sizes larger than 1/4 inch diameter.

5.5.4.2 The cutting speed should be 50 to 60 Foot Per Minute (FPM) for the pure grade of titanium and 30 to 50 FPM for alloy grades. Feeds should be 0.005 to 0.009 inch for 1/4 to 1/2 inch diameter drills; 0.002 to 0.005 inch for smaller drills. Point angle, 90° for drills 1/4 inch diameter and larger and 140° for drills 1/8 inch diameter or less; but 90°, 118° and 140° should be tried on large jobs to determine the angle that will give the best result. Helix angle 28° to 35° and lip relief 10°. Additional information on drills may be obtained from NAS907.

5.5.5 **Tapping.** Due to the galling and seizing that are characteristic of titanium, tapping is one of the more difficult machining operations. Chip removal is one of the problems that will require considerable attention in an effort to tap titanium. Another problem will be the smear of titanium. Build up from smear will cause the tap to freeze or bind in the hole. These problems can be alleviated to some extent by the use of an active cutting fluid such as sulphurized and chlorinated oil.

5.5.5.1 Power equipment should be used when possible and a hole to be tapped should be drilled with a sharp drill to prevent excessive hardening of the hole wall. In the attempt to tap titanium, difficulties involved can be minimized by reducing the thread to 55 percent or 65 percent from the standard 78 percent.

5.5.5.2 The following are procedures and material recommended for tapping titanium:

- a. Cutting speed: 40 to 50 FPM for unalloyed and 20 to 30 FPM for the alloy grades.
- b. Type of Tap: Gun or spiral point, 2 fluted in sizes 1/4-20 or less; 3 fluted in sizes greater than 1/4-20.
- c. Cutting fluid; Active cutting oil such as oil, cutting, sulfurized mineral, Specification VV-O-283, Grade 1.

5.5.6 **Reaming.** Preparation of the hole to be reamed and the type of reamer used is the keynote to successful reaming operations. As with tapping operations, the hole to be reamed should be drilled with a sharp drill. A straight-fluted reamer can be used, but spiral-fluted reamers with carbide tips usually produce the best results. Speeds of 40-200 FPM and feeds of 0.005 to 0.008 inch are satisfactory; however, these factors depend on the size of the hole. Feeds should increase in proportion to the size of the hole. The removal of larger amounts lessens the degree of concentricity. If the degree of concentricity is an important factor, smaller amounts should be removed.

5.5.7 **Grinding.** The essential requirements for grinding are the selection and use of grinding fluids and abrasive wheels. Grinding of titanium is different from grinding steel in that the abrasive grain of the wheel wears or is dissolved by a surface reaction, rather than wheel wear which is caused by breakage. To overcome this problem, lower wheel speeds and the use of aluminum oxide or soft bonded silicone carbide wheels employing wet grinding methods are recommended. Recommended wheel speeds are; 1500-2000 Surface Feet per Minute (SFM) and table feeds of 400 to 500 inches per minute with down feed of 0.001 inch maximum per pass and using 0.05 inch cross feed for highest grinding ratios.



**Table 5-5. Turning Speeds for Titanium Alloys**

Type	Military MIL-T-9047C	Cutting Speed FPM	Feed, Inch per Revolution	Tool Material
Unalloyed 70,000 PSI	Class 1	250-300 150-170 170-200	0.010-0.020 0.004-0.007 0.005-0.010	Carbide Hi-Speed Steel Cast Alloy
5A1, 2.5 Tin 3A1, 5Cr 2Fe, Chromium 2 Molybdenum 6A1, 4V 4A1, 4Mn	Classes 2, 3, 4, 5, and 6	120-160 30-60 50-80	0.008-0.015 0.004-0.007 0.005-0.010	Carbide Bi-Speed Steel Cast Alloy
5A1, 1.5 Iron 1.5 Chromium, 1.5 Molybdenum	Class 7	110-150 20-40 40-70	0.005-0.012 0.003-0.006 0.004-0.008	Carbide Hi-Speed Steel Cast Alloy
<p style="text-align: center;"><b>NOTE</b></p> <p>For cutting forging skin speed 1/4 of that above and feeds about 1/2.</p>				

**Table 5-6. Tool Angles for Alloys**

Tool Angles	Carbide	High Speed Steel	Cast Alloy
Back Rake	0°	5° Position	5° Position
Side Rake	6°	5 - 15°	5 - 15°
Side Cutting Edge Angle	6°	5 - 15°	5 - 15°
End Cutting Edge Angle	6°	5°	5°
Relief	6°	5°	5°
Nose Radius	0.040 inch	0.010 inch	0.005 to 0.010 inch

**Table 5-7. Speeds and Feeds for Milling**

Type	Military	Milling Speed FPM	Feed, Input in Inches	Tool Material
Unalloyed 70,000 PSI	MIL-T-9047C Class 1	160-180 120-140	0.004-0.008 0.004-0.008	Carbide Cast Alloy
5A1, 2.5Sn 3A1, 5CR 2Fe, 2Cr, 2Mo, 6A1, 4V 4A1, 4Mn	Class 2, 3, 4, 5, 6	80-120 80-100	0.004-0.008 0.004-0.008	Carbide Cast Alloy
5A1, 1.5Fe, 1.5Cr 1.5Mo	Class 7	70-110 70-90	0.004-0.008 0.004-0.008	Carbide Cast Alloy



**Table 5-8. Angles for Tool Grinding**

Angles	Cast Alloy Tool	Carbide Tool
Axial Rake	0°	0°
Radial Rake	0°	0°
Corner Angle	30°	60°
End Cutting Edge Angle	6°	6°
Relief	12°	6-10°







## CHAPTER 6

### COPPER AND COPPER BASE ALLOYS

#### 6.1 COPPER AND COPPER BASE ALLOYS.

Most of the commercial coppers are refined to a purity of 99.90 percent, minimum copper plus silver. The two principal copper base alloys are brass and bronze, containing zinc and tin respectively, as the major alloying element. Alloy designations for wrought copper and copper alloys are listed in [Table 6-1](#), with the corresponding specification and common trade names.

#### 6.2 COPPER ALLOYING ELEMENTS.

6.2.1 Zinc. Added to copper to form a series of alloys known as brasses. They are ductile, malleable, corrosion resistant and have colors ranging from pink to yellow.

6.2.2 Tin. Added to copper to form a series of alloys known as bronzes. Bronzes are a quality spring material, and are strong, ductile and corrosion resistant.

6.2.3 Lead. Added to copper in amounts up to 1 percent to form a machinable, high-conductivity copper rod. It is added to brasses or bronzes in amounts of 0.5 to 4 percent to improve machinability and in the range of 2-4 percent to improve bearing properties.

6.2.4 Aluminum. Added to copper as a predominating alloy element to form a series known as aluminum bronzes. These alloys are of high strength and corrosion resistance.

6.2.5 Iron. Added to copper along with aluminum in some aluminum bronzes and with manganese in some manganese bronzes.

6.2.6 Phosphorous. Added to copper principally as a deoxidizer and in some bronzes to improve spring properties.

6.2.7 Nickel. Added to copper for higher strength without loss of ductility. They have excellent corrosion resistance.

6.2.8 Silicon. Added to copper to form the copper - silicon series having high corrosion resistance combined with strength and superior welding qualities. Small amounts are used as deoxidizers.

6.2.9 Beryllium. Added to copper to form a series of age hardenable alloys. In the fully treated condition, it is the strongest of the copper base alloys and has an electrical conductivity of 20 percent. Beryllium-coppers are widely used for tools where nonsparking qualities are desired.

6.2.10 Manganese. Added primarily as a desulfurizing and de-gassing element for alloys containing nickel.

#### 6.3 CHEMICAL COMPOSITION.

The chemical composition of the copper alloys (listed by commercial trade name) is listed in [Table 6-1](#).

#### 6.4 HEAT TREATMENT AND NOT WORKING TEMPERATURE OF COPPER ALLOYS.

#### NOTE

Additional Heat Treatment information is discussed in Chapter 9.

During production and fabrication, copper alloys may be heated for homogenizing, hot working, stress relief for solution treatment, and precipitation hardening. The temperatures commonly used for heating, hot working and annealing after cold working are given in [Table 6-2](#).



## 6.5 STRESS RELIEF OF COPPER ALLOYS.

[Table 6-3](#) below gives a list of typical stress relief treatments commonly used in industry. This table is listed in terms of chemical composition percents, and should be used as representing average stress relieving temperatures.

6.5.1 Machining Copper and Copper Alloys. Free cutting brass is one of the most easily machined metals and serves as a standard for machinability ratings of copper alloys. The following table gives the machinability ratings and recommended speeds and feeds for use with high speed steel tools.

6.5.2 Wrought-Copper-Beryllium Alloys. The beryllium copper alloys are frequently used due to their ability to respond to precipitation or age hardening treatments and other beneficial characteristics. Some of the characteristics are; good electrical and thermal conductivity, high strength hardness, corrosion resistance, good wear resistance, non-magnetic qualities and very good fatigue strength.

6.5.2.1 Typical Engineering properties of alloys 170, Specification QQ-C-530 and 172, Specification QQ-C-533 are cited in [Table 6-5](#).

## 6.6 HEAT TREATING PROCEDURES AND EQUIPMENT REQUIREMENTS.

### NOTE

SAE-AMS-H-7199, Heat Treatment of Wrought Copper-Beryllium Alloys, Process for (Copper Alloy numbers 170, 172 and 175), will be the control document for heat treatment of wrought copper-beryllium alloy, numbers 170, 172 and 175. For complete description of heat treat requirements for these alloys, refer to the latest issue of SAE-AMS-H-7199.

Furnaces for solution heat treating of copper-beryllium items/parts may be heated by electricity, gas or oil, with either controlled gas atmosphere or air (static or forced), used in the chamber, continuous or induction types. Molten salt baths shall not be used because of corrosive attack of beryllium alloys by the molten salts at solution heat treatment temperatures. Air atmosphere furnaces shall not be used when the loss of material due to excessive scaling is detrimental to the finished part. The furnace alloy shall be capable of maintaining a temperature in working zone with a normal load, of  $\pm 20$  °F for solution heat treatment, or  $\pm 5$  °F for aging, or precipitation heat treatment. In addition, the temperature in working zone shall not vary above the maximum or below the minimum specified for the alloy being treated, during the holding portion of the treatment cycles (See [Table 6-6](#)).

6.6.1 Solution Heat Treatment Copper-Beryllium. Normally solution heat treatment is not required because the material is furnished in a condition suitable for accomplishing forming operations and then precipitation heat treating. An exception is when the material has been rendered unsuitable for precipitation or age hardening as result of welding, brazing or other fabrication operations or when, cold working requirements demand intermediate softening (annealing) treatment.

6.6.1.1 The solution heat treatment temperatures for alloys 170 and 172 shall be 1425-1460 °F. The time the material is held at the temperature will determine the potential properties of the material. Insufficient time will make it impossible to achieve maximum strength after precipitation hardening, while excessive time may cause grain growth with attendant harmful possibilities. Once the parts are brought up to temperature it is recommended that material be held at temperature for 1 hour per inch of thickness. For parts less than 1/2 inch in thickness, 1/6-1/2 hour may be sufficient. Test sample should be used to determine specific time or if laboratory facilities are available an examination of microstructure will confirm the adequacy of the time selected. The part/material should be rapidly (10 seconds or under) quenched in water from the annealing temperature. An agitated quench should be used. Some oxidation will occur as a result of the annealing temperatures and it should be removed by pickling or other suitable cleaning process.

6.6.2 Precipitation or Age Hardening. Appreciable changes can be produced in both mechanical and physical by this treatment. The actual changes can be controlled by the time and temperature of hardening. [Table 6-6](#) gives times and temperatures for obtaining various tempers.



Table 6-1. Chemical Composition by Trade Name

Copper Alloy Number	Specification		Trade Name
	Federal	Military	
101	QQ-A-673, Type II QQ-C-502 QQ-C-576 QQ-W-343 WW-P-377	MIL-W-85C	Oxygen free certified copper.
102	QQ-A-673 Type II QQ-C-502 QQ-C-825 QQ-C-576 QQ-R-571, Class FS-RCu-1 QQ-W-343 WW-T-799	MIL-W-85C MIL-W-6712A	Oxygen free copper.
104	QQ-C-502 QQ-C-825	MIL-W-3318 MIL-W-6712	Oxygen free with silver.
105	QQ-C-502 QQ-C-825		Oxygen free with silver.
110	QQ-A-673, Type I QQ-C-502 QQ-C-825 QQ-C-576		Electrolyte tough pitch copper.
128	QQ-C-502 QQ-C-576		Fire refined tough pitch with silver.
130	QQ-C-502 QQ-C-576		Fire refined tough pitch with silver.
170 172	QQ-C-530 QQ-C-533		Beryllium Copper
210	QQ-W-321, Comp 1		Gilding, 95 percent
220	QQ-W-321, Comp 2	MIL-W-85C MIL-W-6712	Commercial bronze, 90 percent
230	QQ-B-613, Comp 4 QQ-B-626, Comp 4 QQ-W-321 Comp 3 WW-P-351 Grade A WW-T-791 Grade 1		Red Brass, 85 percent
240	QQ-B-591 QQ-B-613 Comp 3		Low Brass, 80 percent



Table 6-1. Chemical Composition by Trade Name - Continued

Copper Alloy Number	Specification		Trade Name
	Federal	Military	
	QQ-B-626 Comp 3 QQ-B-650 Comp D QQ-W-321 Comp 4	JAN-W-472	
260	QQ-B-613 Comp 2 and 11 QQ-B-626 Comp 2 and 11 QQ-B-650 Comp C QQ-W-321 Comp 6	*MIL-S-22499  MIL-T-6945 Comp II MIL-T-20219  *Laminated Shim Stock	Cartridge brass, 70 percent
261	Same as 260		
262	QQ-B-613 Comp 11 QQ-B-626 Comp 11		
268	QQ-B-613 Comp 1 and 11 QQ-B-626 Comp 1 and 11		Yellow brass, 66 percent (Sheet)
270	QQ-B-613 Comp 11 QQ-B-626 Comp 11 QQ-W-321 Comp 7		Yellow brass, 65 percent (rod and wire)
274	QQ-B-613 Comp 11 QQ-B-626 Comp 11 QQ-W-321 Comp 8		Yellow brass 63 percent
280	QQ-B-613 Comp 11 QQ-B-626 Comp 11 WW-P-351 Grade C WW-T-791 Grade 3		Muntz metal, 60 percent
298	QQ-B-650		Brazing Alloy



Table 6-1. Chemical Composition by Trade Name - Continued

Copper Alloy Number	Specification		Trade Name
	Federal	Military	
	Comp A		
330	QQ-B-613 Comp 11 QQ-B-626 Comp 11 WW-P-351 Grade B WW-T-791 Grade 2	MIL-T-6945 Comp III	Low leaded brass
331	QQ-B-613 Comp 11 QQ-B-626 Comp 11		
110	QQ-R-571, Class FS-RW-1 QQ-W-343 WW-P-377		
111	QQ-C-502 QQ-C-825 QQ-C-576 QQ-W-343		Electrolytic tough pitch anneal resist copper
114	QQ-C-502 QQ-C-825 QQ-C-576		Tough pitch with silver
116	QQ-C-502 QQ-C-825 QQ-C-576		Tough pitch with silver
120	QQ-C-502 QQ-C-576 WW-P-377 WW-T-797 WW-T-799	MIL-W-85C	Phosphorous deoxidized low residual phosphorus copper
121	QQ-C-502 QQ-C-576		
122	QQ-A-674, Type III QQ-C-502		Phosphorus deoxidized high residual phosphorus copper
122	QQ-C-576 WW-P-377 WW-T-797		
123	QQ-C-502 QQ-C-576		
125	QQ-C-502 QQ-C-576		Fire refined tough pitch copper
127	QQ-C-502 QQ-C-576		Fire refined tough pitch with silver



Table 6-1. Chemical Composition by Trade Name - Continued

Copper Alloy Number	Specification		Trade Name
	Federal	Military	
332	QQ-B-613 Comp 11 QQ-B-626 Comp 11		High leaded brass
340	QQ-B-613 Comp 11 QQ-B-626 Comp 11		Medium leaded brass 64 1/2 percent
335	QQ-B-613 Comp 11 QQ-B-626 Comp 11		Low leaded brass
342	QQ-B-613 Comp 11 and 24 QQ-B-626 Comp 11 and 24		High leaded brass 64 1/2 percent
344	QQ-B-613 Comp 11 QQ-B-626 Comp 11		
347	QQ-B-613 Comp 11 QQ-B-626 Comp 11		
348	QQ-B-613 Comp 11 QQ-B-626 Comp 11		
350	QQ-B-613 Comp 11 QQ-B-626 Comp 11		Medium leaded brass 62 percent
353	QQ-B-613 Comp 11 QQ-B-626 Comp 11		Extra High leaded brass
356	QQ-B-613 Comp 11 QQ-B-626 Comp 11 and 22		Extra High leaded brass
370	QQ-B-613 Comp 11 QQ-B-626 Comp 11		Free cutting Muntz metal
360	QQ-B-613 Comp 11		Free cutting brass



Table 6-1. Chemical Composition by Trade Name - Continued

Copper Alloy Number	Specification		Trade Name
	Federal	Military	
	QQ-B-626 Comp 11 and 22		
377	QQ-B-626 Comp 21		Forging brass
443	WW-T-756		Admiralty, Arsenical
444	WW-T-756		Admiralty, Antimonial
445	WW-T-756		Admiralty, Phosphorized
462	QQ-B-626 Comp 11 QQ-B-637 Comp 4		Naval Brass, 63 1/2 percent
464	QQ-B-613 Comp 11 QQ-B-626 Comp 11 QQ-B-637 Comp 1	MIL-W-6712  MIL-T-6945 Comp 1	Naval Brass
465	QQ-B-613 Comp 11 QQ-B-626 Comp 11 QQ-B-637 Comp 1	MIL-W-6712  MIL-T-6945  Comp 1	Naval brass, Arsenical
466	QQ-B-613 Comp 11 QQ-B-626 Comp 11 QQ-B-637 Comp 1	MIL-W-6712  MIL-T-6945  Comp 1	Naval Brass, Antimonial
467	QQ-B-613 Comp 11 QQ-B-626 Comp 11 QQ-B-637 Comp 1	MIL-W-6712 MIL-T-6945	Naval Brass, Phosphorized
470	QQ-R-571 Class FS-RWZn-1		Naval brass, welding and brazing rod
472	QQ-B 650 Comp B		Brazing alloy
482	QQ-B-626 Comp 11 QQ-B-637 Comp 2	MIL-W-6712 MIL-T-6945 Comp 1	Naval Brass, medium leaded
485	QQ-B-626 Comp 1 QQ-B-637	MIL-W-6712 MIL-T-6945 Comp 1	Naval Brass, High leaded



Table 6-1. Chemical Composition by Trade Name - Continued

Copper Alloy Number	Specification		Trade Name
	Federal	Military	
	Comp 3		
510	QQ-B-750 Comp A QQ-W-401 QQ-R-571, Class FS-RCuSm-2		Phosphor Bronze A
518	QQ-R-571 Class FS-RCu Sm-2		Phosphor Bronze
521	QQ-R-571 Class FS-Rcu Sm-2		Phosphor Bronze C
524	QQ-B-750 Comp D		Phosphor Bronze D
544	QQ-B-750	MIL-B-13501	Phosphor Bronze B-2
606	QQ-C-450 Comp 3		
612	QQ-C-450 Comp 4		
614	QQ-C-450 Comp 5		Aluminum Bronze D
618		MIL-W-6712 MIL-R-18818 MIL-RUA1-2	
622		MIL-R-18818 class MIL-RCA-B	
651	QQ-C-591 Comp B		Low Silicon Bronze B
655	QQ-C-591 Comp A	MIL-T-8231	High Silicon Bronze A
656	QQ-R-571 Class FS-RCuS1	MIL-E13191 class MIL-EcuSi-A	
658		MIL-E-13191 class MIL-ECuSi-A	
661	QQ-C-591 Comp D		
670	QQ-B-728 Class B		Magnesium Bronze B
675	QQ-B-728 Class A		Magnesium Bronze A
680	QQ-R-571 Class FS-RCu-Zinc-3		Bronze Low Fuming (Nickel)
681	QQ-R-571 class FS-RCuZn-2		Bronze, Low Fuming
692	QQ-C-591 Comp E		Silicon Brass



**Table 6-1. Chemical Composition by Trade Name - Continued**

Copper Alloy Number	Specification		Trade Name
	Federal	Military	
715	QQ-R-571 Class FS-RCuNi		Copper Nickel 30 percent
735	QQ-C-585 Comp 6		
745	QQ-C-585 Comp 5 QQ-C-586 comp 5 QQ-W-340 Comp 5		Nickel Silver 65-10
752	QQ-C-585 Comp 1 QQ-C-586 Comp 1 QQ-W-340 Comp 1		Nickel Silver 65-18
764	QQ-C-586 Comp 3 QQ-W-340		
766	QQ-C-585 Comp 7 Comp 3		
770	QQ-C-585 Comp 2 QQ-C-586 Comp 2 QQ-W-340 Comp 2		Nickel Silver 55-18
794	QQ-C-586 Comp 4 QQ-W-340 Comp 4		

**Table 6-2. Hot Working and Annealing Temperatures for Copper and Wrought Copper Alloys**

Commercial Designation	Chemical Composition	Hot Working Temperature °F	Annealing Temperature °F
Copper, commercially pure	99,93 Copper	1300 to 1650	700 to 1200
Gilding Metal	95 Copper, 5 Zinc	1300 to 1650	800 to 1450
Commercial Bronze	90 Copper, 10 Zinc	1400 to 1600	800 to 1450
Red Brass	85 Copper, 15 Zinc	1450 to 1650	800 to 1350
Low Brass	80 Copper, 20 Zinc	1450 to 1650	800 to 1300
Cartridge Brass	70 Copper, 30 Zinc	1350 to 1550	800 to 1300
Yellow Brass	65 Copper, 35 Zinc	(a)	800 to 1300
Muntz Metal	60 Copper, 40 Zinc	1150 to 1450	800 to 1100



**Table 6-2. Hot Working and Annealing Temperatures for Copper and Wrought Copper Alloys - Continued**

Commercial Designation	Chemical Composition	Hot Working Temperature °F	Annealing Temperature °F
Leaded Commercial Bronze	89 Copper, 9.25 Zinc, 1.75 Lead	(a)	800 to 1200
Low Leaded Brass	64.5 Copper, 35 Zinc, 0.5 Lead	(a)	800 to 1300
Medium Leaded Brass	64.5 Copper, 34.5 Zinc, 1 Lead	(a)	800 to 1200
High Leaded Brass	62.5 Copper, 35.75 Zinc, 1.75 Lead	(a)	800 to 1100
Extra High Leaded Brass	62.5 Copper, 35 Zinc, 2.5 Lead	(a)	800 to 1100
Free Cutting Brass	61.5 Copper, 35.5 Zinc, 3 Lead	1300 to 1450	800 to 1100
Leaded Muntz Metal	60 Copper, 39.5 Zinc, 5 Lead	1150 to 1450	800 to 1100
Free Cutting Muntz Metal	60.5 Copper, 38.4 Zinc, 1.1 Lead	1150 to 1450	800 to 1100
Forging Brass	60 Copper, 38 Zinc, 2 Lead	1200 to 1500	800 to 1100
Architectural Bronze	57 Copper, 40 Zinc, 3 Lead	1200 to 1400	800 to 1100
Admiralty	71 Copper, 28 Zinc, 1 Tin	1200 to 1500	800 to 1100
Naval Brass	60 Copper, 39.25 Zinc, 0.75 Tin	1200 to 1400	800 to 1100
Leaded Naval Brass	60 Copper, 37.5 Zinc, 1.75 Tin	1200 to 1450	800 to 1100
Magnesium Bronze	58.5 Copper, 39.2 Zinc 1 Tin, 3 Manganese, 1 Iron	1250 to 1450	800 to 1100
Aluminum Brass	76. Copper, 22 Zinc, Zinc Aluminum	1450 to 1550	800 to 1100
Phosphor Bronze "A"	95 Copper, 5 Tin	(a)	900 to 1250
Phosphor Bronze "C"	92 Copper, 8 Tin	(a)	900 to 1250
Phosphor Bronze "D"	90 Copper, 10 Tin	(a)	900 to 1250
Phosphor Bronze "E"	98- 75 Copper, 1.25 Tin	1450 to 1600	900 to 1200
Cupro-Nickel 30 Percent	70 Copper, 30 Nickel	1700 to 2000	1200 to 1600
Nickel Silver 18 Percent (A)	65 Copper, 17 Zinc, 18 Nickel	(a)	1100 to 1500
Nickel Silver 18 Percent	55 Copper, 27 Zinc, 18 Nickel	(a)	1100 to 1400
High-Silicon Bronze (A)	94.8 Copper, 3 Silicon, 1.5 Magnesium, 0.7 Zinc	1300 to 1650	900 to 1300
Low Silicon Bronze	96. Copper, 2 Silicon, 1.5 Zinc, 0.5 Magnesium	1300 to 1650	900 to 1250

(A) These alloys are usually hot extruded after casting, further hot working is uncommon.

**Table 6-3. Typical Stress-Relief Treatments for Certain Copper Alloys**

Alloy Composition	Temperature °F	Time, Hours
Copper, commercially pure	300	1/2
90 Copper - 10 Zinc	400	1
80 Copper - 20 Zinc	500	1
70 Copper - 30 Zinc	500	1



**Table 6-3. Typical Stress-Relief Treatments for Certain Copper Alloys - Continued**

Alloy Composition	Temperature °F	Time, Hours
63 Copper - 37 Zinc	475	1
60 Copper - 40 Zinc	375	1/2
70 Copper - 29 Zinc - 1 Tin	575	1
85 Copper - 15 Nickel	475	1
70 Copper - 30 Nickel	475	1
64 Copper - 18 Zinc - 18 Nickel	475	1
95 Copper - 5 Tin	375	1
90 Copper - 10 Tin	375	1

**Table 6-4. Standard Machinability Rating of Copper Alloys**

Alloy Designation	Machinability Rating	Surface Speed FPM	Roughing Feed, Inch	Finishing Feed, Inch
Leaded Copper	80	300 to 700	0.006 to 0.020	0.003 to 0.015
Leaded Commercial Bronze	80	300 to 700	0.006 to 0.020	0.003 to 0.015
Low Leaded Brass	60	300 to 700	0.006 to 0.020	0.003 to 0.015
Medium Leaded Brass	70	300 to 700	0.006 to 0.020	0.003 to 0.015
High Leaded Brass	90	300 to 700	0.006 to 0.020	0.003 to 0.015
Free Cutting Brass*	100	300 to 700	0.006 to 0.020	0.003 to 0.015
Forging Brass	80	300 to 700	0.006 to 0.020	0.003 to 0.015
Leaded Naval Brass	70	300 to 700	0.006 to 0.020	0.003 to 0.015
Architectural Bronze	90	300 to 700	0.006 to 0.020	0.003 to 0.015
Red Brass, 85 Percent	30	150 to 300	0.015 to 0.035	0.005 to 0.015
Low Brass, 80 Percent	30	150 to 300	0.015 to 0.035	0.005 to 0.015
Muntz Metal	40	150 to 300	0.015 to 0.035	0.005 to 0.015
Naval Brass	30	150 to 300	0.015 to 0.035	0.005 to 0.015
Magnesium Bronze (A)	30	150 to 300	0.015 to 0.035	0.005 to 0.015
Leaded Nickel Silver, 12 Percent	50	150 to 300	0.015 to 0.035	0.005 to 0.015
Leaded Nickel Silver 18 Percent	50	150 to 300	0.015 to 0.035	0.005 to 0.015
High Silicon Bronze (A)	30	150 to 300	0.015 to 0.035	0.005 to 0.015
Leaded Silicon Bronze (d)	60	150 to 300	0.015 to 0.035	0.005 to 0.015
Aluminum Silicon Bronze	60	150 to 300	0.015 to 0.035	0.005 to 0.015
Electrolytic Tough pitch copper	20	75 to 150	0.015 to 0.040	0.005 to 0.020
Commercial Bronze	20	75 to 150	0.015 to 0.040	0.005 to 0.020
Phosphor Bronze	20	75 to 150	0.015 to 0.040	0.005 to 0.020
Nickel Silver	20	75 to 150	0.015 to 0.040	0.005 to 0.020
Cupro-Nickel	20	75 to 150	0.015 to 0.040	0.005 to 0.020
Aluminum Bronze	20	75 to 150	0.015 to 0.040	0.005 to 0.020
Beryllium Copper	20	75 to 150	0.015 to 0.040	0.005 to 0.020
Chromium Copper	20	75 to 150	0.015 to 0.040	0.005 to 0.020

\*Table based on machining characteristics in comparison to this alloy.



**Table 6-5. Typical Engineering Properties**

	Tensile Strength Kips per Square Inch (KSI)	Yield Strength 0.2 Percent Offset	Percent Elongation In 2 Inches	Fatigue (1) Strength KSI	Rockwell Hardness	Electrical Conductivity Percentage of the International Annealed Copper Standard
A-Annealed	60-78	28-36,000	35-60	30-35	B45-78	17-19
1/4 Hard	75-88	60-80,000	10-35	31-36	B68-90	16-18
1/2 Hard	85-100	55-70,000	5-25	32-38	B88-96	15-17
Hard	100-120	90-112,000	2-8	35-39	B96-102	15-17
Annealed Treated	165-190	100-125,000	4-10	34-38	C36- Minimum	22-25
1/4 Heat Treated	175-200	110-135,000	3-6	35-39	C38- Minimum	22-25
1/2 Heat Treated	785-210	160-195,000	2-5	39-43	C39- Minimum	22-25
Heat Treated	190-215	165-205,000	1-4	41-46	C40- Minimum	22-25
(1) Based on 100,000,000 load cycles.						

**Table 6-6. Age Hardening Time-Temperature Conditions and Material Temper Designations**

Material Form	Temper Designation Before Age Hardening	Age Hardening		Temper Designation After Age Hardening
		Time Hours	Temperature (°F)	
Plate, Sheet or Strip	Annealed	3	600±5	Annealed Treated
	1/4 Hard	2-1/2	600±5	1/4 Heat Treated
	1/2 Hard	2	600±5	1/2 Heat Treated
	Hard	2	600±5	Heat Treated
Forgings Rod and Bar 3/4 Inch or Less Over 3/4 Inch	Annealed	3	600±5	Annealed Treated
	Hard	2	600±5	Heat Treated
	Hard	3	600±5	Heat Treated
Wire	Annealed	3	600±5	Annealed Treated
	1/4 Hard	2	600±5	1/4 Heat Treated
	1/2 Hard	1-1/2	600±5	1/2 Heat Treated
	3/4 Hard	1	600±5	3/4 Heat Treated
<p style="text-align: center;"><b>NOTE</b></p> <p>For additional data see Specification SAE-AMS-H-7199.</p>				



## CHAPTER 7 TOOL STEELS

### 7.1 GENERAL.

Tool steels are essential to the fabrication of aircraft parts. It is therefore necessary to provide guidance in the handling of these important metals. Tool steels are produced and used in a variety of forms. The more common forms are bars, (round, square, hexagonal, or octagonal), drill rods, (round, square, or rectangular), flats, and forged shapes.

### 7.2 ALLOYING ELEMENTS IN TOOL STEELS.

See [Table 7-2](#), Chemical Composition Table.

**7.2.1 Carbon.** Carbon is the most important single element in tool steel. Changing the carbon content a specific amount will change the physical properties a greater degree than the same amount of any other element. Degree of hardness of tool steel quenched from a suitable temperature is a function of carbon content alone.

**7.2.2 Chromium.** In amounts up to 1.80 percent the addition of chromium produced a marked increase in the hardenability (depth of hardness) of steels. Small amounts of chromium toughens the steel (greater impact strength), and increases its strength. Machine ability decreases as chromium increases. The addition of 5 to 15 percent chromium imparts hardening qualities to the steel. A degree of red hardness and resistance to wear and abrasion results from the addition of chromium to steel.

**7.2.3 Cobalt.** Cobalt is sometimes used in high speed tools. Addition of 5 to 8 percent increase the red hardness of these steels.

**7.2.4 Manganese.** This element is present in all steels. In amounts of less than 1/2 percent, it acts as a deoxidizer and desulfurizer. In amounts greater than 15 percent it gives steel air hardening tendencies. In intermediate amounts it is necessary to have other alloying agents present with manganese because of its tendency to make the steel brittle.

**7.2.5 Molybdenum.** Always used in conjunction with other alloying elements, molybdenum acts as an intensifier. It improves the deep hardening and elevated temperature properties of steel.

**7.2.6 Nickel.** Nickel makes the steel more ductile. It is used in only a few applications and only in small amounts.

**7.2.7 Silicon.** This element is present in all steels. In amounts of 1/4 to 1 percent it acts as a deoxidizer. Silicon is added to shock resisting and hot work steels to improve their impact characteristics and hardenability. It has a graphitizing influence and usually requires the addition of carbide stabilizing elements such as molybdenum and chromium.

**7.2.8 Tungsten.** One of the most important features of tungsten steels is their high red hardness. Tungsten steels are fine grained and high strength, which means they hold good cutting edges. Tungsten content is usually 5 - 12 percent in heat resisting tool steels, 4 - 9 percent in tungsten - molybdenum high speed steels, and 14 - 20 percent in straight tungsten high speed steel.

**7.2.9 Vanadium.** This element forms stable carbides and has considerable effect on the hardenability of steels. Undissolved vanadium carbides inhibit grain growth and reduce hardenability. Dissolved carbides increase hardenability. Vanadium is also used as a deoxidizer. It is added to plain carbon tool steels to make them fine grained and tough. It is added to high speed and hot working steels to resist grain growth and help maintain their hardness at elevated temperatures.

### 7.3 SPECIFICATIONS.

The armed services procure tool steels under three different Federal Specifications, dependent upon its intended use. [Table 7-1](#) lists these specifications, and present and past classification of the tool steels. Army Specification 57-108A was superseded by



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

three Army Ordnance Specifications, QQ-S-778, QQ-S-779, and QQ-S-780, which were then superseded by Federal Specification's QQ-T-570, QQ-T-580 and QQ-T-590 respectively.

- D - High carbon-high chromium types
- H - Hot work tool steels
- T - High speed tool steels
- M - Molybdenum Base types
- L - Special purpose, low alloy types
- F - Carbon tungsten tool steels

**Table 7-1. Tool Steel Specifications**

Society of Automotive Engineers (SAE) Designation	Federal Specification		Superseded Specification	
	Number	Class	Number	Classification
W1-0.80 Carbon	QQ-T-580	W1-08	57-108A	A1
W1-0.90 Carbon	QQ-T-580	W1-09	57-108A	A2
W1-1.0 Carbon	QQ-T-580	W1-10	57-108A	A3
W1-1.2 Carbon	QQ-T-580	W1-12	57-108A	A4/A5
W2-0.9 Carbon V	QQ-T-580	W2-09	57-108A	B1
W2-1.0 Carbon V	QQ-T-580	W2-10	57-108A	B1
W3-1.0 Carbon VV	QQ-T-580	W3-10	QQ-S-00779 (Army)	FS-W3-10
A2	QQ-T-570	A2	57-108A	C1
A6	QQ-T-570	A6		
D2	QQ-T-570	D2	57-108A	C2
D3	QQ-T-570	D3	57-108A	C3
D5	QQ-T-570	D5	QQ-S-00778 (Army)	FS-D5
D7	QQ-T-570	D7		
F3	QQ-T-570	F3	57-108A	D1
H11	QQ-T-570	H11		
H12	QQ-T-570	H12	QQ-S-00778 (Army)	FS-H12
H13	QQ-T-570	H13		
H21	QQ-T-570	H21	QQ-S-00778 (Army)	FS-H21
T1	QQ-T-590	T1	QQ-S-00780 (Army)	FS-T1
T2	QQ-T-590	T2	QQ-S-00780 (Army)	FS-T2
T3	QQ-T-590	T3		
T4	QQ-T-590	T4	QQ-S-00780 (Army)	FS-T4
T5	QQ-T-590	T5	QQ-S-00780 (Army)	FS-T5
T6	QQ-T-590	T6	MIL-S-15046 (Ships)	T6
T7	QQ-T-590	T7	QQ-S-00780 (Army)	FS-T7
T8	QQ-T-590	T8	QQ-S-00780 (Army)	FS-T8
M1	QQ-T-590	M1	QQ-S-00780 (Army)	FS-M1
M2	QQ-T-590	M2	QQ-S-00780 (Army)	FS-M2
M3	QQ-T-590	M3	QQ-S-00780 (Army)	FS-M3
M4	QQ-T-590	M4		
M10	QQ-T-590	M-10	57-108A	F1
M15	QQ-T-590	M15		



**Table 7-1. Tool Steel Specifications - Continued**

Society of Automotive Engineers (SAE) Designa- tion	Federal Specification		Superseded Specification	
	Number	Class	Number	Classification
M30	QQ-T-590	M30	57-108A	F3
M34	QQ-T-590	M34	QQ-S-00780 (Army)	FS-M34
01	QQ-T-570	01	57-108A.QQ-T-778	B4
02	QQ-T-570	02	57-108A	B3
06	QQ-T-570	06		
L6	QQ-T-570	L6		
L7	QQ-T-570	L7	QQ-S-00778 (Army)	FS-L7
T15	QQ-T-590	T15		
S1	QQ-T-570	S1	QQ-S-00778 (Army)	FS-S1
S2	QQ-T-570	S2	QQ-S-00778 (Army)	FS-S2
S5	QQ-T-570	S5	QQ-S-00778 (Army)	FS-S5
W5	QQ-T-570	W5	QQ-S-00778 (Army)	FS-W5



Table 7-2. Chemical Composition, Tool Steel

Chemical Composition, Percent (Table II)											
SAE Designation	Carbon	Manga- nese	Silicon	Chro- mium	Vanadium	Molybde- num	Tungsten	Cobalt	Nickel	Cop- per	Phos- phorus
W1-0.80 Carbon	0.70-0.85	0.15-0.35	0.10-0.35	0.15	0.10	0.10	0.15		0.20	0.20	0.025
W1-0.90 Carbon	0.85-0.95	0.15-0.35	0.10-0.35	0.15	0.10	0.10	0.15		0.20	0.20	0.025
W1-1.00 Carbon	0.95-1.10	0.15-0.35	0.10-0.35	0.15	0.10	0.10	0.15		0.20	0.20	0.025
W1-1.20 Carbon	1.10-1.30	0.15-0.35	0.10-0.35	0.15	0.10	0.10	0.15		0.20	0.20	0.025
W2-0.90 Carbon-V	0.85-0.95	0.15-0.35	0.10-0.35	0.15	0.15-0.35				0.20	0.20	0.030
W2-1.00 Carbon-V	0.95-1.10	0.15-0.35	0.10-0.35	0.15	0.15-0.35	0.10	0.15		0.20	0.20	0.030
W3-1.00 Carbon VV	0.95-1.10	0.15-0.35	0.10-0.35	0.15	0.35-0.50	0.10	0.15		0.20	0.20	0.030
A2-5 Percent Chro- mium	0.95-1.05	0.45-0.75	0.20-0.40	4.75-5.50	0.40	0.90-1.40					
A6-Manganese	0.65-0.75	1.80-2.20	0.20-0.40	0.90-1.20		0.90-1.40					
D2	1.40-1.60	0.30-0.50	0.30-0.50	11.0-13.0	0.80	0.70-1.20		0.60			
D3	2.00-2.35	0.24-0.45	0.25-0.45	11.0 13.0	0.80	0.80	0.15				
D5	1.40-1.60	0.30-0.50	0.30-0.50	11.0 13.0	0.80	0.70-1.20		2.5-3.5			
D7	2.15-2.50	0.30-0.50	0.30-0.50	11.5 13.5	2.8-4.4	0.70-1.20					
F3	1.25-1.40	0.20-0.50	0.60-0.90		0.25 maximum		3.00 4.50				
H11	0.30-0.40	0.20-0.40	0.80-1.20	4.75 5.50	0.30-0.50	1.25-1.75					
H12	0.30-0.40	0.20-0.40	0.80-1.20	4.75-5.50	0.50 max	1.25-1.75	1.0-1.7				
H13	0.30-0.40	0.20-0.40	0.80-1.20	4.75-5.50	0.80-1.20	1.25-1.75					
H21	0.30-0.40	0.20-0.40	0.15-0.30	3.00 3.75	0.30-0.50		8.75 10.00				
T1	0.65-0.75	0.20-0.40	0.20-0.40	3.75-4.50	0.90-1.30		17.25- 18.75				
T2	0.75-0.85	0.20-0.40	0.20-0.40	3.75-4.50	1.80-2.40	0.70-1.00	17.50- 19.00				
T3	1.00-1.10	0.20-0.40	0.20-0.40	3.75-4.50	2.90-3.50	0.70-1.00	17.50- 19.00				
T4	0.70-0.80	0.20-0.40	0.20-0.40	3.75-4.50	0.80-1.20	0.10-1.00	17.25- 18.75	4.25 5.75			



Table 7-2. Chemical Composition, Tool Steel - Continued

SAE Designation	Chemical Composition, Percent (Table II)										Phosphorus
	Carbon	Manganese	Silicon	Chromium	Vanadium	Molybdenum	Tungsten	Cobalt	Nickel	Copper	
T5	0.75-0.85	0.20-0.40	0.20-0.40	3.75-4.75	1.80-2.40	0.70-1.00	17.50-19.00	7.00 9.50			
T6	0.75-0.85	0.20-0.40	0.20-0.40	4.00-4.75	1.50-2.10	0.70-1.00	18.50-21.25	10.25 13.75			
T7	0.70-0.76	0.20-0.40	0.20-0.40	3.75-4.25	1.80-2.20	0.70-1.00	13.50-14.50				
T8	0.75-0.85	0.20-0.40	0.20-0.40	3.75-4.50	1.80-2.40	0.70-1.00	13.25-14.75	4.25 5.75			
M1	0.75-0.85	0.20-0.40	0.20-0.40	3.75-4.50	0.90-1.30	7.75-9.25	1.15-1.85				
M2	0.78-0.88	0.20-0.40	0.20-0.40	3.75-4.50	1.60-2.20	4.50-5.50	5.50-6.75				
M3	1.00-1.25	0.20-0.40	0.20-0.40	3.75-4.50	2.35-3.25	4.75-6.25	5.50-6.75				
M4	1.25-1.40	0.20-0.40	0.20-0.40	4.00-4.75	3.90-4.50	4.50-5.50	5.25-6.50				
M10	0.85-0.95	0.20-0.40	0.20-0.40	3.75-4.50	1.80-2.20	7.75-9.00					
M15	1.50-1.60	0.20-0.40	0.20-0.40	4.00-5.00	4.50-5.25	2.75-3.50	6.00-6.75	4.75-5.25			
M30	0.77-0.85	0.20-0.40	0.20-0.40	3.50-4.25	1.00-1.40	7.75-9.00	1.30-2.30	4.50-5.50			
M34	0.85-0.92	0.20-0.30	0.20-0.30	3.50-4.25	1.90-2.30	8.00-9.20	1.30-2.30	1.75 8.75			
O1	0.85-0.95	1.00-1.30	0.20-0.40	0.40-0.60	0.30 max		0.40-0.60				
O2	0.85-0.95	1.40-1.80	0.20-0.40	0.35	0.20	0.30					
O6	1.35-1.55	0.30-1.00	0.80-1.20			0.20-0.30					
L6	0.65-0.75	0.30-0.80	0.20-0.40	0.65-0.85	0.20-0.35	0.20-0.35			1.25 1.75		
L7	0.95-1.05	0.25-0.45	0.20-0.40	1.25-1.75		0.30-0.50					
T15	1.50-1.60			3.75-4.50	4.75-5.25		12.00-13.00	4.75-5.25			
S1	0.45-0.55	0.20-0.40	0.25-0.45	1.25-1.75	0.15-0.30	0.40	1.0-3.0				
S2	0.45-0.55	0.30-0.50	0.80-1.20		0.25	0.40-0.60					
S5	0.50-0.60	0.60-0.90	1.80-2.20	0.30	0.25	0.30-0.50					
W5	1.05-1.25	0.15-0.35	0.10-0.40	0.40-0.60	0.25 max	0.30-0.50					



**Table 7-3. Tool Steel Selection**

Material To Be Cut	Total Quantity Of Parts To Be Made		
	1,000	10,000	100,000
Aluminum, copper and magnesium alloys	W1, AIS14140	W1, 01, A2	01, A2
Carbon and alloy steels, ferritic stainless	W1, AIS14140	W1, 01, A2	01, A2
Stainless steel, austenitic	W1, A2	W1, A2, D2	A2, D2
Spring steel, hardened, Rockwell C52 max	A2	A2, D2	D2
Electrical sheet, transformer grade	A2	A2, D2	D2
Paper, gaskets, and similar soft material	W1	W1	W1, A2
Plastic sheet, not reinforced	01	01	01, A2
Table 7-3 is listed for use as a guide reference in the selection of tool steel types for specific applications.			

**Table 7-4. Tool Steel Hardening and Tempering Temperatures**

Steel	Hardening Treatment	Tempering Treatment	Size Change, In/In
W	1450 °F, Water	300 °F	0.0017 - 0.0025
O	1450 °F, Oil	300 °F	0.0014 - 0.0021
L	1550 °F, Oil	300 °F	0.0014 - 0.0024
F	1600 °F, Oil	300 °F	0.0011 - 0.0021
S	1750 °F, Oil	500 °F	0.0010 - 0.0025
A	1775 °F, Oil	500 °F	0.0005 - 0.0015
D	1875 °F, Oil	500 °F	0.0005 - 0.0005
T	2350 °F, Oil	1050 °F	0.0006 - 0.0014
M	2225 °F, Oil	1025 °F	0.0016 - 0.0024

#### 7.4 CLASS DESIGNATIONS.

- W - Water hardening tool steels
- S - Shock resisting tool steels
- O - Cold work tool steels, oil hardening types
- A - Cold work tool steels, air hardening types

#### 7.5 APPLICATIONS OF TOOL STEELS.

The majority of tool steel applications can be divided into a small number of groups: cutting, shearing, forming, drawing, extrusion, rolling and battering. Cutting tools include drills, taps, broaches, hobs, lathe tools, etc.. Shearing tools include shears, blanking and trimming dies, punches, etc.. Forming tools include draw, forging, cold heading and die casting dies. Battering tools include chisels and all forms of shock tools. Most cutting tools require high hardness, high resistance to the softening effect of heat, and high wear resistance. Shearing tools require high wear resistance and fair toughness. Forming tools must possess high wear resistance or high toughness and strength. In battering tools, high toughness is most important.

#### 7.6 SELECTION OF MATERIAL FOR A CUTTING TOOL.

The selection of material for a cutting tool depends on several factors: the metal being machined, nature of cutting operation, condition of the machine tool, machining practice, size and design of tool, coolant to be used, and cost of tool material. Selection is usually based more on previous experience or applications than on an engineering or metallurgical analysis.



**7.6.1 High Speed Cutting Tools.** High speed cutting tools are usually manufactured from the class “T” or class “M” alloys. Four classes, T1, M1, M2 and M10 make up nearly 90 percent of the general purpose high speed steels. Certain special purpose steels in each class, such as T6, T7, T8 and T15 are advantageous for operations like milling cutters and prehardened forging die blocks.

**7.6.2 High Speed Drills.** High speed drills should possess high strength and toughness, notably M1, M2, M10 and T1. Classes T1 and M1 are used for tools subject to shock, while M2 and M10 are generally used where tools require less toughness and more abrasion resistance.

**7.6.3 Material for Reamers.** Material for reamers should be of high hardness and abrasion resistance, such as M1, M2, M10 and T1. The M3 and M15 and T15 classes possess greater abrasion resistance than the lower vanadium grades.

**7.6.4 Material for Taps.** Material for taps is generally of the M1, M2 or M10 types. In tapping heat-resisting alloys or steels harder than Rockwell C35, M15 or T15 may be justified.

**7.6.5 Milling Cutters.** Milling cutters are usually made from the high speed steels. As the hardness of the workpiece increases beyond Rockwell C35, the cobalt high speed steels should be used.

**7.6.6 Punch and Die Material.** Recommended punch and die material for blanking parts from 0.050 inch sheet materials are shown in following table. This table does not cover all operations, and is a sample table intended for use as a guide only.

## 7.7 HEAT TREAT DATA.

### NOTE

Additional Heat Treatment information is discussed in Chapter 9.

The thermal treatments listed in [Table 7-5](#) cover the generally used treatments for the forgings, normalizing, and annealing of tool and die steels. The thermal treatments listed in [Table 7-7](#) cover the usual ranges of temperatures for hardening and tempering tool and die steels. These tables are listed for use as a guide only, and test samples should be checked prior to use.

## 7.8 DISTORTION IN TOOL STEELS.

Distortion is a general term encompassing all dimensional changes; the two main types being volume change or change in geometrical form. Volume change is defined as expansion or contraction and geometric change is defined as changes in curvature or angular relations. [Table 7-4](#) shows an approximate range of size changes depending upon the type of tool steel, and also dependent on specific tempering and heat treatments. If a very close tolerance is required for a finished tool, specific data covering this item should be obtained from a detailed source.



Table 7-5. Forging, Normalizing and Annealing Treatments of Tool and Die Steels

SAE Designation	Forging/A		Normalizing/B		Annealing/C				
	Heat Slowly To	Start Forging At	Do Not Forge Below	Heat Slowly To	Hold At	Temperature	Maximum Rate Of Cooling F/Hour	Brinell Hardness Approximate	Rockwell B, Approximate
W1 (0.8C)	1450	1800 1950	1500	1450	1500	1400-1450	75	159-202	84-94
W1 (0.9C)	1450	1800 1950	1500	1450	1500	1375-1425	75	159-202	84-94
W1 (1.0C)	1450	1800 1900	1500	1450	1550	1400-1450	75	159-202	84-94
W1 (1.2C)	1450	1800 1900	1500	1450	1625	1400-1450	75	159-202	84-94
W2 (0.9C)	1450	1800 1900	1500	1450	1500	1375-1425	75	159-202	84-94
W2 (1.0C)	1450	1800 1900	1500	1450	1550	1400-1450	75	159-202	84-94
W3 (1.0C)	1450	1800 1900	1500	1450	1550	1400-1450	75	159-202	84-94
A2	1600	1850 2000	1650	Do Not Normalize		1550-1600	40	202-229	94-98
A6	1200-1300			Do Not Normalize				248	102
D2	1650	1850 2000	1650	Do Not Normalize		1600-1650	40	207-255	95-102
D3	1650	1850 2000	1650	Do Not Normalize		1600-1650	50	212-255	96-102
D5	1650	1850 2000	1650	Do Not Normalize		1600-1650	40	207-255	95-102
D7	1650	2050 2125	1800	Do Not Normalize		1600-1650	50	235-262	99-103
F3	1550	1800 2000	1600	Do Not Normalize		1475	50	235	99
H11	1650	1950 2100	1650	Do Not Normalize		1550-1600	50	192-229	92-98
H12	1650	1950 2100	1650	Do Not Normalize		1600-1650	50	192-229	92-98
H13	1650	1950 2100	1650	Do Not Normalize		1550-1600	50	192-229	92-98
H21	1600	2000 2150	1650	Do Not Normalize		1600-1650	50	202-235	94-99
T1	1600	1950 2100	1750	Do Not Normalize		1600-1650	50	217-255	96-102
T2	1600	2000 2150	1750	Do Not Normalize		1600-1650	50	223-255	97-102
T3	1925	2025	1750	Do Not Normalize		1650	50		
T4	1600	2000 2150	1750	Do Not Normalize		1600-1650	50	229-255	98-102
T5	1600	2000 2150	1800	Do Not Normalize		1600-1650	50	248-293	102-106
T6	1600	1950 2150	1700	Do Not Normalize		1600-1650	50	248-293	102-106
T7	1600	1950 2150	1700	Do Not Normalize		1550-1625	50	217-250	96-102
T8	1600	2000 2150	1750	Do Not Normalize		1600-1650	50	229-255	98-102
M1	1500	1900 2050	1700	Do Not Normalize		1525-1600	50	207-248	95-102
M2	1500	1950 2100	1700	Do Not Normalize		1550-1625	50	217-248	96-102
M3	1500	2000 2150	1700	Do Not Normalize		1550-1625	50	223-255	97-102
M4	1500	2000 2150	1700	Do Not Normalize		1550-1625	50	229-255	98-102
M10	1400	1900 2100	1700	Do Not Normalize		1600-1650	50	235-262	99-103



Table 7-5. Forging, Normalizing and Annealing Treatments of Tool and Die Steels - Continued

SAE Designation	Forging/A			Normalizing/B		Annealing/C			
	Heat Slowly To	Start Forging At	Do Not Forge Below	Heat Slowly To	Hold At	Temperature	Maximum Rate Of Cooling F/Hour	Brinell Hardness Approximate	Rockwell B, Approximate
M15	1400	1900 2100	1700	Do Not Normalize		1600-1650	50	235-262	99-103
M30	1400	1900 2100	1600	Do Not Normalize		1600-1650	50	235-262	99-103
M34	1400	1900 2100	1600	Do Not Normalize		1600-1650	50	235-262	99-103
O1	1500	1750 1900	1550	1500	1600	1425-1475	50	183-212	90-96
O2	1500	1750 1900	1550	1500	1550	1375-1425	50	183-212	90-96
O6	1500	1750 1900	1500	1500	1625	1425-1275	50	183-212	90-96
L6	1500	1800 2000	1600	1550	1650	1400-1450	50	183-212	90-96
L7	1500	1800 2000	1550	1550	1650	1450-1500	50	174-212	88-96
T15	1500	2000 2100	1600	Do Not Normalize		1600-1650	35	241-269	100-104
S1	1500	1800 2000	1600	Do Not Normalize		1450-1500	50	192-235	92-99
S2	1500	1900 2100	1600	1500	1650	1400-1450	50	192-229	92-98
S5	1500	1900 2050	1600	1500	1600	1400-1450	50	192-229	92-98
W5	1200	1700 1900	1500	Do Not Normalize		1400-1425	50	192-212	92-96

a. The temperature at which to start forging is given as a range, the higher side of which should be used for large sections and heavy or rapid reductions, and the lower side for smaller sections and lighter reductions, as the alloy content of the steel increases, the time of soaking at forging temperature increases proportionately. Likewise, as the alloy content increases, it becomes more necessary to cool slowly from the forging temperature. With the very high alloy steels, such as high speed or air hardening steels, this slow cooling is imperative in order to prevent cracking and to leave the steel in a semi-soft condition. Either furnace cooling or burying in an insulating medium such as lime, mica, or silocel is satisfactory.

b. The length of time the steel is held after being uniformly heated through at the normalizing temperature, varies from about 15 minutes for a small section to about 1 hour for larger sizes. Cooling from the normalizing temperatures is done in still air. The purpose of normalizing after forging is to refine the grain structure and to produce a uniform structure throughout the forging. Normalizing should not be confused with low temperature (about 1200°F) annealing used for the relief of residual stresses resulting from heavy machining, bending and forming.

c. The annealing temperature is given as a range, the upper limit of which should be used for large sections, and the lower limit for smaller sections. The temperature varies from about 1 hour for light sections and small furnace charges of carbon or low alloy steel, to about 4 hours for heavy sections and large furnace charges of high alloy steel.



Table 7-6. Thermal Treatment for Hardening and Tempering Tool Steel - General

Class	Quench Medium	Preheat Temperature °F	Hardening Temperature Range °F	Hardness After Quenching Rockwell °C	Tempering Temperature Range °F	Hardness After Tempering Rockwell °C	Decarburization (Prevention Of During Heat Treatment)
W1-08	Water	a	1420-1450	65-67	350-525	65-56	b
W1-09	Water	a	1420-1450	65-67	350-525	65-56	b
W1-10	Water	a	1420-1450	65-67	350-525	65-56	b
W1-12	Water	a	1420-1500	65-67	350-525	65-56	b
W2-09	Water	a	1420-1500	65-67	350-525	65-56	b
W2-10	Water	a	1420-1500	65-67	350-525	65-56	b
W3-10	Water	a	1420-1500	65-67	350-525	65-56	b
A2	Air	1200-1300	1725-1775	61-63	400-700	60-57	c
A6	Air	1200-1300	1525-1600	60			
D2	Air	1200-1300	1800-1875	61-63	400-700	60-58	c
D3	Oil	1200-1300	1750-1800	62-64	400-700	62-58	c
D5	Air	1200-1300	1800-1875	60-62	400-700	59-57	c
D7	Air	1200-1300	1850-1950	63-65	300-500 850-1000	65-63 62-58	c
F3	Water	a	1550	62-66	300-500	66-62	c
H11	Air	1450-1500	1825-1875	53-55	1000-1100	51-43	c
H12	Oil-Air	1450-1500	1800-1900	53-55	1000-1100	51-43	c
H13	Air	1400-1450	1825-1575	53-55	1000-1100	51-43	c
H21	Oil-Air	1500-1550	2100-2150	50-52	950-1150	50-47	c
T1	Oil-Air-Salt	1500-1550	2300-2375	63-65	1025-1100	65-63	c
T2	Oil-Air-Salt	1500-1550	2300-2375	63-65	1025-1100	63-65	c
T3	Oil-Air	1500-1550	2275-2325		1000-1050	67-60	c
T4	Oil-Air-Salt	1500-1550	2300-2375	63-65	1026-1100	65-63	c
T5	Oil-Air-Salt	1500-1550	2300-2400	63-65	1050-1100	65-63	c
T6	Oil	1600	2350	60-65	1000-1100	65-60	c
T7	Oil	1600	2325	60-65	1000-1100	65-60	c
T8	Oil-Air-Salt	1500-1550	2300-2375	63-65	1025-1100	65-63	c
M1	Oil-Air-Salt	1400-1500	2150-2250	63-65	1025-1100	65-63	c
M2	Oil-Air-Salt	1450-1500	2175-2250	63-65	1025-1075	65-63	c
M3	Oil-Air-Salt	1450-1500	2150-2225	63-65	1025-1075	65-63	c
M4	Oil-Air-Salt	1450-1500	2150-2225	63-65	1025-1075	65-63	c
M10	Oil	1400	2220	60-65	1000-1100	65-60	c



Table 7-6. Thermal Treatment for Hardening and Tempering Tool Steel - General - Continued

Class	Quench Medium	Preheat Temperature °F	Hardening Temperature Range °F	Hardness After Quenching Rockwell °C	Tempering Temperature Range °F	Hardness After Tempering Rockwell °C	Decarburization (Prevention Of During Heat Treatment)
M15	Oil	1400	2220	60-65	1000-1100	65-60	c
M30	Oil	1400	2220	60-65	1000-1100	65-60	c
M34	Oil	1400	2220	60-65	1000-1100	65-60	c
O1	Oil	a	1450-1500	63-65	300-800	62-50	b
O2	Oil	a	1420-1450	63-65	375-500	62-57	b
O6	Oil	a	1450-1500	63-65	300-800	63-50	b
L6	Oil	a	1500-1600	62-64	400-800	62-48	b
L7	Oil	a	1525-1550	63-65	350-500	62-60	b
T15	Oil-Air	1500-1600	2250-2300	65-66	1025-1100	66-68	c
S1	Oil	1200-1300	1650-1800	57-59	300-1000	57-45	c
S2	Water-oil	a	1550-1575	60-62	300-500	60-54	b
S5	Water		1660-1625	58-60	300-500	58-54	b
	Oil		1550-1600	60-62	300-650	60-54	b
			1600-1675	58-60	300-650	58-54	b
W5	Water	1100-1200	1400-1550	65-66	300-400	62-65	b

a. For large tools and tools having intricate sections, preheating at 1050 to 1200 °F is recommended.

b. Use moderately oxidizing atmosphere in furnace or a suitable neutral salt bath.

c. Use protective pack from which volatile matter has been removed, carefully balanced neutral salt bath or atmosphere controlled furnaces. In the latter case, the furnace atmosphere should be in equilibrium with the carbon content of the steel being treated. Furnace atmosphere dew point is considered a reliable method of measuring and controlling this equilibrium.



Table 7-7. Comparison of Tool Steel Properties

Class	Non Deforming Properties	Toughness	Resistance To Softening Effect Of Heat	Wear Resistance	Machine Ability
W1-08	Poor	Good	Poor	Fair	Best
W1-09	Poor	Good	Poor	Fair	Best
W1-10	Poor	Good	Poor	Good	Best
W1-12	Poor	Good	Poor	Good	Best
W2-09	Poor	Good	Poor	Fair	Best
W2-10	Poor	Good	Poor	Good	Best
W3-10	Poor	Good	Poor	Good	Best
A2	Best	Fair	Fair	Good	Fair
A6	Good	Fair	Poor	Good	Fair
D2	Best	Fair	Fair	Best	Poor
D3	Good	Poor	Fair	Best	Poor
D5	Best	Fair	Fair	Best	Poor
D7	Best	Poor	Fair	Best	Poor
F3	Poor	Poor	Poor	Best	Fair
H11	Good	Good	Good	Fair	Fair
H12	Good	Good	Good	Fair	Fair
H13	Good	Good	Good	Fair	Fair
H21	Good	Good	Good	Fair	Fair
T1	Good	Poor	Good	Good	Fair
T2	Good	Poor	Good	Good	Fair
T3	Good	Poor	Good	Good	Fair
T4	Good	Poor	Best	Good	Fair
T5	Good	Poor	Best	Good	Fair
T6	Good	Fair	Good	Best	Fair
T7	Good	Poor	Good	Best	Fair
T8	Good	Poor	Best	Good	Fair
M1	Good	Poor	Good	Good	Fair
M2	Good	Poor	Good	Good	Fair
M3	Good	Poor	Good	Best	Fair
M4	Good	Poor	Good	Best	Fair
M10	Good	Poor	Good	Best	Fair
M15	Good	Poor	Good	Best	Fair
M30	Good	Poor	Good	Best	Fair
M34	Good	Poor	Good	Best	Fair
01	Good	Fair	Poor	Good	Good
02	Good	Fair	Poor	Good	Good
06	Fair	Fair	Poor	Good	Best
L6	Fair	Fair	Poor	Fair	Fair
L7	Fair	Fair	Poor	Good	Fair
T15	Good	Poor	Best	Best	Fair
S1	Fair	Good	Fair	Fair	Fair
S2	W-Poor	Best	Fair	Fair	Good
S5	O-Fair W-Poor	Good	Poor	Fair	Best



**Table 7-7. Comparison of Tool Steel Properties - Continued**

Class	Non Deforming Properties	Toughness	Resistance To Softening Effect Of Heat	Wear Resistance	Machine Ability
W5	O-Fair Poor	Good	Poor	Fair	Best







## CHAPTER 8

# TESTING AND INSPECTION HARDNESS TESTING

### 8.1 GENERAL.

Hardness testing is used to determine the results of heat treatment as well as the state of the metal prior to heat treatment. Its application in determining the approximate tensile strength of the material by use of a hardness-tensile strength table is very limited and should only be used in the case of ferrous (steel) alloys. [Table 8-1](#) should be used only as a conversion table for converting the various hardness values from one type of test to another, and should not be used as an indication of tensile strength for alloys other than ferrous. In addition, it should be realized that values given in [Table 8-1](#) are only approximate. Whenever a specific type of hardness test is given in a drawing, specification, etc., necessary hardness readings should be made by that test whenever possible, rather than by other means, and a conversion made. In obtaining hardness values, precaution must be taken to assure removal of cladding and decarburized surface layers from area to be tested.

### 8.2 METHODS OF HARDNESS TESTING.

The methods of hardness testing in general use are: Brinell, Rockwell, Vickers (British), Tukon and Shore scleroscope.

**8.2.1 Brinell Hardness Test.** This test consists of pressing a hardened steel ball into a flat surface of the metal being tested by the application of a known pressure. The impression made by the ball is measured by means of a microscope with a micrometer eyepiece. The Brinell “number” is obtained by dividing the load in kilograms by the area of the spherical impression made by the ball, measured in square millimeters. The thickness of all samples used for testing must be sufficient to prevent bulging on the under side. The Brinell tester ([Figure 8-1](#)) consists of the following major parts:

- a. An elevating screw and anvil for bringing the sample into contact with the ball.
- b. A manually operated hydraulic pump for applying the pressure to the hardened steel ball, which is mounted on its actuating member.
- c. A pressure gage for determining the applied pressure.
- d. A release mechanism with micrometer eyepiece for calculating the area of the impression.

**8.2.2 Making The Brinell Test.** The test is preformed as follows:

- a. Prepare the sample by filing, grinding, and polishing to remove all scratches and variations that may affect the reading.
- b. Place the sample on the anvil of the machine and elevate until the hardened ball contacts the surface to be tested.
- c. Apply the load by pumping handle.

#### NOTE

A load of 3,000 kilograms is required for steel, while 500 kilograms is used when testing the softer metals, such as aluminum alloy, brass, and bronze. Normally, the load should be applied for 30 seconds. Although this period may be increased to 1 minute for extremely hard steels, in order to produce equilibrium.

- d. Release the pressure and measure the area of impression with the calibrated microscope.
- e. Calculate the Brinell number, completing the test.

### 8.3 ROCKWELL HARDNESS TEST.

The Rockwell hardness test is based on the degree of penetration of a specifically designed indenter into a material under a given static load. The indenter/penetrator used may be either a diamond or hardened steel ball. The diamond indenter called a “brale” is precision ground and polished and the shape is sphericonica. The steel ball for normal use is 1/16 inch diameter,



## TO 1-1A-9

### NAVAIR 01-1A-9

however, other larger diameter steel balls such as 1/8, 1/4 or 1/2 inch may be used for testing soft metals. The selection of the ball is based on the hardness range of the type of material to be tested.

**8.3.1 Rockwell Machine/Tester.** The Rockwell machine/tester for accomplishing the hardness test applies two loads to obtain the controlled penetration and indicates results on a graduated dial (see [Figure 8-2](#)). A minor load of 10 kilograms is first applied to seat the penetrator in the surface of the test specimen. The actual penetration is then produced by applying a major load, subsequently, releasing and then reading hardness number from the dial. The dial reading is related to the depth of penetration, load and the penetrator used. The shallower the penetration, the higher the hardness value number for given indenter and load. The normal major load is 150 kilograms ("C" Scale) when using the diamond penetrator and 100 kilograms ("B" Scale) when using a 1/16 inch steel ball. A hardness value indicated by a number alone is incomplete. The number must be prefixed with a letter to indicate the load and indenter used to obtain the number. There is a variety of combinations of indentors and loads used to obtain a hardness value in accordance with hardness range of various material. The combinations are listed in [Table 8-2](#) which is based on Specification ASTM E-18.

**8.3.1.1** Review of [Table 8-2](#) will reveal that the Red Dial Numerals "B" scale are used for steel ball indentors regardless of size of ball or load and Black Figure "C" scales are used for the diamond penetrator. When the readings fall below the hardness value, C20 (B98) the material is considered too soft for the diamond cone and 1/16 inch or larger hardened ball should be used. The diamond cone must be used for all hard materials (those above 100 on the "B" scale) as the steel ball may be deformed by the test. If in doubt about the hardness of a material start with the diamond penetrator and switch to the steel ball if the material is below C20-C22.

**8.3.2 Rockwell Test Procedure.** The procedure for making the Rockwell test is outlined as follows: (See [Figure 8-2](#) for machine illustrations.)

- a. Prepare the sample by removing (file, grind and polish) scale, oxide films, pits, variations and foreign material that may affect the reading. The surface should be flat, of one thickness and no bludge should be opposite the indentation.

#### NOTE

Do not perform test closer than 1/8 inch from edge of specimen to assure accurate reading.

- b. Select the proper anvil and penetrator and place proper weight on the weight pan.
- c. Check trip lever for proper location. Lever should be located in the OFF LOAD position.
- d. Place the test specimen on the anvil and by turning the hand wheel, raise it slowly (do not crash) until contact is made with the penetrator. On the older model continue turning until pointer of the indicator has made three revolutions and is within five divisions (plus or minus) of the upright position. On the newer model after contact, continue turning hand wheel until the small pointer is nearly vertical and slightly to right of the dot. Then watching the long pointer, raise specimen until long pointer is approximately upright within three degrees (plus or minus) of C-0. K the C = +3 degrees position is overshot, lower the specimen and start over. When the pointer is within three divisions of C-0, set dial to zero. After this step is complete, the minor load has been applied.
- e. Apply the major load by tripping the trip lever. Trip the lever, do not push.
- f. When the trip lever comes to rest and there is no further movement of pointer, return lever to the original position and read the hardness number indicated by the dial. When dial pointer indicates a fraction, use next lower whole number for the reading.

**8.3.2.1** All hardness tests should be made on a single thickness to obtain accurate results. In testing curved specimens, the concave side should face the indenter; if reversed, an inaccurate reading will result due to flattening of the piece on the anvil. Specimens that do not balance on the anvil because of overhang should be properly supported to obtain accurate readings and to prevent damaging the penetrator. Also to obtain a true indication of hardness of a given part, several readings (3-6 is usually sufficient) at different points should be taken and averaged. If it is necessary to determine the condition of the interior, parts should be cut by some method that does not appreciably change the temper/condition, such as using a water-cooled saw-off wheel. When testing clad material; the clad coat shall be removed. Specimen samples of clad and other materials should be provided when possible. It is not desirable to accomplish the test on the finished part. The Rockwell testers are equipped with various anvils and indentors. Typical anvils and attachments are shown in [Figure 8-3](#). The anvil(s) should be



properly selected to accomplish the job. The tester should also be properly set and in good working order before making any test. The table on which the Rockwell tester is mounted must be rigid and not subject to any vibration if accurate results are to be obtained.

8.3.2.2 The accuracy of the Rockwell hardness tester should be checked regularly. Test blocks are available for testing all ranges of hardness. If the error in the tester is more than  $\pm 2$  hardness numbers, it should be re-calibrated. The dashpot should be checked or oil and properly adjusted for completion of travel. The ball indenter and diameter should also be checked regularly for bluntness and chipping and replaced as required.

**Table 8-1. Hardness Conversion Chart for Hardened Steel and Hard Alloys Scale**

C	A	D	15-N	50-N	45-N	Vickers	Brinell	G	Shore
Rockwell Hardness Teller			Rockwell Superficial				Hultgren 10 mm Ball	Rockwell Test 1/16 Ball	
Penetrator									
“Brale”			“N Brale”						
Load (kilogram)									
150	60	100	15	30	45	10	3000	150	
80	92.0	86.5	96.5	92.0	87.0	1865			
79	91.5	85.5		91.5	86.5	1787			
78	91.0	84.5	96.0	91.0	85.5	1710			
77	90.5	84.0		90.5	84.5	1633			
76	90.0	83.0	95.5	90.0	83.5	1556			
75	89.5	82.5		89.0	82.5	1478			
74	89.0	81.5	95.0	88.5	81.5	1400			
73	88.5	81.0		88.0	80.5	1323			
72	88.0	80.0	94.5	87.0	79.5	1245			
71	87.0	79.5		86.5	78.5	1160			
70	86.5	78.5	94.0	86.0	77.5	1076			
69	86.0	78.0	93.5	85.0	76.5	1004			
68	85.5	77.0		84.5	75.5	942			96
67	85.0	76.0	93.0	83.5	74.5	894			94
66	84.5	75.5	92.5	83.0	73.0	854			
65	84.0	74.5	92.0	82.0	72.0	820			92
64	83.5	74.0		81.0	71.0	789			
63	83.0	73.0	91.5	80.0	70.0	763			89
62	82.5	72.5	91.0	79.0	69.0	730			86
61	81.5	71.5	90.5	78.5	67.5	716			
60	81.0	71.0	90.0	77.5	66.5	695	614		84
59	80.5	70.0	89.5	76.5	65.5	675	600		
58	80.0	69.0		75.5	64.0	655	587		81
57	79.5	68.5	89.0	75.0	63.0	636	573		
56	79.0	67.5	88.5	74.0	62.0	617	560		78
55	78.5	67.0	88.0	73.0	61.0	598	547		75
54	78.0	66.0	87.5	72.0	59.5	580	534		
53	77.5	65.5	87.0	71.0	58.5	562	522		73
52	77.0	64.5	86.5	70.5	57.5	545	509		
51	76.5	64.0	86.0	69.5	56.0	528	496		71
50	76.0	63.0	85.5	68.5	55.0	513	484		68
49	75.5	62.0	85.0	67.5	54.0	498	472		
48	74.5	61.5	84.5	66.5	52.5	485	460		66
47	74.0	60.5	84.0	66.0	51.5	471	448		64



**Table 8-1. Hardness Conversion Chart for Hardened Steel and Hard Alloys Scale - Continued**

C	A	D	15-N	50-N	45-N	Vickers	Brinell	G	Shore
Rockwell Hardness Teller			Rockwell Superficial				Hultgren 10 mm Ball	Rockwell Test 1/16 Ball	
Penetrator									
“Brale”			“N Brale”						
Load (kilogram)									
46	73.5	60.0	83.5	65.0	50.0	458	437		62
45	73.0	59.0	83.0	64.0	49.0	446	426		
44	72.5	58.5	82.5	63.0	48.0	435	415		60
43	72.0	57.5	82.0	62.0	46.5	424	404		58
42	71.5	57.0	81.5	61.5	45.5	413	393		56
41	71.0	56.0	81.0	60.5	44.5	403	382		54
40	70.5	55.5	80.5	59.5	43.0	393	372		
39	70.0	54.5	80.0	58.5	42.0	383	362		52
38	69.5	54.0	79.5	57.5	41.0	373	352		51
37	69.0	53.0	79.0	56.5	39.5	363	342		49
36	68.5	52.5	78.5	56.0	38.5	353	332		48
35	68.0	51.5	78.0	55.0	37.0	343	322		46
34	67.5	50.5	77.0	54.0	36.0	334	313		45
33	67.0	50.0	76.5	53.0	35.0	325	305		
32	66.5	49.0	76.0	52.0	33.5	317	297		43
31	66.0	48.5	75.5	51.5	32.5	309	290		42
30	65.5	47.5	75.0	50.5	31.5	301	283	92.0	41
29	65.0	47.0	74.5	49.5	30.0	293	276	91.0	40
28	64.5	46.0	74.0	48.5	29.0	285	270	90.0	38
27	64.0	45.5	73.5	47.5	28.0	278	265	89.0	37
26	63.5	44.5	72.5	47.0	26.5	271	260	88.0	36
25	63.0	44.0	72.0	46.0	25.5	264	255	87.0	35
24	62.5	43.0	71.5	45.0	24.0	257	250	86.0	34
23	62.0	42.5	71.0	44.0	23.0	251	245	84.5	33
22	61.5	41.5	70.5	43.0	22.0	246	240	84	32
21	61.0	41.0	70.0	42.5	20.5	241	235	82.5	32
20	60.5	40.0	69.5	41.5	19.5	236	230	81.0	31
4 sided 136° Diamond Pyramid, 10 kilogram Load. Measurement of 2 diagonals by microscope.									

**Table 8-2. Hardness Conversion Chart for Unhardened Steel, Steel of Soft Temper, Grey and Malleable Cast Iron and Most Non-Ferrous Metal 100-3000 Load**

For Unhardened Steel, Steel of Soft Temper, Grey and Malleable Cast Iron and Most Non-Ferrous Metal Scale											
B	F	G	15-T	30-T	45-T	E	K	A	Brinell		Shore
Rockwell Hardness Tester			Rockwell Superficial			Rockwell Hardness Tester		Standard Type			
Ball Penetrator											
1/16			1/16			1/8		Brale	10 millimeter		
Load (kilogram)											
100	60	150	15	30	45	100	150	60	500	3000	
100		82.5	93.0	82.0	72.0			61.5	201	240	33
99		81.0	92.5	81.5	71.0			61.0	195	234	32
98		79.0		81.0	70.0			60.0	189	228	32



**Table 8-2. Hardness Conversion Chart for Unhardened Steel, Steel of Soft Temper, Grey and Malleable Cast Iron and Most Non-Ferrous Metal 100-3000 Load - Continued**

For Unhardened Steel, Steel of Soft Temper, Grey and Malleable Cast Iron and Most Non-Ferrous Metal Scale											
B	F	G	15-T	30-T	45-T	E	K	A	Brinell		Shore
Rockwell Hardness Tester			Rockwell Superficial			Rockwell Hardness Tester			Standard Type		
Ball Penetrator											
1/16			1/16			1/8		Brale	10 millimeter		
Load (kilogram)											
97		77.5	92.0	80.5	69.0			59.5	184	222	31
96		76.0		80.0	68.0			59.0	179	216	30
95		74.0	91.5	79.0	67.0			58.0	175	210	30
94		72.5		78.5	66.0			57.5	171	205	29
93		71.0	91.0	78.0	65.5			57.0	167	200	28
92		69.0	90.5	77.5	64.5		100	56.5	163	195	28
91		67.5		77.0	63.5		99.5	56.0	160	190	27
90		66.0	90.0	76.0	62.5		98.5	55.5	157	185	27
89		64.0	89.5	75.5	61.5		98.0	55.0	154	180	25
88		62.5		75.0	60.5		97.0	54.0	151	176	25
87		61.0	89.0	74.5	59.5		96.5	53.5	148	172	24
86		59.0	88.5	74.0	58.5		95.5	53.0	145	169	24
85		57.5		73.5	58.0		94.5	52.5	142	165	23
84		56.0	88.0	73.0	57.0		94.0	52.0	140	162	23
83		54.0	87.5	72.0	56.0		93.0	51.0	137	159	23
82		52.5		71.5	55.0		92.0	50.5	135	156	23
81		51.0	87.0	71.0	54.0		91.0	50.0	133	153	22
80		49.0	86.5	70.0	53.0		90.5	49.5	130	150	22
79		47.5		69.5	52.0		89.5	49.0	128	147	21
78		46.0	86.0	69.0	51.0		88.5	48.5	126	144	21
77		44.0	85.5	68.0	50.0		88.0	48.0	124	141	20
76		42.5		67.5	49.0		87.0	47.0	122	139	
75	99.5	41.0	85.0	67.0	48.5		86.0	46.5	120	137	
74	99.0	39.0		66.0	47.5		85.0	46.0	118	135	
73	98.5	37.5	84.5	65.5	46.5		84.5	45.5	116	132	
72	98.0	36.0	84.0	65.0	45.5		83.5	45.0	114	130	
71	97.5	34.5		64.0	44.5	100	82.5	44.5	112	127	
70	97.0	32.5	83.5	63.5	43.5	99.5	81.5	44.0	110	125	
69	96.0	31.0	83.0	62.5	42.5	99.0	81.0	43.5	109	123	
68	95.5	29.5		62.0	41.5	98.0	80.0	43.0	107	121	
67	95.0	28.0	82.5	61.5	40.5	97.5	79.0	42.5	106	119	
66	94.5	26.5	82.0	60.5	39.5	97.0	78.0	42.0	104	117	
65	94.0	25.0		60.0	38.5	96.0	77.5		102	116	
64	93.5	23.5	81.5	59.5	37.5	95.5	76.5	41.5	101	114	
63	93.0	22.0	81.0	58.5	36.5	95.0	75.5	41.0	99	112	
62	92.0	20.5		58.0	35.5	94.5	74.5	40.5	98	110	
61	91.5	19.0	80.5	57.0	34.5	93.5	74.0	40.0	96	108	
60	91.0	17.5		56.5	33.5	93.0	73.0	39.5	95	107	
59	90.5	16.0	80.0	56.0	32.0	92.5	72.0	39.0	94	106	
58	90.0	14.5	79.5	55.0	31.0	92.0	71.0	38.5	92	104	



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

**Table 8-2. Hardness Conversion Chart for Unhardened Steel, Steel of Soft Temper, Grey and Malleable Cast Iron and Most Non-Ferrous Metal 100-3000 Load - Continued**

For Unhardened Steel, Steel of Soft Temper, Grey and Malleable Cast Iron and Most Non-Ferrous Metal Scale											
B	F	G	15-T	30-T	45-T	E	K	A	Brinell		Shore
Rockwell Hardness Tester			Rockwell Superficial			Rockwell Hardness Tester			Standard Type		
Ball Penetrator											
1/16			1/16			1/8		Brale	10 millimeter		
Load (kilogram)											
57	89.5	13.0		54.5	30.0	91.0	70.5	38.0	91	103	
56	89.0	11.5	79.0	54.0	29.0	90.5	69.5		90	101	
55	88.0	10.0	78.5	53.0	28.0	90.0	68.5	37.5	89	100	
54	87.5	8.5		52.5	27.0	89.5	68.0	37.0	87		
53	87.0	7.0	78.0	51.5	26.0	89.0	67.0	36.5	86		
52	86.5	5.5	77.5	51.0	25.0	88.0	66.0	36.0	85		
51	86.0	4.0		50.5	24.0	87.5	65.0	35.5	84		
50	85.5	2.5	77.0	49.5	23.0	87.0	64.5	35.0	83		
Rockwell B Numbers Above 100'											
SCALE											
BRINELL		B	BRINELL		“B”	BRINELL		B			
Ball Diam-eter	Num-ber (No.)	Rock-well	Ball Diameter	No.	Rock-well	Ball Diam-eter	No.	Rock-well			
3.15	375	110	3.40	321	108	3.65	277	104			
3.20	363	110	3.45	311	107	3.70	269	104			
3.25	352	109	3.50	302	107	3.75	262	103			
3.30	341	109	3.55	293	106	3.80	255	102			
3.35	331	108	3.60	285	105	3.85	248	101			

**Table 8-3. Hardness Conversion Chart for Unhardened Steel, Steel of Soft Temper, Grey and Malleable Cast Iron and Most Non-Ferrous Metal 100-500 Load**

For Unhardened Steel, Steel of Soft Temper, Grey and Malleable Cast Iron and Most Non-Ferrous Metal									
SCALE									
B	F	15-T	30-T	45-T	E	H	K	A	Brinell
Rockwell Hardness Tester		Rockwell Superficial			Rockwell Hardness Tester				
Ball Penetrator									10 millimeter
1/16		1/16			1/8			Brale	
Load (kilogram)									
100	60	15	30	45	100	60	150	60	500
50	85.5	77.0	49.5	23.0	87.0		64.5	35.0	83
49	85.0	76.5	49.0	22.0	86.5		63.5		82
48	84.5		48.5	20.5	85.5		62.5	34.5	81
47	84.0	76.0	47.5	19.5	85.0		61.5	34.0	80
46	83.0	75.5	47.0	18.5	84.5		61.0	33.5	
45	82.5		46.0	17.5	84.0		60.0	33.0	79
44	82.0	75.0	45.5	16.5	83.5		59.0	32.5	78
43	81.5	74.5	45.0	15.5	82.5		58.0	32.0	77
42	81.0		44.0	14.5	82.0		57.5	31.5	76



**Table 8-3. Hardness Conversion Chart for Unhardened Steel, Steel of Soft Temper, Grey and Malleable Cast Iron and Most Non-Ferrous Metal 100-500 Load - Continued**

For Unhardened Steel, Steel of Soft Temper, Grey and Malleable Cast Iron and Most Non-Ferrous Metal									
SCALE									
B	F	15-T	30-T	45-T	E	H	K	A	Brinell
Rockwell Hardness Tester		Rockwell Superficial			Rockwell Hardness Tester				
Ball Penetrator									10 millimeter
1/16		1/16			1/8			Brale	
Load (kilogram)									
100	60	15	30	45	100	60	150	60	500
41	80.5	74.0	43.5	13.5	81.5		56.5	31.0	75
40	79.5	73.5	43.0	12.5	81.0		55.5		
39	79.0		42.0	11.0	80.0		54.5	30.5	74
38	78.5	73.0	41.5	10.0	79.5		54.0	30.0	73
37	78.0	72.5	40.5	9.0	79.0		53.0	29.5	72
36	77.5		40.0	8.0	78.5	100	52.0	29.0	
35	77.0	72.0	39.5	7.0	78.0	99.5	51.5	28.5	71
34	76.5	71.5	38.5	6.0	77.0	99.0	50.5	28.0	70
33	75.5		38.0	5.0	76.5		49.5		69
32	75.0	71.0	37.5	4.0	76.0	98.5	48.5	27.5	
31	74.5		36.5	3.0	75.5	98.0	48.0	27.0	68
30	74.0	70.5	36.0	2.0	75.0		47.0	26.5	67
29	73.5	70.0	35.5	1.0	74.0	97.5	46.0	26.0	
28	73.0		34.5		73.5	97.0	45.0	25.5	66
27	72.5	69.5	34.0		73.0	96.5	44.5	25.0	
26	72.0	69.0	33.0		72.5		43.5	24.5	65
25	71.0		32.5		72.0	96.0	42.5		64
24	70.5	68.5	32.0		71.0	95.5	41.5	24.0	
23	70.0	68.0	31.0		70.5		41.0	23.5	63
22	69.5		30.5		70.0	95.0	40.0	23.0	
21	69.0	67.5	29.5		69.5	94.5	39.0	22.5	62
20	68.5		29.0		68.5		38.0	22.0	
19	68.0	67.0	28.5		68.0	94.0	37.5	21.5	61
18	67.0	66.5	27.5		67.5	93.5	36.5		
17	66.5		27.0		67.0	93.0	35.5	21.0	60
16	66.0	66.0	26.0		66.5		35.0	20.5	
15	65.5	65.5	25.5		65.5	92.5	34.0	20.0	59
14	65.0		25.0		65.0	92.0	33.0		
13	64.5	65.0	24.0		64.5		32.0		58
12	64.0	64.5	23.5		64.0	91.5	31.5		
11	63.5		23.0		63.5	91.0	30.5		
10	63.0	64.0	22.0		62.5	90.5	29.5		57
9	62.0		21.5		62.0		29.0		
8	61.5	63.5	20.5		61.5	90.0	28.0		
7	61.0	63.0	20.0		61.0	89.5	27.0		56
6	60.5		19.5		60.5		26.0		
5	60.0	62.5	18.5		60.0	89.0	25.5		55
4	59.5	62.0	18.0		59.0	88.5	24.5		




**TO 1-1A-9**  
**NAVAIR 01-1A-9**

**Table 8-3. Hardness Conversion Chart for Unhardened Steel, Steel of Soft Temper, Grey and Malleable Cast Iron and Most Non-Ferrous Metal 100-500 Load - Continued**

For Unhardened Steel, Steel of Soft Temper, Grey and Malleable Cast Iron and Most Non-Ferrous Metal									
SCALE									
B	F	15-T	30-T	45-T	E	H	K	A	Brinell
Rockwell Hardness Tester	Rockwell Superficial				Rockwell Hardness Tester				
Ball Penetrator									10 millimeter
1/16	1/16				1/8			Brale	
Load (kilogram)									
100	60	15	30	45	100	60	150	60	500
3	59.0		17.0		58.5	88.0	23.5		54
2	58.0	61.5	16.5		58.0		23.0		
1	57.5	61.0	16.0		57.5	87.5	22.0		
0	57.0		15.0		57.0	87.0	21.0		53
The 15-T, 30-T, 45-T, 15-N, 30-N and 45-N scales values are in scales having lighter loads and more sensitive depth reading system, used where for one or another reason the indentation must be exceptionally shallow.									
The Rockwell B numbers above 100, as shown, are somewhat above the practical range of usefulness, as the Rockwell B versus Brinell hardness curve is very steep in this section, making the Brinell differences per unit change in Rockwell B reading quite large and subject to appreciable inaccuracy.									



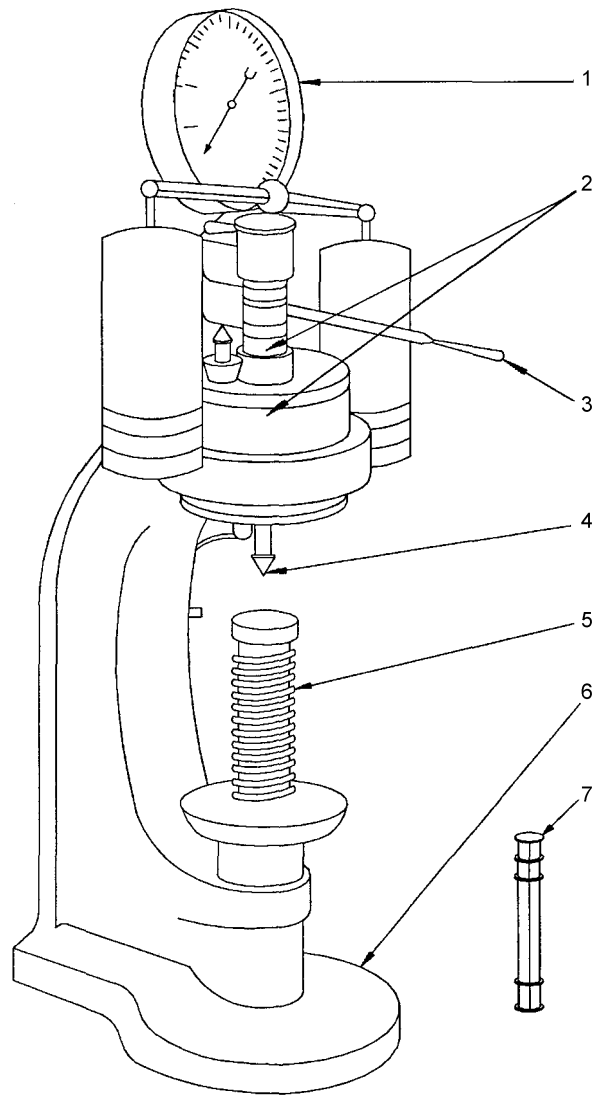


LEGEND:

1. GAGE INDICATING APPLIED PRESSURE
2. HYDRAULIC ACTUATING UNIT
3. LEVER FOR APPLYING PRESSURE
4. HARDENED STEEL BALL
5. ELEVATING SCREW
6. BASE
7. CALIBRATED MICROSCOPE

TO-1-1A-9-015

**Figure 8-1. Brinell Hardness Tester**




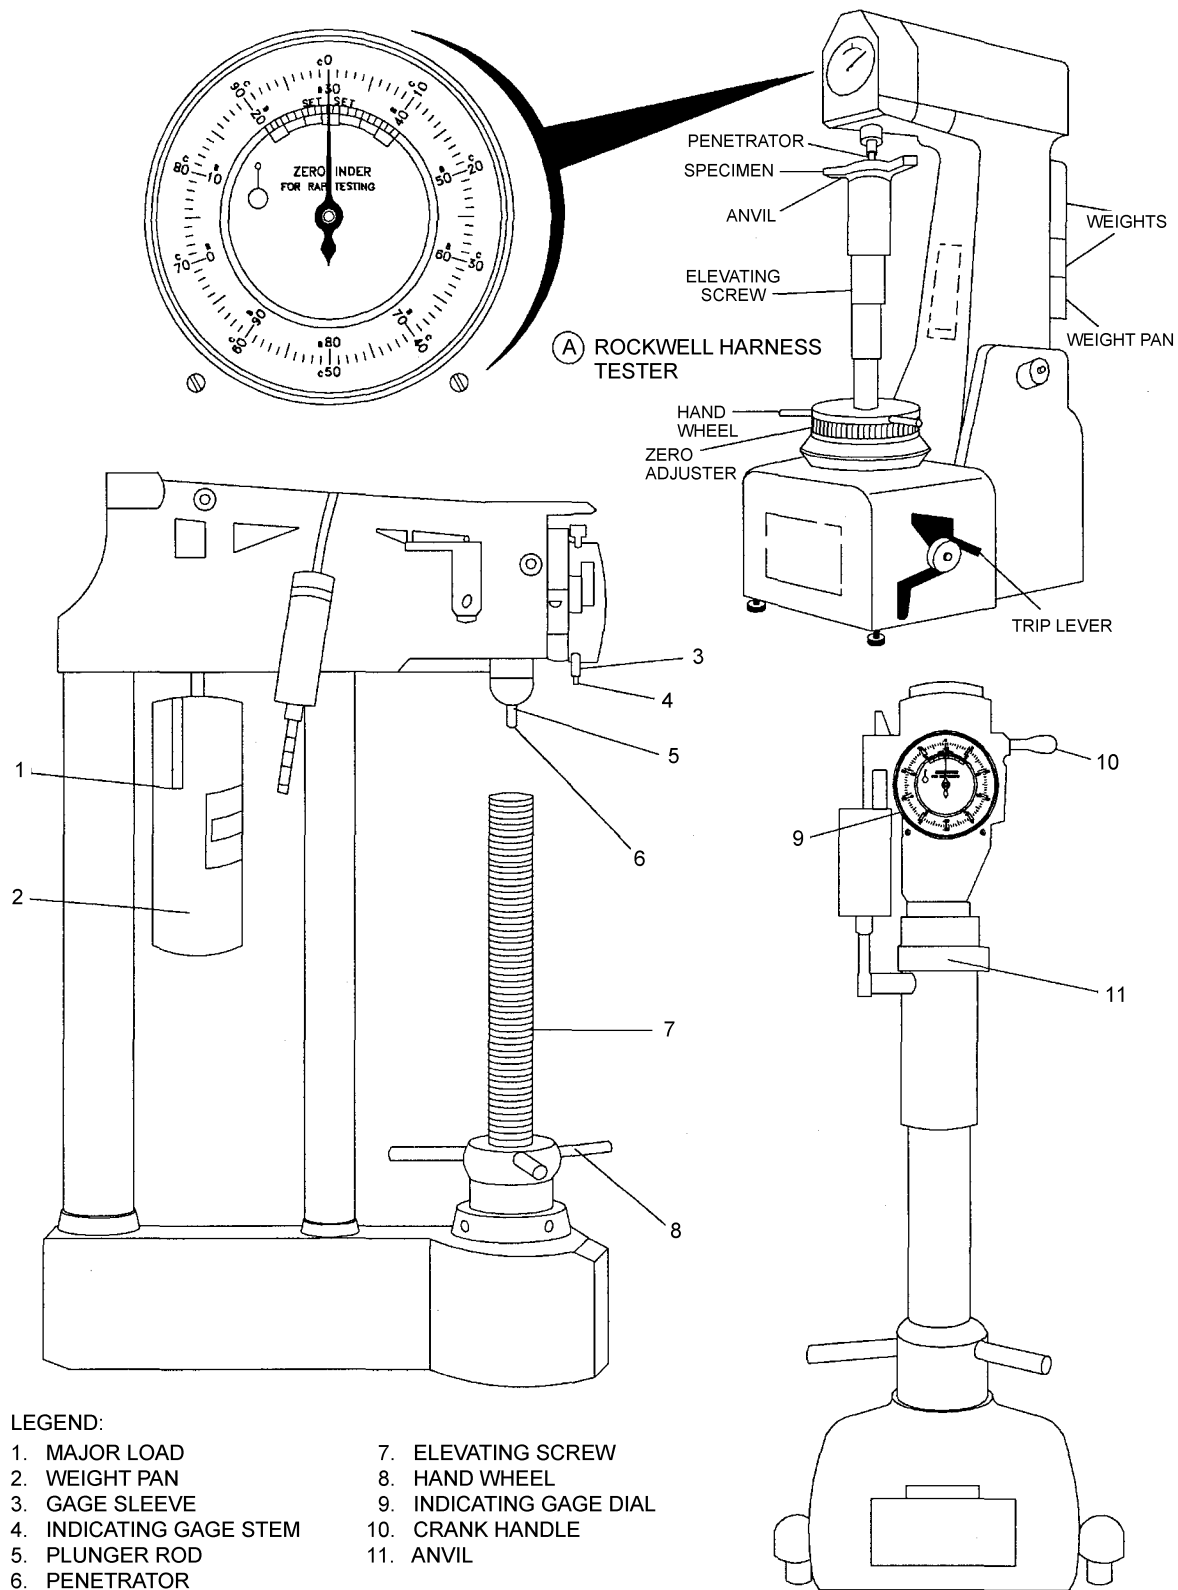

TO-1-1A-9-016

Figure 8-2. Rockwell Hardness Tester



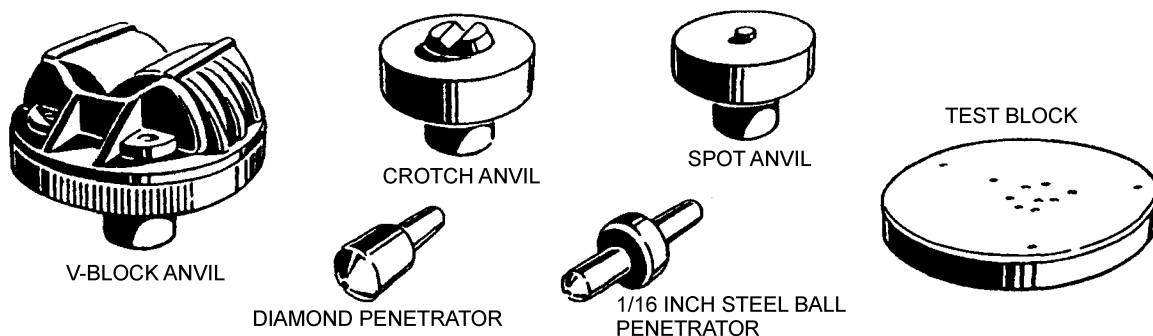

TO-1-1A-9-017

**Figure 8-3. Attachments for Rockwell Tester**

#### 8.4 VICKERS PYRAMID HARDNESS TEST.

The Vickers pyramid hardness test (Figure 8-4) covers a normal range of loading from 2.5 to 127.5 kilograms. However, for special applications such as the hardness testing of thin, soft materials, loads as low as 50 to 100 grams may be used. This test is made by pressing a square base diamond indenter into a flat surface of the metal being tested by the application of known pressure. The indentation left by the indenter is a square, the diagonal of which remains the hardness of the metal. The diagonal of the square impression is measured by a microscope which reads directly to 0.001 millimeters on a large micrometer drum. With the standard pyramidal diamond indenter (Figure 8-5) having an angle of 136° between opposite face of the pyramid, the pyramidal hardness number is determined by dividing the applied load in kilograms by the pyramidal area of the impression in square millimeters by the formula, or from correlation tables accompanying the tester.

$$\text{Hardness} = \frac{1.854 \text{ applied load in kilograms}}{\text{square of the diagonal of impression}}$$

Rapid readings may be taken by means of three knife edges in the field of the eye-piece. The first knife edge is fixed; the second knife is movable through a micrometric screw connected to a counter. The third knife edge, moved by means of a special screw, may be used if rapid reading of values to specified limits is desired. This method of testing is highly flexible and permits testing for very high hardness values. In the Amsler-Vickers variation of this hardness tester the surface of the material to be tested, at which the indenter contacts may be thrown on a ground-glass screen directly in front of the operator, allowing the length of the diagonals to be read directly.

8.4.1 Vickers Tester. The Vickers tester consists of the following major parts:

- Table for supporting the metal to be tested.
- A lever with a 20 to 1 ratio through which a load is applied through a rod to an indenter at the end of a tube moving up and down in a vertical position.
- A frame containing a control in which a plunger moves up and down vertically under the influence of a cam which applies and releases the test load. The cam is mounted on a drum and when the starting handle is depressed, the whole is rotated by a weight attached to a flexible cable, the speed of rotation being controlled by a piston and dashpot of oil. The mechanism provides for a slow and diminishing rate of application for the last portion of the load.
- A foot pedal, which when depressed, returns the cam, drum and weight to their original positions, thus cocking the mechanism and preparing the instrument for another test.
- A tripper, which supports the beam during the return of the cam, weight and drum. The tripper also released the lever for load applications.
- A medium-power compound microscope for measuring the indentation across the diagonal of a square.



8.4.2 Making The Vickers Test. The test is applied as follows (See [Figure 8-4](#)):


- a. Prepare the sample by smooth grinding or polishing to remove all scratches and variations that may affect the readability of the indentation.
- b. Place the test piece (6) on the testing table (5) and turn the table elevating wheel (1) until the indenter (7) fails to contact the metal being tested.



Sudden contact of the indenter and the material under test should be avoided to prevent possible injury to the diamond point. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

- c. Depress the load trip level (8) applying the load. The duration of the load application is fixed by the manufacturers at 10 to 30 seconds, the time being determined by the rate at which oil is allowed to bleed out of the dashpot. The load is fully applied, the indenter is automatically released.
- d. Elevate the indenter by turning the wheel. Lower the testing table by reversing the table elevating wheel.
- e. Swing the microscope (10) into place until locked.
- f. View the impression of the indentation in the form of a square in the field shown by the eyepiece.
- g. Bring the left corner of the impression, by means of the centering screws (13) to a point where it touches the left hand fixed knife edge. Adjust the right hand movable knife edge by means of the micrometric screw connected to the counter until it touches the right hand corner of the impression. The counter (15) will then show an ocular reading which is transposed to the Vickers pyramid numeral by use of correlation tables accompanying the tester.
- h. Where specified hardness limits are desired the third knife edge is used. This is moved by means of special screws to correspond to the smaller dimension or maximum hardness, while the micrometer-controlled knife edge is adjusted to correspond to the minimum hardness or larger dimension. When the settings of the second and third knife edges are made, it is only necessary when taking readings to set the fixed knife edge to the left hand corner of the impression in the usual way. If the right hand corner of the impression appears between the second and third knife edges, the material has the proper hardness for the range desired.



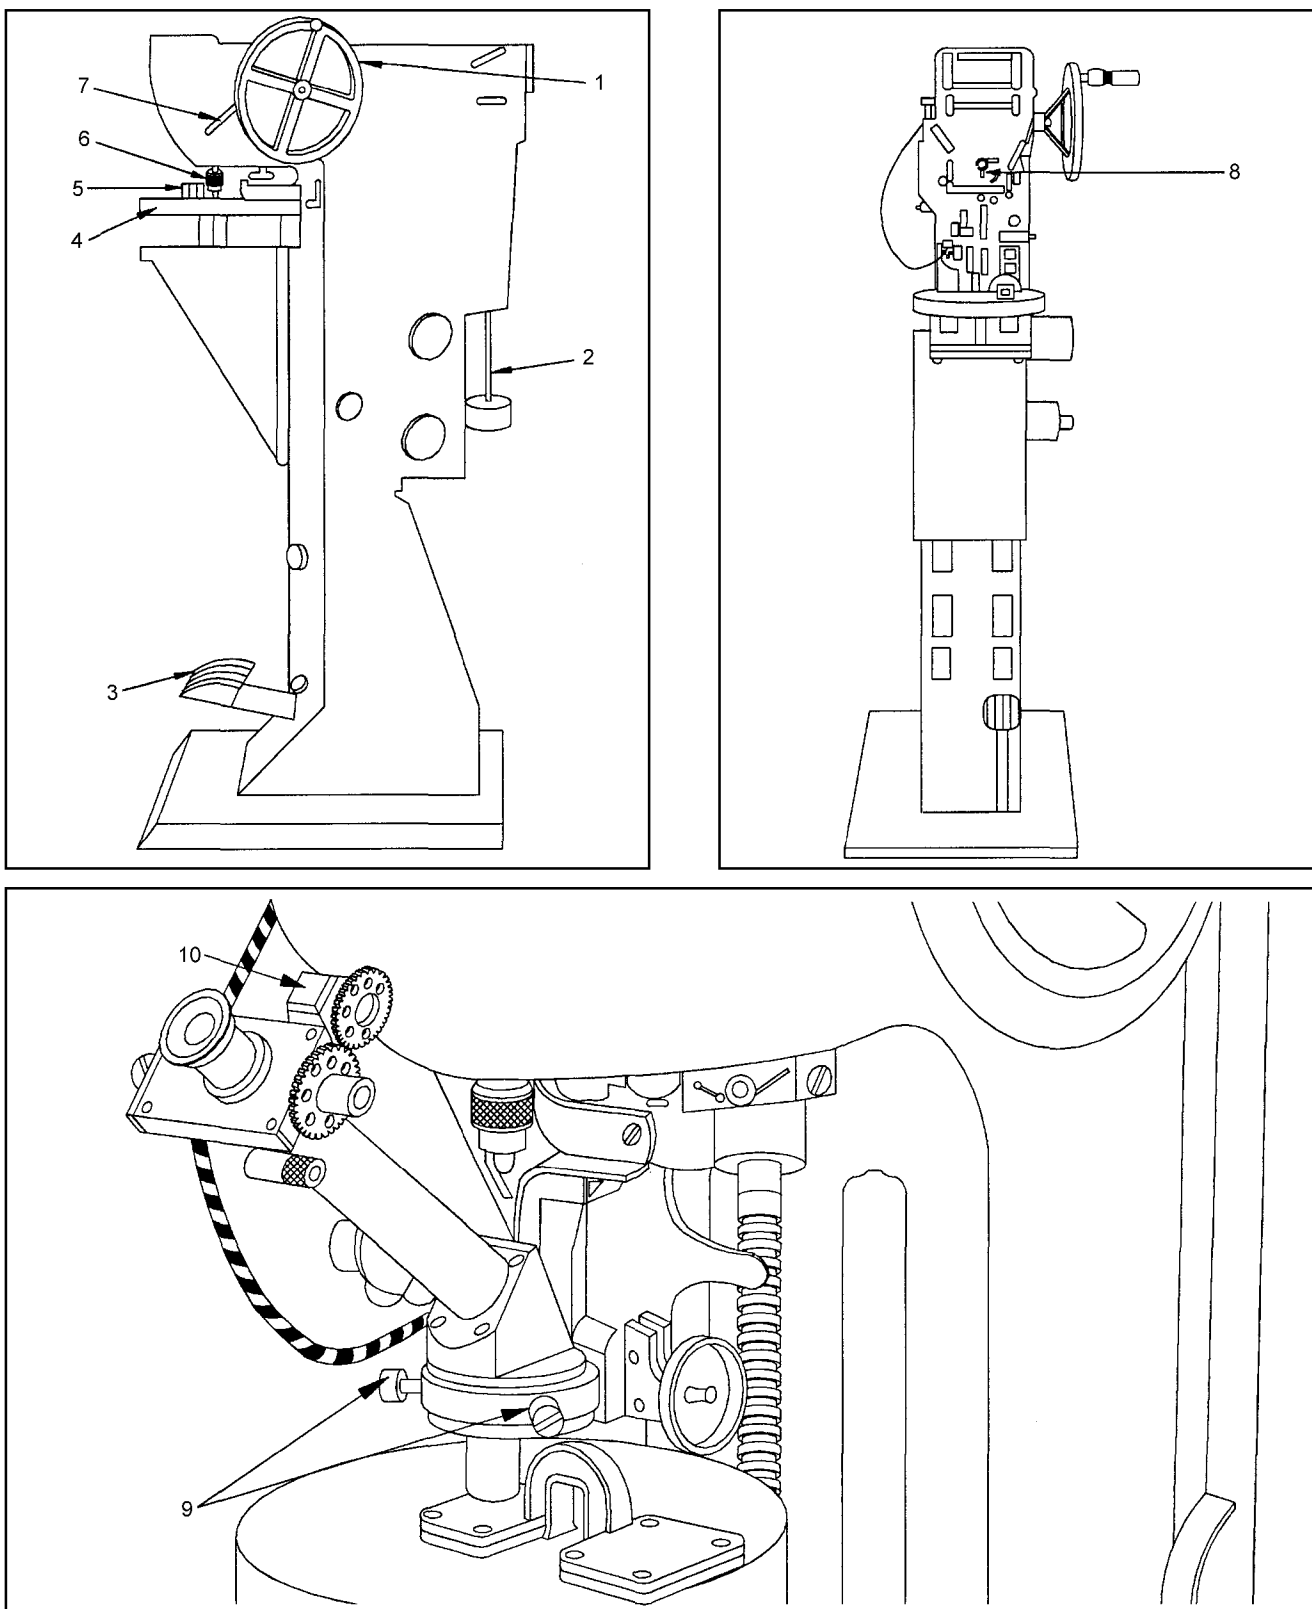

TO-1-1A-9-018


Figure 8-4. Vickers Pyramid Hardness Tester



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

Legend for Figure 8-4:

- 1 Table Elevating Wheel
- 2 Flexible Cable
- 3 Foot Pedal
- 4 Testing Table
- 5 Test Piece
- 6 Indentor
- 7 Load Trip Level
- 8 Microscope
- 9 Centering Screws
- 10 Counter

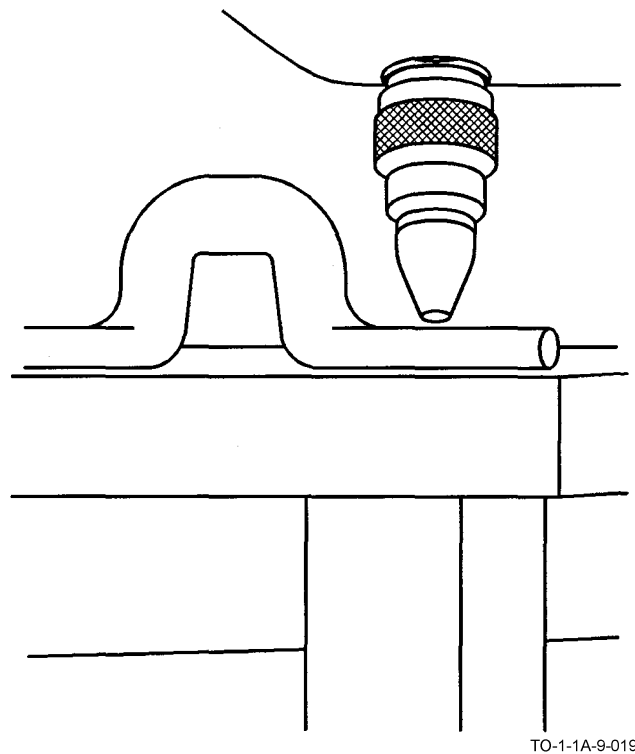

**Figure 8-5. Standard Pyramid Diamond Indentor**

## 8.5 SHORE SCLEROSCOPE HARDNESS TEST.


The Shore Scleroscope is not a precision instrument as the others discussed in preceding paragraphs. It is used to give approximate values for comparative hardness readings. Testing hardness with the scleroscope consists of dropping a diamond tipped hammer upon the test specimen from a definite height and measuring the rebound produced. In one type of tester, the height of the rebound must be measured directly on the scale of the machine, while on another the amount is indicated on a dial.

8.5.1 The Scleroscope Tester. The tester (Figure 8-6) consists of the following major parts:

- a. A base, provided with leveling screws, and a clamping arrangement to hold the sample to be tested.
- b. A vertical glass tube, mounted to the base and containing the cylindrical diamond point hammer.
- c. A suction heat and bulb for lifting and releasing the hammer.



- d. A scale, visible through the glass tube, for determining the height of the rebound.
- e. A magnifier hammer with a larger contact area is supplied for use with extremely soft metals.

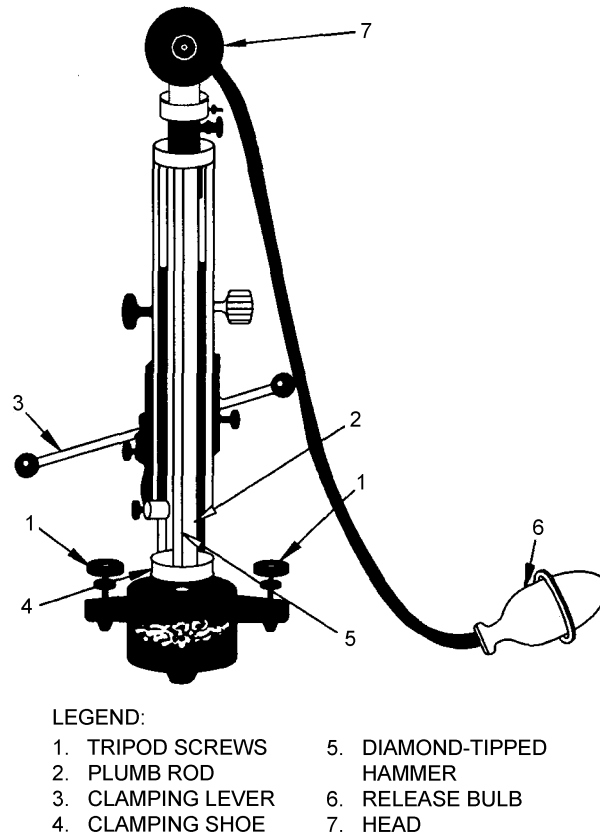

TO-1-1A-9-020

**Figure 8-6. Shore Scleroscope**

## 8.6 TESTING WITH THE SCLEROSCOPE.

The test is made as follows:

- a. Level the instrument by means of the adjusting screws (1). (See [Figure 8-6](#)). The level position is determined by means of the plumb rod (2).
- b. Prepare the test specimen as described for the Brinell and Rockwell tests in preceding paragraphs and clamp it on the base. This is done by raising the lever (3) inserting the sample and exerting the pressure on the clamping shoe (4).
- c. Raise the hammer (5) by squeezing and releasing the bulb (6).
- d. Release the hammer by again squeezing the bulb and observing its rebound.
- e. Several tests should be made at different points of a specimen, and an average reading taken to reduce visual error.

**8.6.1 Tensile Testing.** The terms tension test and compression test are usually taken to refer to tests in which a prepared specimen is subjected to a gradually increasing load applied axially until failure occurs. For the purpose of tensile testing implied by this technical order this type of setting would apply to determining the mechanical properties desired in a material. For this test, the following test specimens are listed. (See [Figure 8-7](#).) This does not exclude the use of other test specimens for special materials or forms of material. The tensile strength shall be determined by dividing the maximum load on the specimen during a tension test by the original cross-sectional area of the specimen.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

- a. Diameter of the reduced section may be smaller at center than at ends. Difference shall not exceed 1 percent of diameter at ends.
- b. When an extensometer is required to determine elastic properties, dimensions C and L may be modified. In all cases the percentage of elongation shall be based on dimension G.
- c. The Type R1 test specimen is circular in cross section and is used for bars, rods, forgings, plates, shapes, heavy-walled tubing, and castings. Types R<sub>2</sub>, R<sub>3</sub>, R<sub>4</sub>, and R<sub>5</sub> are circular in cross-section and are used for material of dimensions insufficient for Type R1.
  - (1) The ends of the reduced section shall not differ in width by more than 0.004 inch.
  - (2) The ends of the specimen shall be symmetrical with the center line of the reduced section within 0.10 inch.
  - (3) When material is over 2 inches thick, machine to 3/4 inch or use Type R1 test specimen. For more detailed information, refer to Federal Test Method Standard Number 151.

## 8.7 DECARBURIZATION MEASUREMENT.

Decarburization is the loss of carbon at the surface of ferrous materials which have been heated for fabricating, welding, etc., or when heated to modify mechanical properties. Effective decarburization is any measurable loss of carbon content which results in mechanical properties below the minimum acceptable specifications for hardened materials. The most common methods used to measure decarburization are microscopic, hardness and chemical. The microscopic method is sufficiently accurate for most annealed and hot rolled material for small amounts of decarburization in high carbon (over 0.60 percent), high hardness steels. The hardness method is insensitive in this case, and recourse must be taken to chemical analysis. In this technical order, only the hardness method is covered. When precise measurements are required, publications giving detailed measurements must be consulted.

**Table 8-4. Rockwell Scales, Loads and Prefix Letters**

Scale Prefix Letters	Indenter/Penetrator	Major Load Kilograms	Dial Numbers
A	Diamond	60	Black
B*	1/16 in Steel Ball	100	Red
C*	Diamond	150	Black
D	Diamond	100	Black
E	1/8 inch Ball	100	Red
F	1/16 inch Ball	60	Red
G	1/16 inch Ball	150	Red
H	1/8 inch Ball	60	Red
K	1/8 inch Ball	150	Red
L	1/4 inch Ball	60	Red
M	1/4 inch Ball	100	Red
P	1/4 inch Ball	150	Red
R	1/2 inch Ball	60	Red
S	1/2 inch Ball	100	Red
V	1/2 inch Ball	150	Red

\* Most commonly Used Scales.

## 8.8 HARDNESS METHOD.


**8.8.1 Taper or Step Grind.** The specimen containing the surface on which decarburization is to be measured is prepared so that it can be manipulated on a Rockwell superficial or Vickers hardness tester. If the specimen is not in the hardened condition, it is recommended that it be hardened by quenching from heating equipment under conditions which avoid further change in carbon distribution. For the taper grind procedure, a shallow taper is ground through the case, and hardness measurements are made along the surface. The angle is chosen so that readings spaced equal distances apart will represent the hardness at the desired increments below the surface of the case. The step grind procedure is essentially the same as the taper




grind, except that hardness readings are made on steps which are known distances below the surface. These steps should be ground at pre-determined depths below the surfaces, and of sufficient areas to allow several hardness readings on each flat.

**8.8.2 File Method.** The file method is often suitable for detecting decarburization of hardened materials during shop processing, but not for accurate measurement. Base metals expected to harden above RC60 and found to be file soft are probably decarburized. Decarburization of base metal that will not harden to RC60 can not be detected by this method unless specially prepared files are used. The extent and severity of any decarburization detected by this method should be verified by either of the other methods.



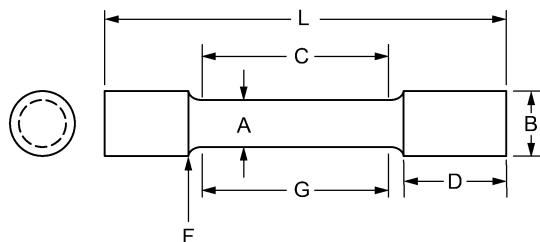

ALL DIMENSIONS IN INCHES

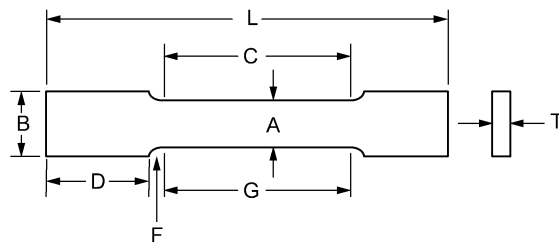

ALL DIMENSIONS IN INCHES

ALL DIMENSIONS IN INCHES

DIMENSIONS	$R_1^3$	$R_2^3$	$R_3^3$	$R_4^3$	$R_5^3$
A. DIAMETER AT CENTER <sup>1</sup>	0.505±0.010	0.357±0.007	0.252±0.005	0.160±0.003	0.113±0.002
B. DIAMETER OF ENDS	3/4	1/2	3/8	5/16	1/4
C. LENGTH OF 2-1/4 REDUCED SECTION MINIMUM <sup>2</sup>		1-3/4	1-1/4	3/4	5/8
D. GRIP LENGTH	1	5/8	5/8	1/2	3/8
F. FILLET RADIUS	3/8	0.25	0.18	0.15	0.09
G. GAGE LENGTH	2.0±0.005	1.4±0.005	1.0±0.005	0.64±0.005	0.45±0.005
L. TOTAL LENGTH	5-1/2	3-1/2	3	2	1-5/8
AREA OF CROSS SECTION INCH <sup>2</sup> APPROXIMATELY	1/5	1/10	1/20	1/50	1/100

ALL DIMENSIONS IN INCHES

DIMENSIONS	FL	F2
A. WIDTH AT CENTER	1-1/2±1/8-1/4	0.500±0.010
B. WIDTH AT GRIPS APPROXIMATELY	2	3/4
C. LENGTH OF REDUCED SECTION	1.2 9 MINIMUM	2-1/4 MINIMUM
D. GRIP LENGTH	3 APPROXIMATELY	2-3/8 MINIMUM
F. FILLET RADIUS, MINIMUM	1	1/2
G. GAGE LENGTH	8±0.01	2±0.005
L. TOTAL LENGTH, MINIMUM	15	8
T. THICKNESS	3/16 TO 2 <sup>3</sup>	5/8 MAXIMUM

Figure 8-7. Test Specimens



**Table 8-5. Approximate Hardness - Tensile Strength Relationship of Carbon and Low Alloy Steels**

Rockwell		Vickers Diamond  Pyramid 50 Kilogram Load	Brinell <sup>3</sup> 300 Kilogram Load - 10 Millimeter Ball		Tensile Strength  1000 Pounds per Square Inch (PSI)
C 150 Kilo- gram Load	B 100 Kilogram Load 1/16 Ball		Tungsten Carbide Ball	Steel Ball	
67		918	820	717	
66		884	796	701	
65		852	774	686	
64		822	753	671	
63		793	732	656	
62		765	711	642	
61		740	693	628	
60		717	675	613	
59		694	657	600	
58		672	639	584	
57		650	621	574	
56	121.3	630	604	561	
55	120.8	611	588	548	
54	120.2	592	571	536	
53	119.6	573	554	524	283
52	119.1	556	538	512	273
51	118.5	539	523	500	264
50	117.9	523	508	488	256
49	117.4	508	494	476	246
48	116.8	493	479	464	237
47	116.2	479	465	453	231
46	115.6	465	452	442	221
45	115.0	452	440	430	215
44	114.4	440	427	419	208
43	113.8	428	415	408	201
42	113.3	417	405	398	194
41	112.7	406	394	387	188
40	112.1	396	385	377	181
39	111.5	386	375	367	176
38	110.9	376	365	357	170
37	110.4	367	356	347	165
36	109.7	357	346	337	160
35	109.1	348	337	327	155
34	108.5	339	329	318	150
33	107.8	330	319	309	147
32	107.1	321	310	301	142
31	106.4	312	302	294	139
30	105.7	304	293	286	136
29	105.0	296	286	279	132
28	104.3	288	278	272	129
27	130.7	281	271	265	126
26	102.9	274	264	259	123
25	102.2	267	258	253	120
24	101.5	261	252	247	118



Table 8-5. Approximate Hardness - Tensile Strength Relationship of Carbon and Low Alloy Steels - Continued

Rockwell		Vickers Diamond  Pyramid 50 Kilogram Load	Brinell <sup>3</sup> 300 Kilogram Load - 10 Millimeter Ball		Tensile Strength  1000 Pounds per Square Inch (PSI)
C 150 Kilo- gram Load	B 100 Kilogram Load 1/16 Ball		Tungsten Carbide Ball	Steel Ball	
23	100.8	255	246	241	115
22	100.2	250	241	235	112
21	99.5	245	236	230	110
20	98.9	240	231	225	107
19	98.1	235	226	220	104
18	97.5	231	222	215	103
17	96.9	227	218	210	102
16	96.2	223	214	206	100
15	95.5	219	210	201	99
14	94.9	215	206	197	97
13	94.1	211	202	193	95
12	93.4	207	199	190	93
11	92.6	203	195	186	91
10	91.8	199	191	183	90
9	91.2	196	187	180	89
8	90.3	192	184	177	88
7	89.7	189	180	174	87
6	89	186	177	171	85
5	88.3	183	174	168	84
4	87.5	179	171	165	83
3	87	177	169	162	82
2	86	173	165	160	81
1	85.5	171	163	158	80
0	84.5	167	159	154	78
	83.2	162	153	150	76
	82	157	148	145	74
	80.5	153	144	140	72
	79	149	140	136	70
	77.5	143	134	131	68
	76	139	130	127	66
	74	135	126	122	64
	72	129	120	117	62
	70	125	116	113	60
	68	120	111	108	58
	66	116	107	104	56
	64	112	104	100	54
	61	108	100	96	52
	58	104	95	92	50
	55	99	91	87	48
	51	95	86	83	46
	47	91	83	79	44
	44	88	80	76	42
	39	84	76	72	40
	35	80	72	68	38



**Table 8-5. Approximate Hardness - Tensile Strength Relationship of Carbon and Low Alloy Steels - Continued**

Rockwell		Vickers Diamond  Pyramid 50 Kilogram Load	Brinell <sup>3</sup> 300 Kilogram Load - 10 Millimeter Ball		Tensile Strength  1000 Pounds per Square Inch (PSI)
C 150 Kilo- gram Load	B 100 Kilogram Load 1/16 Ball		Tungsten Carbide Ball	Steel Ball	
	30	76	67	64	36
	24	72	64	60	34
	20	69	61	57	32
	11	65	57	53	30
	0	62	54	50	28

## 8.9 NONDESTRUCTIVE INSPECTION METHODS.

**8.9.1 Radiographic Inspection.** Radiographic inspection will show internal and external structural details of all types of parts and materials. It is accomplished by passing penetrating radiation (usually X or gamma rays) through the part or assembly being inspected to expose a film. After developing, interpretation of the radiograph will indicate defects or damage. All radiographic inspections shall be accomplished in accordance with TO 33B-1-1, MIL-STD-453, and MIL-STD-410.

**8.9.2 Penetrant Inspection.** Penetrant inspection is a nondestructive inspection method that is used to detect discontinuities open to the surface of nonporous material. It is accomplished by treating the inspection area with a fluid (penetrant) that penetrates the surface discontinuity. Surplus penetrant remaining on the surface is removed and an absorbent material (developer) is applied to the surface. The developer acts as a blotter and draws some of the penetrant from the discontinuity to the surface. Discontinuities are visible due to color contrast between the penetrant drawn out and the background surface. Only fluorescent penetrants are approved for Air Force use. All penetrant inspection materials shall conform to MIL-I-25135. All penetrant inspections shall be accomplished in accordance with TO 33B-1-1 and MIL-STD-410.

**8.9.3 Ultrasonic Inspection.** Ultrasonic inspection uses a high frequency sound wave to detect discontinuities in materials. The pulser in the ultrasonic instrument sends an electrical impulse to a piezoelectric material in the search unit (transducer). The transducer changes the electrical impulse into mechanical vibrations (sound) and transmits them into the material being inspected. Any marked change in acoustic properties, such as a flaw or interface in the material, reflects the sound back to the transducer. Examination of the reflections on a cathode ray tube will reveal discontinuities in the material. All ultrasonic inspections shall be accomplished in accordance with TO 33B-1-1, MIL-I-8950, and MIL-STD-410.

**8.9.4 Magnetic Particle Inspection.** Magnetic particle inspection is used to detect discontinuities in ferromagnetic materials, principally iron and steel. Magnetic particle inspection is accomplished by inducing a magnetic field into the material being inspected. A discontinuity will interrupt this field, creating north and south poles which will attract magnetic particles applied to the material. Discontinuities are visible due to color contrast between the magnetic particles and the background surface. All magnetic particle inspections shall be accomplished in accordance with TO 33B-1-1 and MIL-STD-410.

**8.9.5 Eddy Current Inspection.** Eddy current inspection is used to detect discontinuities in materials that are conductors of electricity. An eddy current is the circulating electrical current induced in a conductor by an alternating magnetic field, which is produced by a small test coil in contact with or close to the material being inspected. Discontinuities in the material being tested cause variations in the induced eddy current. The test coil measures the variations which reveal discontinuities in the material. All eddy current inspections shall be in accordance with TO 33B-1-1 and MIL-STD-410.

## 8.10 CHEMICAL ANALYSIS.

Chemical analysis methods are those in which the elements present in metals are determined by the use of reagents in solution, by combustion methods, or by other none-mission methods. Sample metal from any piece shall be such that it represents as nearly as possible the metal of the entire piece. Drilling, milling and other machining operations for sample metal shall be performed without the use of water, oil, or other lubricants, and cutting speeds shall be such that no burning takes place to cause alternation of the chemical composition of the test metal. Method 112.1 of Federal Method Standard 151A is the controlling document for chemical analysis.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

**8.11 SPECTROCHEMICAL ANALYSIS.**

Spectrochemical analysis includes all methods in which measurements of electromagnetic radiations produced by a sample metal are employed to determine the chemical composition. Samples shall be so selected as to be representative of the entire quantity of metal under inspection. Cutting speeds in all machining operations shall be such that no burning takes place to cause alteration of the chemical composition of the test metal. Method 112.1 of Federal Test Method Standard 151A governs this type of analysis. The result of spectrochemical analysis shall be determined to the number of decimal places shown in the chemical requirements for the material.



## CHAPTER 9

### HEAT TREATMENT

#### 9.1 GENERAL.

Controlled atmosphere ovens are not required for heat treatment operations unless specified for a particular part.

9.1.1 Cold Oven. A cold oven is defined as any oven where the temperature is not over 500 degree Fahrenheit (°F) (260 degree Celsius (°C)). Loading and unloading a cold oven is possible without further lowering the temperature.

9.1.1.1 Parts that are prone to distortion during heat treatment shall be properly supported and temperature raised gradually by steps. Coat fixturing at part contact points and threaded details with PMC 2264 boron nitride coating prior to installing part and before heat treatment. Cooling of these parts shall also be done gradually. Cycles with A suffix are recommended for this purpose.

9.1.1.2 Parts that are not prone to distortion during heat treatment may be loaded into and withdrawn from a hot oven.

9.1.1.3 Temperature and time are the most critical factors in heat treatment. Time required at each specified temperature begins only after all sections of parts have reached that temperature. Furnace operator shall make allowance for size of part, number of parts, and furnace input capacities.

9.1.1.4 Optimum temperatures are given for each cycle, with tolerances included for practical use. However, it is best to hold to basic temperatures listed.

9.1.1.5 Some typical material applications are listed in [Table 9-1](#) for general guidance only. Cycle for which an alloy type is listed may not necessarily be specified for that material.

#### 9.2 SPECIAL HEAT TREATMENT INFORMATION.

9.2.1 Cadmium Plated Parts. All cadmium plate shall be stripped from parts (SPOP 21) and cadmium plated detail parts shall be removed from assemblies prior to subjecting the part or assemblies to any furnace temperature in excess of 500 °F (260 °C). At temperatures above 500 °F (260 °C), stress alloying of molten cadmium will occur with potentially harmful results on the base materials.

#### 9.3 TINT TEST FOR DETERMINING COATING REMOVAL FROM NICKEL BASE AND COBALT BASE ALLOYS.

Perform test as follows:

- a. Remove coating from parts using applicable stripping procedure.
- b. Heat parts and an uncoated, vapor blasted test panel of the same material as the parts at 1075±25 °F (579±14 °C) for 45 to 75 minutes in air.
- c. A uniform color match between the part and the test piece will indicate complete removal of the coating.



Table 9-1. Typical Heat Treatment Application

Cycle Number (No.)	Type*	SPOP No.	Possible Alloy Application
1, 1A	STR	455-1, 455-2	Low alloy steel, as Aeronautical Material Specification (AMS) 6322 and AMS 6415; martensitic stainless steel, as Type 410 (AMS 5504 and AMS 5613) and Greek Ascoloy (AMS 5508 and AMS 5616)
2	STR	456	Aluminum
3	STR	457	-
4, 4A	STR	458-1, 458-2	Inconel X
5, 5A	STR	459-1, 459-2	Nickel alloys: B-1900 (Printed Wiring Assembly (PWA) 663 and PWA 1455); Inconel 713 (PWA 655) Cobalt alloys: Stellite 31 (AMS 5382); WI-52 (PWA 653); MAR-M509 (PWA 647)
6, 6A	STR	460-1, 460-2	Greek Ascoloy (AMS 5508 and AMS 5616) (martensitic stainless steel)
7	STR	461	Waspaloy, Udimet 700
8	STR	455-3	-
9	STR	459-3	Inconel 600 (nickel alloy); Nimonic 75 (PWA 673) (nickel alloy); stainless steel, as Types 310, 316, 321, and 347
11	STR	464	Titanium
12, 12A	PRE	471, 465	Inconel 718 (nickel alloy), as AMS 5596, AMS 5662, and AMS 5663
13	STR	466	17-7PH (stainless steel - austenite conditioning); Type 430 (ferritic stainless steel), welded with Type 430 filler metal
14	STR	467	Type 430 (ferritic stainless steel), welded with AMS 5680 (Type 347 stainless steel)
15	PRE	468	A-286 (modified Tinidur) stainless steel, as AMS 5525, AMS 5731, AMS 5732, and AMS 5737
17	PRE	470	Incoloy 901 (nickel alloy), as AMS 5660 and AMS 5661
20	SOL	480	HASTELLOY X (nickel alloy)
21	SOL	481	Nickel alloy: HASTELLOY X (AMS 5536 and AMS 5754) Cobalt alloys: STELLITE 31 (AMS5382); Haynes 188 (AMS 5608, AMS 5772, and PWA 1042); L-605 (AMS 5537 and AMS 5759)
22	STR	482	Nickel alloys: Inconel 600 (AMS 5540 and AMS 5665); Inconel 625 (AMS 5599 and AMS 5666); HASTELLOY N; HASTELLOY X (AMS 5536, AMS 5754, and PWA 1038); HASTELLOY W Cobalt alloys: STELLITE 31 (AMS 5382); Haynes 188 (AMS 5608, AMS 5772, and PWA 1042); L-605 (AMS 5537 and AMS 5759); MAR-M509 (PWA 647)
101	SOL	761	Waspaloy (nickel alloy), as AMS 5544, AMS 5706, and AMS 5707
102	SOL	762	Waspaloy (nickel alloy), as AMS 5544, AMS 5706, and AMS 5707
103	STA	763	Waspaloy (nickel alloy), as AMS 5544, AMS 5706, AMS 5707, AMS 5708, and AMS 5709
104	PRE	764	Waspaloy (nickel alloy), as AMS 5596, AMS 5706, AMS 5707, AMS 5708, and AMS 5709
105	SOL	765	Inconel 718 (nickel alloy), as AMS 5596, AMS 5662, and AMS 5663
106	SOL	766	Inconel 718 (nickel alloy, as AMS 5596, AMS 5662, and AMS 5663
10	PRE	767	Nickel alloys: Inconel 718, as AMS 5596, AMS 5662, and AMS 5663; Inconel X-750, as AMS 5598, AMS 5670, and AMS 5671

\* PRE = Precipitation

SOL = Solution

STA = Stabilization

STR = Stress-Relief



## 9.4 TITANIUM ALLOY PARTS.

### NOTE

AMS 4901 and 4921 are the only commercially pure titanium material types used widely in the fabrication of PandW engine parts. Virtually all other titanium materials used are titanium alloys and are subject to these instructions.

9.4.1 **General.** All titanium alloy parts shall be cleaned by the following procedure prior to stress-relief. Otherwise, certain impurities that may be present on the parts during the heating cycle could cause stress alloying of the parts. The thin, hard, blue-gray oxide coating sometimes occurring on titanium alloy surfaces and unaffected by this cleaning procedure is harmless in this respect and may be disregarded.



METHYL ETHYL KETONE, ASTM D740

5

### NOTE

Since only light films of oil or grease will be removed by the cleaning solution, it is essential that as much surface contamination as possible be removed before immersing parts into the cleaning solution.

- a. Remove any visible concentrations of oil, grease, dirt, and any other contaminants by wiping with a clean, lint-free cloth dampened with methyl ethyl ketone ASTM D740 or acetone O-A-51.

### WARNING

Alkaline rust remover causes burns. Protect eyes and skin from contact. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

### NOTE

Parts shall be immersed only long enough to obtain optimum results.

- b. Soak in alkaline rust remover (SPS 2, SPS 5, SPS 7, SPS 12, SPS 25, SPS 27, or PS 240) at 180-200 °F (82-93 °C) for 1 to 4 minutes maximum.
- c. Pressure rinse over tank with cold water, then dip rinse in cold water, following with a cold water pressure rinse.
- d. Rinse in hot PMC 1737 deionized water at 150-200 °F (66-93 °C). Air dry; do not use compressed air.
- e. Immediately after completing step d., protect the parts from all contamination, such as dirt, dust, oil mist, fingerprints, etc. Cover parts with clear plastic sheet or store them in clear plastic bags until furnace or other operation is begun. Use clean white gloves for all handling.

9.4.1.1 Type 6Al-4V Titanium Alloy Parts (AMS 4911, 4928, 4930, 4935, 4954, 4956, 4967, and PWA 1213, 1215, 1262). Parts fabricated of these titanium alloys may be stress-relieved in air only to 1015±15 °F (546±8 °C). See Cycles 1 and 1A. At any higher temperatures, an inert atmosphere shall be used regardless of any contrary instructions stipulated in a particular repair.

## 9.5 SOLUTION, STABILIZATION, OR PRECIPITATION HEAT TREATMENT.

9.5.1 **General.** Solution heat treatment of material (particularly HASTELLOY X) is performed to improve ductility and weldability prior to resizing and repair. Long-time exposure to high temperature engine operating environment causes precipitation of carbides into the grain boundaries. Carbides, particularly chromium carbides, are thus precipitated into the grain boundaries of parts fabricated of HASTELLOY X material and subjected for long periods to temperatures of 1200-1700 °F (649-927 °C). The solution treatment dissolves these carbides and puts them back into metallic solution. The cooling cycle,



## TO 1-1A-9

### NAVAIR 01-1A-9

therefore, shall be rapid enough to maintain carbides or precipitation hardeners in solution. Replication and metallurgical examination may be necessary to verify whether fixturing and cooling rate are adequate to obtain desired microstructure and prevent cracking.

**9.5.2 Stabilization Heat Treatment.** Stabilization heat treatment is maintaining a part at a selected temperature long enough to rearrange the atoms into an improved structure.

**9.5.3 Precipitation Heat Treatment.** Precipitation heat treatment is a selected temperature and duration that produces beneficial hardening in certain alloys. It is sometimes referred to as Aging, or Age Hardening.

**9.5.4 Sequence of Solution, Stabilization, or Precipitation Heat Treatment.** When a sequence of solution, stabilization, or precipitation heat treatment is applied to a given part, various temperatures are used. The final condition obtained is a combined effect of this sequence.

**9.5.5 Air Cool and Air Cool or Faster.** The expressions AIR COOL and AIR COOL OR FASTER mean that parts shall be cooled quickly enough to prevent metal structure changes that can happen in certain alloys if cooling is too slow. It does not mean to quench in a liquid. Circulating fans may be used, but fixturing may be required if distortion is a problem.

**9.5.5.1 Air Cool.** AIR COOL is defined as rate of cooling of part obtained by removing that part from furnace at prescribed temperature and allowing it to cool in room temperature still air. Definition has been broadened to include the following situations.

- In vacuum furnace, by force cooling in protective atmosphere.
- In protective atmosphere furnace, by shutting off heat and maintaining atmospheric flow rates.
- In retort furnace, by removing retort from furnace and fan cooling.
- In pit furnace, by removing parts from furnace and cooling in room temperature still air.

**9.5.5.2 Air Cool or Faster.** AIR COOL OR FASTER is defined as cooling not less than 40 °F (22 °C) per minute to 1100 °F (593 °C) and not less than 15 °F (8 °C) from 1100-1000 °F (538 °C).

## **9.6 CYCLE NUMBER, TYPE OF HEAT TREATMENT, SPOP NUMBER, AND MAXIMUM TEMPERATURE.**

### **NOTE**

These cycles apply only to the repair of HASTELLOY X parts that require using one of the following solution heat treatments. The specific cycle required will be included in the repair procedure.

See [Table 9-2](#). Solution heat treatment Cycles 20 and 21 are used for various HASTELLOY X parts. Reference to these cycles will be made in the repair instructions, as necessary, by cycle or SPOP number.

### **9.6.1 Cycle 20 (SPOP 480).**



Do not use this cycle for solution heat treating PWA 1038 HASTELLOY X material. This material was solution treated at 1950 °F (1066 °C) at its manufacture. The beneficial properties derived from this lower temperature treatment could be lost permanently if subjected to a temperature higher than 1800 °F (982 °C). For other HASTELLOY alloys, solution heat treat shall be performed per this cycle unless otherwise directed by a specific repair procedure. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

Perform as follows:

- a. Heat part to 2050±25 °F (1121±14 °C) and hold for 7 to 10 minutes.



**NOTE**

Hydrogen, argon, or air are acceptable atmospheres; however, when solution treating is to be followed by weld repair that requires complete prior removal of oxides, hydrogen is preferred because of its characteristic and beneficial cleaning action over the entire part. Hydrogen cleaning removes oxides from all surfaces, including those difficult to clean mechanically, and to some extent, from the inside of cracks to be welded.

- b. Air cool or faster.

9.6.2 Cycle 21 (SPOP 481). Perform as follows:



Do not use this cycle for solution heat treating PWA 1038 HASTELLOY X material. This material was solution treated at 1950 °F (1066 °C) at its manufacture. The beneficial properties derived from this lower temperature treatment could be lost permanently if subjected to a temperature higher than 1800 °F (982 °C). For regular Hastelloy material, solution heat treat shall be performed in accordance with Cycle 20 (SPOP 480), unless otherwise directed by a specific repair procedure. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

- a. Heat part to 2150±25 °F (1177±14 °C) and hold for 7 to 10 minutes.

**NOTE**

Hydrogen, argon, or air are acceptable atmospheres. However, when solution treating is to be followed by weld repair that requires complete prior removal of oxides, hydrogen is preferred because of its characteristic and beneficial cleaning action over the entire part. Hydrogen cleaning removes oxides from all surfaces including those difficult to clean mechanically, and to some extent, from the inside of cracks to be welded.

- b. Air cool or faster.

9.6.2.1 The following solution, stabilization, or precipitation heat treatment cycles apply primarily to certain age-hardenable alloys such as WASPALOY and INCONEL materials, for stress-relief, and to dissolve precipitated carbides and intermetallics (hardeners).

9.6.3 Cycle 12 (SPOP 471).

**NOTE**

This is a short-term precipitation (aging) heat treatment for INCONEL 718 or other part material specified in engine publication.

Perform as follows:

- a. Place part in oven and heat to 1350±15 °F (732±8 °C).
- b. Hold at 1350 °F (732 °C) for 4 hours.
- c. Cool to 1200±15 °F (649±8 °C) at approximately 100 °F (56 °C) per hour. Hold at temperature for a total of 3 hours, including cool-down time from 1350 °F (732 °C).
- d. Air cool to room temperature.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

9.6.4 Cycle 12A (SPOP 465).

**NOTE**

This is a short-term precipitation (aging) heat treatment for INCONEL 718 or other part material specified in engine publication.

Perform as follows:

- a. Place part in cold oven.
- b. Heat to 600 °F (316 °C) and hold for 30 minutes.
- c. Increase to 800 °F (427 °C) and hold for 30 minutes.
- d. Increase to 1000 °F (538 °C) and hold for 30 minutes.
- e. Increase to 1200 °F (649 °C) and hold for 30 minutes.
- f. Increase to 1350±15 °F (732±8 °C) and hold for 4 hours.
- g. Cool to 1200±15 °F (649±8 °C) at approximately 100 °F (56 °C) per hour. Hold at temperature for a total of 3 hours, including cool-down time from 1350 °F (732 °C).
- h. Air cool to room temperature.

9.6.5 Cycle 15 (SPOP 468).

**NOTE**

Heating and cooling rates are optional. Air is an acceptable atmosphere.

Perform as follows:

- a. Heat part to 1325±25 °F (718±14 °C) and hold for 4 hours.
- b. Air cool.

9.6.6 Cycle 17 (SPOP 470).

**NOTE**

Hydrogen, argon, or a blend of hydrogen and argon, or vacuum, are acceptable atmospheres.

Perform as follows:

- a. Heat part to 1450±15 °F (788±8 °C) and hold for 4 hours.
- b. Cool to 500 °F (260 °C) at a rate equivalent to air cool.
- c. Heat part to 1325±15 °F (718±8 °C) and hold for 14 hours.
- d. Cool at a rate equivalent to air cool.



9.6.7 Cycle 101 (SPOP 761).



Heating or cooling rate between 1000 °F (538 °C) and 1850 °F (1010 °C) shall be at least 40 °F (22 °C) per minute to prevent cracking and to control aging characteristics. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

**NOTE**

This is a solution heat treatment using an argon atmosphere.

Perform as follows:

- a. Place part with thermocouples (TCs) in retort, and seal retort.
- b. Purge retort at approximately 150 cubic feet per hour argon until dew point reaches -40 °F (-40 °C) or lower at retort exhaust.
- c. Insert retort into furnace.

**NOTE**

Furnace may initially be set higher than 1850 °F (1010 °C).

- d. Heat to 1825±25 °F (996±14 °C) using lower thermocouple for controlling. Do not exceed 1850 °F (1010 °C) on higher thermocouple. Hold at temperature for 2 hours unless otherwise specified.
- e. Remove retort from furnace and cool with forced argon to 1000 °F (538 °C) in no longer than 18 minutes; then complete cooling with argon or air.

9.6.8 Cycle 102 (SPOP 762).



Heating or cooling rate between 1000 °F (538 °C) and 1850 °F (1010 °C) shall be at least 40 °F (22 °C) per minute to prevent cracking and to control aging characteristics. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

**NOTE**

- This is a solution heat treatment using vacuum. Heat cycle shall be completed in the 0.010 torr range or lower.
- Furnace system shall provide for argon forced cooling, in order to satisfy cooling rate requirement.

Perform as follows:

- a. Place part, with TC, in furnace.
- b. Evacuate to 0.009 torr or lower. Static leak rate shall not exceed 50 microns per hour.

**NOTE**

Furnace may initially be set higher than 1850 °F (1010 °C).

- c. Heat to 1825±25 °F (996±14 °C) using lower thermocouple for controlling. Do not exceed 1850 °F (1010 °C) on higher thermocouple. Hold at temperature for 2 hours unless otherwise specified.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

- d. Cool at required rate using forced argon.

**9.6.9** Cycle 103 (SPOP 763). Perform as follows:

**NOTE**

This is a stabilization heat treatment using air, argon, or vacuum.

- a. Place part in cold furnace.
- b. Heat to 1550±15 °F (843±8.3 °C) for 4 hours.
- c. Air cool.

**9.6.10** Cycle 104 (SPOP 764). Perform as follows:

**NOTE**

This is a precipitation heat treatment using air, argon, or vacuum.

- a. Place part in cold furnace.
- b. Heat to 1400±15 °F (760±8.3 °C) for 16 hours.
- c. Air cool.

**9.6.11** Cycle 105 (SPOP 765).



Heating or cooling rate between 1000 °F (538 °C) and 1775 °F (968 °C) shall be at least 40 °F (22 °C) per minute to prevent cracking and to control aging characteristics.

**NOTE**

This is a solution heat treatment using an argon atmosphere.

Perform as follows:

- a. Place part with TC in retort, and seal retort.
- b. Purge retort at approximately 150 cubic feet per hour argon until dew point reaches -40 °F (-40 °C) or lower, at retort exhaust.
- c. Insert retort into furnace.

**NOTE**

Furnace may initially be set higher than 1775 °F (968 °C).

- d. Heat to 1750±25 °F (954±14 °C), using lower thermocouple for controlling. Do not exceed 1775 °F (968 °C) on higher thermocouple. Hold at temperature for 1 hour unless otherwise specified.
- e. Remove retort from furnace and cool with forced argon to 1000 °F (538 °C) in no longer than 16 minutes; then complete cooling with argon or air.



9.6.12 Cycle 106 (SPOP 766).



Heating or cooling rate between 1000 °F (538 °C) and 1775 °F (968 °C) shall be at least 40 °F (22 °C) per minute to prevent cracking and to control aging characteristics.

**NOTE**

- This is a solution heat treatment using vacuum. Heat cycle shall be completed in the 0.010 torr range or lower.
- Furnace system shall provide for argon forced cooling, in order to satisfy cooling rate requirement.

Perform as follows:

- a. Place part, with TC, in furnace.
- b. Evacuate to 0.009 torr or lower. Static leak rate shall not exceed 0.05 torr per hour.

**NOTE**

Furnace may initially be set higher than 1775 °F (968 °C)

- c. Heat to 1750±25 °F (954±14 °C), using lower thermocouple for controlling. Do not exceed 1775 °F (968 °C) on higher thermocouple. Hold at temperature for 1 hour unless otherwise specified.
- d. Cool at required rate using forced argon.

9.6.13 Cycle 107 (SPOP 767).

**NOTE**

This is a precipitation heat treatment using air or argon.

Perform as follows:

- a. Place part in cold furnace.
- b. Heat to 1325±15 °F (718±8.3 °C) for 8 hours.
- c. Furnace cool at a rate not to exceed 100 °F (56 °C) per hour to 1150±15 °F (621±8.3 °C); hold for 8 hours.
- d. Air cool.

**Table 9-2. Cross-Index for Solution, Stabilization, or Precipitation Heat Treatments**

Cycle Number	Type	SPOP Number	Peak Temperature, °F (°C)*	
12	Precipitation	471	1350	(732)
12A	Precipitation	465	1350	(732)
15	Precipitation	468	1325	(718)
17	Precipitation	470	1450	(788)
20	Solution	480	2050	(1121)
21	Solution	481	2150	(1177)
101	Solution	761	1825	(996)
102	Solution	762	1825	(996)
103	Stabilization	763	1550	(843)



Table 9-2. Cross-Index for Solution, Stabilization, or Precipitation Heat Treatments - Continued

Cycle Number	Type	SPOP Number	Peak Temperature, °F (°C)*
104	Precipitation	764	1400 (760)
105	Solution	765	1750 (954)
106	Solution	766	1750 (954)
107	Precipitation	767	1325 (718)

\* (disregarding tolerance)

## 9.7 STRESS-RELIEF AFTER WELDING.

### NOTE

Local stress-relief of engine parts following minor repairs is authorized only if procedure has been developed to be compatible with applicable parts, material, size, and operating environment, and is approved by the cognizant engineering authority.

### 9.7.1 General.



The required stress-relief (Cycle 1 or Cycle 1A) after welding or brazing Type 410 or Greek Ascoloy materials eliminates the brittleness in the joint areas. To avoid cracking, parts shall be handled carefully until stress-relief is accomplished. Failure to comply could result in damage to, or destruction of, equipment or loss of mission or effectiveness.

Parts that have been repaired by fusion welding shall ordinarily be stress-relieved.

### NOTE

On certain parts, experience has indicated that stress-relief is not required. This permissible omission will be included in appropriate manual repair section for such parts.

## 9.8 CYCLE NUMBER, SPOP NUMBER, AND MAXIMUM TEMPERATURE.

### NOTE

- Parts may require a cycle different from one of the following. This will result in cycle being included in specific repair procedure.
- Parts that are susceptible to distortion during heat treatment shall be adequately supported, and temperature raised and lowered stepwise. The Suffix A following a cycle number indicates a stepwise cycle.

See [Table 9-3](#). The following stress-relief cycles are used throughout manual for various parts. Reference to these cycles will be made, as necessary, by cycle or SPOP number.

9.8.1 Cycle 1 (SPOP 455-1). Heat part to 1015±15 °F (546±8 °C) and hold for 2 hours.

9.8.2 Cycle 1A (SPOP 455-2).

### NOTE

To minimize distortion, use Cycle 1A as an alternate. Other cycles are permissible provided stress-relief requirement of 1015±15 °F (546±8 °C) for 2 hours is met.

Perform as follows:

- Put part in cold oven.



- b. Heat to 600 °F (316 °C) and hold for 30 minutes.
- c. Increase to 800 °F (427 °C) and hold for 30 minutes.
- d. Increase to 1015±15 °F (546±8 °C) and hold for 2 hours.
- e. Cool to 500 °F (260 °C) not faster than 100 °F (56 °C) every 15 minutes.

9.8.3 Cycle 2 (SPOP 456). Heat part to 350±10 °F (177±6 °C) and hold for 1 hour.

9.8.4 Cycle 3 (SPOP 457). Perform as follows:

- a. Put part in cold oven.
- b. Heat to 600 °F (316 °C) and hold for 30 minutes.
- c. Increase to 900±15°F (482±8 °C) and hold for 4 hours.
- d. Cool to 500 °F (260 °C) not faster than 100 °F (56 °C) every 15 minutes.

9.8.5 Cycle 4 (SPOP 458-1). Heat part to 1300±25 °F (704±14 °C) and hold for 2 hours.

9.8.6 Cycle 4A (SPOP 458-2).

#### NOTE

To minimize distortion, temperature may be raised and cooled gradually in accordance with Cycle 4A. Other cycles are permissible provided stress-relief requirement of 1300±25 °F (704±14 °C) for 2 hours is met.

Perform as follows:

- a. Put part in cold oven.
- b. Heat to 600 °F (316 °C) and hold for 30 minutes.
- c. Increase to 800 °F (427 °C) and hold for 30 minutes.
- d. Increase to 1100 °F (593 °C) and hold for 30 minutes.
- e. Increase to 1300±25 °F (704±15 °C) and hold for 2 hours.
- f. Cool to 500 °F (260 °C) not faster than 100 °F (56 °C) every 15 minutes.

9.8.7 Cycle 5 (SPOP 459-1). Heat part to 1600±25 °F (871±14 °C) and hold for 2 hours.

9.8.8 Cycle 5A (SPOP 459-2).

#### NOTE

To minimize distortion, temperature may be raised and lowered gradually in accordance with Cycle 5A. Other cycles are permissible provided stress-relief requirement of 1600±25 °F (871±14 °C) for 2 hours is met.

Perform as follows:

- a. Put part in cold oven.
- b. Heat to 700 °F (371 °C) and hold for 30 minutes.
- c. Increase to 1000 °F (538 °C) and hold for 30 minutes.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

- d. Increase to 1300 °F (704 °C) and hold for 30 minutes.
- e. Increase to 1600±25 °F (871±14 °C) and hold for 2 hours.
- f. Cool to 500 °F (260 °C) not faster than 100 °F (56 °C) every 15 minutes.

9.8.9 Cycle 6 (SPOP 460-1). Heat part to 1050±15 °F (566±8 °C) for 2 hours.

9.8.10 Cycle 6A (SPOP 460-2).

**NOTE**

To minimize distortion, temperature may be raised and lowered gradually in accordance with Cycle 6A. Other cycles are permissible provided stress-relief requirement of 1050±15 °F (566±8 °C) for 2 hours is met.

Perform as follows:

- a. Put part in cold oven.
- b. Heat to 600 °F (316 °C) and hold for 30 minutes.
- c. Increase to 800 °F (427 °C) and hold for 30 minutes.
- d. Increase to 1050±15 °F (566±8 °C) and hold for 2 hours.
- e. Cool to 500 °F (260 °C) not faster than 100 °F (56 °C) every 15 minutes.

9.8.11 Cycle 7 (SPOP 461). Heat part to 1500±25 °F (815±14 °C) and hold for 4 hours.

9.8.12 CYCLE 8 (SPOP 455-3). Perform as follows:

- a. Put part in cold oven.
- b. Heat to 600 °F (316 °C) and hold for 30 minutes.
- c. Increase to 800 °F (427 °C) and hold for 30 minutes.
- d. Increase to 1010 °F (543±8 °C) and hold for 30 minutes.
- e. Cool to 500 °F (260 °C) not faster than 100 °F (56 °C) every 15 minutes.

9.8.13 Cycle 9 (SPOP 459-3). Heat part to 1600±25 °F (871±14 °C) and hold for 1 hour.



9.8.14 Cycle 11 (SPOP 464).



- For titanium parts, a vacuum of 0.5 microns mercury, maximum, or argon or helium with a dew point no higher than -60 °F (-51 °C) shall be used. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- Longer heat treatment at specified temperature, or shorter heat treatment at higher temperature may be required by engine publication for certain parts. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

**NOTE**

For materials other than titanium, air or argon may be used.

Perform as follows:

- a. Heat part to 1150±15 °F (621±8 °C) and hold for 1 hour.
- b. Air cool.

9.8.15 Cycle 13 (SPOP 466). Perform as follows:

- a. Heat part to 1400±25 °F (760±14 °C) in air and hold for 2 hours.
- b. Air cool, or faster.


9.8.16 Cycle 14 (SPOP 467). Perform as follows:

**NOTE**

A protective atmosphere is suggested.

- a. Heat part to 1500±25 °F (816±14 °C) and hold for 30 minutes.
- b. Furnace cool at a rate of 50 °F (28 °C) per hour to 1100° (593 °C), then air cool or faster.

9.8.17 Cycle 22 (SPOP 482).



Parts shall be thoroughly cleaned before entering oven. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

**NOTE**

Hydrogen, argon, vacuum, or air are acceptable atmospheres; however, when heat treatment is to be followed by weld repair, hydrogen is preferable because of its cleaning action on oxides and impurities difficult to clean mechanically, as within cracks or cavities.

Previously designated Cycle 10.

- a. Place part in cold oven; however, this step may be omitted for thin sheet metal parts.
- b. Heat part to 1800±25 °F (982±14 °C) and hold for 1 hour.
- c. Air cool.



Table 9-3. Cross-Index for Stress-Relief Heat Treatments

Cycle Number	SPOP Number	Peak Temperature, °F (°C)	
1	455-1	1015	(546)
1A	455-2	1015	(546)
2	456	350	(177)
3	457	900	(482)
4	458-1	1300	(704)
4A	458-2	1300	(704)
5	459-1	1600	(871)
5A	459-2	1600	(871)
6	460-1	1050	(566)
6A	460-2	1050	(566)
7	461	1500	(816)
8	455-3	1010	(543)
9	459-3	1600	(871)
11	464	1150	(621)
13	466	1400	(760)
14	467	1500	(816)
22	482	1800	(982)

\*(Disregarding tolerance)

## 9.9 LOCAL STRESS-RELIEF.

9.9.1 **General.** Local stress-relief is the application of a heat treatment cycle, using a portable heating system, to a part that has been weld repaired, usually without disassembly. Elaborate fixturing is avoided when stress-relieving minor areas of large components.

9.9.1.1 Approval for local stress-relief is governed in part by accessibility, temperature requirement, and configuration and material of part.

9.9.1.2 Local stress-relief is especially useful when applied to parts on a mounted or partly disassembled engine.

9.9.1.3 Besides avoiding disassembly, local stress-relief provides significant cost and time savings.



Gas burner shall not be used to stress-relieve titanium parts. Exhaust gases can produce harmful surface reaction. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

9.9.1.4 Typical local stress-relief methods include the following:

- Resistance
- Induction
- Quartz lamp
- Gas burner radiant heater.

9.9.1.5 Choice of method depends upon size and shape of joint, part configuration, and accessibility. Resistance blankets and quartz lamps can be used to 1350 °F (732 °C); induction heaters and radiant gas burners can be used to 1825 °F (996 °C).





TCs shall not be tack welded to titanium parts. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

9.9.1.6 Temperature profile shall be monitored with tack welded TC to provide accurate readout for manual or automatic control during heat treat cycle. Thermocouples shall be located every 2 inches of area that is to be stress-relieved. Following the cycle, TC are broken or ground off, and part blended to original contour.

9.9.1.7 Stress-relief duration and temperature shall be the same as for a corresponding furnace heat treat, unless otherwise specified in applicable engine technical orders.

#### 9.10 DESCRIPTION OF METHODS.


Local stress-relief methods are defined in the following paragraphs.

9.10.1 Resistance. Heaters consist of nichrome wire elements insulated with ceramic fiber and contained within a flexible wire jacket. These components are woven into a thermal blanket, which shall be held in close contact with surface to be stress-relieved. Supplementary flexible heaters may be added to ensure that adjacent parts do not conduct heat away in such a manner as to make heat distribution non-uniform.

9.10.2 Induction. Requirements include a high frequency generator, with a water-cooled copper induction coil of sufficient number of turns to be positioned over entire area to be heat treated, such as a welded patch. Coils shall be insulated from metal contact, which will produce electrical arcing. Typical applications include small weld repair of holes or bosses, or replacement of small detail parts.

9.10.3 Quartz Lamp. Radiant lamp provides intense infrared heat, which can be easily directed toward part being stress-relieved. Temperature can be controlled by pulsing lamp on and off. Typical applications include inlet guide vanes, exhaust struts, intermediate cases, door assemblies, accessory housing, and thrust reversers.

#### 9.10.4 Radiant Gas Burner.



Gas burner shall not be used to stress-relieve titanium parts. Exhaust gases can produce harmful surface reaction. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

Good heating patterns and temperature control are permitted by using as burners. Heat treat of several areas can be accomplished simultaneously. Radiant gas burners are fueled with a mixture of air and natural gas.







## APPENDIX A SUPPLEMENTAL DATA

A.1 THE FOLLOWING IS SUPPLEMENTAL DATA FOR THIS MANUAL.

**Table A-1. Chemical Symbols**

Element	Symbol	Atomic Number	Element	Symbol	Atomic Number (No.)
Aluminum	Al	13	Neodymium	Nd	60
Antimony	Sb	51	Neon	Ne	10
Argon	A	18	Nickel	Ni	28
Arsenic	As	33	Nitrogen	N	7
Barium	Ba	56	Osmium	Os	76
Beryllium	Be	4	Oxygen	O	8
Bismuth	Bi	83	Palladium	Pd	46
Boron	B	5	Phosphorus	P	15
Bromine	Br	35	Platinum	Pt	78
Cadmium	Cd	48	Polonium	Po	84
Cesium	Cs	55	Potassium	K	19
Calcium	Ca	20	Praseodymium	Pr	59
Carbon	C	6	Protactinium	Pa	91
Cerium	Ce	58	Radium	Ra	8
Chlorine	Cl	17	Radon (radium emanation)	Rn	86
Chromium	Cr	24	Rhenium	Re	75
Cobalt	Co	27	Rhodium	Rh	45
Columbium (Niobium)	Cb (Nb)	-	Rubidium	Rb	37
Copper	Cu	29	Ruthenium	Ru	44
Dysprosium	Dy	66	Samarium	Sm	62
Erbium	Er	68	Scandium	Sc	21
Europium	Eu	63	Selenium	Se	34
Fluorine	F	9	Silicon	Si	14
Gadolinium	Gd	64	Silver	Ag	47
Gallium	Ga	31	Sodium	Na	11
Germanium	Ge	32	Strontium	Sr	38
Gold	Au	79	Sulphur	S	16
Hafnium	Hf	72	Tantalum	Ta	73
Helium	He	2	Tellurium	Te	52
Holmium	Ho	67	Terbium	Tb	65
Hydrogen	H	1	Thallium	Tl	81
Indium	In	49	Thorium	Th	90
Iodine	I	53	Thulium	Tm	69
Iridium	Ir	77	Tin	Sn	50
Iron	Fe	26	Titanium	Ti	22
Krypton	Kr	36	Tungsten	W	74
Lanthanum	La	57	Uranium	U	92
Lead	Pb	82	Vanadium	V	23
Lithium	Li	3	Xenon	Xe	54



Table A-1. Chemical Symbols - Continued

Element	Symbol	Atomic Number	Element	Symbol	Atomic Number (No.)
Lutecium	Lu	71	Ytterbium	Yb	70
Magnesium	Mg	12	Yttrium	Yo	39
Manganese	Mn	25	Zinc	Zn	30
Mercury	Hg	80	Zirconium	Zr	40
Molybdenum	Mo	42			

Table A-2. Decimal Equivalents

Inch	Milli-meter	Drill Size Number or Letter	Decimals of an Inch	Inch	Milli-meter	Drill Size Number or Letter	Decimals of an Inch
1/64	0.4	80	0.0135	5/64	1.7		0.066929
		79	0.0145			51	0.067
			0.015625		1.75		0.068897
			0.15748			50	0.07
	0.5	78	0.016		1.8		0.070866
		77	0.018		1.85		0.072834
			0.019685			49	0.073
		76	0.02		1.9		0.074803
	0.55	75	0.021			48	0.076
			0.021653		1.95		0.076771
	0.6	74	0.0225				0.078125
			0.023622			47	0.0785
		73	0.024		2.0		0.07874
		72	0.025		2.05		0.080708
	0.65		0.02559			46	0.081
		71	0.026			45	0.082
1/32	0.7		0.027559		2.1		0.082877
		70	0.028		2.15		0.084645
		69	0.02925			44	0.086
			0.029527		2.2		0.086614
	0.75	68	0.031		2.25		0.088582
			0.03125			43	0.089
			0.031496		2.3		0.090551
		67	0.032		2.35		0.092519
	0.8	66	0.033			42	0.0935
			0.033464				0.09375
		65	0.035		2.4		0.094488
			0.035433			41	0.096
	0.85	64	0.036		2.45		0.096456
		63	0.037			40	0.098
			0.037401		2.5		0.098425
		62	0.038			39	0.0995
0.9	0.9	61	0.039			38	0.1015
			0.03937		2.6		0.102362
		60	0.04			37	0.104
		59	0.041		2.7		0.106299



Table A-2. Decimal Equivalents - Continued

Inch	Milli- meter	Drill Size Number or Letter	Decimals of an Inch	Inch	Millime- ter	Drill Size Number or Letter	Decimals of an Inch
3/64	1.05		0.041338	7/64	2.75	36	0.1065
		58	0.042				0.108267
		57	0.043				0.109375
	1.1		0.043307			35	0.11
	1.15		0.045275		2.8		0.110236
		56	0.0465			34	0.111
			0.046875			33	0.113
	1.2		0.047244		2.9		0.114173
	1.25		0.049212			32	0.116
	1.3		0.051181		3.0		0.11811
1/16		55	0.052	1/8		31	0.12
	1.35		0.053149		3.1		0.122047
		54	0.055				0.125
	1.4		0.055118		3.2		0.125984
	1.45		0.057086		3.25		0.127952
	1.5		0.059055			30	0.1285
		53	0.0595		3.3		0.129921
	1.55		0.061023		3.4		0.133858
			0.0625			29	0.136
	1.6		0.062992		3.5		0.137795
5/32		52	0.635	9/64		28	0.1405
	1.65		0.06496				0.140625
	3.6		0.141732			A	0.234
		27	0.144				0.234375
	3.7		0.145669		6.0		0.23622
		26	0.147			B	0.238
	3.75		0.147637		6.1		0.240157
		25	0.1495			C	0.242
	3.8		0.149606		6.2		0.244094
		24	0.152			D	0.246
11/64	3.9		0.153543	1/4	6.25		0.246062
		23	0.154		6.3		0.248031
			0.15625			E	0.25
		22	0.157		6.4		0.251968
	4.0		0.15748		6.5		0.255905
		21	0.159			F	0.257
		20	0.161		6.6		0.259842
	4.1		0.161417			G	0.261
	4.2		0.165354		6.7		0.263779
		19	0.166				0.265625
11/64	4.25		0.167322	17/64	6.75		0.265747
	4.3		0.169291			H	0.266
		18	0.1695		6.8		0.267716
			0.171875		6.9		0.271653
		17	0.173			I	0.272
	4.4		0.173228		7.0		0.27559



Table A-2. Decimal Equivalents - Continued

Inch	Milli- meter	Drill Size Number or Letter	Decimals of an Inch	Inch	Millime- ter	Drill Size Number or Letter	Decimals of an Inch
3/16	4.5	16	0.177	9/32	7.1	J	0.277
			0.177165				0.279527
	4.6	15	0.18		7.2	K	0.281
			0.181102				0.28125
		14	0.182				0.283464
	4.7	13	0.185		7.25		0.285432
			0.185039				0.287401
	4.75		0.187007		7.3	L	0.29
	4.8		0.1875		7.4		0.291338
			0.188976			M	0.295
	4.9	12	0.189	19/64	7.5		0.295275
		11	0.191				0.296875
			0.192913		7.6		0.299212
	5.0	10	0.1935		7.7	N	0.302
		9	0.196				0.303149
	5.1		0.19685		7.75		0.305117
		8	0.199		7.8		0.307086
13/64	5.2		0.200787	5/16	7.9		0.311023
		7	0.201				0.3125
	5.3		0.203125		8.0		0.31496
		6	0.204		8.1	O	0.316
			0.204724				0.318897
	5.4	5	0.2055		8.2		0.322834
			0.206692		8.25	P	0.323
	5.5		0.208661				0.324802
	5.6	4	0.209	21/64	8.3		0.326771
			0.212598		8.4		0.328125
	5.7	3	0.213				0.330708
			0.216535		8.5	Q	0.332
	5.8		0.21875				0.334645
			0.220472		8.6		0.338582
	5.9	2	0.221		8.7	R	0.339
			0.224409				0.342519
7/32	5.75		0.226377	11/32			0.34375
	5.8	1	0.228		8.75		0.344487
			0.228346		8.8		0.346456
	5.9		0.232283			S	0.348
	8.9		0.350393				0.71875
			0.35433	23/32			0.728345
	9.0		0.358	47/64	18.5		0.734375
		T	0.358267		19.0		0.74803
	9.1		0.359375				0.75
	9.2		0.362204	3/4			0.765625
			0.364172	49/64			0.767715
	9.25		0.366141	25/32	19.5		0.78125
	9.3				20.0		0.7874
		U	0.368				



Table A-2. Decimal Equivalents - Continued

Inch	Milli- meter	Drill Size Number or Letter	Decimals of an Inch	Inch	Millime- ter	Drill Size Number or Letter	Decimals of an Inch
3/8	9.4	V	0.370078	51/64	20.5		0.796875
	9.5		0.374015	13/16			0.807085
			0.375				0.8125
			0.377				0.82677
	9.6		0.377952	53/64			0.828125
	9.7		0.381889	27/32			0.84375
	9.75		0.383857				0.846455
25/64	9.8	W	0.385826	55/64	21.5		0.859375
			0.386				0.86614
	9.9		0.389763	7/8			0.875
			0.390625				0.885825
	10.0		0.3937	57/64			0.890625
			0.397				0.90551
		X	0.404	29/32			0.90625
13/32		Y	0.40625	59/64	23.0		0.921875
		Z	0.413				0.925195
	10.5		0.413385	15/16			0.9375
	27/64		0.421875				0.94488
	11.0		0.43307	61/64			0.953125
	7/16		0.4375				0.964565
	11.5		0.452755	31/32			0.96875
29/64			0.453125		25.0		0.98425
15/32			0.46875	63/64			0.984375
	12.0		0.47244	1			1.0
31/64			0.484375				
	12.5		0.492125				
1/2			0.5				
	13.0		0.51181				
33/64			0.515625				
17/32			0.53125				
	13.5		0.531495				
35/64			0.546875				
	14.0		0.55118				
9/16			0.5625				
	14.5		0.570865				
37/64			0.578125				
	15.0		0.59055				
19/32			0.59375				
39/64			0.609375				
	15.5		0.610235				
5/8			0.625				
	16.0		0.62992				
41/64			0.640625				
	16.5		0.649605				
21/32			0.65625				
	17.0		0.66929				



**Table A-2. Decimal Equivalents - Continued**

Inch	Milli-meter	Drill Size Number or Letter	Decimals of an Inch	Inch	Milli-meter	Drill Size Number or Letter	Decimals of an Inch
43/64			0.671875				
11/16			0.6875				
	17.5		0.688975				
45/64			0.703125				
	18.0		0.70866				

**Table A-3. Engineering Conversion Factors**

LENGTH	
1 Inch	= 2.54 Centimeters = 0.0833 Foot = 0.0278 Yard
1 Foot	= 0.305 Meter = 0.333 Yard
1 Yard	= 0.914 Meter = 3 Feet
1 Rod	= 16 1/2 Feet = 5 1/2 Yards
1 Mile	= 1.609 Kilometers = 5280 Feet = 1760 Yards
1 Centimeter	= 0.3937 Inch = 0.0328 Foot
1 Meter	= 39.37 Inches = 3.281 Feet = 1.094 Yards
1 Kilometer	= 1000 Meters = 3280.83 Feet = 1093.61 Yards = 0.62137 Mile
AREA	
1 Square Inch	= 6.452 Square Centimeters
1 Square Foot	= 144 Square Inches = 929.032 Square Centimeters
1 Square Yard	= 1296 Square Inches = 9 Square Feet = 0.836 Square Meter
1 Square Rod	= 272 1/4 Square Feet = 30 1/4 Square Yards
1 Acre	= 43,560 Square Feet = 160 Square Rods
1 Square Mile	= 640 Acres
1 Square Centimeter	= 0.155 Square Inch
1 Square Meter	= 1550 Square Inches = 10.764 Square Feet = 1.196 Square Yards
1 Square Kilometer	= 0.3861 Square Miles = 247.104 Acres
VOLUME	
1 Cubic Inch	= 16.39 Cubic Centimeters = 0.00433 Gallons*
1 Cubic Foot	= 1728 Cubic Inches = 7.48 Gallons* = 28.317 Liters = 0.037 Cubic Yards
1 Cubic Yard	= 27 Cubic Feet = 0.7646 Cubic Meter = 202 Gallons*
1 Cubic Centimeter	= 0.001 Liter = 0.061 Cubic Inch
1 Cubic Meter	= 35.31 Cubic Feet = 1.308 Cubic Yards = 264.2 Gallons*
1 Quart*	= 0.25 Gallons* = 57.75 Cubic Inches = 0.946 Liter = 2 Pints*
1 Gallon*	= 0.832702 Imperial Gallon = 231 Cubic Inches = 0.1377 Cubic Feet = 3.785 Liters = 3785 Cubic Centimeters
1 Gallon, Imperial	= 1.20091 U.S. Gallons
1 Barrel (Standard)	= 31 1/2 Gallons
1 Barrel (Oil)	= 42 Gallons
*U.S. Measure	
WEIGHT	
1 Ounce	= 16 Drams = 437.5 Grains = 0.0625 Pound = 28.35 Grams = 0.9155 Ounce (Troy)
1 Pound	= 16 Ounces = 453.593 Grams = 0.453593 Kilogram
1 Ton (Short)	= 2000 Pounds = 907.185 Kilograms = 0.892857 Long Ton = 0.907185 Metric Ton



Table A-3. Engineering Conversion Factors - Continued

1 Ton (Metric)	= 2204.62 Pounds = 0.98421 Long Ton = 1.10231 Short Tons
1 Ton (Long)	= 2240 Pounds = 1016.05 Kilograms = 1.120 Short Tons = 1.01605 Metric Tons
1 Gram	= 15.43235 Grains = 0.001 Kilogram
1 Kilogram	= 2.20462 Pounds
COMPOUND UNITS	
1 Gram per Square Millimeter	= 1.422 Pounds per Square Inch
1 Kilogram per Square Millimeter	= 1.422.32 Pounds per Square Inch
1 Kilogram per Square Centimeter	= 14.2232 Pounds per Square Inch
1 Kilogram per Square Meter	= 0.2048 Pound per Square Foot
	= 1.8433 Pounds per Square Yard
COMPOUND UNITS	
1 Kilogram Meter	= 7.2330 Foot Pounds
1 Kilogram per Meter	= 0.6720 Pound per Foot
1 Pound per Square Inch	= 0.07031 Kilogram per Square Centimeter
1 Pound per Square Foot	= 0.0004882 Kilogram per Square Centimeter
1 Pound per Square Foot	= 0.006944 Pound per Square Inch
1 Pound per Cubic Inch	= 27679.7 Kilograms per Cubic Meter
1 Pound per Cubic Foot	= 16.0184 Kilograms per Cubic Meter
1 Kilogram per Cubic Meter	= 0.06243 Pound per Cubic Foot
1 Foot per Second	= 0.30480 Meter per Second
1 Meter per Second	= 3.28083 Feet per Second
1 Meter per Second	= 2.23693 Miles per Hour
MULTIPLES	
Circumference of Circle	= Diameter x 3.1416
Area of Circle	= Square of Diameter x 0.7854, or Square of Radius x 3.1416, or Square of Circumference x 0.07958
Area of Triangle	= Base x One-Half Altitude
Surface of Sphere	= Circumference x Diameter, or Square of Diameter x 3.1416
Volume of Sphere	= Surface x One-Sixth Diameter, or Cube of Diameter x 0.5236
Area of Hexagon	= Square of Diameter of Inscribed Circle x 0.866
Area of Octagon	= Square of Diameter of Inscribed Circle x 0.828
ENGINEERING UNITS	
1 Horsepower =	1 Kilowatt Hour =
33,000 Foot Pounds per Minute	1,000 Watt Hours
550 Foot Pounds per Second	1.34 Horsepower Hours
746 Watts	2,655,220 Foot Pounds
0.746 Kilowatts	3,412 Heat Units British Thermal Unit (BTU)
1 Horsepower Hour =	1 BTU =
0.746 Kilowatt Hours	1,055 Watt Seconds
1,980,000 Foot Pounds	778 Foot Pounds
2,545 Heat Units BTU	0.000293 Kilowatt Hour
	0.000393 Horsepower Hour
1 Kilowatt =	1 Watt =
1,000 Watts	1 Joule per Second



Table A-3. Engineering Conversion Factors - Continued

1.34 Horsepower	0.00134 Horsepower
737.3 Foot Pounds per Second	3.3412 Heat Units BTU per Hour
44.240 Foot Pounds per Minute	0.7373 Foot Pounds per Second
56.9 Heat Units BTU per minute	44.24 Foot Pounds per Minute

Table A-4. Table of Weights - Aluminum and Aluminum Alloy (Length)

Size	Pounds Per Linear Feet
Bars-Flat	
1/2 x 1	0.578
1/2 x 2	1.174
3/4 x 2	1.7604
3/4 x 3	2.6408
1 x 2	2.3472
1 x 3	3.5208
1-1/2 x 2	3.5208
13/4 x 3-1/2	7.1883
2 x 3	7.0416
2-3/4 x 4	12.9096
3 x 4	14.350
Bars-Hexagon	
3/8	0.147
7/16	0.20
1/2	0.262
9/16	0.331
5/8	0.409
3/4	0.639
1	1.047
1-1/4	1.620
1-1/2	2.340
Rods-Round	
3/16	0.032
1/4	0.058
5/16	0.090
3/8	0.129
7/16	0.176
1/2	0.230
9/16	0.291
5/8	0.360
11/16	0.435
3/4	0.518
13/16	0.608
7/8	0.705
15/16	0.809
1	0.921
1-1/4	1.439
13/8	1.741
1-1/2	2.072



**Table A-4. Table of Weights - Aluminum and Aluminum Alloy (Length) - Continued**

Size	Pounds Per Linear Feet
1 3/4	2.82
2	3.683
2-1/2	5.755
2-3/4	6.964
3	8.287
3-1/2	11.550
4	15.200
Tubing-Streamline	
1.500 x 0.250 x 0.020	0.082
1.500 x 0.375 x 0.020	0.085
1.625 x 0.375 x 0.025	0.115
1.875 x 0.375 x 0.035	0.16
2.00 x 0.875 x 0.049	0.27
2.01563 x 0.375 x 0.025	0.12
2.625 x 0.375 x 0.035	0.22
3.00 x 0.375 x 0.035	0.25
3.125 x 0.375 x 0.032	0.25
3.350 x 1.50 x 0.065	0.61
4.0625 x 1.71 x 0.065	0.73
Tubing-Round	
1/4 x 0.028	0.025
1/4 x 0.032	0.027
1/4 x 0.035	0.03
1/4 x 0.049	0.036
1/4 x 0.058	0.044
1/4 x 0.065	0.047
5/16 x 0.025	0.027
5/16 x 0.028	0.032
5/16 x 0.035	0.039
5/16 x 0.065	0.061
3/8 x 0.025	0.033
3/8 x 0.028	0.037
3/8 x 0.035	0.0435
3/8 x 0.042	0.053
3/8 x 0.049	0.063
7/16 x 0.035	0.054
7/16 x 0.049	0.075
1/2 x 0.032	0.056
1/2 x 0.035	0.063
1/2 x 0.042	0.073
1/2 x 0.049	0.086
1/2 x 0.065	0.11
9/16 x 0.032	0.067
5/8 x 0.035	0.08
5/8 x 0.042	0.093
5/8 x 0.049	0.11
5/8 x 0.058	0.13



Table A-4. Table of Weights - Aluminum and Aluminum Alloy (Length) - Continued

Size	Pounds Per Linear Feet
5/8 x 0.065	0.14
11/16 x 0.049	0.105
3/4 x 0.035	0.096
3/4 x 0.049	0.1245
3/4 x 0.058	0.15
3/4 x 0.065	0.17
3/4 x 0.083	0.21
13/16 x 0.032	0.095
13/16 x 0.049	0.13
7/8 x 0.028	0.09
7/8 x 0.035	0.11
7/8 x 0.049	0.16
15/16 x 0.032	0.11
15/16 x 0.049	0.17
15/16 x 0.083	0.27
1 x 0.032	0.12
1 x 0.035	0.13
1 x 0.042	0.16
1 x 0.049	0.18
1 x 0.058	0.210
1 x 0.065	0.23
1 x 0.083	0.29
1-1/16 x 0.032	0.13
1-1/16 x 0.083	0.31
1-1/8 x 0.035	0.15
1-1/8 x 0.049	0.20
1-1/8 x 0.058	0.24
1-1/8 x 0.065	0.27
1-3/16 x 0.083	0.35
1-1/4 x 0.035	0.16
1-1/4 x 0.049	0.2134
1-1/4 x 0.058	0.27
1-1/4 x 0.065	0.30
1-1/4 x 0.083	0.37
1-5/16 x 0.083	0.39
1-3/8 x 0.032	0.17
1-3/8 x 0.049	0.25
1-3/8 x 0.058	0.29
1-3/8 x 0.065	0.33
1-3/8 x 0.083	0.41
1-3/8 x 0.120	0.58
1-7/16 x 0.095	0.48
1-1/2 x 0.035	0.19
1-1/2 x 0.049	0.27
1-1/2 x 0.058	0.32
1-1/2 x 0.065	0.36
1-1/2 x 0.083	0.45



**Table A-4. Table of Weights - Aluminum and Aluminum Alloy (Length) - Continued**

Size	Pounds Per Linear Feet
1-5/8 x 0.065	0.39
1-5/8 x 0.125	0.72
1-11/14 x 0.095	0.58
1-3/4 x 0.035	0.23
1-3/4 x 0.049	0.32
1-3/4 x 0.065	0.3934
1-3/4 x 0.083	0.53
1-3/4 x 0.125	0.79
2 x 0.042	0.29
1-7/8 x 0.049	0.34
2 x 0.049	0.36
2 x 0.065	0.48
2 x 0.083	0.61
2 x 0.125	0.92
2-1/4 x 0.025	0.2052
2-1/2 x 0.065	0.61

**Table A-5. Table of Weights - Aluminum and Aluminum Alloy (Area)**

Thickness	Pounds Per Square Feet
Sheets	
0.0126	0.1797
0.016	0.2253
0.020	0.2817
0.0253	0.357
0.032	0.4501
0.0359	0.5055
0.0403	0.5676
0.0508	0.7158
0.0641	0.9026
0.0808	1.1382
0.0907	1.2781
0.128	1.8099
0.156	2.202
0.1875	2.6481
0.250	3.5215
0.375	5.2822
0.500	7.212

**Table A-6. Table of Weights - Brass**

Size	Pounds per Linear Feet
Bars-Flat	
1/8 x 1/2	0.238
1/8 x 3/4	0.358
1/8 x 1	0.475



Table A-6. Table of Weights - Brass - Continued

Size	Pounds per Linear Feet
1/8 x 1-3/4	0.815
1/8 x 2	0.935
6/32 x 1	0.625
3/16 x 3/4	0.535
3/16 x 1	0.715
3/16 x 1-1/4	0.895
3/16 x 1-1/2	1
3/16 x 1-3/4	1.175
3/16 x 2	1.385
3/16 x 2-1/2	1.785
3/16 x 3	2.055
1/4 x 1	0.9575
1/4 x 1-1/8	1.075
1/4 x 1-1/4	1.185
1/4 x 1-3/4	1.585
1/4 x 2	1.885
1/4 x 2-1/2	2.375
1/4 x 3	2.815
1/4 x 6	5.65
5/16 x 3/4	0.957
5/16 x 1	1.075
5/16 x 1-1/4	1.475
5/16 x 1-1/2	1.975
5/16 x 1-3/4	2.075
5/16 x 2	2.375
5/16 x 2-1/2	3.075
5/16 x 3	3.875
5/16 x 4	5.125
5/16 x 6	8.75
3/8 x 1	1.285
3/8 x 1-1/4	1.575
3/8 x 1-1/2	2.00
3/8 x 1-3/4	2.275
3/8 x 2	2.675
3/8 x 2-1/2	3.475
3/8 x 3	4.175
3/8 x 4	5.725
3/8 x 6	8.325
1/2 x 1	1.795
1/2 x 1-1/2	2.685
1/2 x 2	3.675
1/2 x 2-1/2	4.675
1/2 x 3	5.675
1/2 x 4	7.705
1/2 x 6	11.10
5/8 x 1	2.156
5/8 x 2	4.250



Table A-6. Table of Weights - Brass - Continued

Size	Pounds per Linear Feet
3/4 x 1	2.875
3/4 x 2	5.750
7/8 x 2-1/2	8.325
1 x 1-1/4	4.525
1 x 2	7.705
Bars-Hexagon	
3/16	0.1123
1/4	0.1997
5/16	0.3120
3/8	0.4493
7/16	0.6115
1/2	0.7987
9/16	1.001
5/8	1.248
11/16	1.510
3/4	1.797
12/16	2.109
7/8	2.446
15/16	2.808
1	3.195
1-1/8	4.043
1-3/16	4.505
1-1/4	4.992
1-5/16	5.503
1-3/8	6.040
1-1/2	7.188
1-9/16	7.800
1-5/8	8.436
1-11/16	9.097
1-3/4	9.784
1-13/16	10.50
1-7/8	11.23
1-15/16	11.99
2	12.78
2-1/2	19.97
3	26.41
Bars-Square	
3/16	0.1297
1/4	0.2306
9/16	0.3602
3/8	0.5188
7/16	0.7061
1/2	0.9222
5/8	1.441
3/4	2.075
1	3.689
1-1/4	5.764



Table A-6. Table of Weights - Brass - Continued

Size	Pounds per Linear Feet
1-1/2	8.300
2	14.76
Rods-Round	
1/16	0.01132
3/32	0.03625
1/8	0.04527
6/32	0.0915
3/16	0.1019
7/32	0.1475
1/4	0.1811
9/32	0.2375
9/14	0.2829
11/32	0.3480
3/8	0.4074
28/64	0.4185
12/32	0.4866
7/16	0.5546
1/2	0.7243
9/16	0.9167
5/8	1.132
11/14	1.369
3/4	1.630
13/16	1.913
7/8	2.218
18/14	2.546
1	2.897
1-1/8	3.667
1-3/14	4.086
1-1/4	4.527
1-5/16	4.991
1-3/8	5.478
1-7/16	5.987
1-1/2	6.519
1-9/16	7.073
1-5/8	7.651
1-11/16	8.250
1-3/4	8.873
1-13/14	9.518
1-7/8	10.19
1-15/16	10.88
2	11.59
2-1/4	14.67
2-1/2	18.11
2-3/4	21.91
2-7/8	23.95
3	26.08
3-1/2	36.75



Table A-6. Table of Weights - Brass - Continued

Size	Pounds per Linear Feet
4	46.93
5	74.25
6	108.25
Tubing-Round	
1/8 x 0.020	0.024
1/8 x 0.032	0.034
3/16 x 0.028	0.052
1/4 x 0.032	0.081
1/4 x 0.049	0.114
5/16 x 0.032	0.104
3/8 x 0.028	0.112
3/8 x 0.032	0.127
3/8 x 0.042	0.162
3/8 x 0.065	0.233
7/16 x 0.028	0.133
1/2 x 0.032	0.173
1/2 x 0.035	0.188
1/2 x 0.065	0.327
5/8 x 0.032	0.220
5/8 x 0.049	0.327
5/8 x 0.065	0.421
3/4 x 0.025	0.210
3/4 x 0.032	0.266
3/4 x 0.049	0.397
7/8 x 0.032	0.312
7/8 x 0.049	0.468
7/8 x 0.065	0.609
1 x 0.032	0.358
1 x 0.035	0.391
1 x 0.049	0.567
1 x 0.065	0.703
1-1/8 x 0.032	0.404
1-1/8 x 0.049	0.610
1-1/8 x 0.058	0.716
1-1/8 x 0.065	0.797
1-1/8 x 0.095	1.132
1-1/8 x 0.134	1.1537
1-1/4 x 0.020	0.285
1-1/4 x 0.032	0.451
1-1/4 x 0.049	0.681
1-1/4 x 0.058	0.800
1-1/4 x 0.065	0.891
1-1/4 x 0.072	0.981
1-3/8 x 0.035	0.543
1-3/8 x 0.049	0.752
1-3/8 x 0.065	0.935
1-1/2 x 0.032	0.544



Table A-6. Table of Weights - Brass - Continued

Size	Pounds per Linear Feet
1-1/2 x 0.049	0.823
1-1/2 x 0.065	1.08
1-5/8 x 0.032	0.59
1-5/8 x 0.049	0.893
1-5/8 x 0.065	1.173
1-3/4 x 0.032	0.636
1-3/4 x 0.049	0.964
1-3/4 x 0.065	1.267
1-7/8 x 0.049	1.035
2 x 0.032	0.729
2 x 0.035	0.796
2 x 0.065	1.455
2-1/4 x 0.049	1.248
2-1/4 x 0.065	1.643
2-3/8 x 0.035	0.9275
2-1/2 x 0.035	0.998
2-1/2 x 0.065	1.831
2-7/8 x 0.1875	5.875
3 x 0.032	1.200
Wire	
0.0010	0.000002884
0.0031	0.00002852
0.0035	0.00003596
0.004	0.00004535
0.0045	0.00005718
0.005	0.00007210
0.0056	0.00009092
0.0063	0.0001146
0.0071	0.0001446
0.008	0.0001823
0.0089	0.0002299
0.010	0.0002898
0.0113	0.0003655
0.0126	0.0004609
0.0142	0.0005812
0.0159	0.0007328
0.0179	0.0009241
0.0201	0.001165
0.0226	0.001469
0.0254	0.001853
0.0285	0.002336
0.032	0.002946
0.0359	0.003715
0.0403	0.004684
0.0453	0.005907
0.0508	0.007449
0.0571	0.009393



**Table A-6. Table of Weights - Brass - Continued**

Size	Pounds per Linear Feet
0.0641	0.01184
0.072	0.01493
0.0800	0.01883
0.0907	0.02375
0.1019	0.02994
0.1144	0.03776
0.1285	0.04761
0.1443	0.06004
0.162	0.07571
0.1819	0.09547
0.2043	0.1204
0.2294	0.1518
0.2576	0.1914
0.2893	0.2414
0.3249	0.3044
0.3648	0.3838
0.4096	0.4839
0.460	0.6102

**Table A-7. Table of Weights - Brass (Area)**

Thickness	Pounds per Square Feet
Sheet	
0.0031	0.1393
0.0035	0.1564
0.004	0.1756
0.0045	0.1972
0.005	0.2214
0.0056	0.2486
0.0063	0.2792
0.0071	0.3135
0.008	0.3521
0.0089	0.3953
0.010	0.4439
0.0113	0.4985
0.0126	0.5598
0.0142	0.6286
0.0159	0.7059
0.0179	0.7927
0.0201	0.8901
0.0226	0.9995
0.0253	1.122
0.0285	1.260
0.032	1.415
0.0359	1.589
0.0403	1.785
0.0453	2.004



**Table A-7. Table of Weights - Brass (Area) - Continued**

Thickness	Pounds per Square Feet
0.0508	5.060
0.0571	5.061
0.0641	5.062
0.072	5.063
0.0808	5.064
0.0907	5.065
0.1019	5.066
0.1144	5.067
0.1285	5.690
0.1443	6.389
0.162	7.175
0.1819	8.057
0.2043	9.047
0.2294	10.16
0.2576	11.41
0.2893	12.81
0.3249	14.39
0.3648	16.15
0.4096	18.14
0.460	20.37

**Table A-8. Table of Weights - Brass Shim Stock**

Thickness	Number Of Ounces per Square Feet
0.002	1.40
0.004	2.75
0.006	4.50
0.008	6.00
0.010	6.75
0.012	9.00

**Table A-9. Table of Weights - Bronze (Length)**

Size	Pounds per Linear Feet
Bars-Hexagon	
5/16	0.3081
3/8	0.4437
7/16	0.6039
1/2	0.7888
9/16	0.9983
5/8	1.232
3/4	1.775
1	3.155
Rods-Round	
1/8	0.04471
3/16	0.1006



**Table A-9. Table of Weights - Bronze (Length) - Continued**

Size	Pounds per Linear Feet
1/4	0.1788
9/16	0.2794
3/8	0.4024
1/2	0.7154
9/16	0.9054
5/8	1.118
11/16	1.353
3/4	1.610
13/14	1.889
7/8	2.191
1	2.862
1-1/8	3.622
1-3/16	4.035
1-1/4	4.471
1-3/8	5.410
1-7/14	5.913
1-1/2	6.438
13/4	8.763
2	11.45
2-1/8	12.92
2-1/2	17.88
3	25.75
3-1/2	35.05
4	45.78

**Table A-10. Table of Weights - Bronze (Area)**

Thickness	Pounds per Square Feet
Sheet	
0.010	0.4406
0.012	0.5552
0.0159	0.7006
0.0201	0.8857
0.0253	1.115
0.032	1.410
0.0359	1.582
0.0403	1.776
0.050	2.238
0.0641	2.825
0.0808	3.567
0.0907	3.997
0.1285	5.662



Table A-11. Table of Weights - Copper

Size	Pounds per Linear Feet
Bars-Flat	
1/16 x 3/4	0.1809
1/8 x 1	0.4823
1/8x2	0.9646
1/4 x 1	0.9646
1/4 x 2	1.929
1/4x3	3.894
1/4x4	3.858
3/8x1	1.447
3/8x2	2.894
1/2 x 3/4	1.425
1/2 x 1	1.929
5/8 x 1-1/2	3.675
Rods-Round	
1/4	0.1894
9/16	0.2959
3/8	0.4261
7/16	0.580
1/2	0.7576
5/8	1.184
3/4	1.705
7/8	2.320
1	3.030
1-1/8	3.835
1-1/4	4.735
1-1/2	6.818
1-3/4	9.281
2	12.12
2-1/2	18.94
3	27.27
Tubing-Round	
1/8 x 0.020	0.026
1/8 x 0.025	0.030
1/8 x 0.028	0.033
1/8 x 0.032	0.036
1/8 x 0.049	0.045
3/16 x 0.022	0.044
3/16 x 0.028	0.055
3/16 x 0.032	0.061
3/16 x 0.035	0.065
3/16 x 0.042	0.075
3/16 x 0.049	0.083
7/22 x 0.065	0.132
1/4 x 0.028	0.076
1/4 x 0.032	0.085
1/4 x 0.035	0.092
1/4 x 0.042	0.106



Table A-11. Table of Weights - Copper - Continued

Size	Pounds per Linear Feet
1/4 x 0.049	0.120
1/4 x 0.065	0.146
9/22 x 0.042	0.122
3/16 x 0.025	0.088
5/16 x 0.028	0.097
5/16 x 0.032	0.110
5/16 x 0.035	0.119
5/16 x 0.042	0.139
5/16 x 0.049	0.158
5/16 x 0.058	0.180
5/16 x 0.065	0.196
3/8 x 0.025	0.106
3/8 x 0.028	0.118
3/8 x 0.032	0.134
3/8 x 0.035	0.145
3/8 x 0.042	0.170
3/8 x 0.049	0.194
3/8 x 0.065	0.245
3/8 x 0.083	0.295
3/8 x 0.095	0.325
7/16 x 0.032	0.158
7/16 x 0.035	0.171
7/16 x 0.042	0.202
7/16 x 0.049	0.232
7/16 x 0.065	0.295
1/2 x 0.028	0.161
1/2 x 0.032	0.182
1/2 x 0.035	0.198
1/2 x 0.042	0.234
1/2 x 0.049	0.269
1/2 x 0.058	0.312
1/2 x 0.065	0.344
1/2 x 0.120	0.554
1/2 x 0.134	0.596
9/16 x 0.032	0.207
9/16 x 0.035	0.225
9/16 x 0.042	0.266
9/16 x 0.049	0.306
9/16 x 0.120	0.645
9/16 x 0.134	0.704
5/8 x 0.032	0.231
5/8 x 0.035	0.251
5/8 x 0.042	0.298
5/8 x 0.049	0.343
5/8 x 0.065	0.443
5/8 x 0.083	0.547
5/8 x 0.120	0.737



Table A-11. Table of Weights - Copper - Continued

Size	Pounds per Linear Feet
11/14 x 0.120	0.812
3/4 x 0.025	0.220
3/4 x 0.028	0.246
3/4 x 0.032	0.280
3/4 x 0.035	0.304
3/4 x 0.042	0.362
3/4 x 0.049	0.418
3/4 x 0.058	0.488
3/4 x 0.065	0.542
3/4 x 0.083	0.673
3/4 x 0.120	0.920
3/4 x 0.134	1.00
13/16 x 0.042	0.396
13/16 x 0.049	0.452
7/8 x 0.028	0.289
7/8 x 0.032	0.328
7/8 x 0.035	0.358
7/8 x 0.049	0.492
7/8 x 0.058	0.576
7/8 x 0.095	0.901
7/8 x 0.109	1.02
7/8 x 0.120	1.10
1 x 0.025	0.297
1 x 0.028	0.331
1 x 0.032	0.377
1 x 0.035	0.411
1 x 0.042	0.489
1 x 0.049	0.567
1 x 0.065	0.739
1 x 0.120	1.29
1-1/16 x 0.032	0.403
1-1/16 x 0.035	0.438
1-1/8 x 0.032	0.425
1-1/8 x 0.042	0.553
1-1/8 x 0.049	0.641
1-1/8 x 0.065	0.838
1-1/8 x 0.148	1.759
1-3/16 x 0.032	0.453
1-1/4 x 0.032	0.474
1-1/4 x 0.035	0.517
1-1/4 x 0.049	0.716
1-1/4 x 0.065	0.937
1-1/4 x 0.072	1.03
1-1/4 x 0.148	1.98
1-5/16 x 0.032	0.498
1-5/16 x 0.042	0.648
1-5/16 x 0.049	0.758



Table A-11. Table of Weights - Copper - Continued

Size	Pounds per Linear Feet
1-3/8 x 0.028	0.459
1-3/8 x 0.032	0.523
1-3/8 x 0.035	0.570
1-3/8 x 0.042	0.681
1-3/8 x 0.049	0.790
1-3/8 x 0.065	1.036
1-3/8 x 0.148	2.209
1-7/16 x 0.035	0.597
1-1/2 x 0.032	0.571
1-1/2 x 0.042	0.745
1-1/2 x 0.049	0.865
1-1/2 x 0.058	1.017
1-1/2 x 0.065	1.135
1-1/2 x 0.148	2.434
1-5/8 x 0.032	0.620
1-5/8 x 0.042	0.809
1-5/8 x 0.049	0.939
1-5/8 x 0.058	1.106
1-5/8 x 0.065	1.238
1-5/8 x 0.148	2.659
1-3/4 x 0.032	0.669
1-3/4 x 0.042	0.873
1-3/4 x 0.049	1.014
1-3/4 x 0.065	1.332
1-3/4 x 0.148	2.884
1-7/8 x 0.032	0.717
1-7/8 x 0.042	0.937
1-7/8 x 0.049	1.088
1-7/8 x 0.065	1.431
1-7/8 x 0.148	3.109
2 x 0.032	0.766
2 x 0.035	0.837
2 x 0.042	1.00
2 x 0.049	1.163
2 x 0.065	1.530
2 x 0.083	1.936
2 x 0.095	2.202
2-1/4 x 0.049	1.31
2-1/4 x 0.065	1.73
2-1/2 x 0.065	1.93
2-3/4 x 0.095	3.07
3 x 0.120	4.20



**Table A-12. Table Of Weights - Copper (Area)**

Thickness	Pounds per Square Feet
Sheet	
0.002	0.125
0.003	0.1434
0.005	0.2312
0.006	0.2914
0.010	0.4625
0.0126	0.5827
0.0142	0.6567
0.0159	0.7353
0.0201	0.9296
0.0226	1.0452
0.0253	1.170
0.032	1.4799
0.0359	1.6602
0.0403	1.8637
0.0453	2.095
0.0508	2.3493
0.0571	2.6407
0.0641	2.9644
0.0808	3.7367
0.0907	4.1946
0.1285	5.9427

**Table A-13. Table of Weights - Copper Wire**

Size	Number of Feet per Pound
Wire	
0.020	826.9
0.0253	516.7
0.032	323.0
0.0359	256.6
0.0403	203.7
0.0508	128.2
0.0625	84.67
0.064	80.75
0.072	63.80
0.0808	50.66
0.0907	40.21
0.1019	31.85
0.1285	20.03
0.2576	4.984



**Table A-14. Table of Weights - Iron**

Size	Pounds per Linear Feet
Angle	
1-1/16 x 1 x 1	0.40
1/8 x 3/4 x 3/4	0.59
1/8 x 1 x 1	0.80
1/8 x 1-1/2 x 1-1/2	1.23
1/8 x 1-3/4 x 1-3/4	1.44
1/8 x 2 x 2	1.65
3/16 x 1 x 1	1.16
3/16 x 1-1/4 x 1-1/4	1.48
3/16 x 1-1/2 x 1-1/2	1.80
3/16 x 1-1/2 x 2	2.12
3/16 x 2 x 2-1/2	2.75
3/16 x 2-1/2 x 2-1/2	3.07
1/4 x 1-1/4 x 1-1/4	1.92
1/4 x 1-1/2 x 1-1/2	2.34
1/4 x 2 x 2	3.19
1/4 x 2-1/2 x 2-1/2	4.10
1/4 x 3 x 3	4.9
1/4 x 4 x 4	6.6
5/16 x 2-1/2 x 3	5.6
5/16 x 3 x 3	6.1
3/8 x 1-1/2 x 1-1/2	3.35
3/8 x 2-1/2 x 2-1/2	5.90
5/8 x 6 x 6	24.2

**Table A-15. Table of Weights - Iron (Area)**

Thickness	Pounds per Square Feet
Sheet-Black	
0.0156	0.625
0.0188	0.75
0.025	1.00
0.032	1.25
0.0375	1.50
0.0438	1.723
0.050	2.00
0.0625	2.55
0.0781	3.2
0.093	3.757
0.125	5.1
0.156	6.4
0.1875	7.56
0.250	10.2
0.375	15.178
0.500	20.4
Sheet-Galvanized	
0.0156	0.781



**Table A-15. Table of Weights - Iron (Area) - Continued**

Thickness	Pounds per Square Feet
0.0188	0.906
0.025	1.156
0.032	1.406
0.0375	1.656
0.0438	1.9064
0.050	2.156
0.0625	2.62
0.0938	3.9603
0.125	5.1563
Sheet-Terne Plate	
0.0156	0.6377
0.0186	0.7685
0.025	1.022
0.0313	1.2795
0.037	1.5329
0.050	2.044

**Table A-16. Table of Weights - Lead**

Thickness	Pounds per Square Feet
1/32	2.10
1/16	4.25
3/52	6.031
1/8	7.812
3/16	11.720

**Table A-17. Table of Weights - Magnesium and Magnesium Alloy**

Size	Pounds per Linear Feet
Bars-Flat	
1/2 x 1	0.372
1/2 x 2	0.756
3/4 x 2	1.135
3/4 x 3	1.700
1 x 2	1.513
1 x 3	2.270
1-1/2 x 2	2.290
1-3/4 x 3-1/2	4.630
2 x 3	4.535
2-3/4 x 4	8.320
3 x 4	9.240
Bars-Hexagon	
3/8	0.095
7/16	0.129
1/2	0.169
9/16	0.213



**Table A-17. Table of Weights - Magnesium and Magnesium Alloy - Continued**

Size	Pounds per Linear Feet
5/8	0.263
3/4	0.412
1	0.674
1-1/4	1.043
1-1/2	1.510
Rods-Round	
3/16	0.021
1/4	0.037
3/16	0.058
3/8	0.083
7/16	0.114
1/2	0.148
3/16	0.188
5/8	0.232
11/16	0.280
3/4	0.334
13/16	0.392
7/8	0.454
15/16	0.522
1	0.593
1-1/4	0.927
1-3/8	1.122
1-1/2	1.348
1-3/4	1.818
2	2.385
2-1/2	3.710
2 3/4	4.480
3	5.340
3-1/2	7.450
4	9.800

**Table A-18. Table of Weights - Magnesium and Magnesium Alloy (Area)**

Thickness	Pounds per Square Feet
Sheets	
0.0126	0.1158
0.020	0.1814
0.016	0.1451
0.0253	0.230
0.032	0.290
0.0359	0.3258
0.0403	0.366
0.0508	0.462
0.0641	0.582
0.0808	0.733
0.128	1.167
0.0907	1.823



**Table A-18. Table of Weights - Magnesium and Magnesium Alloy (Area) - Continued**

Thickness	Pounds per Square Feet
0.156	1.418
0.1875	1.708
0.250	2.270
0.375	3.405
0.500	4.650

**Table A-19. Table of Weights - Nickel Chromium Iron Alloy (Inconel)**

Size	Pounds per Linear Feet
Rods-Round	
1/4	0.182
3/16	0.285
3/8	0.409
1/2	0.728
3/4	1.638
1	2.912
1-1/4	4.55
1-1/2	6.553
2	11.651
2-1/2	18.203
Tubing	
1/4 x 0.028	0.071
1/4 x 0.035	0.088
1/4 x 0.049	0.113
1/4 x 0.065	0.139
5/16 x 0.028	0.091
5/16 x 0.035	0.113
5/16 x 0.049	0.150
5/16 x 0.065	0.188
3/8 x 0.028	0.113
3/8 x 0.035	0.139
3/8 x 0.049	0.188
3/8 x 0.058	0.217
3/8 x 0.065	0.236
1/2 x 0.035	0.191
1/2 x 0.049	0.257
1/2 x 0.058	0.299
1/2 x 0.065	0.329
5/8 x 0.049	0.329
5/8 x 0.065	0.424
3/4 x 0.035	0.292
3/4 x 0.049	0.400
3/4 x 0.058	0.468
3/4 x 0.065	0.519
7/8 x 0.035	0.343
7/8 x 0.049	0.472
7/8 x 0.058	0.552



**Table A-19. Table of Weights - Nickel Chromium Iron Alloy (Inconel) - Continued**

Size	Pounds per Linear Feet
7/8 x 0.065	0.613
1 x 0.035	0.393
1 x 0.049	0.543
1 x 0.058	0.636
1 x 0.065	0.708
1-1/4 x 0.049	0.686
1-1/4 x 0.065	0.897
1-3/8 x 0.049	0.757
1-3/8 x 0.065	0.988
1-1/2 x 0.035	0.597
1-1/2 x 0.049	0.828
1-1/2 x 0.065	1.09
1-3/4 x 0.049	0.969
1-3/4 x 0.065	1.28
2 x 0.049	1.11
2 x 0.065	1.46
2-1/4 x 0.049	1.26
2-1/4 x 0.065	1.65
2-1/2 x 0.049	1.40
2-1/2 x 0.065	1.84
3-1/4 x 0.120	4.38

**Table A-20. Table of Weights - Nickel Chromium Iron Alloy (Inconel) (Area)**

Thickness	Pounds per Square Feet
Sheets	
0.018	0.84
0.025	1.11
0.032	1.39
0.037	1.65
0.043	1.91
0.050	2.22
0.0625	2.76
0.093	4.14
0.125	5.56
0.156	6.94
0.1875	8.32
0.250	11.12

**Table A-21. Table of Weights - Nickel Copper Alloy**

Size	Pounds per Linear Feet
Rods-Round	
1/4	0.190
3/16	0.309
3/8	0.428



**Table A-21. Table of Weights - Nickel Copper Alloy - Continued**

Size	Pounds per Linear Feet
1/2	0.761
3/4	1.172
1	3.044
1-1/4	4.756
1-1/2	6.849
2	12.178
2-1/2	19.027

**Table A-22. Table of Weights - Nickel Copper Alloy (Area)**

Thickness	Pounds per Square Feet
Sheets	
0.018	0.86
0.025	1.15
0.032	1.44
0.037	1.72
0.125	5.75

**Table A-23. Table of Weights - Steel**

Size	Pounds per Linear Feet
Bars-Flat	
1/14 x 1/2	0.106
1/14 x 3/4	0.1594
1/14 x 1	0.212
1/14 x 1-1/2	0.319
1/14 x 2	0.425
1/14 x 2-1/2	0.531
1/14 x 3	0.638
1/8 x 1/2	0.2125
1/8 x 3/4	0.3188
1/8 x 1	0.425
1/8 x 1-1/2	0.638
1/8 x 2	0.850
1/8 x 2-1/2	1.06
1/8 x 3	1.27
3/16 x 1/2	0.319
3/16 x 3/4	0.478
3/16 x 1	0.638
3/16 x 1-1/4	0.797
3/16 x 1-1/2	0.956
3/16 x 2	1.28
3/16 x 2-1/2	1.59
3/16 x 3	1.91
1/4 x 1/2	0.425
1/4 x 3/4	0.636



Table A-23. Table of Weights - Steel - Continued

Size	Pounds per Linear Feet
1/4 x 1	0.850
1/4 x 1-1/4	1.06
1/4 x 1-1/2	1.28
1/4 x 1-3/4	1.49
1/4 x 2	1.70
1/4 x 2 1/2	2.13
1/4 x 3	2.55
3/16 x 1/2	0.531
3/16 x 3/4	0.797
5/16 x 1	1.06
5/16 x 1-1/4	1.33
5/16 x 1-1/2	1.59
5/16 x 1-3/4	1.86
5/16 x 2	2.13
5/16 x 2-1/4	2.39
5/16 x 2-1/2	2.66
5/16 x 2-3/4	2.92
5/16 x 3	3.19
3/8 x 1/2	0.638
3/8 x 1	1.28
3/8 x 1-1/4	1.59
3/8 x 1-1/2	1.91
3/8 x 2	2.55
3/8 x 2-1/2	3.19
3/8 x 3	3.83
3/8 x 3-1/2	4.46
3/8 x 4	5.10
3/8 x 6	7.65
1/2 x 1	1.70
1/2 x 1-1/4	2.13
1/2 x 1-1/2	2.55
1/2 x 2	3.40
1/2 x 2-1/2	4.25
1/2 x 3	5.10
1/2 x 3-1/2	5.95
1/2 x 4	6.80
1/2 x 4-1/2	7.65
1/2 x 5	8.50
1/2 x 6	10.20
5/8 x 2	4.25
5/8 x 2-1/2	5.31
5/8 x 3	6.38
5/8 x 3-1/2	7.44
5/8 x 4	8.50
5/8 x 6	12.75
3/4 x 1	2.55
3/4 x 1-1/2	3.85



Table A-23. Table of Weights - Steel - Continued

Size	Pounds per Linear Feet
3/4 x 2	5.10
3/4 x 2-1/2	6.38
3/4 x 3	7.65
3/4 x 4	10.20
3/4 x 5	12.75
3/4 x 6	15.30
1 x 2	6.80
1 x 2-1/2	8.50
1 x 3	10.20
1 x 4	13.60
1 x 5	17.00
1 x 6	20.40
1-1/4 x 2	8.50
1-1/4 x 3	12.75
1-1/4 x 4	17.00
1-1/2 x 2	10.20
1-1/2 x 3	15.30
1-1/2 x 5	25.50
2 x 2-1/2	17.00
2 x 3	20.40
2 x 4	27.20
2-1/2 x 3	25.50
3 x 4	40.80
Bars-Hexagon	
1/4	0.195
5/16	0.29
3/8	0.43
7/16	0.56
1/2	0.73
9/16	0.93
5/8	1.15
11/16	1.40
3/4	1.66
13/16	1.91
7/8	2.25
13/16	2.58
1	2.94
1-1/16	3.33
1-1/8	3.73
1-1/4	4.60
1-5/16	5.07
1-3/8	5.57
1-1/2	6.62
1-3/4	9.00
2	11.78
Bars-Square	
1/8	0.053



Table A-23. Table of Weights - Steel - Continued

Size	Pounds per Linear Feet
3/16	0.120
1/4	0.212
5/16	0.332
3/8	0.478
7/16	0.651
1/2	0.850
9/16	1.076
5/8	1.328
3/4	1.913
7/8	2.603
1	3.40
1-1/8	4.303
1-1/4	5.313
1-5/16	5.857
1-3/8	6.428
1-1/2	7.650
1-3/4	10.41
2	13.60
2-1/4	17.21
2-1/2	21.25
3	30.60
Rods-Rounds	
1/16	0.010
3/32	0.023
1/8	0.042
5/32	0.065
3/16	0.094
7/32	0.128
1/4	0.167
9/32	0.211
5/16	0.261
11/32	0.316
3/8	0.376
7/16	0.511
1/2	0.668
9/16	0.845
5/8	1.043
11/16	1.262
3/4	1.502
13/16	1.763
7/8	2.044
15/16	2.347
1	2.670
1-1/16	3.015
1-1/8	3.380
1-3/16	3.766
1-1/4	4.172



Table A-23. Table of Weights - Steel - Continued

Size	Pounds per Linear Feet
1-3/8	5.049
1-7/16	5.518
1-1/2	6.008
1-5/8	7.051
1-3/4	8.178
1-7/8	9.388
2	10.68
2-1/4	13.52
2-5/16	14.28
2-3/8	15.06
2-1/2	16.69
2-3/4	20.19
3	24.03
3-1/4	28.21
3-1/2	32.71
3-3/4	37.55
4	42.73
4-1/2	54.07
5	66.76
5-1/2	80.78
6	96.13
7	130.8
8	170.9
Tubing-Round	
3/16 x 0.028	0.0476
3/16 x 0.035	0.0569
1/4 x 0.028	0.0663
1/4 x 0.035	0.0803
1/4 x 0.049	0.1051
1/4 x 0.058	0.1188
1/4 x 0.065	0.1283
5/16 x 0.028	0.0850
5/16 x 0.035	0.1036
5/16 x 0.049	0.1378
5/16 x 0.058	0.1575
5/16 x 0.065	0.1716
5/16 x 0.095	0.2204
3/8 x 0.028	0.1037
3/8 x 0.035	0.1270
3/8 x 0.049	0.1704
3/8 x 0.058	0.1962
3/8 x 0.065	0.2150
3/8 x 0.083	0.2586
3/8 x 0.095	0.2838
7/16 x 0.028	0.1223
7/16 x 0.035	0.1503
7/16 x 0.049	0.2030



Table A-23. Table of Weights - Steel - Continued

Size	Pounds per Linear Feet
7/16 x 0.065	0.2583
7/16 x 0.083	0.3139
7/16 x 0.095	0.3471
1/2 x 0.028	0.1410
1/2 x 0.035	0.1736
1/2 x 0.042	0.2052
1/2 x 0.049	0.2358
1/2 x 0.058	0.2735
1/2 x 0.065	0.3017
1/2 x 0.083	0.3693
1/2 x 0.095	0.4105
9/16 x 0.035	0.1969
9/16 x 0.049	0.2684
9/16 x 0.065	0.3450
9/16 x 0.095	0.4738
5/8 x 0.028	0.1783
5/8 x 0.035	0.2203
5/8 x 0.049	0.3011
5/8 x 0.058	0.3509
5/8 x 0.065	0.3883
5/8 x 0.083	0.480
5/8 x 0.095	0.5372
5/8 x 0.120	0.6465
11/14 x 0.035	0.2437
11/14 x 0.049	0.3338
11/14 x 0.065	0.4317
11/14 x 0.095	0.6005
3/4 x 0.028	0.2157
3/4 x 0.035	0.2670
3/4 x 0.049	0.3665
3/4 x 0.058	0.4282
3/4 x 0.065	0.4750
3/4 x 0.083	0.5906
3/4 x 0.095	0.6639
3/4 x 0.120	0.8066
13/14 x 0.035	0.2903
13/16 x 0.049	0.3991
13/16 x 0.058	0.4669
13/16 x 0.065	0.5184
7/8 x 0.028	0.2530
7/8 x 0.035	0.3137
7/8 x 0.049	0.4318
7/8 x 0.058	0.5056
7/8 x 0.065	0.5617
7/8 x 0.095	0.7906
7/8 x 0.120	0.9666
15/16 x 0.035	0.3370



Table A-23. Table of Weights - Steel - Continued

Size	Pounds per Linear Foot
15/16 x 0.049	0.4645
15/16 x 0.065	0.6051
15/16 x 0.083	0.7567
1 x 0.028	0.2904
1 x 0.035	0.3603
1 x 0.049	0.4972
1 x 0.058	0.5829
1 x 0.065	0.6484
1 x 0.083	0.8120
1 x 0.095	0.9173
1 x 0.120	1.127
1-1/16 x 0.035	0.3837
1-1/16 x 0.049	0.5298
1-1/16 x 0.065	0.6917
1-1/8 x 0.035	0.4070
1-1/8 x 0.049	0.5625
1-1/8 x 0.058	0.6603
1-1/8 x 0.065	0.7351
1-1/8 x 0.083	0.9227
1-1/8 x 0.095	1.044
1-1/8 x 0.120	1.287
1-3/16 x 0.035	0.4304
1-3/16 x 0.049	0.5952
1-3/16 x 0.065	0.7784
1-3/16 x 0.095	1.107
1-3/16 x 0.120	1.367
1-1/4 x 0.028	0.3650
1-1/4 x 0.035	0.4537
1-1/4 x 0.049	0.6279
1-1/4 x 0.058	0.7376
1-1/4 x 0.065	0.8218
1-1/4 x 0.083	1.034
1-1/4 x 0.095	1.171
1-1/4 x 0.120	1.447
1-1/4 x 0.125	1.500
1-1/4 x 0.134	1.595
1-5/16 x 0.035	0.4770
1-5/16 x 0.049	0.6605
1-5/16 x 0.065	0.8651
1-5/16 x 0.095	1.234
1-5/16 x 0.120	1.527
1-3/8 x 0.035	0.5004
1-3/8 x 0.049	0.6932
1-3/8 x 0.058	0.8150
1-3/8 x 0.065	0.9085
1-3/8 x 0.083	1.144
1-3/8 x 0.120	1.607



Table A-23. Table of Weights - Steel - Continued

Size	Pounds per Linear Feet
1-7/16 x 0.049	0.7259
1-7/16 x 0.065	0.9518
1-7/16 x 0.095	1.361
1-1/2 x 0.035	0.547
1-1/2 x 0.040	0.7585
1-1/2 x 0.058	0.8923
1-1/2 x 0.065	0.9951
1-1/2 x 0.083	1.255
1-1/2 x 0.095	1.424
1-1/2 x 0.120	1.767
1-1/2 x 0.1875	2.626
1-9/16 x 0.049	0.7912
1-9/16 x 0.065	1.038
1-9/16 x 0.095	1.487
1-5/8 x 0.049	0.8239
1-5/8 x 0.058	0.9697
1-5/8 x 0.065	1.082
1-5/8 x 0.083	1.365
1-5/8 x 0.095	1.551
1-5/8 x 0.120	1.927
1-11/16 x 0.049	0.8566
1-11/16 x 0.065	1.125
1-11/16 x 0.095	1.614
1-3/4 x 0.035	0.6404
1-3/4 x 0.049	0.8892
1-3/4 x 0.058	1.047
1-3/4 x 0.065	1.169
1-3/4 x 0.083	1.476
1-3/4 x 0.095	1.677
1-3/4 x 0.120	2.087
1-3/4 x 0.125	2.167
1-3/4 x 0.1875	3.126
1-13/16 x 0.049	0.9219
1-13/16 x 0.065	1.212
1-13/16 x 0.095	1.741
1-7/8 x 0.049	0.9546
1-7/8 x 0.058	1.124
1-7/8 x 0.065	1.255
1-7/8 x 0.095	1.804
1-7/8 x 0.120	2.247
1-15/16 x 0.049	0.9873
1-15/16 x 0.065	1.299
1-15/16 x 0.095	1.867
2 x 0.035	0.7338
2 x 0.049	1.020
2 x 0.058	1.202
2 x 0.065	1.340



Table A-23. Table of Weights - Steel - Continued

Size	Pounds per Linear Feet
2 x 0.083	1.698
2 x 0.095	1.931
2 x 0.120	2.407
2 x 0.125	2.501
2 x 0.1875	3.626
2-1/8 x 0.035	0.7804
2-1/8 x 0.049	1.085
2-1/8 x 0.058	1.279
2-1/8 x 0.065	1.429
2-1/8 x 0.095	2.057
2-1/8 x 0.120	2.567
2-1/4 x 0.035	0.8271
2-1/4 x 0.049	1.151
2-1/4 x 0.058	1.356
2-1/4 x 0.065	1.515
2-1/4 x 0.083	1.919
2-1/4 x 0.095	2.184
2-1/4 x 0.120	2.727
2-1/4 x 0.125	2.834
2-1/4 x 0.1875	4.126
2-3/8 x 0.049	1.216
2-3/8 x 0.065	1.602
2-3/8 x 0.095	2.311
2-3/8 x 0.120	2.887
2-1/2 x 0.049	1.281
2-1/2 x 0.065	1.689
2-1/2 x 0.083	2.140
2-1/2 x 0.095	2.438
2-1/2 x 0.120	3.047
2-1/2 x 0.125	3.167
2-3/4 x 0.083	2.362
2-3/4 x 0.095	2.691
2-3/4 x 0.120	3.367
2-3/4 x 0.125	3.501
3 x 0.095	2.944
3 x 0.120	3.687
3-3/4 x 0.120	4.647
3-3/4 x 0.15625	5.991
3-3/4 x 0.1875	7.127
Tubing-Streamline	
1.697 x 0.707 x 0.049	0.6279
1.70 x 0.70 x 0.035	0.4537
1.874 x 0.781 x 0.035	0.5004
1.875 x 0.786 x 0.049	0.6932
2.047 x 0.854 x 0.049	0.7585
2.047 x 0.854 x 0.058	0.8923
2.215 x 0.823 x 0.035	0.5937



**Table A-23. Table of Weights - Steel - Continued**

Size	Pounds per Linear Feet
2.21875 x 0.921 x 0.049	0.8239
2.386 x 0.994 x 0.049	0.8892
2.386 x 0.994 x 0.058	1.047
2.386 x 0.994 x 0.065	1.169
2.726 x 1.136 x 0.035	0.7338
3.00 x 0.375 x 0.035	0.7338
3.067 x 1.278 x 0.049	1.151
3.067 x 1.278 x 0.065	1.515
3.748 x 1.563 x 0.083	2.362

**Table A-24. Table of Weights - Steel (Area)**

Thickness	Pounds per Square Feet
Sheets	
0.0156	0.6377
0.020	0.8952
0.025	1.022
0.03125	1.2795
0.0375	1.5329
0.050	2.044
0.0625	2.5549
0.0781	3.1928
0.093	3.8344
0.109	4.4557
0.125	5.1096
0.156	6.377
0.1875	7.6851
0.250	10.219

**Table A-25. Table of Weights - Steel (Length)**

Thickness	Number of Feet Per Pound
Wire	
0.006	10415.0
0.008	5858.0
0.009	4629.0
0.010	3749.0
0.011	2936.0
0.012	2604.0
0.013	2218.0
0.014	1913.0
0.016	1465.0
0.018	1157.0
0.020	937.3
0.024	650.9
0.025	599.9



**Table A-25. Table of Weights - Steel (Length) - Continued**

Thickness	Number of Feet Per Pound
0.028	478.2
0.031	383.9
0.032	366.1
0.035	306.1
0.036	289.3
0.040	234.3
0.041	223.0
0.045	182.7
0.047	166.2
0.049	156.2
0.0508	145.3
0.054	128.6
0.058	111.5
0.0625	95.98
0.0641	91.25
0.071	72.32
0.080	58.58
0.0907	45.58
0.101	36.11
0.118	26.04
0.1285	22.71
0.162	14.29

**Table A-26. Table of Weights - Zinc**

Thickness	Pounds per Square Feet
Sheet	
0.018	0.67
0.032	1.20
0.045	1.68
0.049	1.87
0.0508	1.87
0.109	3.98



Table A-27. Temperature Conversion Chart (-459.4 - 75)

-459.4 to -220			-210 to 0		1 to 25			26 to 50			51 to 75		
°C	°C or °F	°F	°C	°C or °F	°F	°C	°C or °F	°F	°C	°C or °F	°C	°C or °F	°F
-273	-459.4		-134	-210	-346	-17.2	1	33.8	-3.33	26	10.6	51	123.8
-268	-450		-129	-200	-328	-16.7	2	35.6	-2.78	27	11.1	52	125.6
-262	-440		-123	-190	-310	-16.1	3	37.4	-2.22	28	11.7	53	127.4
-257	-430		-118	-180	-292	-15.6	4	39.2	-1.67	29	12.2	54	129.2
-251	-420		-112	-170	-274	-15.0	5	41.0	-1.11	30	12.8	55	131.0
-246	-410		-107	-160	-256	-14.4	6	42.8	-0.56	31	13.3	56	132.8
-240	-400		-101	-150	-238	-13.9	7	44.6	0	32	13.9	57	134.6
-234	-390		-95.6	-140	-220	-13.3	8	46.4	0.56	33	14.4	58	136.4
-229	-380		-90.0	-130	-202	-12.8	9	48.2	1.11	34	15.0	59	138.2
-223	-370		-84.4	-120	-184	-12.2	10	60.0	1.67	35	15.6	60	140.0
-218	-360		-78.9	-110	-166	-11.7	11	51.8	2.22	36	16.1	61	141.8
-212	-350		-73.3	-100	-148	-11.1	12	53.6	2.78	37	16.7	62	143.6
-207	-340		-67.8	-90	-130	-10.6	13	55.4	3.33	38	17.2	63	145.4
-201	-330		-62.2	-80	-112	-10.0	14	57.2	3.89	39	17.8	64	147.2
-196	-320		-56.7	-70	-94	-9.44	15	59.0	4.44	40	18.3	65	149.0
-190	-310		-51.1	-60	-76	-8.89	16	50.8	6.00	41	18.9	66	150.8
-184	-300		-45.6	-50	-68	-8.33	17	62.6	6.56	42	19.4	67	152.6
-179	-290		-40.0	-40	-40	-7.78	18	64.4	6.11	43	20.0	68	154.4
-173	-280		-34.4	-30	-22	-7.22	19	66.2	6.67	44	20.6	69	156.2
-169	-273	-459.4	-28.9	-20	-4	-6.67	20	68.0	7.22	45	21.1	70	158.0
-168	-270	-454	-23.3	-10	14	-6.11	21	69.8	7.78	46	21.7	71	159.8
-162	-260	-436	-17.8	0	32	-6.56	22	71.6	8.33	47	22.2	72	161.6
-157	-250	-418				-5.00	23	73.4	8.89	48	22.8	73	163.4
-151	-240	-400				-4.44	24	76.2	9.44	49	23.3	74	165.2
-146	-230	-382				-3.89	25	77.0	10.0	50	23.9	75	167.0
-140	-220	-364											



Table A-28. Temperature Conversion Chart (76 - 750)

76 to 100			101 to 340			341 to 490			491 to 750		
°C	°C or °F	°F	°C	°C or °F	°F	°C	°C or °F	°F	°C	°C or °F	°F
24.4	76	168.8	43	110	230	177	350	662	260	500	932
25.0	77	170.6	49	120	248	182	360	680	266	510	950
25.6	78	172.4	54	130	266	188	370	698	271	520	968
26.1	79	174.2	60	140	284	193	380	716	277	530	986
26.7	80	176.0	66	150	302	199	390	734	282	540	1004
27.2	81	177.8	71	160	320	204	400	752	288	550	1022
27.8	82	179.6	77	170	338	210	410	770	293	560	1040
28.3	83	181.4	82	180	356	216	420	788	299	570	1058
28.9	84	183.2	88	190	374	221	430	806	304	580	1076
29.4	85	185.0	93	200	392	227	440	824	310	590	1094
30.0	86	186.8	99	210	410	232	450	842	316	600	1112
30.6	87	188.6	100	212	413	238	460	860	321	610	1130
31.1	88	190.4	104	220	428	243	470	878	327	620	1148
31.7	89	192.2	110	230	446	249	480	896	332	630	1166
32.2	90	194.0	115	240	464	254	490	914	338	640	1184
32.8	91	195.8	121	250	482				343	650	1202
33.3	92	197.6	127	260	500				349	660	1220
33.9	93	199.4	132	270	518				354	670	1238
34.4	94	201.2	138	280	536				360	680	1256
35.0	95	203.0	143	290	554				366	690	1274
35.6	96	204.8	149	300	572				371	700	1292
36.1	97	206.6	154	310	590				377	710	1310
36.7	98	208.4	160	320	608				382	720	1328
37.2	99	210.2	166	330	626				388	730	1346
37.8	100	212.0	171	340	644				393	740	1364
									399	760	1382



Table A-29. Temperature Conversion Chart (751 - 2000)

751 to 1000			1001 to 1250			1251 to 1490			1491 to 1750			1751 to 2000		
°C	°C or °F	°F	°C	°C or °F	°F	°C	°C or °F	°F	°C	°C or °F	°F	°C	°C or °F	°F
404	760	1400	543	1010	1850	682	1260	2300	816	1500	2732	960	1760	3200
410	770	1418	549	1020	1868	688	1270	2318	821	1510	2750	966	1770	3218
416	780	1436	554	1030	1886	693	1280	2336	827	1520	2768	971	1780	3236
421	790	1454	560	1040	1904	699	1290	2354	832	1530	2786	977	1790	3254
427	800	1472	566	1050	1922	704	1300	2372	838	1540	2804	982	1800	3272
432	810	1490	571	1060	1940	710	1310	2390	843	1550	2822	988	1810	3290
438	820	1508	577	1070	1958	716	1320	2408	849	1560	2840	993	1820	3308
443	830	1526	582	1080	1976	721	1330	2426	854	1570	2858	999	1830	3326
449	840	1544	588	1090	1994	727	1340	2444	860	1580	2876	1004	1840	3344
454	850	1562	593	1100	2012	732	1350	2462	866	1590	2894	1010	1850	3362
460	860	1580	599	1110	2030	738	1360	2480	871	1600	2912	1016	1860	3380
466	870	1598	604	1120	2048	743	1370	2498	877	1610	2930	1021	1870	3398
471	880	1616	610	1130	2066	749	1380	2516	882	1620	2948	1027	1880	3416
477	890	1634	616	1140	2084	754	1390	2534	888	1630	2966	1032	1890	3434
482	900	1662	621	1150	2102	760	1400	2552	893	1640	2984	1038	1900	3462
488	910	1670	627	1160	2120	766	1410	2570	899	1650	3002	1043	1910	3470
493	920	1688	632	1170	2138	771	1420	2588	904	1660	3020	1049	1920	3488
499	930	1706	638	1180	2156	777	1430	2606	910	1670	3038	1054	1930	3506
504	940	1724	643	1190	2174	782	1440	2624	916	1680	3056	1060	1940	3524
510	950	1742	649	1200	2192	788	1450	2642	921	1690	3074	1066	1950	3542
516	960	1760	654	1210	2210	793	1460	2660	927	1700	3092	1071	1960	3560
521	970	1778	660	1220	2228	799	1470	2678	932	1710	3110	1077	1970	3578
527	980	1796	666	1230	2246	804	1480	2696	938	1720	3128	1082	1980	3596
532	990	1814	671	1240	2264	810	1490	2714	943	1730	3146	1088	1990	3614
538	1000	1832	677	1250	2282				949	1740	3164	1093	2000	3632
									954	1750	3182			

**NOTE**

The numbers in bold face type refer to the temperature either in degrees Centigrade or Fahrenheit which it is desired to convert into the other scale. If converting from Fahrenheit degrees to Centigrade degrees the equivalent temperature will be found in the left column, while if converting from degrees Centigrade to degrees Fahrenheit, the answer will be found in the column on the right.



Table A-29. Temperature Conversion Chart (751 - 2000) - Continued

751 to 1000		1001 to 1250		1251 to 1490		1491 to 1750		1751 to 2000	
°C	°C or °F	°F	°C	°C or °F	°F	°C	°C or °F	°F	°C
°F = $\frac{9}{5}$ (°C) +32									
°C = $\frac{5}{9}$ (°F) -32									



Table A-30. Temperature Conversion Chart (2001 - 3000)

2001 to 2250				2251 to 2490				2491 to 2750				2751 to 3000			
°C	°C or °F	°F		°C	°C or °F	°F		°C	°C or °F	°F		°C	°C or °F	°F	
1099	2010	3650	1238	2260	4100	1371	2500	4532	1516	2760	5000				
1104	2020	3668	1243	2270	4118	1377	2510	4550	1521	2770	5018				
1110	2030	3686	1249	2280	4136	1382	2520	4568	1527	2780	5036				
1116	2040	3704	1254	2290	4154	1388	2530	4586	1532	2790	5054				
1121	2050	3722	1260	2300	4172	1393	2540	4604	1538	2800	5072				
1127	2060	3740	1266	2310	4190	1399	2550	4622	1543	2810	5090				
1132	2070	3758	1271	2320	4208	1404	2560	4640	1549	2820	5108				
1138	2080	3776	1277	2330	4226	1410	2570	4658	1554	2830	5125				
1143	2090	3794	1282	2340	4244	1416	2580	4676	1560	2840	5144				
1149	2100	3812	1288	2350	4262	1421	2590	4694	1566	2850	5162				
1154	2110	3830	1293	2360	4280	1427	2600	4712	1571	2860	5180				
1160	2120	3848	1299	2370	4298	1432	2610	4730	1577	2870	5198				
1166	2130	3866	1304	2380	4316	1438	2620	4748	1582	2880	5216				
1171	2140	3884	1310	2390	4334	1443	2630	4766	1588	2890	5234				
1177	2150	3902	1316	2400	4352	1449	2640	4784	1593	2900	5252				
1182	2160	3920	1321	2410	4370	1454	2650	4802	1599	2910	5270				
1188	2170	3938	1327	2420	4388	1460	2660	4820	1604	2920	5288				
1193	2180	3956	1332	2430	4406	1466	2670	4838	1610	2930	5306				
1199	2190	3974	1338	2440	4424	1471	2680	4856	1616	2940	5324				
1204	2200	3992	1343	2450	4442	1477	2690	4874	1621	2950	5342				
1210	2210	4010	1349	2460	4460	1482	2700	4892	1627	2960	5360				
1216	2220	4028	1354	2470	4478	1488	2710	4910	1632	2970	5378				
1221	2230	4046	1360	2480	4496	1493	2720	4928	1638	2980	5396				
1227	2240	4064	1366	2490	4514	1499	2730	4946	1643	2990	5414				
1232	2250	4082				1504	2740	4964	1649	3000	5432				
						1510	2750	4982							
				°C		°F		°C		°F					
			INTERPOLATION FACTORS	0.56	1	1.8		3.33	6	10.8					
				1.11	2	3.6		3.89	7	12.6					
				1.67	3	5.4		4.44	8	14.4					
				2.22	4	7.2		5.00	9	16.2					
				2.78	5	9.0		5.56	10	18.0					



Table A-31. Standard Bend Radii for 90° Cold Forming-Flat Sheet (0.008 - 0.050)

	Material	Material Condition	Forming Temperature	Gauge							
				0.008	0.012	0.016	0.020	0.025	0.032	0.040	0.050
ALUMINUM	3003-0, 5052-0, 6061-0	Noted	Room		0.03	0.03	0.03	0.03	0.03	0.06	0.06
	2014-0, 2024-0, 5052-H34, 6061-T4, 7075-0, 7178-0	Noted	Room		0.03	0.03	0.03	0.03	0.06	0.06	0.06
	2014-T4, 2024-T3, 2024-T4, 6061-T6, 7075-W, 7178-W	Noted	Room		0.03	0.03	0.03	0.06	0.09	0.09	0.12
	2014-T6, 2024-T36, 7075-T6, 7178-T6	Noted	Room		0.06	0.06	0.08	0.09	0.12	0.19	0.25
	2024-W	Noted	Room		0.03	0.03	0.03	0.03	0.06	0.06	0.09
	7075-T6	Noted	Hot 300±25 °F		0.06	0.06	0.06	0.06	0.06	0.06	0.09
	7178-T6	Noted	Hot 275±25 °F		0.06	0.06	0.06	0.06	0.06	0.06	0.09
	AZ31A (SPEC.QQ-M-44)	A	Hot 400-625 °F			0.03	0.06	0.06	0.06	0.09	0.09
	AZ31A (SPEC.QQ-M-44)	A	Room			0.09	0.09	0.12	0.16	0.19	0.25
	AZ31A (SPEC.QQ-M-44)	H	Hot 325±25 °F			0.06	0.09	0.12	0.12	0.22	0.25
MAGNESIUM	AZ31A (SPEC.QQ-M-44)	H	Room			0.19	0.19	0.25	0.31	0.38	0.50



Table A-31. Standard Bend Radii for 90° Cold Forming-Flat Sheet (0.008 - 0.050) - Continued

	Material	Material Condition	Forming Temperature	Gauge							
				0.008	0.012	0.016	0.020	0.025	0.032	0.040	0.050
STEEL	1025		Room	0.03	0.03	0.03	0.06	0.06	0.06	0.06	0.09
	4130	65,000 to 90,000 Pound-force per square inch (PSI)	Room	0.03	0.03	0.03	0.06	0.06	0.06	0.06	0.09
	4130	90,000 to 125,000 PSI	Room	0.03	0.03	0.06	0.06	0.09	0.09	0.12	0.12
	Corrosion Resistant	Annealed	Room	0.03	0.03	0.03	0.03	0.03	0.03	0.03	0.03
	Corrosion Resistant	1/4 Hard	Room	0.03	0.03	0.03	0.03	0.06	0.06	0.06	0.06
	Corrosion Resistant	1/2 Hard	Room	0.03	0.03	0.06	0.06	0.09	0.09	0.12	0.12
	Corrosion Resistant	Full Hard	Room	0.06	0.09	0.09	0.12	0.16	0.16	0.16	0.19
	Commercially Pure Aeronautical Material Specification (AMS) 4901	Annealed	Room	0.03	0.03	0.06	0.06	0.09	0.09	0.12	0.12
	Alloy AMS 4908	Annealed	Room	0.03	0.03	0.06	0.06	0.09	0.09	0.12	0.12
	Alloy Convair Spec 0-01014	Annealed	Room			0.09	0.09	0.12	0.16	0.19	0.19
TITANIUM											



Table A-32. Standard Bend Radii for 90° Cold Forming-Flat Sheet (0.063 - 0.250)

	Material	Material Condition	Forming Temperature	Gauge									
				0.063	0.071	0.080	0.090	0.100	0.125	0.160	0.190	0.250	
ALUMINUM	3003-0, 5052-0, 6061-0	Noted	Room	0.06	0.09	0.09	0.12	0.12	0.16	0.16	0.19	0.25	
	2014-0, 2024-0, 5052-H34, 6061-T4, 7075-0, 7178-0			0.09	0.09	0.12	0.16	0.16	0.19	0.25	0.31	0.44	
	2014-T4, 2024-T3, 2024-T4, 6061-T6, 7075-W, 7178-W	Noted	Room	0.16	0.19	0.22	0.25	0.31	0.38	0.44	0.69	1.00	
	2014-T6, 2024-T36, 7075-T6, 7178-T6			0.31	0.36	0.44	0.50	0.56	0.69	0.88	1.00	1.50	
	2024-W	Noted	Room	0.12	0.12	0.16	0.18	0.22	0.25	0.31	0.44	0.69	
	7075-T6			0.14	0.15	0.15	0.18	0.22	0.31	0.38	0.50	0.69	
	7178-T6	Noted	Hot 300±25°F	0.14	0.15	0.15	0.18	0.22	0.31	0.38	0.50	0.69	
	AZ31A (SPEC. QQ-M-44)			0.12	0.16	0.19	0.19	0.22	0.25	0.31	0.38	0.50	
	MAGNESIUM	AZ31A (SPEC. QQ-M-44)	A	Room	0.31	0.38	0.44	0.44	0.50	0.62	0.75	1.00	1.25
		AZ31A (SPEC. QQ-M-44)			0.38	0.44	0.44	0.44	0.44	0.50	0.62	0.81	1.00
AZ31A (SPEC. QQ-M-44)		H	Hot 325±25°F	0.62	0.81	0.81	0.88	1.00	1.25	1.50	2.00	2.50	
AZ31A (SPEC. QQ-M-44)				0.62	0.81	0.81	0.88	1.00	1.25	1.50	2.00	2.50	



Table A-32. Standard Bend Radii for 90° Cold Forming-Flat Sheet (0.063 - 0.250) - Continued

	Material	Material Condition	Forming Temperature	Gauge								
				0.063	0.071	0.080	0.090	0.100	0.125	0.160	0.190	0.250
STEEL	1025		Room	0.09	0.12	0.16	0.19	0.22	0.25	0.31	0.38	0.50
	4130	65,000 to 90,000 Pound-force per Square Inch (PSI)	Room	0.09	0.12	0.16	0.19	0.22	0.25	0.31	0.38	0.50
	4130	90,000 to 125,000 PSI	Room	0.16	0.19	0.25	0.31	0.38	0.44	0.50	0.62	0.75
	Corrosion Resistant	Annealed	Room	0.06	0.06	0.09	0.12	0.12	0.16	0.16	0.19	0.25
	Corrosion Resistant	1/4 Hard	Room	0.09	0.09	0.12	0.16	0.19	0.22	0.25	0.31	0.38
	Corrosion Resistant	1/2 Hard	Room	0.16	0.16	0.19	0.25	0.31	0.38	0.50	0.62	0.75
	Corrosion Resistant	Full Hard	Room	0.19	0.25	0.31	0.38	0.44	0.50	0.62	0.75	1.00
	Commer- cially Pure AMS 4901	Annealed	Room	0.16	0.19	0.25	0.31	0.38	0.38	0.44	0.56	0.75
	Alloy AMS 4908	Annealed	Room	0.16	0.19	0.25	0.31	0.38	0.38	0.44	0.56	0.75
	Alloy Convair Spec 0-01014	Annealed	Room	0.25	0.31	0.38	0.44	0.56	0.62	0.78	0.94	1.25
TITANIUM												



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

**Table A-33. Metal Bending and Bend Radii Bend Allowances Sheet Metal Bend Allowances per Degree of Bend Aluminum Alloys**

Bend Radius	Stock Thickness							
	0.022	0.032	0.040	0.051	0.064	0.091	0.128	0.187
	Bend Allowance per One Degree							
1/32	0.00072	0.00079	0.00086	0.00094	0.00104	0.00125	0.00154	0.00200
1/16	0.00126	0.00135	0.00140	0.00149	0.00159	0.00180	0.00209	0.00255
3/32	0.00180	0.00188	0.00195	0.00203	0.00213	0.00234	0.00263	0.00309
1/8	0.00235	0.00243	0.00249	0.00258	0.00268	0.00289	0.00317	0.00364
5/32	0.00290	0.00297	0.00304	0.00312	0.00322	0.00343	0.00372	0.00418
3/16	0.00344	0.00352	0.00358	0.00367	0.00377	0.00398	0.00426	0.00473
7/32	0.00398	0.00406	0.00412	0.00421	0.00431	0.00452	0.00481	0.00527
1/4	0.00454	0.00461	0.00467	0.00476	0.00486	0.00507	0.00535	0.00582
9/32	0.00507	0.00515	0.00521	0.00530	0.00540	0.00561	0.00590	0.00636
5/16	0.00562	0.00570	0.00576	0.00584	0.00595	0.00616	0.00644	0.00691
11/32	0.00616	0.00624	0.00630	0.00639	0.00649	0.00670	0.00699	0.00745
3/8	0.00671	0.00679	0.00685	0.00693	0.00704	0.00725	0.00753	0.00800
13/32	0.00725	0.00733	0.00739	0.00748	0.00758	0.00779	0.00808	0.00854
7/16	0.00780	0.00787	0.00794	0.00802	0.00812	0.00834	0.00862	0.00908
15/32	0.00834	0.00842	0.00848	0.00857	0.00867	0.00888	0.00917	0.00963
1/2	0.00889	0.00896	0.00903	0.00911	0.00921	0.00943	0.00971	0.01017
17/32	0.00943	0.00951	0.00957	0.00966	0.00976	0.00997	0.01025	0.01072
9/16	0.00998	0.01005	0.01012	0.01020	0.01030	0.01051	0.01080	0.01126
19/32	0.01051	0.01058	0.01065	0.01073	0.01083	0.01105	0.01133	0.01179
5/8	0.01107	0.01114	0.01121	0.01129	0.01139	0.01160	0.01189	0.01235
21/32	0.01161	0.01170	0.01175	0.01183	0.01193	0.01214	0.01245	0.01289
11/16	0.01216	0.01223	0.01230	0.01238	0.01248	0.01268	0.01298	0.01344
23/32	0.01269	0.01276	0.01283	0.01291	0.01301	0.01322	0.01351	0.01397
3/4	0.01324	0.01332	0.01338	0.01347	0.01357	0.01378	0.01407	0.01453

Example: To determine bend allowance

Given: Stock = 0.064 aluminum alloy, Bend Radius = 1/8, Bend Angle = 50°

Find bend allowance for 1° in column for 0.064 Aluminum opposite 1/8 in column "Bend Radius".

Multiply this bend allowance (0.00268 in this case) by the number of degrees of the desired bend angle:  $0.00268 \times 50 = 0.1340$  = total bend allowance to be added to the length of the straight sides of the part to determine the total length of the material needed.



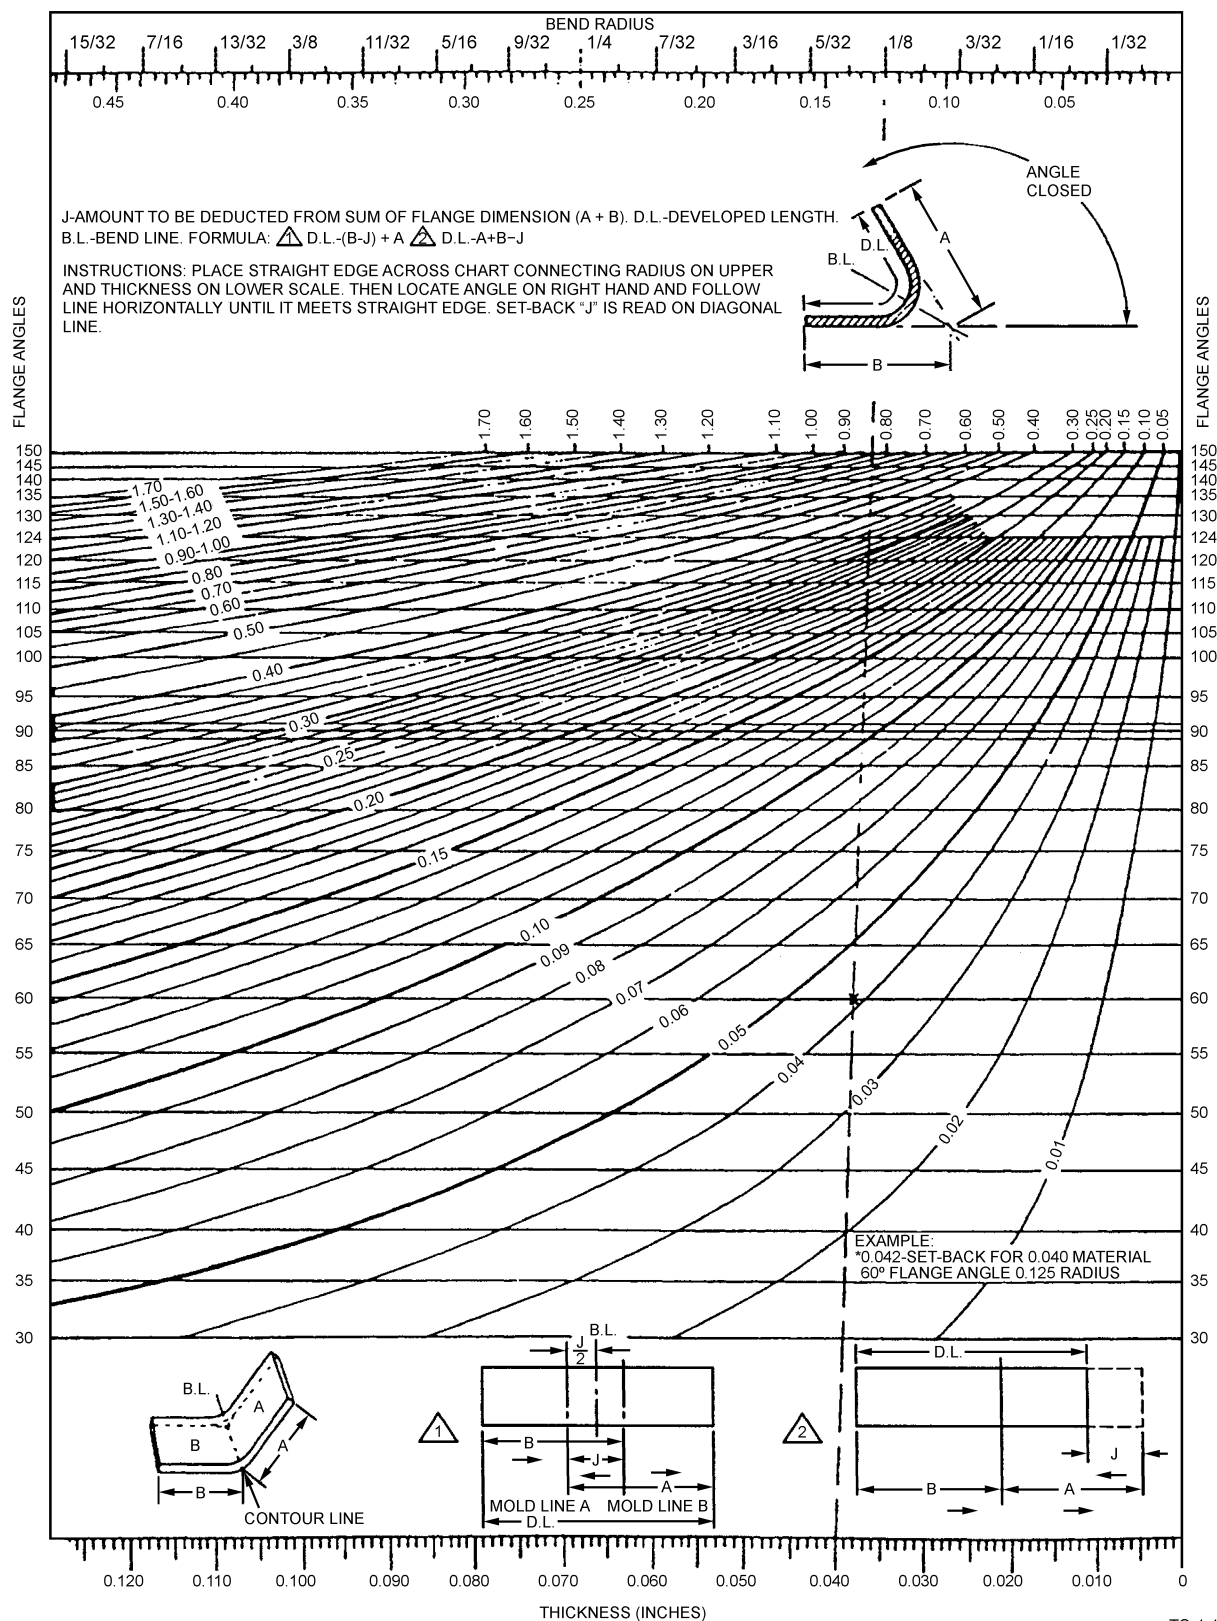


Figure A-1. Bend Set Back Chart



Table A-34. Comparative Table of Standard Gages

Thickness In Decimals Of An Inch							
Gage Number	United States Steel Wire	British Imperial Standard Wire	Browne and Sharpe	Birmingham Wire	Standard Birmingham Sheet and Hoop	United States Standard (Revised)	
						Thickness Approximate	Weight Ounces/ Square Feet
0000000	0.4900	0.500			0.6666		
000000	0.4615	0.464	0.580000		0.6250		
00000	0.4305	0.432	0.516500	0.500	0.5883		
0000	0.3938	0.400	0.460000	0.454	0.5416		
000	0.3625	0.372	0.409642	0.425	0.5000		
00	0.3310	0.348	0.364796	0.380	0.4452		
0	0.3065	0.324	0.324861	0.340	0.3964		
1	0.2830	0.300	0.289297	0.300	0.3532		
2	0.2625	0.276	0.257627	0.284	0.3147		
3	0.2437	0.252	0.229423	0.259	0.2804	0.2391	160
4	0.2253	0.232	0.204307	0.238	0.2500	0.2242	150
5	0.2070	0.212	0.181940	0.220	0.2225	0.2092	140
6	0.1920	0.192	0.162023	0.203	0.1981	0.1943	130
7	0.1770	0.176	0.144285	0.180	0.1764	0.1793	120
8	0.1620	0.160	0.128490	0.165	0.1570	0.1644	110
9	0.1483	0.144	0.114423	0.148	0.1398	0.1494	100
10	0.1350	0.128	0.101897	0.134	0.1250	0.1345	90
11	0.1205	0.116	0.090742	0.120	0.1113	0.1196	80
12	0.1055	0.104	0.080808	0.109	0.0991	0.1046	70
13	0.0915	0.092	0.071962	0.095	0.0882	0.0897	60
14	0.0800	0.080	0.064084	0.083	0.0785	0.0749	50
15	0.0720	0.072	0.057068	0.072	0.0699	0.0673	45
16	0.0625	0.064	0.050821	0.065	0.0625	0.0598	40
17	0.0540	0.056	0.045257	0.058	0.0556	0.0538	36
18	0.0475	0.048	0.040303	0.049	0.0495	0.0478	32
19	0.0410	0.040	0.035890	0.042	0.0440	0.0418	28
20	0.0348	0.036	0.031961	0.035	0.0392	0.0359	24
21	0.03175	0.032	0.028462	0.032	0.0349	0.0329	22
22	0.0286	0.028	0.025346	0.028	0.03125	0.0299	20
23	0.0258	0.024	0.022572	0.025	0.02782	0.0269	18
24	0.0230	0.022	0.020101	0.022	0.02476	0.0239	16
25	0.0204	0.020	0.017900	0.020	0.02204	0.0209	14
26	0.0181	0.018	0.015941	0.018	0.01961	0.0179	12
27	0.0173	0.0164	0.014195	0.016	0.01745	0.0164	11
28	0.0162	0.0148	0.012641	0.014	0.015625	0.0149	10
29	0.0150	0.0136	0.011257	0.013	0.0139	0.0135	9
30	0.0140	0.0124	0.010025	0.012	0.0123	0.0120	8
31	0.0132	0.0116	0.008928	0.010	0.0110	0.0105	7
32	0.0128	0.0108	0.007950	0.009	0.0098	0.0097	6.5
33	0.0118	0.0100	0.007080	0.008	0.0087	0.0090	6
34	0.0104	0.0092	0.006305	0.007	0.0077	0.0082	5.5
35	0.0095	0.0084	0.005615	0.005	0.0069	0.0075	5
36	0.0090	0.0076	0.005000	0.004	0.0061	0.0067	4.5



**Table A-34. Comparative Table of Standard Gages - Continued**

Thickness In Decimals Of An Inch							
Gage Number	United States Steel Wire	British Imperial Standard Wire	Browne and Sharpe	Birmingham Wire	Standard Birmingham Sheet and Hoop	United States Standard (Revised)	
						Thickness Approximate	Weight Ounces/ Square Feet
37	0.0085	0.0068	0.004453		0.0054	0.0064	4.25
38	0.0080	0.0060	0.003965		0.0048	0.0060	4
39	0.0075	0.0052	0.003531		0.0043		
40	0.0070	0.0048	0.003144		0.0038		
<p>1. United States Steel Wire Gage. Also known as: National Wire, Standard Steel Wire, Steel Wire, American Steel and Wire Company, Roebling, Washburn and Moen Gages. Used for bare wire of galvanized, black annealed, bright basic tinned or copper coated, iron or steel, spring steel wire. Not used for telephone and telegraph wire.</p> <p>2. British Imperial Standard Wire Gage. Also known as British Imperial Wire or English Legal Standard Gages. Used for bare copper telephone wires in the U.S. and for all wires and aluminum sheets in England.</p> <p>3. Browne and Sharpe Gage. Also known as American or American Wire Gages. Used for bare wire of brass, phosphor bronze, German silver, aluminum, zinc and copper (not for copper telephone or telegraph wire). Also resistance wire of German silver and other alloys, and for insulated wire of aluminum and copper. Also for rods of brass, copper, phosphor bronze and aluminum; sheets of copper, brass, phosphor bronze, aluminum and German silver; brazed brass and brazed copper tubing.</p> <p>4. Birmingham Wire Gage. Also known as Birmingham, Stubs or Studs Iron Wire Gages. Used for iron and steel telephone and telegraph wire and strip steel, steel bands, hoop steel, crucible spring steel, round-edged flat wire, and with limited usage for copper sheets. Also for seamless brass, seamless copper, seamless steel, stainless steel and aluminum tubes, and for boiler tubes.</p> <p>5. Standard Birmingham Sheet and Hoop Gage, used in England for iron and steel sheets and hoops.</p> <p>6. United States Standard. Also known as U.S. Standard Sheet Metal or U.S. Standard for Steel and Iron Sheets and Plates Gages. This is a gage based on the weight per square foot of sheets rather than on thickness. It is used for commercial iron and steel sheets and plates including planished, galvanized, tinned and terne plates, black sheet iron, blue annealed soft steel, steel plate, hot-rolled sheet steel, cold-rolled sheet steel, hot-rolled monel metal, cold-rolled monel metal.</p> <p>Other gages in use:</p> <p>Trenton Iron Company Gage.</p> <p>Zinc gage for sheet zinc only.</p> <p>Birmingham Metal Gage-in England for brass sheets. American Steel and Wire Company's music wire gage. Twist Drill and Steel Wire Gage for twist drill and steel drill rods.</p>							

**Table A-35. Melting Points Approximate**

Elements	Degrees	
	°C	°F
Aluminum	660	1220
Antimony	631	1167
Barium	850	1562
Beryllium	1350	2462
Bismuth	271	520
Cadmium	321	610
Calcium	810	1490
Carbon	3500	6332
Chromium	1765	3209
Cobalt	1480	2696
Copper	1083	1981
Gold	1063	1945



Table A-35. Melting Points Approximate - Continued

Elements	Degrees	
	°C	°F
Iron	1535	2795
Lead	327	621
Lithium	186	367
Magnesium	651	1204
Magnesium	1260	2300
Mercury	-39	-38
Molybdenum	2620	4748
Nickel	1446	2635
Phosphorous (Yellow)	44	111
Platinum	1773	3223
Silicon	1420	2588
Silver	961	1761
Tin	232	449
Tungsten	3400	6152
Vanadium	1710	3110
Zinc	420	787



## GLOSSARY

### A

**ACID BRITTLENESS** — Brittleness of steel resulting from use of acid solutions to remove scale, clean and electroplate. Brittleness is caused by the absorption of hydrogen into the metal from the acid solutions (also called hydrogen embrittlement).

**AGING** — (a) Generally any change in properties with time which occurs at relatively low temperature (room or elevated) after a final heat treatment of a cold marking operation. Aging is a process in which the trend is toward restoration of real equilibrium and away from an unstable condition induced by a prior operation. (b) Specifically the formation of a new phase by cooling a solid solution to super saturated state and allowing the super saturated solution to partially return to equilibrium by the formation of a less concentrated solid solution and a new phase.

**AIR HARDENING** — An alloy which does not require quenching from a high temperature to harden. Hardening of the material occurs simply by cooling in air from above critical temperature. The term refers only to the ability of the material to harden in air and does not imply any definite analysis or composition.

**AIR COOLING/QUENCHING** — Cooling from an elevated temperature in air, still or forced.

**ALLOY** — A mixture with metallic properties composed of two or more elements of which at least one is a metal. However, a metal is not designated an “alloy” based on elements incidental to its manufacture. For example; iron, carbon, manganese, silicon, phosphorus, sulphur, oxygen, nitrogen and hydrogen are incidental to the manufacture of plain carbon steel. It does not become an “alloy steel” until the elements are increased beyond regular composition or until other elements (metal) are added in significant amounts for a specific purpose.

**ALLOY ELEMENTS** — Chemical elements comprising an alloy, usually limited to the metallic elements added to modify the basic metal properties.

**AMORPHOUS** — Non-crystalline.

**ANNEALING** — Generally it is a controlled heating procedure which leads to maximum softness, ductility and formability. The annealing procedure is utilized for the following: (a) Remove stresses. (b) Induce softness. (c) After ductility, toughness, electrical, magnetic, or physical properties. (d) Refine crystalline structure. (e) Remove gases. (f) Produce a definite micro-structure.

**ANNEALING FULL** — A controlled heating procedure which leads to maximum softness, ductility and formability.

**ANNEALING, ISOTHERMAL** — Heating of a ferritic steel to a austenitic structure (fully or partial) followed by cooling to and holding at a temperature that causes transformation of the austenite to a relatively soft ferrite and carbide structure.

**ANODIC OXIDE COATING** — A thin film of aluminum oxide formed on the surface of aluminum and aluminum alloy parts by electro-chemical means.

**AS CAST** — Condition of a casting as it leaves the mold with no heat treatment.

**AUSTENITE** — A solid solution of iron carbide in gamma iron. It forms when the metal solidifies and remains a solution until it cools to about 732 °C (1350 °F). Theoretically the solution would remain if the iron or steel were cooled instantaneously from a bright red heat to atmospheric temperature, but in practice, this degree of rapidity is impracticable, and only a



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

portion of the austenite is preserved by rapid cooling. Addition of certain alloying elements such as nickel and manganese preserves austenite below - 17 °C (0 °F).

**B**

**BARK** — The decarburized skin or layer just beneath the scale found after heating steel in an oxidizing atmosphere.

**BASE METAL** — The metal to which other elements are added to form an alloy possessing specific properties.

**BESSEMER PROCESS** — A process for making steel by blowing air through molten pig iron contained in a suitable vessel. The process is one of rapid oxidation primarily of silicon and carbon.

**BILLET** — An ingot or bloom that has been reduced through rolling or hammering to an approximate square ranging from 1 1/2 inches square to 6 inches square, or to an approximate rectangular cross-section of equivalent area. Billets are classified as semi-finished products for re-rolling or forging.

**BINARY ALLOY** — An alloy containing two elements, apart from minor impurities.

**BLACK ANNEALING** — A process of box annealing of sheets prior to tinning whereby a black color is imparted to the surface of the product.

**BLUE ANNEALING** — A process of annealing sheets after rolling. The sheets, if fairly heavy, are allowed to cool slowly after the hot rolling; if of lighter gage, as is usually the case, they are passed singly through an open furnace for heating to the proper annealing temperature. The sheets have a bluish-black appearance.

**BLUE BRITTLINESS** — Brittleness occurring in steel when in the temperature range of 149 °C to 371 °C (300-700 °F), or when cold after being worked within this temperature range.

**BOX ANNEALING** — Softening steel by heating it, usually at a sub-critical temperature, in a suitable closed metal box or pot to protect it from oxidation, employing a slow heating and cooling cycle; also called closed annealing or pot annealing.

**BRIGHT ANNEALING** — A process of annealing, usually with reducing gases, such that surface oxidation is reduced to a minimum, thereby yielding a relatively bright surface.

**BRITTLINESS** — Brittleness is the property of a material which permits little bending or deformation without fracture. Brittleness and hardness are closely associated.

**BURNING** — The heating of a metal to temperatures sufficiently close to the melting point to cause permanent injury. Such injury may be caused by the melting of the more fusible constituents, by the penetration of gases such as oxygen into the metal with consequent reactions, or perhaps by the segregation of elements already present in the metal.

**BUTT-WELD** — The welding of two abutting edges.

**C**

**CARBON FREE** — Metals and alloys which are practically free from carbon.

**CARBURIZING (CEMENTATION)** — Adding carbon to the surface of iron-base alloys by heating the metal below its melting point in contact with carbonaceous solids, liquids, or gases.



**CASE** — The surface layer of an iron-base alloy which has been made substantially harder than the interior by the process of case hardening.

**CASE HARDENING** — A heat treatment of a combination of heat treatments in which the surface layer of an iron-base alloy is made substantially harder than the interior by altering its composition by carburizing, cyaniding, or nitriding.

**CHAPMANIZING** — A process for hardening steel by bubbling ammonia through a cyaniding salt bath and holding the finished part in the gas stream. This method produces a case almost as hard as nitriding at a time factor of slightly longer than required for cyaniding.

**CHARPY IMPACT** — An impact test made by measuring in a Charpy machine the energy required to fracture a standard notched specimen in bending. The values so obtained are merely comparative between different materials tested by the same method.

**COLD DRAWING** — The permanent deformation of metal below its recrystallization temperature, by drawing the bar through one or more dies.

**COLD ROLLING** — The permanent deformation of metal below its recrystallization temperature by rolling. This process is frequently applied in finishing rounds, sheets, strip, and tin plate.

**COLD TREATING** — Cooling to sub-zero temperature for various purposes, but primarily to promote transformation of austenite.

**COLD WORKING** — Plastic deformation of a metal at a temperature low enough to ensure strain hardening.

**CORE** — The interior portion of an iron-base alloy which is substantially softer than the surface layer as the result of case hardening. Also, that portion of a forging removed by trepanning; the inner part of a rolled section of rimmed steel as distinct from the rimmed portion or rim; a body of sand or other material placed in a mold to produce a cavity in a casting.

**CONVERSION COATING (CHEMICAL)** — A film intentionally produced on a metal by subjection to a selected chemical solution for the purpose of providing improved corrosion resistance or to improve the adhesion of subsequently applied organic coating.

**CYANIDING** — Surface hardening by carbon and nitrogen absorption of an iron-base alloy article or portion of it by heating at a suitable temperature in contact with a cyanide salt, followed by quenching.

**COOLING** — Any decrease in temperature; however, specific term usually applies to reducing metal temperature in a gaseous environment rather than quenching in a liquid.

## D

**DECALESCENCE** — When a piece of steel is heated, the temperature rises uniformly until it reaches a point between 718 °C and 732 °C (1,325 °F and 1,350 °F). At this point the rise in temperature suddenly halts due to the fact that the metal absorbs the heat necessary for the change of state. After this halt the temperature will continue its normal rate of increase. It is the halting in the temperature range that is termed decalescence. At the point of decalescence, the carbon and iron are forming a solid solution and the steel is passing from its annealed condition into its hardened condition.

**DECARBURIZATION** — The removal of carbon (usually refers to the surface of solid steel) by the (normally oxidizing) action of media which reacts with carbon. The decarburized area is sometimes referred to as the bark.

**DEFECTS IN METALS** — Damage occurring to metal during manufacture/fabrication process. Some typical defects are as follows: (a) Blister - a defect in metal produced by gas bubbles either on the surface or formed beneath the surface. Very fine



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

blisters are called pinhead or pepper blisters. (b) Blow hole - a hole produced during the solidification of metal by evolved gas which in falling to escape, is held in pockets. (c) Bursts - ruptures made in forging or rolling. (d) Fin (Flash) - a thin fin of metal formed at the side of a forging or weld where a small portion of the metal is forced out between the edges of the forging or welding case. (e) Flake -Internal fissures (cracks or clefts) in large steel forgings or large (MASS) rolled shapes. In a factured surface or test piece, they appear as sizable areas of silvery brightness and coarser grain size than their surroundings. Sometimes known as "chrome checks" and "hairline cracks." (f) Ghost - (Ferrite ghost) a faint band of ferrite. (g) Lap - a surface defect appearing as a seam caused from folding over hot metal, fins, or sharp corners and then rolling or forging, but not welding, them into the surface. (h) Pipe - a cavity formed in metal (especially ingots) during solidification of the last portion of liquid metal causes the cavity or pipe. (i) Scab - a rough projection on a casting caused by the mold breaking or being washed by the molten metal; or occurring where the skin from a blowhole has partly burned away and is not welded. (j) Seam - a crack on the surface of metal which has been closed but not welded; usually produced by blowholes which have become oxidized. If very fine, a seam may be called a hair crack or hair seam. (k) Segregation a mixture of compounds and elements, which, when cooled from the molten state, solidify at different temperatures. (l) Ductility the ability of a metal to withstand plastic deformation without rupture. Ductility is usually determined by tension test using a standard test (2" gauge length) specimen. The test specimen is loaded in tension to rupture. The specimen is then assembled and measured for length and diameter at the fracture. The increase in length is expressed as per cent elongation and the decrease in diameter as per cent reduction of area. The above terms measure ductility and since they are comparative, considerable experience is required for proper evaluation of material for the purpose intended.

**DUCTILITY** — The property that permits permanent deformation before fracture by stress in tension.

**E**

**ELASTIC LIMIT** — The elastic limit of a material is the greatest load per unit area which will not produce a measurable permanent deformation after complete release of load.

**ELECTRICAL CONDUCTIVITY** — A material property of a metal that indicates its ability to conduct electricity; the inverse of resistivity. It is used to verify proper heat treatment in non-ferrous alloys. Commonly measured as a Percentage of the International Annealed Copper Standard.

**ELONGATION** — The amount of permanent extension at any stage in any process which continuously elongates a body.

**EMBRITTLEMENT** — Loss of ductility of a metal, which may result in premature failure. (See acid brittleness).

**ENDURANCE LIMIT** — The highest unit stress at which a material can be subjected to a very large number of repetitions of loading and still show no evidence of failure. Above this limit failure occurs by the generation and growth of cracks until fracture results in the remaining section.

**ENDURANCE RATIO** — The ratio of the endurance limit for cycles of reversed flexural stress to the tensile strength.

**EQUALIZING** — Intermediate heat treatment (special) which assists in developing desired properties, primary use is for equalizing/relieving stresses resulting from cold working.

**EUTECTIC ALLOY** — An alloy which has a lower melting point than neighboring compositions. More than one eutectic composition may occur in a given alloy system.

**EXFOLIATION** — The cracking or flaking off of the outer layer of an object.

**EXPOSURE** — Heating to or subjecting to an elevating temperature or environment for a certain period of time.

**ETCHING** — Attack of metals structure by reagents. In metallography, the process of revealing structural details by the preferential attack of reagents on a metal surface. (a) Micro-etching is for the examination of the sample under a microscope and for this purpose the sample must be very carefully polished (by an experienced person) prior to etching. (b) Macro-etching is



for the examination of the sample under a low power magnifying glass or by unaided eye. High polishing for this purpose is not absolutely essential; however, a good polish is necessary. (c) Deep-etching is a form of macro-etching in which the sample with regular cut surface may be immersed in hot hydrochloric acid (50 percent aqueous solution) and then examined for major defects such as inclusions, segregations, cracks; etc.

## F

**FATIGUE** — The phenomenon of the progressive fracture of a metal by means of a crack which spreads under repeated cycles of stress.

**FATIGUE LIMIT** — Usually used as synonymous with endurance limit.

**FERRITE** — A solution in which alpha iron is the solvent, and which is characterized by a body centered cubic crystal structure.

**FILLET** — A concave junction of two surfaces usually perpendicular.

**FLAME HARDENING** — A process of hardening a ferrous alloy by heating it above the transformation range by means of a high-temperature flame and then cooling as required.

**FORGING STRAINS** — Elastic strains resulting from forging or from cooling from the temperature.

**FORMING** — To shape or fashion with hand/tools or by a shape or mold.

**FRACTURE TESTING** — A test used to determine type of structure, carbon content and the presence of internal defects. The test specimen is broken by any method that will produce a clean sharp fracture. The fracture is then examined by eye or with the aid of a low power magnifying glass. A trained/experienced observer will determine grain size; approximate depth of carburized or decarburized surface area; the presence of inclusions of dirty steel; and defects such as seams, cracks, pipes bursts and flakes.

**FULLY HARDENED** — Applies generally to the maximum hardness obtainable. (In particular, applies to materials that are hardened by a strain and/or age hardening process).

**FUSIBLE ALLOYS** — A group of nonferrous alloys which melt at relatively low temperatures. They usually consist of bismuth, lead, tin, etc., in various proportions, and iron only as an impurity.

## G

**GALVANIC SERIES** — A list of metals and alloys arranged in order of their relative potentials in a given environment. The galvanic series indicates the tendency of the several metals and alloys to set up galvanic corrosion. The relative position within a group sometimes changes with external conditions, but it is only rarely that changes occur from group to group.

**GRAINS** — Individual crystals in metal. When metal is in molten state, the atoms have no uniform grouping. However, upon solidification they arrange themselves in a geometric pattern.

**GRAIN GROWTH** — An increase in the grain size of metal.

## H

**HARDENABILITY** — The ability of an alloy to harden fully throughout the entire section thickness either by cold working or heat treatment. The maximum thickness at which this may be accomplished can be used as a measure of hardenability.



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

**HARDENING** — Hardening accomplished by heating the metal to a specified temperature, then rapidly cooling by quenching in oil, water, or brine. This treatment produces a fine grain structure, extreme hardness, maximum tensile strength, and minimum ductility.

**HARDNESS** — Hardness refers to the ability of a material to resist abrasion, penetration, indentation, or cutting action. The wearing qualities of a material are in part dependent upon its hardness. Hardness and strength are properties which are closely related for wrought alloys.

**HARDNESS TESTING** — Test used to determine the ability of a metal to resist penetration. The test results are usually directly related to tensile and yield strength of the metal involved. An exception would be case hardness. See Chapter 8 for typical testing methods.

**HEAT TINTING** — Heating a specimen with a suitable surface in air for the purpose of developing the structure by oxidizing or otherwise affecting the different constituents.

**HEAT TREATMENT** — An operation, or combination of operations, involving the heating and cooling of a metal or alloy in the solid state for the purpose of obtaining certain desirable conditions or properties. Heating and cooling for the sole purpose of mechanical working are excluded from the meaning of this definition.

**HOMOGENIZING** — Annealing or soaking at very high temperatures in order to reduce alloy segregation by diffusion.

**HOT SHORTNESS** — Brittleness in metal when hot. In iron when sulphur is in excess of the manganese necessary to combine with it to form manganese sulfide the excess sulphur combines with the iron to form iron sulfide. This constituent has a lower melting point than the iron and the result can be that steel may crack during hot working.

**HYDROGEN EMBRITTLEMENT** — See Acid Brittleness.

**I**

**IMPACT TEST** — A test in which one or more blows are suddenly applied to a specimen. The results are usually expressed in terms of energy absorbed or number of blows (of a given intensity) required to break the specimen. See Charpy Impact and Izod Impact

**INCLUSION** — Particles of impurities, usually oxides, sulfides, silicates, and such which are mechanically held during solidification or which are formed by subsequent reaction of the solid metal.

**INDUCTION HARDENING** — A process of hardening a ferrous alloy by heating above the transformation range by means of electrical induction and then cooling as required.

**INTERNATIONAL ANNEALED COPPER STANDARD (IACS)** — An established standard for the electrical conductivity of commercially pure annealed copper. At 68 °F (20 °C), commercially pure, annealed copper has an electrical conductivity of  $0.58 \times 10^7$  S/m (Siemens/meter). This is considered 100 Percentage of the International Annealed Copper Standard.

**M**

**MACHINABILITY** — The cutting characteristic of metal and resulting surface finish using standard cutting tools and coolant/lubricants. There are various factors that effect the machinability of a metal such as hardness, grain size, alloy constituents, structure, inclusions; shape, type, condition of tool and coolant. The standard machinability ratings are usually based on comparison to SAE 1112/Aisi B 1112 Bessemer screw stock which is rated at 100 percent machinability.

**MAGNA FLUX TESTING** — A method of inspection used to detect/locate defects such as cavities, cracks or seams in steel parts at or very close to the surface. The test is accomplished by magnetizing the part with equipment specially designed for



the purpose and applying magnetic powder, wet or dry. Flaws are then indicated by the powder clinging to them (see Chapter 8 for additional data).

**MALLEABILITY** — Malleability is the property of a material which enables it to be hammered, rolled, or to be pressed into various shapes without fracture. Malleability refers to compression deformation as contrasted with ductility where the deformation is tensile.

**MARTEMPERING** — This is a method of hardening steel by quenching from the austenitizing temperature into a medium at a temperature in the upper part of or slightly above the martensite range and holding it in the medium until temperature is substantially uniform throughout the alloy is then allowed to cool in air through the martensite range.

**MARTENSITE** — It is the decomposition product which results from very rapid cooling of austenite. The lower the carbon content of the steel, the faster it must be cooled to obtain martensite.

**MECHANICAL HARDNESS** — See Hardness.

**MECHANICAL PROPERTIES** — Those properties that reveal the reaction, elastic and inelastic, of a material to an applied force, or that involve the relationship between stress and strain; for example, tensile strength, yield strength, and fatigue limit.

**MECHANICAL TESTING** — Testing methods by which mechanical properties are determined.

**MECHANICAL WORKING** — Subjecting metal to pressure exerted by rolls, presses, or hammers, to change its form, or to affect the structure and therefore the mechanical and physical properties.

**MODULUS OF ELASTICITY** — The ratio, within the limit of elasticity, of the stress in the corresponding strain. The stress in pounds per square inch is divided by the elongation in fractions of an inch for each inch of the original gage length of the specimen.

## N

**NITRIDING** — Adding nitrogen to iron-base alloys by heating the metal in contact with ammonia gas or other suitable nitrogenous material. Nitriding is conducted at a temperature usually in the range 502-538 °C (935-1000 °F) and produces surface hardening of the metal without quenching.

**NORMALIZING** — Heating iron-base alloys to approximately 55 °C (100 °F) above the critical temperature range, followed by cooling to below that range in still air at ordinary temperatures. This process is used to remove stresses caused by machining, forging, bending, and welding.

## O

**OVERHEATING** — Heating to such high temperatures that the grains have become coarse, thus impairing the properties of the metal.

## P

**PATENTING** — Heating iron-base alloys above the critical temperature range followed by cooling below that range in air, or in molten lead, or a molten mixture of nitrate or nitrites maintained at a temperature usually between 427-566 °C (800-1050 °F), depending on the carbon content of the steel and the properties required of the finished product. This treatment is applied to wire and to medium or high carbon steel as a treatment to precede further wire drawing.

**PHYSICAL PROPERTIES** — Those properties exclusive of those described under mechanical properties; for example,



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

density, electrical conductivity, coefficient of thermal expansion. This term has often been used to describe mechanical properties, but this usage is not recommended.

**PHYSICAL TESTING** — Testing methods by which physical properties are determined. This term is also unadvisedly used to mean the determination of the mechanical properties.

**PICKLING** — Removing scale from steel by immersion in a diluted acid bath.

**PLASTIC DEFORMATION** — The permanent change in size or shape of a material under stress.

**POTENTIOMETER** — Potentiometer is an instrument used to measure thermocouple voltage by balancing a known battery voltage against it.

**PROCESS ANNEALING** — Heating iron-base alloys to a temperature below or close to the lower limit of the critical temperature range, followed by cooling desired. This treatment is commonly applied to sheet and wire and the temperatures generally used are from 549-649 °C (1020-1200 °F)

**PROOF STRESS** — The proof stress of a material is that load per unit area which a material is capable of withstanding without resulting in a permanent deformation of more than a specified amount per unit of gage length after complete release of load.

**PROPORTIONAL LIMIT** — The proportional limit of a material is the load per unit area beyond which the increases in strain cease to be directly proportional to the increases in stress.

**PYROMETER** — An instrument for measuring temperature.

**Q**

**QUENCHING** — Rapid cooling by immersion in liquids or gases.

**QUENCHING MEDIA** — Quenching media are liquids or gases in which metals are cooled by immersion. Some of the more common are brine (10 percent sodium chloride solution), water 18 °C (65 °F), fish oil, paraffin base petroleum oil, machine oil, air, engine oil, and commercial quenching oil.

**R**

**RECALESCENCE** — When steel is slowly cooled from a point above the critical temperature, the cooling proceeds at a uniform rate until the piece reaches a point between 677 °C and 704 °C (1,250 °F and 1,300 °F). At this time, the cooling is noticeably arrested and the metal actually rises in temperature as the change of state again takes place. This change is the opposite of decalescence and is termed recalescence.

**REDUCTION OF AREA** — The difference between the original cross-sectional area and that of the smallest area at the point of rupture. It is usually stated as a percentage of the original area; also called “contraction of area.”

**REFINING TEMPERATURE OR HEAT** — A temperature employed in case hardening to refine the case and core. The first quench is from a high temperature to refine the core and the second quench is from a lower temperature to further refine and harden the case.



## S

**SCALE** — A coating of metallic oxide that forms on heated metal.

**SENSITIZING** — Developing a condition in stainless steels, which is susceptible to intergranular corrosion. The condition is usually formed by heating the steel above 800 °F and cooling slowly, e.g., welding.

**SHEETS COLD ROLLED** — The flat products resulting from cold rolling of sheets previously produced by hot rolling.

**SHEETS HOT ROLLED** — The flat-rolled products resulting from reducing sheet bars on a sheet mill, or slabs, blooms, and billets on a continuous strip-sheet mill.

**SOAKING** — Holding steel at an elevated temperature for the attainment of uniform temperature throughout the piece.

**SOLIDIFICATION RANGE** — The temperature range through which metal freezes or solidifies.

**SPALLING** — The cracking and flaking of small particles of metal from the surface.

**SPHEROIDAL OR SPHEROIDIZED CEMENTITE** — The globular condition of iron carbide resulting from a spheroidizing treatment. The initial structure may be either pearlitic or martensitic.

**SPHEROIDIZING** — Any process of heating and cooling steel that produces a rounded or globular form of carbide. The spheroidizing methods generally used are: (a) Prolonged heating at a temperature just below the lower critical temperature, usually followed by relatively slow cooling. (b) In the case of small objects of high carbon steels, the spheroidizing result is achieved more rapidly by prolonged heating to temperatures alternately within and slightly below the critical temperature range. (c) Tool steel is generally spheroidized by heating to a temperature of 749-804 °C (1380-1480 °F) for carbon steels and higher for many alloy tool steels, holding at heat from 1 to 4 hours, and cooling slowly in the furnace.

**STRAIN** — The elongation per unit length.

**STRESS** — The internal load per unit area.

**STRESS-RELIEF** — This is annealing process which removes or reduces residual stresses retained after forming, heat treating, welding or machining. The anneal is accomplished at rather low temperatures for the primary purposes of reducing residual stresses, without material affecting other properties.

## T

**TEMPERING (ALSO TERMED DRAWING)** — Reheating hardened steel to some temperature below the lower critical temperature, followed by any desired rate of cooling. Although the terms “tempering” and “drawing” are practically synonymous as used in commercial practice, the term “tempering” is preferred.

**TENSILE STRENGTH** — The tensile strength is the maximum load per unit area which a material is capable of withstanding before failure. It is computed from the maximum load carried during a tension test and the original cross-sectional area of the specimen.

**TENSION** — That force tending to increase the dimension of a body in the direction of the force.

**THERMOCOUPLE** — Thermocouple consists of a pair of wires of dissimilar metals connected at both ends. When the two junctions are subjected to different temperatures an electric potential is set up between them. This voltage is almost in direct



**TO 1-1A-9**  
**NAVAIR 01-1A-9**

proportion to the temperature difference, and hence, a voltage measuring instrument inserted in the circuit will measure temperature. The voltage measuring instrument is usually calibrated in °C or °F.

**TOLERANCES** — Slight deviations in dimensions or weight or both, allowable in the various products.

**V**

**VISCOSITY** — Viscosity is the resistance offered by a fluid to relative motion of its parts.

**W**

**WIRE** — The product obtained by drawing rods through a series of dies.

**WORK HARDNESS** — Hardness developed in metal resulting from mechanical working, particularly cold working.

**Y**

**YIELD POINT** — The load per unit of original cross section at which a marked increase in deformation occurs without increase in load.

**YIELD STRENGTH** — Stress arbitrarily defined as the stress at which the material has a specified permanent set (the value of 0.2 percent is widely accepted).

**YOUNG'S MODULUS** — See Modulus of Elasticity.