### **TECHNICAL MANUAL**

## APPLICATION AND REMOVAL OF ORGANIC COATINGS, AEROSPACE AND NON-AEROSPACE EQUIPMENT

This manual supersedes TO 1-1-8 dated 15 December 2020.

DISTRIBUTION STATEMENT A - Approved for public release; distribution is unlimited. PA Case Number 05-0758. Other requests for this document shall be referred to 406 SCMS/GUEE, Robins AFB, GA 31098. Questions concerning technical content shall be referred to AFLCMC/EZPT-CPCO.

Published Under Authority of the Secretary of the Air Force

	ECTIVE PAG	NOTE	The portion of the text affected by margins of the page. Changes to i areas, or by miniature pointing har	illustrations are indicated by sh	
Original	issue for original and o	8 June 202		OF THE FOLLOWING:	
Page No.	*Change No.	Page No.	*Change No.	Page No.	*Chan No
Title       A         i       xvii         i       xviii         xix       xxviii         1-1       1-3         1-4       Blank         2-1       2-31         2-32       Blank         3-1       3-21         3-22       Blank         4-1       4-23         4-24       Blank         5-1       5-21         5-22       Blank         6-1       6-36         7-1       7-8         8-1       8-9         8-10       Blank         Blank       Blank         C-1       C-3         C-4       Blank         C-1       C-3         C-4       Blank         Blank       Glossary 1	$\begin{array}{cccccccccccccccccccccccccccccccccccc$				

### TABLE OF CONTENTS

Ch	apter		Page
LIS	ST OF ILLUSTR	ATIONS	. xi
LIS	ST OF TABLES		. xii
IN	FRODUCTION		xiii
SA	FETY SUMMA	RY	xix
1	INTRODUCTI	ON AND GENERAL DISCUSSION OF COATING MATERIALS AND TERMS	1-1
1	intitobeen		1 1
	1.1	INTRODUCTION	1-1
	1.2	GENERAL DISCUSSION OF ORGANIC COATINGS	1-1
	1.2.1	Coatings Systems for Metal Surfaces	1-1
	1.2.2	Aircraft Protective Finish Systems	1-1
	1.3	ORGANIC COATING	1-2
	1.4	CONSUMABLE MATERIALS	1-2
2	ORGANIC FIN	JISH SYSTEM REMOVAL	2-1
	2.1	INTRODUCTION	2-1
	2.1	GENERAL	2-1
	2.2	PREPARATION FOR PAINT REMOVAL	2-1
	2.3		2-2
		Application	
	2.3.2	Equipment and Materials Recommended	2-4
	2.3.3	Procedures	2-5
	2.4	ORGANIC FINISH SYSTEM REMOVAL	2-6
	2.5	CHEMICAL REMOVAL OF ORGANIC FINISH SYSTEMS FROM METAL	•
	•	SUBSTRATES	2-6
	2.6	CHEMICAL REMOVERS	2-6
	2.6.1	Remover for Epoxy and Polyurethane Primers and Epoxy and Polyurethane Top-Coats Over	
		Epoxy or Polyurethane Primers	2-7
	2.6.2	Remover for Polysulfide Primer with a Polyurethane Topcoat	2-7
	2.6.3	Removers for Environmental Compliance	2-7
	2.6.4	Chemical Depaint Materials Authorized for Air Force Use	2-8
	2.7	GENERAL OVERALL CHEMICAL REMOVAL PROCEDURES	2-8
	2.8	CHEMICAL REMOVAL PROCEDURES FOR CONFINED LOCATIONS	2-12
	2.9	CHEMICAL DIP TANK MATERIALS AND PROCEDURES	2-12
	2.9.1	MIL-PRF-83936, Heated Tank Type for Aircraft Wheels, Landing Gear Components, and	
		Other Aircraft and Support Equipment	2-13
	2.9.2	Chemical Dip Tank Procedures	2-13
	2.10	MECHANICAL REMOVAL OF ORGANIC FINISH SYSTEMS	2-14
	2.11	MECHANICAL REMOVAL METHODS OTHER THAN PLASTIC MEDIA OR ME- DIUM PRESSURE WATER BLASTING FOR METAL SUBSTRATES	2-15
	2.11.1		2-15
	2.11.1	Abrasive Blasting	
			2-15
	2.11.3	Hand Held Abrasive Removal	2-16
	2.11.4	Motor Driven Abrasive Removal	2-16
	2.11.5	Stainless Steel Corrosion Resistant Steel (CRES) and Nickel Based Alloys	2-16
	2.11.6	Cold Spray Repairs	2-16
	2.11.7	Dust Removal	2-17
	2.12	ENGINEERED MEDIA BLASTING REMOVAL METHOD	2-21
	2.12.1	Media Type	2-21
	2.12.1.1	Type II	2-22

ii

### **TABLE OF CONTENTS - CONTINUED**

Ch	apter		Page
	2.12.1.2	Type III	2-22
	2.12.1.3	Type V	2-22
	2.12.1.4	Type VII	2-22
	2.12.1.5	Type VIII	2-22
	2.12.2	Media Authorized for Air Force Use	2-22
	2.12.3	Operational Parameters for Metallic Surfaces	2-22
	2.12.4	Usage Restrictions	2-23
	2.12.4.1	Type II	2-23
	2.12.4.2	Type III	2-23
	2.12.4.3	Type V	2-23
	2.12.5	Operational Parameters for Non-Metallic (Composite) Surfaces	2-23
	2.12.6	Operation Safety Requirements	2-24
	2.12.6.1	Walk-In Blast Booth	2-24
	2.12.6.2	EMB Blasting Cabinets	2-25
	2.12.7	Personnel Qualifications	2-25
	2.12.8	Pre-blast Preparation	2-25
	2.12.9	Post-blast Cleaning	2-25
	2.12.10	Specific Technical Data and Work Directives	2-25
	2.12.11	Disposal of Engineered Media Used in Paint Removal Operations	2-25
	2.12.12	Contamination Testing of Engineered Media	2-26
	2.12.12.1	Equipment and Materials Recommended	2-26
	2.12.12.2	Sampling Procedure	2-27
	2.12.12.2.1	Used Media	2-27
	2.12.12.3	Contamination Test Procedure	2-27
	2.13	MEDIUM PRESSURE WATER (MPW) REMOVAL METHOD	2-28
	2.13.1	Preparation	2-28
	2.13.2	Paint Removal Operations	2-29
	2.13.3	Post-Paint Removal Cleaning	2-29
	2.13.4	Operational Safety Requirements	2-30
	2.13.5	Personnel Qualification	2-30
	2.13.5.1	Equipment Manufacturer's Training	2-30
	2.13.5.2	Air Force Supplied Local Training	2-30
	2.14	REMOVAL OF THERMOPLASTIC POWDER COATING	2-30
	2.14.1	Removal Procedures	2-30
	2.15	PAINT REMOVAL ON NON-METALLICS	2-31
	2.15.1	Removal Requirements	2-31
	2.15.2	Mechanical Paint Removal on Fiber Glass, Arranged Fiber (Kevlar®)/Epoxy, and Graphite or Boron Fiber/Epoxy Composite Surfaces	2-31
2			2 1
3	SURFACE PRE	PARATION AND CHEMICAL PREPAINT SURFACE TREATMENT	3-1
	3.1	SURFACE PREPARATION FOR PAINTING AND CHEMICAL PREPAINT SURFACE	2.1
	0.1.1	TREATMENT	3-1
	3.1.1	Surface Preparation for Painting	3-1
	3.1.2	Surface Preparation for Repair or Over Coating of Damaged Organic Coating	3-1
	3.1.3	Scuff Sanding for Overspraying Existing Coating Systems on Aircraft	3-2
	3.1.4	Solvent Wiping for Surface Preparation	3-3
	3.1.4.1	Solvent-Wipe, Aircraft Prepaint for Environmental Compliance	3-5
	3.1.5	Surface Preparation for SAE AMS-C-27725 Integral Fuel Cell Coating	3-5
	3.1.6	Reactivation of Newly Applied Primer or Tie Coat	3-7
	3.1.7	Surface Preparation, Unpainted Surfaces	3-7
	3.1.8	Corrosion Removal, Chemical and Mechanical.	3-8
	3.1.9	Preparation for Prepaint Treatment, Unpainted Surfaces	3-8
	3.1.10	Water Break Inspection	3-8
	3.1.11	Evidence of Inadequate Cleaning	3-8

	3.1.12	Corrosion Removal Prepaint Compound, Aluminum	3-8
	3.1.12	Prepaint Chemical Corrosion Removal Materials	3-9
	3.1.14		3-9
		Application of SAE AMS-1640 Solution/Not LOX Compatible	
	3.1.15	Surface Treatment Materials for Aluminum	3-9
	3.1.16	Touch-Up of Damaged Aluminum Surface Treatment MIL-DTL-5541	3-10
	3.1.17	"No-Rinse Process" for Surface Treatment of Aluminum	3-11
	3.1.18	Mixing MIL-DTL-81706 Solution	3-12
	3.1.19	Application of MIL-DTL-81706 Solutions	3-14
	3.1.20	Alternate Surface Preparations for Aluminum Surfaces (PreKote SP)	3-15
	3.1.20.1	Surface Preparation	3-16
	3.1.21	Application of PreKote SP	3-16
	3.1.22	Use of PreKote SP on Exterior Surfaces Where Paint and Primer Have Been Removed dur-	0 10
	5.1.22	ing Scuff Sand, Touch-up, or Repair	3-17
	3.1.23	Corrosion Removal Solution for Magnesium	3-18
	3.1.24	Surface Treatment Process for Magnesium	3-19
		Surface Treatment Flocess for Magnesium	
	3.1.25	Surface Preparation for Steel	3-20
	3.1.26	Masking	3-20
	3.1.27	Tack Ragging	3-21
4	PAINTING API	PLICATION METHODS	4-1
	4.1	GENERAL	4-1
	4.2	SPRAY METHODS	4-1
	4.2.1	HVLP Spray	4-1
	4.2.1.1	HVLP Touch-Up Spray Gun	4-1
	4.2.2	Hot Spray	4-1
	4.2.3	Airless Spray	4-1
	4.2.4	Air-Assisted Airless Spray	4-2
	4.2.5	Electrostatic Spray	4-2
	4.3	SPRAY PAINTING EQUIPMENT, GENERAL	4-2
	4.3.1	HVLP Spraying Systems	4-2
	4.3.2	Spray Gun, General	4-3
	4.3.3	Classes of Spray Guns	4-3
	4.3.4	Material Containers	4-3
	4.3.5	Air Compressors	4-4
	4.3.6	Air Regulators or Transformers	4-4
	4.3.7	Air Condensers	4-4
	4.3.8	Air Supply	4-7
	4.3.9	Hose	4-7
	4.4	SPRAY PAINTING	4-8
	4.4.1	Gun Techniques	4-8
	4.4.1.1	Distance	4-8
	4.4.1.2	Stroking	4-8
	4.4.1.3	Triggering	4-8
	4.4.2	Gun Adjustments	4-10
	4.4.3	Painting Difficulties and Remedies	4-11
	4.5	CLEANING AND MAINTENANCE	4-21
	4.6	MECHANICAL PAINT GUN WASHER	4-21
	- <b>T</b> .U		-23
5	PAINTING OP	ERATIONS FOR AIRCRAFT AND EQUIPMENT	5-1
	5.1	GENERAL	5-1
	5.2	SAFETY AND HEALTH ASPECTS OF PAINTING	5-1
	5.2.1	Respiratory Protection	5-2

	5.3	SPRAY BOOTHS AND PAINTING AREAS, GENERAL	5-2
	5.4	PAINT BOOTH TYPES	5-3
	5.4.1	Dry-Type Booth	5-3
	5.4.2	Air-Water Wash Type Booth	5-3
	5.4.3	Cleaning and Maintenance	5-3
	5.4.4	Part and Equipment Painting Operations	5-3
	5.5	AIRCRAFT PAINTING OPERATIONS	5-3
	5.5.1	Depot Level Aircraft Painting Operations	5-3
	5.5.2	Field Level Aircraft Painting Operations	5-5
	5.5.3	Electrostatic Aircraft Painting	5-5
	5.5.4	Atmospheric Conditions for Painting	5-6
	5.5.5	Test Panels	5-7
	5.5.6	Material Requirements, General	5-7
	5.6	THE AIRCRAFT PAINTING PROCESS SEQUENCE OF EVENTS	5-7
	5.6.1	Aircraft Paint Application Sequence	5-8
	5.6.1.1	Small Aircraft-Tail Toward Hanger/Insert Exhaust	5-8
	5.6.1.1.1	Priming	5-8
	5.6.1.1.2	Topcoating	5-9
	5.6.1.2	Large Aircraft-Nose Toward Hanger Exhaust	5-9
	5.6.1.2.1	Priming	5-9 5-9
	5.6.1.2.2		5-9 5-9
	5.6.1.3	Topcoating	5-9 5-9
		Walkway Coatings	5-9 5-9
	5.6.2	Overspraying Existing Coating Systems on Aircraft and Aerospace Equipment	
	5.6.3	Curing of Finishes	5-10
	5.6.4	Coating Thickness Measurements	5-10
	5.6.5	Allowable Coating Thickness	5-11
	5.6.6	Inspection Control	5-11
	5.6.6.3	Frequency of Inspection	5-13
	5.6.7	Soil Barrier Coating	5-13
	5.7	INTERIOR FINISHING PROCEDURES AND OPERATIONS	5-13
	5.7.1	Preparation for Coating	5-13
	5.7.2	Coating Application	5-13
	5.7.3	Refinishing of Fiber Glass Components	5-14
	5.8	MAINTENANCE PAINTING	5-14
	5.8.1	Epoxy or Polyurethane Primer/Polyurethane Topcoat	5-14
	5.8.2	Primer and Polyurethane Touch-Up	5-15
	5.8.2.1	Brush or Spray	5-15
	5.8.2.2	Touch-Up Pen	5-15
	5.8.3	Aerosol Touch-Up	5-17
	5.8.4	Brush/Roller Touch-Up	5-19
	5.8.5	Brush Application	5-19
	5.8.6	Roller Application	5-19
	5.8.7	Temporary Protection	5-20
	5.8.8	Powder Coating	5-21
	5.8.8.1	Surface Preparation	5-21
	5.8.8.2	Maintenance Painting	5-21
6	UNITED STAT	ES AIR FORCE (USAF) STANDARD COATING SYSTEMS FOR AIRCRAFT AND	
	EQUIPMEN	Τ	6-1
	-		
	6.1	CLASSIFICATION OF ORGANIC COATINGS	6-1
	6.2	CONSTITUENTS OF ORGANIC COATINGS	6-1
	6.3	PIGMENTS	6-1
	6.4	VEHICLE	6-1
	6.5	PREPARATION OF COATING MATERIALS FOR USE, GENERAL	6-2

pter		Page
6.6	MIXING AND THINNING OF COATING MATERIALS, GENERAL	6-2
6.6.1	Method of Mixing	6-3
6.6.2	Mixing Test	6-3
6.7	SOLVENTS, DILUENTS, AND THINNERS	6-3
6.7.1	Volatility	6-3
6.7.2	Thinners	6-4
6.7.3	Viscosity	6-4
6.7.3.1	No. 2 Zahn Cup	6-4
6.7.3.2	No. 4 Ford Cup	6-5
6.7.3.3	Adjustments	6-5
6.8	BLUSHING	6-5
6.9	RESINS	6-5
6.9.1	Alkyds	6-6
6.9.2	Acrylics	6-6
6.9.3	Vinyls	6-6
6.9.4	Phenolics	6-6
6.9.5	Silicones	6-6
6.9.6	Epoxies	6-6
6.9.7	Polyurethane	6-6
6.10	ADHESION	6-6
6.11	PRIMERS	6-6
6.12	COATINGS AND COATING SYSTEMS	6-6
6.12.1	USAF Standard Polyurethane Aircraft Coating System	6-6
6.12.2	Primer Coating, Epoxy, For Aircraft Application, MIL-PRF-23377	6-7
6.12.2.1	Characteristics	6-7
6.12.2.2	Uses	6-7
6.12.2.3	Mixing	6-7
6.12.2.4	Thinning	6-8
6.12.2.5	Application	6-8
6.12.2.6	Drying Time	6-8
6.12.3	Primer Coating, Epoxy, VOC Complaint, Chemical and Solvent Resistant, MIL-PRF-85582	6-9
6.12.3.1	Characteristics	6-9
6.12.3.2	Uses	6-9
6.12.3.3	Mixing	6-9
6.12.3.4	Thinning	6-9
6.12.3.5	Application	6-9
6.12.3.6	Drying Time	6-9
6.12.4	Primer Coating, Polyurethane, TT-P-2760	6-10
6.12.4.1	Characteristics	6-10
6.12.4.2	Uses	6-10
6.12.4.3	Mixing	6-10
6.12.4.4	Thinning	6-11
6.12.4.5	Application	6-11
6.12.4.6	Drying Time	6-11
6.12.5	Primer Coating, Elastomeric, Polysulfide Corrosion Inhibiting, PR-1432GV	6-12
6.12.5.1	Characteristics	6-12
6.12.5.2	Uses	6-12
6.12.5.3	Mixing	6-12
6.12.5.4	Thinning	6-13
6.12.5.5	Application	6-13
6.12.5.6	Drying Time	6-13
6.12.6	Tiecoat, Non-Chromated	6-13
6.12.6.1	Characteristics	6-13
6.12.6.2	Uses	6-14

Page

6.12.6.3	Mixing	6-14
6.12.6.4	Thinning	6-14
6.12.6.5	Application	6-14
6.12.6.6	Drying Time	6-15
6.12.7	Coating. Polyurethane, Aircraft and Support Equipment, MIL-PRF-85285	6-15
6.12.7.1	Coating Classifications	6-15
6.12.7.1.1	Туре	6-15
6.12.7.1.2	Class	6-15
6.12.7.2	Uses	6-15
6.12.7.3	Advanced Performance Coating (APC)	6-15
6.12.7.4	Mixing	6-16
6.12.7.5	APC Mixing	6-16
6.12.7.6	Thinning	6-17
6.12.7.7	Application	6-17
6.12.7.7.1	APC (MIL-PRF-85285, Type IV) Application	6-17
6.12.7.7.2	Maintenance Painting	6-17
6.12.8	Curing of Complete Polyurethane System	6-17
6.12.8.1	Maintenance Painting for Low Speed Aircraft	6-18
6.12.8.1.1	Maintenance Painting for High Speed Aircraft	6-18
6.12.9	Coating, Heat Resisting, TT-P-28	6-19
6.12.9.1	Characteristics	6-19
6.12.9.2 6.12.9.3	Uses	6-19 6-19
6.12.9.4	Thinning	6-19 6-19
6.12.9.5		6-19
6.12.10	Drying Time	6-19
6.12.10.1	Characteristics	6-19
6.12.10.2	Uses	6-19
6.12.10.2	Thinning	6-19
6.12.10.4	Application	6-19
6.12.10.5	Drying Time	6-19
6.12.11	Coating, Sprayable, Strippable, Protective, MIL-PRF-6799	6-20
6.12.11.1	Characteristics	6-20
6.12.11.2	Uses	6-20
6.12.11.2.1	Type II, Class 1	6-20
6.12.11.2.2	Type II, Class 5	6-20
6.12.11.2.3	Type II, Class 6	6-20
6.12.11.2.4	Type II, Class 7	6-20
6.12.11.3	Thinning	6-20
6.12.11.4	Application	6-20
6.12.11.5	Drying Time	6-20
6.12.12	Resin Coating, Unpigmented, for Engine Components and Metal Parts, MIL-PRF-3043	6-20
6.12.12.1	Characteristics	6-20
6.12.12.2	Uses	6-20
6.12.12.3	Thinning	6-21
6.12.12.4	Application	6-21
6.12.12.5	Drying Time	6-21
6.12.12.5.1	Baking in Oil	6-21
6.12.12.5.2	Oven Baking	6-21
6.12.13	Coating Kit, Epoxy, for Interior of Steel Fuel Tanks, MIL-PRF-23236	6-21
6.12.13.1	Characteristics	6-21
6.12.13.2	Uses	6-21
6.12.13.3	Mixing	6-21
6.12.13.4	Thinning	6-21
6.12.13.5	Application	6-21

Page

### **TABLE OF CONTENTS - CONTINUED**

6.12.13.6	Drying Time	6-21
6.12.14	Coating, Corrosion Preventive, for Aircraft Integral Fuel Tanks for Use to 250 °F (121 °C),	
	SAE AMS-C-27725	6-22
6.12.14.1	Characteristics	6-22
6.12.14.2	Uses	6-22
6.12.14.3	Mixing	6-23
6.12.14.4	Application	6-24
6.12.14.4.2	Spray Application	6-24
6.12.14.4.3	Brush Coating	6-24
6.12.14.5	Drying Time	6-24
6.12.15	Coating Compound, Nonslip (for Walkways), CID A-A-59166	6-25
6.12.15.1	Characteristics	6-25
6.12.15.2	Uses	6-25
6.12.15.3	Thinning	6-25
6.12.15.4	Mixing and Application	6-25
6.12.15.5	Drying Time	6-25
6.12.16	Coating, Polyurethane, Rain Erosion Resistant for Exterior Aircraft and Missile Parts, SAE	
	AMS-C-83231	6-25
6.12.16.1	Characteristics	6-25
6.12.16.2	Uses	6-26
6.12.16.3	Thinning	6-26
6.12.16.4	Application	6-26
6.12.16.5	Drying Times	6-26
6.12.17	Coating System, Polyurethane, Non-Yellowing White, Rain Erosion Resistant, Thermally	
	Reflective, SAE AMS-C-83445	6-26
6.12.17.1	Characteristics	6-26
6.12.17.2	Uses	6-26
6.12.17.3	Thinning	6-26
6.12.17.4	Application	6-26
6.12.17.5	Drying Times	6-26
6.12.18	Primer Coating, Magnesium-Rich, Non-Chromated	6-26
6.12.18.1	Characteristics	6-26
6.12.18.2	Uses	6-26
6.12.18.3	Mixing	6-27
6.12.18.4	Thinning	6-27
6.12.18.5	Application	6-27
6.12.18.6	Drying Time	6-27
6.12.19	Rare Earth Compound Coating (RECC) System, Non-Chromated	6-27
6.12.19.1	Deoxidizer, Non-Chromated, RECC 1015	6-27
6.12.19.1.1	Characteristics	6-27
6.12.19.1.2	Uses	6-28
6.12.19.1.3	Mixing	6-28
6.12.19.1.4	Application	6-28
6.12.19.2	Conversion Coating, Non-Chromated, RECC 3021	6-28
6.12.19.2.1	Characteristics	6-28
6.12.19.2.2	Uses	6-28
6.12.19.2.3	Mixing	6-28
6.12.19.2.4	Application	6-28
6.12.19.3	Primer Coating, Epoxy Polyamide, Non-Chromated, 02GN093	6-29
6.12.19.3.1	Characteristics	6-29
6.12.19.3.2	Uses	6-29
6.12.19.3.3	Mixing	6-29
6.12.19.3.4	Thinning	6-29
6.12.19.3.5	Application	6-29
6.12.19.3.6	Drying Time	6-30

	$\begin{array}{c} 6.12.20\\ 6.12.20.1\\ 6.12.20.2\\ 6.12.21\\ 6.12.21.1\\ 6.12.21.2\\ 6.12.22.2\\ 6.12.22.1\\ 6.12.22.2\\ 6.12.22.3\\ 6.12.22.3\\ 6.12.22.4\\ 6.12.22.5\\ 6.12.22.5.1\\ 6.12.22.5.2\\ 6.12.22.6\end{array}$	Primer Coating, Anodic Electrodeposition for Aircraft Applications, SAE AMS-3144CharacteristicsUsesCoating Systems, Advanced Performance, For Aerospace Applications, MIL-PRF-32239CharacteristicsUsesLeading Edge Polyurethane Rain Erosion Resistant TapeDescription and UseInstallationApplication of Edge SealerRepair of Damaged AreaTape RemovalRemoval DiscScraping and Solvent RemovalPainting Instructions	$\begin{array}{c} 6-30\\ 6-30\\ 6-30\\ 6-30\\ 6-30\\ 6-30\\ 6-31\\ 6-31\\ 6-31\\ 6-33\\ 6-34\\ 6-34\\ 6-34\\ 6-35\\ 6-35\\ 6-35\\ \end{array}$
7	APPLICATION	AND REMOVAL OF DECALS AND SILK SCREENING	7-1
	7.1 7.1.1 7.1.2 7.2 7.2.1 7.2.2 7.3 7.4 7.5 7.6 7.7 7.7.1 7.8 7.8.1 7.8.2 7.8.3 7.8.4 7.9 7.9.1 7.9.2 7.9.3 7.9.4	DECALS - GENERAL Surface Preparation Application Procedures for Decals and Colored Marking Stripes SMALL DECALS AND MARKING STRIPES Decals Up to 12 x 2 Inches Film for Striping LARGE EMBLEMS AND LETTERS USING HINGE APPLICATION METHOD DECALS APPLIED USING APPLICATION TAPE EDGE SEALING APPLICATION OF PREMASKED DECALS DECAL REMOVAL Mechanical Removal APPLICATION OF MARKINGS WITH SILKSCREEN Materials and Equipment for Silkscreening Surface Preparation Application Topcoat Application APPLICATION OF MARKINGS USING STENCILS Surface Preparation Mounting Stencil Painting of Stencils Adhesion Promoters	7-1 7-2 7-2 7-2 7-2 7-3 7-4 7-5 7-6 7-6 7-6 7-6 7-6 7-7 7-8 7-7
8		VISHES, INSIGNIA, AND MARKINGS APPLICABLE TO UNITED STATES AIR FORCE CRAFT	8-1
	8.1 8.1.1 8.1.2 8.1.3 8.1.4 8.1.5 8.1.6 8.1.6.1 8.1.6.2 8.1.6.3	GENERALPurposeResponsibilitiesMaintenance and ApplicationMajor Command InstructionsAuthorized DeviationsPaint Scheme and Marking Approval Process89th AW, 201AS, and the 1st Helicopter SquadronUSAF Aerial Demonstration Squadron "The Thunderbirds"76th Airlift Squadron	8-1 8-1 8-1 8-1 8-1 8-1 8-1 8-1 8-1

Page

### **TABLE OF CONTENTS - CONTINUED**

8.1.6.4	Low Observable Aircraft	8-1
8.1.6.5	Aircraft Received from Other Services	8-2
8.1.7	Service Tests	8-2
8.1.8	Decals	8-2
8.1.9	Applicable References	8-2
8.2	STANDARD EXTERIOR FINISHES, MARKINGS, AND INSIGNIA FOR USAF	8-2
8.2.1	AIRCRAFT	8-2 8-2
8.2.2	Titanium and Corrosion Resistant Steel	8-2
8.2.3	Treatment of Metal Exteriors	8-2
8.2.4	Policy Guidance	8-2
8.2.5	Camouflage	8-3
8.2.6	Special Purpose Exterior Solar Resistant Finishes	8-3
8.2.7	Paint Facility/Finish Identification Block	8-3
8.3	MARKINGS AND INSIGNIA FOR USAF AIRCRAFT	8-3
8.3.1	General	8-3
8.3.1.1	National Star Insignia	8-4
8.3.1.2	The National Star Insignia on Aircraft Fuselage	8-4
8.3.1.3	The National Star Insignia on Fixed Wing Aircraft	8-4
8.3.1.4	The National Star Insignia on Helicopters	8-4
8.3.2	"USAF" Wing Marking	8-4
8.3.3	American Flag Marking	8-4
8.3.4	United States of America Marking	8-5
8.3.5	Aircraft Radio Call Numbers	8-5
8.3.6	AMC Standard Radio Call Numbers	8-5
8.3.7	ACC Standard Radio Call Numbers	8-5
8.3.7.1	Distinctive Unit Identifiers	8-5
8.4	ORGANIZATION INSIGNIA OR EMBLEMS	8-5
8.4.1	Outstanding Unit Award Marking	8-6
8.4.2	Crew Names	8-6
8.4.2.1	Combat Deployment Requirements	8-6
8.4.3	Aircraft Names	8-6
8.4.4	Local Station Numbers and Markings	8-6
8.4.4.1	Station Numbers	8-6
8.4.4.2	Tail Stripe	8-6
8.4.5	Propeller Markings	8-6
8.4.6	Helicopter Main Rotor Blade Markings	8-7
8.4.7	Helicopter Tail Rotor Blade Markings	8-7
8.4.8	Identification Markings of Jettisonable Aircraft Components	8-7
8.4.8.1	Canopies	8-7
8.4.8.2	Ejection Seats	8-7
8.4.8.3	Jettisonable Components	8-7
8.4.9	Markings for Servicing, Ground Handling, and Hazard Warning	8-7
8.4.10	Markings for Engine Compartment Fire Access Panel	8-8
8.4.11	Ejection Seats	8-8
8.4.12	Identification of Ballistic Hose Assemblies	8-8
8.4.13	Markings for Tank Filler Areas	8-8
8.4.14	Marking of Emergency Lighting (Flashlight) for Cargo and Transport Aircraft	8-8
8.4.15	Markings for Walkways and Steps	8-8
8.4.16	Markings for Composite/Honeycomb Panels	8-8
8.4.17	Removable Escape Panels	8-8
8.4.17.1	Internal Markings	8-8
8.4.17.2	External Markings	8-8 8-9
8.4.18 8.4.18.1	Markings for Unmanned Aerial Vehicles	8-9
0.4.10.1	Target Drones	0-9

Chapter		Page
8.4.18.2 8.4.19 8.4.20 8.5	Other Unmanned Aerial Vehicles (UAV)	8-9 8-9 8-9
8.3	MENT, AND ESPRIT DE CORPS INSIGNIA AND MARKINGS	8-9
APPENDIX A	SHELF-LIFE EXTENSION PROCEDURES	A-1
A.1 A.2 A.2.1 A.2.2 A.2.3 A.2.4 A.3 A.3.1 A.3.2 A.3.3 A.3.4 A.4 A.4 A.4.1 A.4.2 A.4.3 A.4.4 A.4.3 A.4.4 A.5 A.5.1 A.5.2 A.5.3	GENERAL TESTING PROCEDURESMIL-PRF-23377 EPOXY PRIMERCondition in the ContainerViscosity and Pot LifeDrying TimeSurface AppearanceMIL-PRF-85582 WATERBORNE EPOXY PRIMERCondition in the ContainerViscosity and Pot LifeDrying TimeSurface AppearanceTT-P-2760 POLYURETHANE PRIMERCondition in the ContainerViscosity and Pot LifeDrying TimeSurface AppearanceTT-P-2760 POLYURETHANE PRIMERCondition in the ContainerViscosity and Pot LifeDrying TimeSurface AppearanceMIL-PRF-85285 POLYURETHANE COATINGCondition in the ContainerViscosity and Pot LifeDrying TimeSurface AppearanceMIL-PRF-85285 POLYURETHANE COATINGCondition in the ContainerViscosity and Pot LifeDrying TimeSurface The AppearanceMIL-PRF-85285 POLYURETHANE COATINGCondition in the ContainerViscosity and Pot LifeDrying Time	A-1 A-1 A-2 A-2 A-2 A-2 A-2 A-2 A-2 A-2 A-2 A-2
A.5.4 APPENDIX B	Surface Appearance          STANDARD AIR FORCE AIRCRAFT MARKINGS	A-3 B-1
B.1 B.2	NATIONAL STAR INSIGNIA	B-1 B-2
APPENDIX C	RESPIRATOR PROTECTION EQUIPMENT	C-1
C.1	INTRODUCTION	C-1
GLOSSARY .	Glos	sary 1

### LIST OF ILLUSTRATIONS

#### Number

#### Title

#### Page

4-1	Nozzle Pressure Gauge	4-1
4-2	Simple Spray System Setup	4-3
4-3	Airless Spray System	4-4
4-4	Complete Spray System	4-5
4-5	Sectional View of Spray Gun	4-6
4-6	Proper Installation of Air Compressor, Piping	4-7
4-7	Right and Wrong Methods of Spraying	4-9
4-8	Fifty Percent Overlap	4-10
4-9	Cross Coating	4-10
4-10	Spray Gun Adjustments	4-11
4-11	Excessive Spray Fog	4-16
4-12	Paint Leaks From Spray Gun	4-16
4-13	Gun Sputters Constantly	
4-14	Orange Peel	4-17
4-15	Sandpaper Finish	
4-16	Wrinkling	4-18
4-17	Crazing	
4-18	Cracking	
4-19	Blistering	
4-20	Fish Eyes	
4-20	Lifting	
4-21	Pitting or Cupping	
4-22 5-1	Sempen	
5-1 5-2	Sempen Mixing	
5-2 5-3		
5-5 5-4	Sempen Application	5-17
5-4 5-5	Spray Tool	5-17
5-5 6-1	Two-Component Aerosol	
	Zahn Cup	
7-1	Applying Small Decal	
7-2	Applying Marking Stripe	7-2
7-3	Applying Large Emblems (Step 1)	7-3 7-3
7-4	Applying Large Emblems (Step 2)	
7-5	Applying Large Emblems (Step 3)	7-3
7-6	Applying Large Emblems (Step 4)	7-4
7-7	Use of Application Tape (Step 1)	7-4
7-8	Use of Application Tape (Step 2)	7-4
7-9	Use of Application Tape (Step 3)	7-5
7-10 7-11	Use of Application Tape (Step 4)	7-5
	Edge Sealing	7-6
B-1	Dimensions of National Star Insignia	B-3
B-2	National Star Insignia on Swept Wings	
B-3	Form of Letters and Numerals	B-5
B-4	Typical Marking For Paint Facility/Finish Identification Block	B-6
B-5	"UNITED STATES OF AMERICA" and AMC Standard Marking Sample	B-7
B-6	Distinctive Unit, Serial Number, and ACC Standard Sample	B-8
B-7	Aircraft Markings, Servicing, and Precautioning	B-9
B-8	Ground Here, International Symbol	B-11
B-9	Markings For Fire Access Panel	B-11
B-10	Helicopter Tail Boom Markings	B-12
B-11	Typical Emergency Instruction Markings	B-12
B-12	Typical Emergency Entry Markings	B-13

### LIST OF TABLES

#### Number

#### Title

#### Page

1-1	Consumable Materials List	1-2
2-1	Aluminum Backed Pressure Sensitive Tape for Use with Chlorinated Chemical Removers	2-3
2-2	Aluminum Backed Pressure Sensitive Tape for Use with BA/HPA Chemical Removers	2-4
2-3	Hand Held Abrasives	2-18
2-4	Motor Driven Abrasives	2-19
2-5	Abrasive Materials	
2-6	Recommended Controls and PPE for Abrasive Blasting Operations <sup>a</sup>	2-20
2-7	Blast Parameters for Blast Cabinets	
2-8	Blast Parameters for Walk-In Booths	2-23
3-1	Recommended Controls and PPE for Surface Preparation Operations <sup>a</sup>	3-4
3-2	Wipe Solvents	3-6
4-1	Spray Coating Troubles, Possible Causes, and Remedies	4-12
5-1	Minimum Recommended Controls and Personal Protective Equipment (PPE) for Priming and Paint-	
	ing Operations <sup>a</sup>	5-2
5-2	Allowable Coating Thickness for Production Level Finishing (Depot, Original Manufacture, Field)	5-11
5-3	Gloss Requirements	5-12
5-4	Suggested/Approved Rollers for Primer	5-20
5-5	Suggested/Approved Rollers for Topcoat	5-20
6-1	Leading Edge Tape Materials/Tools	6-33
7-1	Adhesive Removal Disc System	7-7
7-2	Adhesion Promoters	7-8
8-1	Standard Markings	8-4
8-2	Aircraft Authorized American Flag Markings	8-4
8-3	Aircraft Authorized United States of America Markings	
8-4	Aircraft Authorized Multi-Colored Blade Tip Markings	8-6
A-1	Viscosity and Pot Life	A-3
C-1	Respirator Protection Equipment	C-1

## INTRODUCTION

#### 1 PURPOSE.

The purpose of this Technical Order (TO) is to prescribe standard procedures for the removal, application, and maintenance of coating systems on Air Force (AF) systems and equipment. Its applicability is generally imposed by reference in system or item technical data. It also should be used where there is an absence of paint process requirements in system or item technical data. System Management (SM) and Item Management (IM) activities have an obligation to require the use of this technical manual to the maximum practical extent. It reflects the use of standard materials and procedures that meet Defense Standardization Program, AF Corrosion Prevention and Control Program, and AF policy (Department of the Air Force Instruction (DAFI) 63-140) requirements. SM/IM offices should modify standard requirements or specify alternate requirements only as needed to support the specific requirements of their systems and equipment as stated in TO 00-5-1. Where there is a conflict between this general TO and the weapon system specific TO, the weapon system specific TO will take precedence. Such departures from standard should also be coordinated with all applicable Office of Coordinating Responsibilities (OCR) (e.g., Corrosion Control, Ground Safety, Bioenvironmental Engineering, and Environmental Management).

#### 2 <u>SCOPE</u>.

This technical manual specifies procedures, materials, and equipment for preparing surfaces and correctly applying effective finishes to interiors and exteriors of AF aircraft, missiles, and associated equipment. Painting techniques are suggested and common difficulties discussed. Procedures for applying complete coating systems are given. Some basic discussion of paint technology is included and a glossary of painting terms appended. This manual consists of the following chapters:

Chapter 1	Introduction and General Discussion of Coating Materials and Terms
Chapter 2	Organic Finish System Removal
Chapter 3	Surface Preparation and Chemical Prepaint Surface Treatment
Chapter 4	Painting Application Methods
Chapter 5	Painting Operations for Aircraft and Equipment
Chapter 6	United States Air Force (USAF) Standard Coating Systems for Aircraft and Equipment
Chapter 7	Application and Removal of Decals and Silk Screening
Chapter 8	Exterior Finishes, Insignia, and Markings Applicable to United States Air Force (USAF) Aircraft
Appendix A	Shelf-Life Extension Procedures
Appendix B	Standard Air Force Aircraft Markings
Appendix C	Respirator Protection Equipment

#### 3 ABBREVIATIONS.

All abbreviations used in this manual are shown in the list of abbreviations below. Standard abbreviations are in accordance with ASME Y14.38, Abbreviations and Acronyms for Use on Drawings and Related Documents.

°C	degree Celsius
°F	degree Fahrenheit
ACC	Air Combat Command
ACGIH	American Conference of Government Industrial Hygienists
AF	Air Force
AFCPCO	Air Force Corrosion Prevention and Control Office
AFH	Air Force Handbook
AFI	Air Force Instruction
AFMAN	Air Force Manual
AFMC	Air Force Material Command
AFPAM	Air Force Pamphlet
AFPD	Air Force Policy Directive

#### TO 1-1-8

AFRC	Air Force Reserve Command
AFRL	Air Force Research Laboratory
AFTO	Air Force Technical Order
ALC	Air Logistic Complex
AMC	Air Mobility Command
ANG	Air National Guard
APC	Advanced Performance Coating
APU	Auxiliary Power Unit
ARIA	Apollo Range Instrumentation Aircraft
ASCC	Air Standard Coordinating Committee
ASM	Aircraft Structural Manager
ASTM	American Standard Test Method
AWB	Airworthiness Bulletin
BCE	Base Civil Engineer
BEE	Bioenvironmental Engineer
BES	Base Environmental Services
CAGE	Commercial and Government Entity
CC	Command Center
CFM	Cubic Feet per Minute
CID	Commercial Item Description
CM	Corrosion Manager
CRES	Corrosion Resistant Steel
DAFI	Department of Air Force Instruction
dB	Decibels
DLA	Defense Logistics Agency
DoD	Department of Defense
EAID	Equipment Authorization Inventory Data
EMB	Engineered Media Blasting
ELT	Extended Life Topcoat
EPA	Environmental Protection Agency
ESDS	Electrostatic Discharge Sensitive
ETIMS	Enhanced Technical Information Management System
F	Final Cleaning
FCF	Functional Check Flight
FED LOG	Federal Logistics Data
FOD	Foreign Object Damage
FSC	Federal Stock Classes
FSG	Federal Supply Group
FTF	Functional Test Flight
G	General Cleaning
GSA	General Services Administration
H <sub>2</sub> O	Water
HAP	Hazardous Air Pollutants
HAZMAT	Hazardous Materials
HCI	Hardness Critical Items
HDI	Hexamethylene Diisocyanate
HEPA	High-Efficiency Particulate Air
HFC	Hydrofluorocarbon
Hg	Mercury
HQ	Headquarters

HVLP	High Volume Low Pressure
ID	Inside Diameter
ID IM	Item Manager
IPB	Illustrated Parts Breakdown
IPG	Intertape Polymer Group
IPU	
JP	In-Process Inspection Jet Propellant
KIAS	Knots Indicated Air Speed
LEL	Lower Explosive Limit
LEL	Liquid Oxygen
	Microampere
μA MAAG	*
MAJCOM	Military Assistance Advisory Group Major Command
MAJCOM	•
MEK	Mission-Design Series
	Methyl-Ethyl-Ketone
Mg-R MIL-STD	Magnesium-Rich Military Standard
	Military Standard Milliliter
mL MOH	Mininter Measure of Hardness
MPW	Medium Pressure Water
NATO	
NDI	North Atlantic Treaty Organization Non-Destructive Inspection
NESHAP	National Emission Standards for Hazardous Air Pollutants
NFPA	National Fire Protection Association
NFFA No.	Number
NSN	National Stock Number
OCR OSHA	Office of Coordinating Responsibilities
OV OV	Occupational Safety and Health Act
PAPR	Organic Vapor
PCBTF	Powered Air-Purifying Respirator Parachlorobenzotrifluoride
PD	
PMB	Purchase Description Plastic Media Blasting
PN	Part Number
PPE PPM	Personal Protective Equipment Part Per Million
PSI	Pound-force per Square Inch
PSIG	
	Pound-force per Square Inch, Gauge
PVC	Polyvinyl Chloride
QPD OPI	Qualified Products Database Qualified Products List
QPL RECC	-
RH	Rare Earth Compound Coating Relative Humidity
RPM	Revolutions Per Minute
SDS	Safety Data Sheet
SDS SE	Support Equipment
SE SG	Support Equipment Specific Gravity
SLES	Shelf-Life Extension System
SLES SM	System Manager
SN	System Manager Serial Number
<b>DIN</b>	

#### TO 1-1-8

SPO	System Program Office	
STANAG	Standardization Agreement	
ТСТО	Time Compliance Technical Order	
TNP	Touch-N-Prep	
ТО	Technical Order	
UAV	Unmanned Aerial Vehicle	
UI	Unit of Issue	
USAF	United States Air Force	
USAFE	United States Air Force in Europe	
UV	Ultra Violet	
VOC	Volatile Organic Compound	

#### 4 RELATED PUBLICATIONS.

#### NOTE

When searching TO numbers in the Enhanced Technical Information Management System (ETIMS) catalog, please use the wildcard (\*) after typing in the TO number. Many TOs are not available in paper format, (i.e., digital (WA-1) or Compact Disk (CD-1)). This ensures TOs in all media formats will populate the search.

The following publications contain information in support of this technical manual.

#### **List of Related Publications**

Number	Title
AFI 32-7001	Environmental Management
AFI 48-137	Respiratory Protection Program
AFPD 91-2	Safety Programs
ASME Y14.38	Abbreviations and Acronyms for Use on Drawings and Related Documents
DAFI 21-101	Aircraft and Equipment Maintenance Management
DAFI 63-140	Aircraft Structural Integrity Program, and Air and Space Equipment Structural Management
DODI 5330.03	Defense Logistics Agency (DLA) Document Services
ETL 02-15	Fire Protection Engineering Criteria - New Aircraft Facilities
ETL 98-8	Fire Protection Engineering Criteria - Existing Aircraft Facilities
NFPA 10	Standard for Portable Fire Extinguishers
NFPA 13	Standards for the Installation of Sprinkler Systems
NFPA 33	Standard for Spray Application Using Flammable or Combustible Materials
NFPA 70	National Electrical Code
NFPA 91	Standard for Exhaust Systems for Air Conveying of Vapors, Gases, Mists, and Noncombustible Particulate Solids
TO 00-25-172	Ground Servicing of Aircraft and Static Grounding/Bonding
TO 00-25-234	General Shop Practice Requirements for the Repair, Maintenance, and Test of Electrical Equipment
TO 00-25-4	Depot Maintenance of Aerospace Vehicles and Training Equipment
TO 00-5-1	AF Technical Order System
TO 1-1-24	Maintenance, Repair, and Electrical Requirements for Fiberglass Airborne Radomes
TO 1-1-689-1	Cleaning and Corrosion Control: Volume I, Corrosion Program and Corrosion Theory
TO 1-1-689-3	Cleaning and Corrosion Control: Volume III, Avionics and Electronics
TO 1-1-690	General Advanced Composite Repair Manual
TO 1-1-691	Aircraft Weapon Systems Cleaning and Corrosion Control
TO 35-1-3	Corrosion Prevention, Painting, and Marking of USAF Support Equipment (SE)

#### List of Related Publications - Continued

Number	Title		
TO 42B1-1-15	Cross Reference - NATO/ASCC Interchangeability of Aviation Fuels, Lubricants and Allied Products		
5 RECORD OF APPLICABLE TIME COMPLIANCE TECHNICAL ORDERS (TCTOS).			
List of Time Compliance Technical Orders			

ТСТО	ТСТО
Title	Date

None

TCTO

Number

#### 6 HCI HARDNESS CRITICAL ITEMS (HCI).

CAUTION

The HCI symbol (HCI) establishes special requirements limiting changes and substitutions and that the specific parts listed must be used to ensure hardness is not degraded.

If included, items with nuclear survivability requirements are marked with the HCI symbol (HCI). All changes to, or proposed substitutions of, HCIs must be approved by the acquiring activity.

#### 7 SELECTROSTATIC DISCHARGE SENSITIVE (ESDS) ITEMS.

**CAUTION** 

All ESDS parts shall be handled in accordance with the ESDS device handling procedures in TO 00-25-234.

If included, items containing ESDS parts are marked with the ESDS symbol (🔅).

#### 8 **IMPROVEMENT REPORTS.**

Recommended changes to this manual shall be submitted in accordance with TO 00-5-1.

## SAFETY SUMMARY

#### 1 GENERAL SAFETY INSTRUCTIONS.

This manual describes physical and/or chemical processes which may cause injury or death to personnel, or damage to equipment, if not properly followed. This safety summary includes general safety precautions and instructions that must be understood and applied during operation and maintenance to ensure personnel safety and protection of equipment. Prior to performing any specific task, the WARNINGS, CAUTIONS, and NOTEs included in that task shall be reviewed and understood.

#### 2 WARNINGS, CAUTIONS, AND NOTES.

WARNINGs and CAUTIONs are used in this manual to highlight operating or maintenance procedures, practices, conditions, or statements which are considered essential to protection of personnel (WARNING) or equipment (CAUTION). WARN-INGs and CAUTIONs immediately precede the step or procedure to which they apply. WARNINGs and CAUTIONs consist of four parts: heading (WARNING, CAUTION, or icon), a statement of the hazard, minimum precautions, and possible results if disregarded. NOTEs are used in this manual to highlight operating or maintenance procedures, practices, conditions, or statements which are not essential to protection of personnel or equipment. NOTEs may precede or follow the step or procedure, depending upon the information to be highlighted. The headings used and their definitions are as follows:



Highlights an essential operating or maintenance procedure, practice, condition, statement, etc. Failure to comply could result in injury to, or death of, personnel or long term health hazards.



Highlights an essential operating or maintenance procedure, practice, condition, statement, etc. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

#### NOTE

Highlights an essential operating or maintenance procedure, condition, or statement.

#### 3 HAZARDOUS MATERIALS WARNINGS.

Hazardous Materials Warnings are provided through use of the following Hazard Symbols. Consult the HAZARDOUS MA-TERIALS DESCRIPTION or Safety Data Sheet (SDS) (formerly MSDS) (Occupational Safety and Health Administration (OSHA) Form 20 or equivalent) for specific information on hazards, effects, and protective equipment requirements. If you do not have an SDS for the material involved, contact your supervisor, or the base Safety or Bioenvironmental Engineering Offices.

3.1 <u>Hazardous Materials Icons</u>. The following icons are used throughout this Air Force technical manual to indicate the use of hazardous materials:



The symbol of a human figure in a cloud shows that the material gives off vapors that are a danger to life or health.



The symbol of drops of liquid onto a hand shows that the material will cause burns or irritation of skin and tissue.

#### TO 1-1-8





The symbol of a flame shows that the material can ignite and burn.

The symbol of a person wearing goggles shows that the material will injure eyes.

tures, sources of ignition or high pressure.

The symbol of a skull and crossbones shows that the material is poisonous or a danger to life.

The rapidly expanding symbol shows that the material may explode if subjected to high tempera-



The symbol of a liquid entering the mouth shows that eating or drinking this material can cause a health hazard.



The symbol of an O with a flame shows a material that is a fire hazard when near flammable or organic materials.

The hand symbol shows a material that can irritate the skin or enter the body through the skin and cause a health hazard.

1

2

3.2 <u>Hazardous Materials Description</u>. The following detailed HAZMAT warnings pertain to materials or substances used in connection with procedures called out or described in this technical manual. Use these advisory warnings and their associated precautions in conjunction with the current SDS for each material or substance. If there is conflict between this safety summary and the SDS, the SDS takes precedence.



#### PURGING THINNER, TT-T-2935

Purging thinner is toxic and flammable. May be fatal if swallowed. May cause skin, eye and respiratory irritation. Avoid contact with skin and eyes. Use in a well ventilated area and avoid breathing vapors. Keep away from heat, sparks and flame. Appropriate skin and eye protection must be worn. Half mask respirator with organic vapor cartridge required in poorly ventilated areas.



#### PRIMER COATING, POLYURETHANE, ELASTOMERIC, HIGH SOLIDS, TT-P-2760

Polyurethane Coating is flammable and may irritate skin and respiratory tract. Can cause serious eye damage. Exposure to high vapor concentrations may cause central nervous system depression. Aspiration of liquid may cause pneumonitis, pulmonary edema, and hemorrhaging. Do not take internally. Use only in well ventilated areas. Avoid breathing dust, fume, gas, mist vapors, and spray. Appropriate skin and eye protection must be worn. Wash thoroughly after handling.

3

4



CLEANING COMPOUND, AIRCRAFT EXTERIOR, MIL-PRF-85570

Cleaning Compound is irritating to the skin and eyes. Vapor/aerosol concentrations above recommended exposure levels are irritating to the eyes and respiratory tract, and may cause headaches, dizziness, drowsiness, unconsciousness and other central nervous system effects. Do not breathe fumes, vapors or mists if inhalable mists occur during use. Use only outdoors or in a well-ventilated area. Wear protective gloves, eye protection, and face protection. Wash hands and exposed skin thoroughly after handling. Do not eat, drink or smoke when using this product.



COATING COMPOUND, NON-SLIP, CID A-A-59166

Non-Slip Coating Compound is a highly flammable liquid and vapor. May cause an allergic skin reaction. May cause genetic defects. May cause cancer. Keep away from heat, sparks, open flames, or hot surfaces. No smoking. Use explosion-proof electrical, ventilating, lights, equipment. Use only non-sparking tools. Avoid breathing dust, fume, gas, mist, vapors, or spray. Wear protective gloves, protective clothing, eye protection, face protection. IF exposed or concerned: Get medical advice, attention. Store in a well-ventilated place. Keep cool.



RESIN COATING, MIL-PRF-3043

Resin Coating is flammable and toxic. It may cause breathing problems, eye damage, skin irritation, and may be harmful if swallowed. Use only with adequate ventilation. Appropriate skin and eye protection must be worn. Do not ingest. May require a respirator. Wash thoroughly after handling. Keep away from heat, sparks and flame. Keep container tightly closed when not in use. Store in a cool, dry, ventilated area, away from incompatible substances.



#### COATING KIT, EPOXY, FOR INTERIOR OF STEEL FUEL TANKS, MIL-PRF-23236

Epoxy Coating is a flammable liquid and vapor. Harmful if swallowed. Causes serious eye damage. Causes skin irritation. May cause an allergic skin reaction. Suspected of causing cancer. May cause respiratory irritation. May cause drowsiness or dizziness. May cause damage to organs through prolonged or repeated exposure. Wear protective gloves. Wear eye or face protection. Wear protective clothing. Keep away from heat, hot surfaces, sparks, open flames and other ignition sources. No smoking. Use only non-sparking tools. Take precautionary measures against static discharge. Keep container tightly closed. Use only outdoors or in a well-ventilated area. Do not breathe vapor. Do not eat, drink or smoke when using this product. Wash hands thoroughly after handling.



COATING, SPRAYABLE, STRIPPABLE, PROTECTIVE, WATER EMULSION, MIL-PRF-6799

Sprayable protective coating is suspected of causing cancer. May be harmful if swallowed. Causes skin, eye, and respiratory irritation. Emits toxic fumes when heated. Wear protective gloves. Wear eye or face protection. Wear protective clothing. May require a respirator. Use only outdoors or in a well-ventilated area. Do not breathe vapor. Wash hands thoroughly after handling.

6



#### ACETONE, ASTM-D329

Acetone is extremely flammable and an eye, skin, and respiratory irritant. Harmful if swallowed. Avoid contact with skin and eyes, and avoid breathing vapors. Do not ingest. Keep away from heat, sparks and flame. Protection: butyl gloves and chemical goggles. Face shield is required when splashing is possible or expected. Use in a well ventilated area. Half mask respirator required in poorly ventilated areas. Keep container tightly closed when not in use. Store in a cool, dry, ventilated area, away from incompatible substances.



#### SOLVENT COMPOUND, CID A-A-59281

Solvent compound is highly flammable and an eye, skin, and respiratory irritant. Is hazardous if ingested. Avoid contact with skin and eyes. Use in a well ventilated area and avoid breathing vapors. Keep away from heat, sparks and flame. Appropriate skin and eye protection must be worn.



#### CORROSION REMOVING COMPOUND, SAE AMS-1640

Corrosion removing compound is corrosive to the eyes and skin. Causes irritation to the nose and throat, and is hazardous if ingested. Avoid contact with skin and eyes. Use in a well ventilated area and avoid breathing vapors. Keep container tightly closed when not in use. Appropriate skin and eye protection must be worn.



#### CHEMICAL CONVERSION COATING, MIL-DTL-81706

Chemical Conversion Coating is an oxidizer and harmful if swallowed. May cause severe burns to the eyes, skins, and respiratory tract. May cause cancer. Do not get this material in your eyes, on your skin, or on your clothing. Do not inhale vapors or mist of this product. Wash thoroughly after handling. Clothing or other material wet with this product and allowed to dry may become flammable. Use in a well ventilated area. Appropriate skin, body, and eye protection must be worn. If ventilation is not sufficient to effectively prevent buildup of dust, appropriate NIOSH/MSHA respiratory protection must be provided. Do not store with incompatible materials.



#### IRIDITE NO. 14-2 CHEMICAL FILM, MIL-DTL-5541

Iridite Chemical Film is a severe eye, skin and respiratory irritant. It may be toxic if ingested. Chemical film materials are strongly oxidizing and present a potential fire and explosion hazard in contact with flammable materials. Avoid repeated or prolonged exposure. Keep off of skin, out of eyes and avoid breathing vapors. Appropriate skin, body, and eye protection must be worn. If spray applicators are used, wear a respirator to prevent inhalation of the atomized solution. Avoid contact with organic materials. Do not dispose of in same container as combustible materials. Do not eat, drink, or smoke when using this product. Wash exposed areas thoroughly with soap and water. Thoroughly wash all materials used to apply or remove the Iridite Solution before allowing them to dry or discard them. If allowed to dry without being washed, they may constitute a fire hazard.

9

8

10

11

18

13

EPOXY PRIMER, MIL-PRF-23377 Epoxy primer is a highly flammable liquid and vapor. May cause serious eye damage. May cause respiratory and skin irritation. May cause cancer. May cause burns to mouth, throat, and stomach if ingested. Avoid repeated and prolonged Expo-

tion. May cause cancer. May cause burns to mouth, throat, and stomach if ingested. Avoid repeated and prolonged Exposure. Use with adequate ventilation. Appropriate skin and eye protection must be worn. Do not ingest. Keep away from heat, spark, and flames.



### LUBRICATING OIL, AIRCRAFT TURBINE ENGINE, SYNTHETIC BASE, MIL-PRF-7808

May cause skin, eye, and respiratory irritation. Ingestion may cause aspiration into the lungs. Appropriate skin and eye protection is required and needs to be worn when using this substance. Use in a well-ventilated area. Do not ingest.



### POLYURETHANE COATING, MIL-PRF-85285

Polyurethane Coating is flammable and may irritate skin and respiratory tract. Can cause serious eye damage. Exposure to high vapor concentrations may cause central nervous system depression. Aspiration of liquid may cause pneumonitis, pulmonary edema, and hemorrhaging. Do not take internally. Use only in well ventilated areas. Avoid breathing dust, fume, gas, mist vapors, and spray. Appropriate skin and eye protection must be worn. Wash thoroughly after handling.



WATER BORNE EPOXY PRIMER, MIL-PRF-85582

Water borne epoxy primer is highly flammable and may contain isocyanates which are toxic to the skin, eyes, and respiratory tract. May be harmful if swallowed. Contact with the eyes may cause irritation. Avoid contact with eyes, skin and clothing. Do not ingest. Appropriate skin and eye protection is required and local exhaust ventilation and/or respiratory protection may be required. Do not ingest. Keep away from heat, sparks and flame. Keep container tightly closed when not in use.



AIRCRAFT COATING THINNER, MIL-T-81772

Thinner is a highly flammable liquid and vapor, and can cause serious eye damage. Is a skin, eye, and respiratory irritant. Is suspected of causing cancer. May damage unborn children. Prolonged or repeated exposure may cause organ damage. Avoid contact with skin and eyes, and avoid breathing vapors. Do not ingest. Keep away from sources of ignition. Appropriate skin and eye protection must be worn. Use in a well ventilated area.



CHEMICALS, ANALYTICAL, CID A-A-59282

Ethyl Alcohol is flammable and an eye, skin and respiratory irritant. Harmful if swallowed. Avoid contact with skin and eyes and avoid breathing vapors. Do not ingest. Keep away from heat, sparks and flame. Appropriate skin and eye protection must be worn. Use in a well ventilated area. Half mask respirator required in poorly ventilated areas.

15

16

14



#### PAINT GLOSS, SEMI-GLOSS ALKYD ENAMEL, MPI NO. 6, MPI NO. 94

Alkyd enamel is a flammable liquid and vapor. May cause eye, skin, and respiratory tract irritation. May cause asphyxiation or brain, lung, or other organ injury if inhaled, swallowed, or absorbed through the skin. Use only in well ventilated areas. Do not ingest. Appropriate skin and eye protection must be worn. Contact lenses should not be worn. Use approved respirator in poorly ventilated areas. Keep away from heat, spark, and flames.



#### ISOPROPYL ALCOHOL, TT-I-735

Isopropyl Alcohol is flammable, and an eye, skin and respiratory irritant. It may be harmful if swallowed. Avoid contact with skin and eyes, and avoid breathing vapors. Do not ingest. Keep away from heat, sparks and flame. Appropriate skin and eve protection must be worn. Use in a well ventilated area. Half mask respirator required in poorly ventilated areas.



CLEANING COMPOUND, AEROSPACE EQUIPMENT, MIL-PRF-87937

Liquid alkaline cleaner is an eye, skin and respiratory irritant. Ingestion may cause digestive tract irritation. Do not ingest. Appropriate skin and eye protection must be worn.



CHROMIUM TRIOXIDE, CID A-A-55827

Chromium Trioxide is toxic if swallowed. Fatal in contact with skin. Fatal if inhaled. Causes severe skin burns and eye damage. May cause allergy or asthma symptoms or breathing difficulties if inhaled. May cause an allergic skin reaction. May cause genetic defects. May cause cancer. Suspected of damaging fertility or the unborn child. Causes damage to organs through prolonged or repeated exposure. May cause fire or explosion; strong oxidizer. Use personal protective equipment as required. Do not get in eyes, on skin, or on clothing. Do not breathe dust/fume/gas/mist/vapors/spray. Use only outdoors or in a well-ventilated area. Wear respiratory protection. Wear protective gloves. Do not eat, drink or smoke when using this product. Keep/Store away from clothing/combustible materials. Take any precaution to avoid mixing with combustibles. Keep away from heat/sparks/open flames/hot surfaces.



COATING, CORROSION PREVENTIVE, POLYURETHANE, FOR AIRCRAFT INTEGRAL FUEL TANKS (FOR USE TO 250 °F (121 °C)), SAE AMS-C-27725

Polyurethane Coating is flammable and may irritate skin and respiratory tract. Can cause serious eye damage. Exposure to high vapor concentrations may cause central nervous system depression. Aspiration of liquid may cause pneumonitis, pulmonary edema, and hemorrhaging. Do not take internally. Use only in well ventilated areas. Avoid breathing dust, fume, gas, mist vapors, and spray. Appropriate skin and eye protection must be worn. Wash thoroughly after handling.

19

20

22

21



#### POLYSULFIDE PRIMER, PR-1432GV

Polysulfide Primer is toxic to the skin, eyes, and respiratory tract. Use only with adequate ventilation. Avoid breathing of vapor or spray mist. Avoid prolonged or repeated contact with skin. Wear goggles or face shield, gloves, apron, and footwear impervious to material.



PAINT, ALUMINUM, HEAT RESISTING (1200 °F), TT-P-28

Aluminum Paint is a flammable liquid and vapor. Causes skin irritation. May cause an allergic skin reaction. Causes serious eye damage. May cause allergy or asthma symptoms or breathing difficulties if inhaled. Causes damage to organs through prolonged or repeated exposure. Keep away from heat/sparks/open flames/hot surfaces. Ground/bond container and receiving equipment. Use explosion-proof electrical/ventilating/lighting/equipment. Avoid breathing dust/fume/gas/mist/vapors/spray. Do not get in eyes, on skin, or on clothing. Use only outdoors or in a well-ventilated area. Wear protective gloves/protective clothing/eye protection/face protection. (In case of inadequate ventilation) wear respiratory protection. Wash contaminated clothing before reuse. Store in a well-ventilated place. Keep container tightly closed. Keep cool.



#### COATING, POLYURETHANE, RAIN EROSION RESISTANT, FOR EXTERIOR AIRCRAFT AND MISSILE PLAS-TIC PARTS, SAE AMS-C-83231 26

Polyurethane Coating is flammable and may irritate skin and respiratory tract. Can cause serious eye damage. Exposure to high vapor concentrations may cause central nervous system depression. Aspiration of liquid may cause pneumonitis, pulmonary edema, and hemorrhaging. Do not take internally. Use only in well ventilated areas. Avoid breathing dust, fume, gas, mist vapors, and spray. Appropriate skin and eye protection must be worn. Wash thoroughly after handling.



# COATING SYSTEM, POLYURETHANE, NON-YELLOWING WHITE, RAIN EROSION RESISTANT, THERMALLY REFLECTIVE, SAE AMS-C-83445 27

Polyurethane Coating is flammable and may irritate skin and respiratory tract. Can cause serious eye damage. Exposure to high vapor concentrations may cause central nervous system depression. Aspiration of liquid may cause pneumonitis, pulmonary edema, and hemorrhaging. Do not take internally. Use only in well ventilated areas. Avoid breathing dust, fume, gas, mist vapors, and spray. Appropriate skin and eye protection must be worn. Wash thoroughly after handling.



#### CONVERSION COATING, NON-CHROMATED, RECC 3021

Emits toxic fumes when heated Good general ventilation should be sufficient to control worker exposure to airborne contaminants. Use Safety glasses with side shields. Wash hands, forearms and face thoroughly after handling chemical product. Wash contaminated clothing before reusing.



#### EPOXY PRIMER, NON-CHROMATED, 02GN093

Highly flammable liquid and vapor. Causes skin irritation. May cause an allergic skin reaction. Causes serious eye damage. May cause respiratory irritation. May cause cancer. May damage fertility or the unborn child. May cause damage to organs through prolonged or repeated exposure(kidneys). Put on appropriate personal protective equipment. Avoid exposure during pregnancy. Do not handle until all safety precautions have been read and understood. Do not get in eyes or on skin or clothing. Do not breathe vapor or mist. Do not ingest. Use only with adequate ventilation. Wear appropriate respirator when ventilation is inadequate. Store and use away from heat, sparks, open flame or any other ignition source. Use explosionproof electrical equipment. Use only non-sparking tools.



#### PARACHLOROBENZOTRIFLUORIDE, PCBTF

Combustible liquid. May cause an allergic skin reaction. May be fatal if swallowed and enters airways. Keep away from open flames, hot surfaces and sources of ignition. When using do not smoke. Avoid breathing mist or vapor. Avoid contact with eyes, skin, and clothing. Provide adequate ventilation. Wear appropriate personal protective equipment. Wash hands thoroughly after handling. Observe good industrial hygiene practices.



#### TIECOAT, NON-CHROMATED

Highly flammable liquid and vapor. Harmful if inhaled. Causes skin irritation. Causes serious eye irritation. May cause an allergic skin reaction. May cause damage to organs (Lungs). May cause drowsiness or dizziness. May cause respiratory irritation. Causes damage to organs(Central nervous system). May be fatal if swallowed and enters airways. Keep away from heat/sparks/open flames/hot surfaces. No smoking. Use explosion-proof electrical/ventilating/lighting equipment. Use only non-sparking tools. Take precautionary measures against static discharge. Wear protective gloves/protective clothing/eye protection/face protection. Do not breathe dust/fume/gas/mist/vapors/spray. Wash thoroughly after handling. Do not eat, drink or smoke when using this product. Use only outdoors or in a well-ventilated area. Contaminated work clothing should not be allowed out of the workplace. Avoid release to the environment.



#### THINNER, ALKYD ENAMEL, A-A-3007

Thinner, Alkyd Enamel is a highly flammable liquid and vapor, and can cause serious eye damage. Is a skin, eye, and respiratory irritant. Prolonged or repeated exposure may cause organ damage. Avoid contact with skin and eyes, and avoid breathing dust/fumes/gas/mist/vapors. Do not ingest. Keep away from heat and sources of ignition. Appropriate skin and eye protection must be worn. Use in a well ventilated area.



#### PRIMER COATING, MAGNESIUM RICH, NON-CHROMATED, AERODUR 2100 MGRP

Flammable liquid and vapor. Causes serious eye irritation. Causes skin irritation. May cause an allergic skin reaction. Suspected of causing cancer. Toxic to aquatic life with long lasting effects. Wear protective gloves. Wear eye or face protection. Wear protective clothing. Keep away from heat, hot surfaces, sparks, open flames and other ignition sources. No smoking. Use explosion-proof electrical, ventilating, lighting and all material-handling equipment. Use only non-sparking tools. Wash hands thoroughly after handling.

30

29

32

34

35



#### DEOXIDIZER, NON-CHROMATED, RECC 1015

Emits toxic fumes when heated. Good general ventilation should be sufficient to control worker exposure to airborne contaminants. Use Safety glasses with side shields. Wash hands, forearms and face thoroughly after handling chemical product. Wash contaminated clothing before reusing.



#### SEALANT, CORROSION INHIBITIVE, MIL-PRF-81733

Sealant, Corrosion Inhibitive is flammable and can cause moderate eye and skin irritation. Breathing of vapors can cause dizziness and nausea. Concentrated vapors are explosive. Maintain standard hygiene for chemical handling. Use grounding and bonding procedures when transferring. No cutting or welding on empty containers. Use in ventilated area. Keep containers closed. Use air respirator or air mask suitable for organic vapors. Appropriate skin and eye protection must be worn.



#### ADHESION PROMOTER

Highly flammable liquid and vapor. Causes serious eye irritation. May cause drowsiness or dizziness. Keep away from heat/ sparks/open flames/hot surfaces. No smoking. Use only non-sparking tools. Keep container tightly closed. Use explosionproof electrical/ventilating/lighting equipment. Avoid breathing dust/fume/gas/mist/vapors/spray. Use only outdoors or in a well-ventilated area. Wear protective gloves and eye/face protection. Wash thoroughly after handling.



#### EDGE SEALER

Flammable liquid and vapor. Causes eye irritation. May cause drowsiness or dizziness. May damage fertility or the unborn child. Suspected of causing cancer. Causes damage to organs: sensory organs nervous system Keep away from heat/ sparks/open flames/hot surfaces. No smoking. Ground/bond container and receiving equipment. Use only non-sparking tools. Take precautionary measures against static discharge. Keep container tightly closed. Use explosion-proof electrical/ventilat-ing/lighting equipment. Do not breathe dust/fume/gas/mist/vapors/spray. Use only outdoors or in a well-ventilated area. Wear protective gloves and eye/face protection. Do not eat, drink or smoke when using this product. Wash thoroughly after handling.



#### ADHESIVE REMOVER

Extremely flammable aerosol. Contains gas under pressure; may explode if heated. Causes serious eye irritation. Causes skin irritation. May cause drowsiness or dizziness. May damage fertility or the unborn child. Suspected of causing cancer. Causes damage to organs: sensory organs, nervous system. Keep away from heat/sparks/open flames/hot surfaces. No smoking. Do not spray on an open flame or other ignition source. Pressurized container: Do not pierce or burn, even after use. Do not breathe dust/fume/gas/mist/vapors/spray. Use only outdoors or in a well-ventilated area. Wear protective gloves and eye/face protection. Do not eat, drink or smoke when using this product. Wash thoroughly after handling.

36

#### 37

#### TO 1-1-8

#### 4 SAFETY PRECAUTIONS.

The following safety precautions shall be observed while performing procedures in this manual.

- Dangerous voltages are present at system connectors. Ensure power is OFF prior to connecting or disconnecting cables.
- Do not wear metal frame glasses, rings, watches, or other metal jewelry while working on electronic equipment.
- Some cleaning materials specified herein are flammable and/or toxic. Keep away from open flame or other ignition sources. Provide adequate ventilation and avoid skin/eye exposure.
- Cleaning with compressed air can create airborne particles that may enter eyes or penetrate skin. Pressure shall not exceed 30 Pound-force per Square Inch, Gauge (PSIG). Wear goggles. Do not direct compressed air against skin.

### CHAPTER 1 INTRODUCTION AND GENERAL DISCUSSION OF COATING MATERIALS AND TERMS

#### 1.1 INTRODUCTION.

#### NOTE

See Chapter 8 for Air Force policy on determining when individual aircraft are to be repainted or touched up.

The surfaces of aircraft, missiles, and associated equipment are subjected to hostile environments both natural and man-made. Inadequate control or prevention of metal corrosion or other forms of surface deterioration is costly and can shorten weapon or equipment life, hinder mission accomplishment, or endanger personnel or equipment. To add to their ability to resist detrimental environments, surfaces are coated in various ways with a variety of materials. Coatings are divided into two main groups: inorganic and organic. The principal and most versatile means of protection is organic coating, or "paint". In general, a suitable organic coating system, properly applied, offers greater protection against corrosion on metals than an inorganic finish (such as a metallic plating) alone and is more easily maintained. This technical manual also covers some inorganic materials, insofar as they are applied in surface preparation for painting by personnel involved with paint removal and painting operations.

#### 1.2 GENERAL DISCUSSION OF ORGANIC COATINGS.

#### NOTE

Precautionary measures shall be taken to prevent paint and paint removal waste from contaminating air, water, or soil. Some of the chemicals utilized for painting and paint removal require treatment or other special control prior to disposal. Disposal of materials shall be accomplished under the direction of the Base Safety Office, Base Civil Engineer, Bioenvironmental Engineer, and Environmental Management in accordance with applicable directives and in a manner that will not result in violation of local, state, or federal pollution criteria. Detailed information for disposal is cited in Air Force Instruction (AFI) 32-1067, AFI 32-7001, AFI 32-7041, AFI 32-7042, Air Force Pamphlet (AFPAM) 32-7043, AFI 32-7086, AFI 90-803 and AFI 91-203.

To provide optimum protection from deterioration and corrosion, the proper coating systems (combination of pretreatment, primer, and topcoat) must be selected for a specific application. The selection of the proper coating system depends on the material to be coated, the environment to which the item will be subjected, and the service life requirement of the coating. No single coating or coating system can perform adequately on all types of surfaces under all conditions to which Air Force equipment is subjected. For example, a coating paint conforming to Specification SAE AMS-C-27725 is good for fuel immersion service, but is inadequate for exposure to an industrial atmosphere or high humidity conditions. Many primers and topcoats can be used in various combinations; however, some primers are specifically formulated for a particular type topcoat. One Component, Alkyd Base Primers are for use under enamels. Use of this primer under epoxy or polyurethane coatings will result in premature failure of the coating system.

1.2.1 <u>Coatings Systems for Metal Surfaces</u>. Unless protected, metals surfaces (with the exception of stainless steel, titanium and some of the more exotic metals) react with oxygen and various contaminants in the atmosphere, particularly in the presence of moisture, to form rust or other corrosion products. The most common method of preserving metals is by applying organic coatings.

**1.2.1.1** Polishing, buffing, and waxing of aircraft and parts is prohibited unless authorized and directed by the Major Command (MAJCOM) Senior Logistics Official.

1.2.2 <u>Aircraft Protective Finish Systems</u>. Military Standard (MIL-STD)-7179 covers the general requirements for protective finishes and coatings on aerospace weapon system structures and parts. (It does not necessarily govern coatings on aeronautical equipment such as propellers or power plants, nor those on accessories such as motors, generators, instruments, etc.) The level of coating protection is specified depending on the environment to which the weapon system is to be subjected.

#### 1.3 ORGANIC COATING.

An organic coating or paint may be defined as a carbon based liquid or semi-liquid material which is applied to a surface by some mechanical means and which, when dried or cured, will provide an adherent film of certain desired characteristics. Organic coatings are variously classed as paints, enamels, varnishes and lacquers. As these classifications are not always practical, due to modern formulations, and because the coating materials dealt with in this technical manual are almost exclusively organic in chemical structure, the preferred term "organic coating" is used to designate finishing materials in general. For the purposes of this technical manual the term is extended to include some heavy elastomeric materials which are not truly "paints," and also certain chemical surface-treating materials which are not truly organic. These materials may or may not be applied by painters, but are closely associated with painting operations. Also, the term "to paint" will continue to be used to signify the application of organic coatings by painters.

#### 1.4 CONSUMABLE MATERIALS.

Abrasive Mats, Non-Woren, Non-Metallic (Repl. MIL-A-9962)       CID A-A-58054         Adhesion Promoter       PN         Adhesion Promoter       PN         Adhesive Remover       PN         Anodic Coatings for Aluminum and Aluminum Alloy       MIL-PRF-8625         Barrier Materials, Water vapor proof, Flexible, Heat-Sealable       MIL-PRF-121         Barrier Materials, Water vapor proof, Greaseproof, Flexible, Heat-Sealable       MIL-PRF-131         Brush, Plater's, Hand (Curved Handle Type) (Repl. H-B-178)       CID A-A-3118         Brush, Plater's, Hand Curved Handle Type) (Repl. H-B-178)       CID A-A-3289         Chemical Conversion Coatings for Aluminum and Aluminum Alloys       MIL-DTL-5541         MIL-C-81706)       CID A-A-59282         Chromium Trioxide, Technical (Repl. O-C-303)       CID A-A-59282         Chromium Trioxide, Technical (Repl. O-C-303)       CID A-A-59282         Cleaning Compound, Aerospace Equipment       MIL-PRF-87937         Cleaning Compound, Aircraft Exterior       CID A-A-59281         Cloth, Cheese, Cotton, Bleached and Unbleached       CCC-2440         Cotting System, Polyurethane, Non-Yellowing White, Rain Erosion Resistant, Thermally Reflective (Repl. MIL-C-83453)       MIL-PRF-85236         Coating Compound, Non-Slip, for Walkways (Repl. MIL-W5044)       CID A-A-59282         Coating System, Polyurethane, Ner-Yellowing White,	Nomenclature	Specification Number
Adhesion Promoter       PN 700701-8275-6         Adhesive Remover       PN 38987         Anodic Coatings for Aluminum and Aluminum Alloy       MIL-PRF-8625         Barrier Materials, Greaseproof, Waterproof, Flexible, Heat-Sealable       MIL-PRF-121         Barrier Materials, Water vapor proof, Greaseproof, Flexible, Heat-Sealable       MIL-PRF-131         Brush, Plater's, Hand (Curved Handle Type) (Repl. H-B-178)       CID A-A-3118         Brush, Plater's, Hand (Curved Handle Type) (Repl. H-B-178)       CID A-A-3118         Chemical Conversion Coatings for Aluminum and Aluminum Alloys       MIL-DTL-5541         MIL-Centrolo       MIL-DTL-5541         MIL-281706)       CID A-A-59282         Chromium Trioxide, Technical (Repl. O-C-303)       CID A-A-59282         Cleaning Compound, Aerospace Equipment       MIL-PRF-82295         Cleaning Compound, Aircraft Exterior       MIL-PRF-85770         Cleaning Compound, Aircraft Exterior       MIL-PRF-85730         Cloth, Cheese, Cotton, Bleached and Unbleached       CCC-C-440         Cloth, Scee, Cotton, Bleached and Unbleached       CID A-A-59281         Coating Compound, Metal Pretreatment, Resin-Acid       MIL-PRF-85730         Coating Compound, Metal Pretreatment, Resin-Acid       MIL-2814         Coating Compound, Metal Pretreatment, Resin-Acid       MIL-2814         Coating System,	Abrasive Mats, Non-Woven, Non-Metallic (Repl. MIL-A-9962)	CID A-A-58054
PNN 700718275-6Adhesive RemoverPN 38987Adhesive RemoverPN 8098Anodic Coatings for Aluminum and Aluminum AlloyMIL-PRF-8625Barrier Materials, Greaseproof, Waterproof, Flexible, Heat-SealableMIL-PRF-121Barrier Materials, Water vapor proof, Greaseproof, Flexible, Heat-SealableMIL-PRF-131Brush, Cleaning, Aircraft, Metal BrighteningMIL-B23958Brush, Plater's, Hand (Curved Handle Type) (Repl. H-B-178)CID A-A-3118Chemical Conversion Coatings for Aluminum and Aluminum AlloysMIL-DTL-5541Chemical Conversion Materials for Coating Aluminum and Aluminum Alloys (Repl.MIL-DTL-81706MIL-C-81706)CID A-A-59282Chromium Trioxide, Technical (Repl. O-C-303)CID A-A-59282Cleaning Compound, Aerospace EquipmentMIL-PRF-32295Cleaning Compound, Aircraft ExteriorMIL-PRF-85570Cleaning Compound, Aircraft ExteriorMIL-PRF-85570Cleaning Compound, Aircraft ExteriorMIL-PRF-85570Cloth, Cheese, Cotton, Bleached and UnbleachedCCC-C-440Cloth, Cheese, Cotton, Bleached and UnbleachedCCC-C-440Coating Compound, Metal Pretreatment, Resin-AcidMIL-PRF-32326Coating System, Polyurethane, Non-Yellowing White, Rain Erosion Resistant, Ther- mally Reflective (Repl. MIL-C-2725)SAE AMS-C-83445Coating System, Ship Structures (Repl. MIL-PRF-23236)MIL-PRF-23236Coating, Corrosion Preventive, Polyurethane, for Aircraft Integral Fuel Tanks (for Use SAE AMS-C-83445SAE AMS-C-83231Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85285Coating,	A dhasian Dromatan	PN 86A
Adhesive RemoverPN 8098Anodic Coatings for Aluminum and Aluminum AlloyMIL-PRF-8625Barrier Materials, Greaseproof, Waterproof, Flexible, Heat-SealableMIL-PRF-121Barrier Materials, Water vapor proof, Greaseproof, Flexible, Heat-SealableMIL-PRF-131Brush, Cleaning, Aircraft, Metal BrighteningMIL-B-23958Brush, Plater's, Hand (Curved Handle Type) (Repl. H-B-178)CID A-A-3118Crowersion Coatings for Aluminum and Aluminum AlloysCID A-A-289Chemical Conversion Materials for Coating Aluminum and Aluminum Alloys (Repl.MIL-DTL-5541Chemical Conversion Materials for Coating Aluminum and Aluminum Alloys (Repl.MIL-DTL-81706Chemicals, Analytical (Repl. O-E-760)CID A-A-58282Chomium Trioxide, Technical (Repl. O-C-303)CID A-A-55827Cleaner, Non-Aqueous, Low-VOC, Hap-Free (Repl. P-D-680)MIL-PRF-32295Cleaning Compound, Aircraft ExteriorMIL-PRF-87937Cleaning Compound, Aircraft ExteriorMIL-PRF-85570Cloth, Cheese, Cotton, Bleached and UnbleachedCCC-C-440Cloth, Cheese, Cotton, Bleached and UnbleachedCID A-A-59281Coting Compound, Non-Slip, for Walkways (Repl. MIL-W-5044)CID A-A-59166Coating System, Ship Structures (Repl. MIL-PRF-23236)MIL-PRF-23236Coating, System, Ship Structures (Repl. MIL-PRF-23236)MIL-PRF-23236Coating, Corrosion Preventive, Polyurethane, for Aircraft Integral Fuel Tanks (for Use to 2595 (F (12 °C)) (Repl. MIL-C-27725)SAE AMS-C-27725Coating, Pory, High SolidsMIL-PRF-22750Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-23236 </td <td>Adnesion Promoter</td> <td>PN 700701-8275-6</td>	Adnesion Promoter	PN 700701-8275-6
PN 8098Anodic Coatings for Aluminum and Aluminum AlloyMIL-PRF-8625Barrier Materials, Greaseproof, Waterproof, Flexible, Heat-SealableMIL-PRF-121Barrier Materials, Water vapor proof, Greaseproof, Flexible, Heat-SealableMIL-PRF-131Brush, Cleaning, Aircraft, Metal BrighteningMIL-B-23958Brush, Plater's, Hand (Curved Handle Type) (Repl. H-B-178)CID A-A-3118Brushing, Acid, SwabbingCID A-A-3118Chemical Conversion Coatings for Aluminum and Aluminum AlloysMIL-DTL-5541Chemical Conversion Materials for Coating Aluminum and Aluminum Alloys (Repl.MIL-DTL-581706Chemicals, Analytical (Repl. O-E-760)CID A-A-51822Chromium Trioxide, Technical (Repl. O-C-303)CID A-A-55827Cleaner, Non-Aqueous, Low-VOC, Hap-Free (Repl. P-D-680)MIL-PRF-85570Cleaning Compound, Acrospace EquipmentMIL-PRF-85737Cleaning Compound, Aircraft ExteriorMIL-PRF-85570Cleaning Compound, Aircraft SteriorCID A-A-59281Cloth, Cheese, Cotton, Bleached and UnbleachedCCC-C-440Cloth, Scleaning, Low-LintCID A-A-59166Coating Compound, Non-Slip, for Walkways (Repl. MIL-W-5044)CID A-A-59166Coating System, Ship Structures (Repl. MIL-PRF-23236)MIL-PRF-23236Coating, Spexm, Ship Structures (Repl. MIL-PRF-23236)MIL-PRF-23236Coating, Epoxy, High SolidsMIL-PRF-22750Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-32231Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85285Coating, Polyurethane, Aircraft and Support EquipmentSAE AMS-C		PN 38987
Barrier Materials, Greaseproof, Waterproof, Flexible, Heat-SealableMIL-PRF-121Barrier Materials, Water vapor proof, Greaseproof, Flexible, Heat-SealableMIL-PRF-131Brush, Cleaning, Aircraft, Metal BrighteningMIL-B23958Brush, Plater's, Hand (Curved Handle Type) (Repl. H-B-178)CID A-A-3118Brushing, Acid, SwabbingCID A-A-289Chemical Conversion Coatings for Aluminum and Aluminum AlloysMIL-DTL-5541MIL-C-81706)CID A-A-289Chemical, Analytical (Repl. O-E-760)CID A-A-59282Chromium Trioxide, Technical (Repl. O-C-303)CID A-A-55827Cleaning Compound, Aerospace EquipmentMIL-PRF-87937Cleaning Compound, Aircraft ExteriorMIL-PRF-87937Cleaning Compound, Aircraft ExteriorCID A-A-59281Cloth, Cheese, Cotton, Bleached and UnbleachedCCC-C-440Cloth, Scleaning, Low-LintCID A-A-59263Coating Compound, Non-Slip, for Walkways (Repl. MIL-W-5044)CID A-A-59166Coating System, Polyurethane, Non-Yellowing White, Rain Erosion Resistant, Thermally Reflective (Repl. MIL-C-83445)SAE AMS-C-83445Coating System, Ship Structures (Repl. MIL-PRF-23236)MIL-PRF-23236Coating, Epoxy, High SolidsMIL-PRF-23236Coating, Epoxy, High SolidsMIL-PRF-23236Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85285Coating, Polyurethane, Aircraft and Support EquipmentSAE AMS-C-83231Coating, Polyurethane, Aircraft and Support EquipmentSAE AMS-C-83231Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile PlasticSAE AMS-C-83231 </td <td>Adnesive Remover</td> <td>PN 8098</td>	Adnesive Remover	PN 8098
Barrier Materials, Water vapor proof, Greaseproof, Flexible, Heat-SealableMIL-PRF-131Brush, Cleaning, Aircraft, Metal BrighteningMIL-B-23958Brush, Plater's, Hand (Curved Handle Type) (Repl. H-B-178)CID A-A-3118Brushing, Acid, SwabbingCID A-A-289Chemical Conversion Coatings for Aluminum and Aluminum AlloysMIL-DTL-5541Chemical Conversion Materials for Coating Aluminum and Aluminum Alloys (Repl.MIL-DTL-81706MIL-C-81706)CID A-A-59282Chemicals, Analytical (Repl. O-E-760)CID A-A-59282Chomium Trioxide, Technical (Repl. O-C-303)CID A-A-59282Cleaning Compound, Aerospace EquipmentMIL-PRF-87937Cleaning Compound, Aerospace EquipmentMIL-PRF-87937Cleaning Compound, Aircraft ExteriorMIL-PRF-87937Cleaning Compound, Aircraft ExteriorCID A-A-59281Cloth, Cheese, Cotton, Bleached and UnbleachedCCC -C-440Cloths, Cleaning, Low-LintCID A-A-59166Coating Compound, Non-Slip, for Walkways (Repl. MIL-W5044)CID A-A-59166Coating System, Polyurethane, Non-Yellowing White, Rain Erosion Resistant, Thermally Reflective (Repl. MIL-C-27725)SAE AMS-C-27725Coating System, Ship Structures (Repl. MIL-PRF-23236)MIL-PRF-23236Coating, Corrosion Preventive, Polyurethane, for Aircraft Integral Fuel Tanks (for Use to 250 °F (121 °C)) (Repl. MIL-C-27725)MIL-PRF-22750Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85285Coating, Polyurethane, Aircraft and Support EquipmentSAE AMS-C-83231Coating, Polyurethane, Aircraft and Support EquipmentSAE AMS-C-83231 <t< td=""><td>Anodic Coatings for Aluminum and Aluminum Alloy</td><td>MIL-PRF-8625</td></t<>	Anodic Coatings for Aluminum and Aluminum Alloy	MIL-PRF-8625
Brush, Cleaning, Aircraft, Metal BrighteningMIL-B-23958Brush, Plater's, Hand (Curved Handle Type) (Repl. H-B-178)CID A-A-3118Brushing, Acid, SwabbingCID A-A-289Chemical Conversion Coatings for Aluminum and Aluminum AlloysMIL-DTL-5541Chemical Conversion Materials for Coating Aluminum and Aluminum Alloys (Repl.MIL-DTL-81706Chemicals, Analytical (Repl. O-E-760)CID A-A-59282Chromium Trioxide, Technical (Repl. O-C-303)CID A-A-55827Cleaning Compound, Aerospace EquipmentMIL-PRF-82295Cleaning Compound, Aircraft ExteriorMIL-PRF-85570Cleaning Compound, Aircraft ExteriorMIL-PRF-85570Cleaning Compound, Solvent Mixtures (Repl. MIL-C-38736)CID A-A-59281Cloth, Cheese, Cotton, Bleached and UnbleachedCCC-C-440Cloths, Cleaning, Low-LintCID A-A-59233Coating Compound, Non-Slip, for Walkways (Repl. MIL-W-5044)CID A-A-59166Coating System, Ship Structures (Repl. MIL-PRF-23236)CID A-A-59166Coating System, Ship Structures (Repl. MIL-PRF-23236)SAE AMS-C-83445Coating System, Ship Structures (Repl. MIL-PRF-23236)MIL-PRF-23236Coating, Epoxy, High SolidsMIL-PRF-23236Coating, Epoxy, High SolidsMIL-PRF-22750Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85285Coating, Polyurethane, Aircraft and Support EquipmentSAE AMS-C-83231Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-6799	Barrier Materials, Greaseproof, Waterproof, Flexible, Heat-Sealable	MIL-PRF-121
Brush, Plater's, Hand (Curved Handle Type) (Repl. H-B-178)CID A-A-3118Brushing, Acid, SwabbingCID A-A-289Chemical Conversion Coatings for Aluminum and Aluminum AlloysMIL-DTL-5541Chemical Conversion Materials for Coating Aluminum and Aluminum Alloys (Repl. MIL-C-81706)MIL-DTL-81706Chemicals, Analytical (Repl. O-E-760)CID A-A-59282Chromium Trioxide, Technical (Repl. O-C-303)CID A-A-55827Cleaner, Non-Aqueous, Low-VOC, Hap-Free (Repl. P-D-680)MIL-PRF-87937Cleaning Compound, Aerospace EquipmentMIL-PRF-85700Cleaning Compound, Aircraft ExteriorMIL-PRF-85701Cloth, Cheese, Cotton, Bleached and UnbleachedCCC-C-440Cloth, Cleaning, Low-LintCID A-A-59232Coating Compound, Metal Pretreatment, Resin-AcidMIL-C-8514Coating Compound, Non-Slip, for Walkways (Repl. MIL-W-5044)CID A-A-59166Coating System, Polyurethane, Non-Yellowing White, Rain Erosion Resistant, Ther- mally Reflective (Repl. MIL-C-27725)SAE AMS-C-83445Coating, Corrosion Preventive, Polyurethane, for Aircraft Integral Fuel Tanks (for Use to 250 °F (121 °C)) (Repl. MIL-C-27725)MIL-PRF-23236Coating, Poyurethane, Aircraft and Support Equipment Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85285Coating, Polyurethane, Aircraft and Support Equipment Coating, Polyurethane, Rin Erosion Resistant, for Exterior Aircraft and Missile Plastic Parts (Repl. MIL-C-83231)MIL-PRF-6799	Barrier Materials, Water vapor proof, Greaseproof, Flexible, Heat-Sealable	MIL-PRF-131
Brushing, Acid, SwabbingCID A-A-289Chemical Conversion Coatings for Aluminum and Aluminum AlloysMIL-DTL-5541Chemical Conversion Materials for Coating Aluminum and Aluminum Alloys (Repl.MIL-DTL-81706MIL-C-81706)CID A-A-59282Chemicals, Analytical (Repl. O-E-760)CID A-A-55827Chemicals, Chronium Trioxide, Technical (Repl. O-C-303)CID A-A-55827Cleaner, Non-Aqueous, Low-VOC, Hap-Free (Repl. P-D-680)MIL-PRF-32295Cleaning Compound, Aerospace EquipmentMIL-PRF-87937Cleaning Compound, Aircraft ExteriorMIL-PRF-85570Cleaning Compound, Solvent Mixtures (Repl. MIL-C-38736)CID A-A-59281Cloth, Cheese, Cotton, Bleached and UnbleachedCCC -C-440Cloths, Cleaning Compound, Metal Pretreatment, Resin-AcidMIL-C-8514Coating Compound, Non-Slip, for Walkways (Repl. MIL-W5044)CID A-A-59166Coating System, Polyurethane, Non-Yellowing White, Rain Erosion Resistant, Thermally Reflective (Repl. MIL-C-83745)MIL-PRF-23236Coating System, Ship Structures (Repl. MIL-PRF-23236)MIL-PRF-23236Coating, Corrosion Preventive, Polyurethane, for Aircraft Integral Fuel Tanks (for Use to 250 °F (121 °C)) (Repl. MIL-C-27725)MIL-PRF-22750Coating, Epoxy, High SolidsMIL-PRF-22750Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85285Coating, Polyurethane, Aircraft and Support EquipmentSAE AMS-C-83231Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile PlasticSAE AMS-C-83231Coating, Sprayable, Strippable, Protective, Water EmulsionMIL-PRF-6799	Brush, Cleaning, Aircraft, Metal Brightening	MIL-B-23958
Chemical Conversion Coatings for Aluminum and Aluminum AlloysMIL-DTL-5541Chemical Conversion Materials for Coating Aluminum and Aluminum Alloys (Repl.MIL-DTL-81706MIL-C-81706)CID A-A-59282Chemicals, Analytical (Repl. O-E-760)CID A-A-55827Cleaner, Non-Aqueous, Low-VOC, Hap-Free (Repl. P-D-680)MIL-PRF-32295Cleaning Compound, Aerospace EquipmentMIL-PRF-87937Cleaning Compound, Aircraft ExteriorMIL-PRF-85570Cleaning Compound, Solvent Mixtures (Repl. MIL-C-38736)CID A-A-59281Cloth, Cheese, Cotton, Bleached and UnbleachedCCC-C-440Cloths, Cleaning, Low-LintCID A-A-59323Coating Compound, Metal Pretreatment, Resin-AcidMIL-C-8514Coating System, Polyurethane, Non-Yellowing White, Rain Erosion Resistant, Ther- mally Reflective (Repl. MIL-C-83445)SAE AMS-C-83445Coating System, Ship Structures (Repl. MIL-PRF-3226)MIL-PRF-23236Coating, Corrosion Preventive, Polyurethane, for Aircraft Integral Fuel Tanks (for Use to 250 °F (121 °C)) (Repl. MIL-C-27725)MIL-PRF-22750Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85285Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85281Coating, Polyurethane, Aircraft and Support EquipmentSAE AMS-C-83231Coating, Sprayable, Strippable, Protective, Water EmulsionMIL-PRF-6799	Brush, Plater's, Hand (Curved Handle Type) (Repl. H-B-178)	CID A-A-3118
Chemical Conversion Materials for Coating Aluminum and Aluminum Alloys (Repl. MIL-C-81706)MIL-DTL-81706MIL-C-81706)CID A-A-59282Chemicals, Analytical (Repl. O-E-760)CID A-A-59282Chromium Trioxide, Technical (Repl. O-C-303)CID A-A-55827Cleaner, Non-Aqueous, Low-VOC, Hap-Free (Repl. P-D-680)MIL-PRF-32295Cleaning Compound, Aerospace EquipmentMIL-PRF-87937Cleaning Compound, Aircraft ExteriorMIL-PRF-85570Cleaning Compound, Solvent Mixtures (Repl. MIL-C-38736)CID A-A-59281Cloth, Cheese, Cotton, Bleached and UnbleachedCCC-C-440Cloths, Cleaning, Low-LintCID A-A-59233Coating Compound, Metal Pretreatment, Resin-AcidMIL-C-8514Coating Compound, Non-Slip, for Walkways (Repl. MIL-W-5044)CID A-A-59166Coating System, Polyurethane, Non-Yellowing White, Rain Erosion Resistant, Thermally Reflective (Repl. MIL-C-87725)SAE AMS-C-83445Coating System, Ship Structures (Repl. MIL-PRF-23236)MIL-PRF-23236Coating, Corrosion Preventive, Polyurethane, for Aircraft Integral Fuel Tanks (for Use to 250 °F (121 °C)) (Repl. MIL-C-27725)MIL-PRF-22750Coating, Fpoxy, High SolidsMIL-PRF-22750Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85285Coating, Polyurethane, Aircraft and Support EquipmentSAE AMS-C-83231Coating, Polyurethane, Aircraft and Support EquipmentSAE AMS-C-83231Coating, Sprayable, Strippable, Protective, Water EmulsionMIL-PRF-6799	Brushing, Acid, Swabbing	CID A-A-289
MIL-C-81706)CID A-A-59282Chromium Trioxide, Technical (Repl. O-C-303)CID A-A-55827Cleaner, Non-Aqueous, Low-VOC, Hap-Free (Repl. P-D-680)MIL-PRF-32295Cleaning Compound, Aerospace EquipmentMIL-PRF-87937Cleaning Compound, Aircraft ExteriorMIL-PRF-87937Cleaning Compound, Solvent Mixtures (Repl. MIL-C-38736)CID A-A-59281Cloth, Cheese, Cotton, Bleached and UnbleachedCCC-C-440Cloths, Cleaning, Low-LintCID A-A-59323Coating Compound, Netal Pretreatment, Resin-AcidMIL-C-8514Coating Compound, Non-Slip, for Walkways (Repl. MIL-W-5044)CID A-A-59166Coating System, Polyurethane, Non-Yellowing White, Rain Erosion Resistant, Thermally Reflective (Repl. MIL-C-83445)SAE AMS-C-83445Coating System, Ship Structures (Repl. MIL-PRF-23236)MIL-PRF-23236Coating, Corrosion Preventive, Polyurethane, for Aircraft Integral Fuel Tanks (for Use to 250 °F (121 °C)) (Repl. MIL-C-27725)SAE AMS-C-27725Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-22750Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile PlasticSAE AMS-C-83231Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile PlasticSAE AMS-C-83231Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile PlasticSAE AMS-C-83231Coating, Sprayable, Strippable, Protective, Water EmulsionMIL-PRF-6799	Chemical Conversion Coatings for Aluminum and Aluminum Alloys	MIL-DTL-5541
Chemicals, Analytical (Repl. O-E-760)CID A-A-59282Chromium Trioxide, Technical (Repl. O-C-303)CID A-A-55827Cleaner, Non-Aqueous, Low-VOC, Hap-Free (Repl. P-D-680)MIL-PRF-32295Cleaning Compound, Aerospace EquipmentMIL-PRF-87937Cleaning Compound, Aircraft ExteriorMIL-PRF-85570Cleaning Compound, Solvent Mixtures (Repl. MIL-C-38736)CID A-A-59281Cloth, Cheese, Cotton, Bleached and UnbleachedCCC-C-440Cloths, Cleaning, Low-LintCID A-A-59323Coating Compound, Metal Pretreatment, Resin-AcidMIL-C-8514Coating Compound, Non-Slip, for Walkways (Repl. MIL-W-5044)CID A-A-59166Coating System, Polyurethane, Non-Yellowing White, Rain Erosion Resistant, Thermally Reflective (Repl. MIL-C-83445)SAE AMS-C-83445Coating, System, Ship Structures (Repl. MIL-PRF-23236)MIL-PRF-23236Coating, Gorrosion Preventive, Polyurethane, for Aircraft Integral Fuel Tanks (for Use to 250 °F (121 °C)) (Repl. MIL-C-27725)MIL-PRF-22750Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85285Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile PlasticSAE AMS-C-83231Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile PlasticSAE AMS-C-83231Coating, Sprayable, Strippable, Protective, Water EmulsionMIL-PRF-6799		MIL-DTL-81706
Cleaner, Non-Aqueous, Low-VOC, Hap-Free (Repl. P-D-680)MIL-PRF-32295Cleaning Compound, Aerospace EquipmentMIL-PRF-87937Cleaning Compound, Aircraft ExteriorMIL-PRF-85570Cleaning Compound, Solvent Mixtures (Repl. MIL-C-38736)CID A-A-59281Cloth, Cheese, Cotton, Bleached and UnbleachedCCC-C-440Cloths, Cleaning, Low-LintCID A-A-59323Coating Compound, Metal Pretreatment, Resin-AcidMIL-C-8514Coating Compound, Non-Slip, for Walkways (Repl. MIL-W-5044)CID A-A-59166Coating System, Polyurethane, Non-Yellowing White, Rain Erosion Resistant, Ther- mally Reflective (Repl. MIL-C-83445)SAE AMS-C-83445Coating, Corrosion Preventive, Polyurethane, for Aircraft Integral Fuel Tanks (for Use to 250 °F (121 °C)) (Repl. MIL-C-27725)MIL-PRF-23236Coating, Poyyurethane, Aircraft and Support Equipment Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85285Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile Plastic Parts (Repl. MIL-C-83231)SAE AMS-C-83231Coating, Sprayable, Strippable, Protective, Water EmulsionMIL-PRF-6799		CID A-A-59282
Cleaning Compound, Aerospace EquipmentMIL-PRF-87937Cleaning Compound, Aircraft ExteriorMIL-PRF-85570Cleaning Compound, Solvent Mixtures (Repl. MIL-C-38736)CID A-A-59281Cloth, Cheese, Cotton, Bleached and UnbleachedCCC-C-440Cloths, Cleaning, Low-LintCID A-A-59323Coating Compound, Metal Pretreatment, Resin-AcidMIL-C-8514Coating Compound, Non-Slip, for Walkways (Repl. MIL-W-5044)CID A-A-59166Coating System, Polyurethane, Non-Yellowing White, Rain Erosion Resistant, Ther- mally Reflective (Repl. MIL-C-83445)SAE AMS-C-83445Coating System, Ship Structures (Repl. MIL-PRF-23236)MIL-PRF-23236Coating, Corrosion Preventive, Polyurethane, for Aircraft Integral Fuel Tanks (for Use to 250 °F (121 °C)) (Repl. MIL-C-27725)SAE AMS-C-27725Coating, Heat ResistingTT-P-28Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85285Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile Plastic Parts (Repl. MIL-C-83231)SAE AMS-C-83231Coating, Sprayable, Strippable, Protective, Water EmulsionMIL-PRF-6799	Chromium Trioxide, Technical (Repl. O-C-303)	CID A-A-55827
Cleaning Compound, Aircraft ExteriorMIL-PRF-85570Cleaning Compound, Solvent Mixtures (Repl. MIL-C-38736)CID A-A-59281Cloth, Cheese, Cotton, Bleached and UnbleachedCCC-C-440Cloths, Cleaning, Low-LintCID A-A-59323Coating Compound, Metal Pretreatment, Resin-AcidMIL-C-8514Coating Compound, Non-Slip, for Walkways (Repl. MIL-W-5044)CID A-A-59166Coating System, Polyurethane, Non-Yellowing White, Rain Erosion Resistant, Thermally Reflective (Repl. MIL-C-83445)SAE AMS-C-83445Coating System, Ship Structures (Repl. MIL-PRF-23236)MIL-PRF-23236Coating, Corrosion Preventive, Polyurethane, for Aircraft Integral Fuel Tanks (for Use to 250 °F (121 °C)) (Repl. MIL-C-27725)SAE AMS-C-27725Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-22750Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile PlasticSAE AMS-C-83231Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile PlasticSAE AMS-C-83231Coating, Sprayable, Strippable, Protective, Water EmulsionMIL-PRF-6799	Cleaner, Non-Aqueous, Low-VOC, Hap-Free (Repl. P-D-680)	MIL-PRF-32295
Cleaning Compound, Solvent Mixtures (Repl. MIL-C-38736)CID A-A-59281Cloth, Cheese, Cotton, Bleached and UnbleachedCCC-C-440Cloths, Cleaning, Low-LintCID A-A-59323Coating Compound, Metal Pretreatment, Resin-AcidMIL-C-8514Coating Compound, Non-Slip, for Walkways (Repl. MIL-W-5044)CID A-A-59166Coating System, Polyurethane, Non-Yellowing White, Rain Erosion Resistant, Thermally Reflective (Repl. MIL-C-83445)SAE AMS-C-83445Coating System, Ship Structures (Repl. MIL-PRF-23236)MIL-PRF-23236Coating, Corrosion Preventive, Polyurethane, for Aircraft Integral Fuel Tanks (for Use to 250 °F (121 °C)) (Repl. MIL-C-27725)SAE AMS-C-27725Coating, Heat ResistingTT-P-28Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85285Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile Plastic Parts (Repl. MIL-C-83231)SAE AMS-C-83231Coating, Sprayable, Strippable, Protective, Water EmulsionMIL-PRF-6799	Cleaning Compound, Aerospace Equipment	MIL-PRF-87937
Cloth, Cheese, Cotton, Bleached and UnbleachedCCC-C-440Cloths, Cleaning, Low-LintCID A-A-59323Coating Compound, Metal Pretreatment, Resin-AcidMIL-C-8514Coating Compound, Non-Slip, for Walkways (Repl. MIL-W-5044)CID A-A-59166Coating System, Polyurethane, Non-Yellowing White, Rain Erosion Resistant, Thermally Reflective (Repl. MIL-C-83445)SAE AMS-C-83445Coating System, Ship Structures (Repl. MIL-PRF-23236)MIL-PRF-23236Coating, Corrosion Preventive, Polyurethane, for Aircraft Integral Fuel Tanks (for Use to 250 °F (121 °C)) (Repl. MIL-C-27725)SAE AMS-C-27725Coating, Heat ResistingMIL-PRF-22750Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85285Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile PlasticSAE AMS-C-83231Coating, Sprayable, Strippable, Protective, Water EmulsionMIL-PRF-6799	Cleaning Compound, Aircraft Exterior	MIL-PRF-85570
Cloths, Cleaning, Low-LintCID A-A-59323Coating Compound, Metal Pretreatment, Resin-AcidMIL-C-8514Coating Compound, Non-Slip, for Walkways (Repl. MIL-W-5044)CID A-A-59166Coating System, Polyurethane, Non-Yellowing White, Rain Erosion Resistant, Ther- mally Reflective (Repl. MIL-C-83445)SAE AMS-C-83445Coating System, Ship Structures (Repl. MIL-PRF-23236)MIL-PRF-23236Coating, Corrosion Preventive, Polyurethane, for Aircraft Integral Fuel Tanks (for Use to 250 °F (121 °C)) (Repl. MIL-C-27725)SAE AMS-C-27725Coating, Heat ResistingMIL-PRF-22750Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85285Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile Plastic Parts (Repl. MIL-C-83231)SAE AMS-C-83231Coating, Sprayable, Strippable, Protective, Water EmulsionMIL-PRF-6799	Cleaning Compound, Solvent Mixtures (Repl. MIL-C-38736)	CID A-A-59281
Coating Compound, Metal Pretreatment, Resin-AcidMIL-C-8514Coating Compound, Non-Slip, for Walkways (Repl. MIL-W-5044)CID A-A-59166Coating System, Polyurethane, Non-Yellowing White, Rain Erosion Resistant, Ther- mally Reflective (Repl. MIL-C-83445)SAE AMS-C-83445Coating System, Ship Structures (Repl. MIL-PRF-23236)MIL-PRF-23236Coating, Corrosion Preventive, Polyurethane, for Aircraft Integral Fuel Tanks (for Use to 250 °F (121 °C)) (Repl. MIL-C-27725)SAE AMS-C-27725Coating, Epoxy, High SolidsMIL-PRF-22750Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85285Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile PlasticSAE AMS-C-83231Coating, Sprayable, Strippable, Protective, Water EmulsionMIL-PRF-6799	Cloth, Cheese, Cotton, Bleached and Unbleached	CCC-C-440
Coating Compound, Non-Slip, for Walkways (Repl. MIL-W-5044)CID A-A-59166Coating System, Polyurethane, Non-Yellowing White, Rain Erosion Resistant, Ther- mally Reflective (Repl. MIL-C-83445)SAE AMS-C-83445Coating System, Ship Structures (Repl. MIL-PRF-23236)MIL-PRF-23236Coating, Corrosion Preventive, Polyurethane, for Aircraft Integral Fuel Tanks (for Use to 250 °F (121 °C)) (Repl. MIL-C-27725)SAE AMS-C-27725Coating, Epoxy, High SolidsMIL-PRF-22750Coating, Polyurethane, Aircraft and Support EquipmentTT-P-28Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile PlasticSAE AMS-C-83231Coating, Sprayable, Strippable, Protective, Water EmulsionMIL-PRF-6799	Cloths, Cleaning, Low-Lint	CID A-A-59323
Coating System, Polyurethane, Non-Yellowing White, Rain Erosion Resistant, Ther- mally Reflective (Repl. MIL-C-83445)SAE AMS-C-83445Coating System, Ship Structures (Repl. MIL-PRF-23236)MIL-PRF-23236Coating, Corrosion Preventive, Polyurethane, for Aircraft Integral Fuel Tanks (for Use to 250 °F (121 °C)) (Repl. MIL-C-27725)SAE AMS-C-27725Coating, Epoxy, High SolidsMIL-PRF-22750Coating, Heat ResistingTT-P-28Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85285Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile PlasticSAE AMS-C-83231Coating, Sprayable, Strippable, Protective, Water EmulsionMIL-PRF-6799	Coating Compound, Metal Pretreatment, Resin-Acid	MIL-C-8514
mally Reflective (Repl. MIL-C-83445)MIL-PRF-23236)Coating System, Ship Structures (Repl. MIL-PRF-23236)MIL-PRF-23236Coating, Corrosion Preventive, Polyurethane, for Aircraft Integral Fuel Tanks (for Use to 250 °F (121 °C)) (Repl. MIL-C-27725)SAE AMS-C-27725Coating, Epoxy, High SolidsMIL-PRF-22750Coating, Heat ResistingTT-P-28Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85285Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile PlasticSAE AMS-C-83231Parts (Repl. MIL-C-83231)MIL-PRF-6799	Coating Compound, Non-Slip, for Walkways (Repl. MIL-W-5044)	CID A-A-59166
Coating, Corrosion Preventive, Polyurethane, for Aircraft Integral Fuel Tanks (for Use to 250 °F (121 °C)) (Repl. MIL-C-27725)SAE AMS-C-27725Coating, Epoxy, High SolidsMIL-PRF-22750Coating, Heat ResistingTT-P-28Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85285Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile PlasticSAE AMS-C-83231Parts (Repl. MIL-C-83231)MIL-PRF-6799		SAE AMS-C-83445
to 250 °F (121 °C)) (Repl. MIL-C-27725)MIL-PRF-22750Coating, Epoxy, High SolidsMIL-PRF-22750Coating, Heat ResistingTT-P-28Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85285Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile PlasticSAE AMS-C-83231Parts (Repl. MIL-C-83231)MIL-PRF-6799	Coating System, Ship Structures (Repl. MIL-PRF-23236)	MIL-PRF-23236
Coating, Heat ResistingTT-P-28Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85285Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile PlasticSAE AMS-C-83231Parts (Repl. MIL-C-83231)NIL-PRF-6799		SAE AMS-C-27725
Coating, Heat ResistingTT-P-28Coating, Polyurethane, Aircraft and Support EquipmentMIL-PRF-85285Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile PlasticSAE AMS-C-83231Parts (Repl. MIL-C-83231)NIL-PRF-6799		MIL-PRF-22750
Coating, Polyurethane, Rain Erosion Resistant, for Exterior Aircraft and Missile PlasticSAE AMS-C-83231Parts (Repl. MIL-C-83231)Coating, Sprayable, Strippable, Protective, Water EmulsionMIL-PRF-6799		TT-P-28
Parts (Repl. MIL-C-83231)MIL-PRF-6799Coating, Sprayable, Strippable, Protective, Water EmulsionMIL-PRF-6799	Coating, Polyurethane, Aircraft and Support Equipment	MIL-PRF-85285
		SAE AMS-C-83231
Colors, Interior, Aircraft, Requirements for MIL-C-8779	Coating, Sprayable, Strippable, Protective, Water Emulsion	MIL-PRF-6799
	Colors, Interior, Aircraft, Requirements for	MIL-C-8779

#### Table 1-1. Consumable Materials List

Nomenclature	Specification Number
Conversion Coating, Non-Chromated	RECC 3021
Corrosion Preventive Compound, Water Displacing, Transparent	MIL-DTL-85054
Corrosion Removing Compound, for Aircraft Surfaces (Repl. MIL-C-38334)	SAE AMS-1640
Degreasing Solvent (Repl. P-D-680)	MIL-PRF-680
Deoxidizer, Non-Chromated	RECC 1015
	PN 3950
Edge Sealer	PN 4150
Engineered Media for Removal of Organic Coatings	MIL-DTL-85891
Epoxy Primer, Non-Chromated	02GN093
Fluorocarbons and Other Refrigerants	CID A-A-58060
Grading of Certain Abrasive Grain on Coated Abrasive Products (Repl. GGG-C-520)	ANSI B74.18
Hydraulic Fluid, Petroleum, Inhibited	MIL-PRF-17672
Isopropyl Alcohol	TT-I-735
Lubricating Oil, Aircraft Turbine Engine, Synthetic Base	MIL-PRF-7808
Lubricating Oil, General Purpose, Preservative (Water-Displacing, Low Temperature)	MIL-PRF-32033
Master Painters Institute, Alkyd, Exterior, Gloss, (MPI Gloss Level 6) (Repl. TT-E-489)	MPI No. 6
Master Painters Institute, Alkyd, Exterior, Semi-gloss, (MPI Gloss Level 5) (Repl.	MPI No. 94
ТТ-Е-489)	
Naphtha, Aliphatic	TT-N-95
Parachlorobenzotrifluoride	PCBTF
Plastic Material, Pressure Sensitive Adhesive, for Aerospace Identification and Marking (Repl. MIL-P-38477)	CID A-A-59485
Polyurethane Foam, Rigid or Flexible, for Packaging	MIL-PRF-26514
Primer Coating, Alkyd Base, One Component	TT-P-1757
Primer Coating, Polyurethane, Elastomeric, High Solids	TT-P-2760
Primer Coating, Magnesium Rich, Non-Chromated	AERODUR 2100 MGRP
Primer Coatings, Epoxy, High Solids	MIL-PRF-23377
Primer Coatings, Epoxy, Waterborne	MIL-PRF-85582
Primer, Polysulfide	PR-1432GV
Processes for Pretreatment and Prevention of Corrosion on Magnesium Alloy (Repl. MIL-M-3171)	SAE AMS-M-3171
Rags, Wiping (Cotton and Cotton Synthetic)	CID A-A-2522
Resin Coating, Permanent, for Engine Components and Metal Parts	MIL-PRF-3043
Sealant, Corrosion Inhibitive	MIL-PRF-81733
Spray Kit, Self-Pressurized (Repl. MIL-S-22805)	SAE AS-22805
Standard Specification for Acetone, Technical (Repl. O-A-51)	ASTM-D329
Tapes, Pressure Sensitive Adhesive, for Masking During Paint Removal Operations (Repl. MIL-T-23397)	SAE AMS-T-23397
Tapes, Pressure-Sensitive Adhesive, Masking, Non-Staining for Aircraft Painting Applications (Repl. MIL-T-21595)	SAE AMS-T-21595
Thinner for Phenol-Formaldehyde and Medium Oil and Styrenated Alkyd Paints and Varnishes (Repl. TT-T-306)	CID A-A-3007
Thinner, Aircraft Coating	MIL-T-81772
Thinner, Purging	TT-T-2935
Tiecoat, Non Chromated	AEROGLAZE 97XX
Varnish, Oil, Spar (Repl. TT-V-119)	CID A-A-1800
Wool, Metallic (Copper and Aluminum) (Repl. FF-W-1825 aluminum type)	CID A-A-1044
Wool, Steel (Repl. FF-W-1825 steel type)	CID A-A-1043
(1001, 5001 (10p1, 11 - 11-1025 5001 type)	

#### Table 1-1. Consumable Materials List - Continued

### CHAPTER 2 ORGANIC FINISH SYSTEM REMOVAL

#### 2.1 INTRODUCTION.

The most important factor in removal of organic finish systems (coatings/paints) is complete removal without damaging surfaces on which they are applied. A variety of materials and either chemical or mechanical methods can remove finish systems. In choosing a material and a method, a compromise between maximum removal power and maximum protection for the equipment being stripped must be made. Accessibility of areas to be stripped can dictate the types of materials and methods to be used. For these reasons, only those materials and methods described in this chapter, subject to noted restrictions, are authorized for general use in organic finish system removal from Air Force (AF) equipment. Adherence to removal procedures and their sequence of performance in this chapter is mandatory. Other removal materials and methods can be authorized for limited and specific applications, but only when specifically approved and defined in system peculiar aircraft and/or equipment Technical Order (TO) s. The term "Depot Level" in this chapter refers to organizations and facilities which are involved in complete aircraft stripping operations on a routine, if not daily basis. This includes the Air Logistics Centers (ALC) and contract stripping operations. It does not include field level maintenance facilities.

#### NOTE

National Stock Numbers (NSN), if assigned, for chemical removers, abrasives, and other materials and equipment authorized in this chapter are in Federal Stock Classes (FSC) 5345/50, 6850, and 8135 and FSC 7500, 7900, and 8000. Consult the current Federal Logistics Data (FED LOG) and General Services Administration (GSA) Catalog and/or the DO43 System to convert specification and Part Numbers (PN) to NSNs and for ordering and pricing information and shelf life codes.

#### 2.2 GENERAL.



- Engineered Media Blasting (EMB) can peen or smear soft metals therefore it shall not be used to remove paint from aluminum or magnesium components requiring subsequent fluorescent penetrant inspection unless specifically directed by the component e-coat. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- Distortion caused by EMB could result in limited crack/flaw detection. Failure to comply could result in damage to, or destruction of, equipment or loss of mission.

#### NOTE

Each time an aircraft is completely depainted, the following information shall be documented in the aircraft historical record, Air Force Technical Order (AFTO) Form 95-1. Type of paint removal process used, 2. Where accomplished, and 3. Date accomplished.

Organic finish systems shall be removed from Air Force aircraft and equipment only when the condition of deterioration of the system indicates the need for removal or when required in a system peculiar technical manual to perform a specified inspection of the underlying structure. This applies to stripping of components and small areas of aircraft and equipment as well as to the entire surface of aircraft or equipment. Removal of the entire exterior organic finish system from aircraft shall be accomplished in accordance with the criteria specified in this manual and the Aircraft System Program Manager's Service Life Paint Plan. Prior to any organic finish system removal, the following steps shall be taken in all cases:

a. Ensure that the facility to be used for finish system removal operations meets all the safety, fire precaution, health promotion, and environmental requirements in applicable Air Force Instruction (AFI) and National Fire Protection Association (NFPA) standards. Precautionary measures shall be taken to prevent paint and paint removal waste from contaminating air, water, or soil. Prior to performance of finish system removal operations, all personnel must be trained on Personal Protective Equipment (PPE) as required in AFI 48-137 and AFMAN 91-203. Personnel who are not wearing appropriate PPE shall not perform finish system removal operations.

#### TO 1-1-8

- b. Ensure that the facility to be used for finish system removal operations provides the proper precautionary measures for disposal of finish system removal waste products as required by AFI 32-7001, AFMAN 32-1067, and AFMAN 32-7002 to prevent contamination of lakes, rivers, and streams. Many chemicals used in finish system removal operations and finish system residues require special treatment and control prior to disposal. Disposal shall be accomplished under the direction of the Base Safety Office, the Base Civil Engineer (BCE) and Bioenvironmental Engineer, and the Environmental Management Office in a manner which will not violate local, state, and federal pollution regulations. Consult AFMAN 32-1067, AFMAN 32-7002, AFMAN 91-203, AFI 32-7001, and AFPAM 90-803 for detailed information on disposal of finish system removal waste.
- c. Determine the type of organic finish system to be removed so that the proper material and method for removal can be chosen from those listed in this chapter. Consult aircraft and/or equipment system peculiar TOs and drawings, component drawings, aircraft historical records (AFTO Form 95), and/or the aircraft exterior finish identification marking on the aircraft (reference <u>Chapter 8</u>) to help in this determination. If the finish system cannot be determined from these documents or they are not available, determine the finish system as follows:



#### ACETONE, ASTM-D329

- (1) Rub a small area on the surface from which the finish system is to be removed vigorously with a cotton rag wet with American Standard Test Method (ASTM) D 329 acetone. If the finish system is removed, it is a lacquer or alkyd enamel coating. If it is not removed, or very little is removed, it is a polyurethane or an epoxy coating.
- (2) For polyurethane and epoxy coatings, scrape off the topcoat from a small area down to the primer coating with a knife blade or razor blade. If the primer is rubbery and a tan-gray color, it is a polysulfide primer. If the primer is hard and either a yellow, light brown, or dark green (olive drab) color, it is either an epoxy or a polyure-thane primer.
- d. As a last step, study the removal operation to be performed and determine the most logical and efficient process for the job. If confined areas are involved, they shall be protected during a general overall removal operation, and shall be stripped using the special procedures in this chapter for these areas. If fiberglass, Kevlar®, or other composites are involved, they shall be stripped using the special procedures outlined later in this TO. For extensive removal operations, such as removal of the entire exterior finish system on aircraft and large pieces of equipment, a detailed sequential step-by-step process specification confirming to all of the requirements in this chapter shall be prepared and followed. All personnel involved with finish system removal shall be trained in and thoroughly familiar with all requirements of this chapter.

#### 2.3 PREPARATION FOR PAINT REMOVAL.

All aircraft will be de-energized per AFMAN 91-203, support equipment or components must be properly prepared for paint removal operations. Additionally, it is essential that all facilities and equipment for paint removal operations meet the safety and environmental requirements for the processes to be employed. Once the process for paint removal has been selected, use the following preparation requirements to prepare the aircraft, support equipment or component.

- a. Inspect all surfaces to be stripped for grease, oil, and dirt. These materials act as a barrier between the finish system and the chemical or abrasive removers and will contaminate recoverable air-driven abrasives. This can cause excessive man-hour expenditures, longer flow times, and additional waste generation during removal operations. Small amounts of these contaminants do not cause a problem; but if surfaces are exceptionally dirty, oily, or greasy, they shall be washed in accordance with TO 1-1-691 prior to removal operations. After washing, surfaces shall be either wiped dry, or sufficient time shall be allowed for them to air dry prior to removal operations. Small areas or components may be cleaned using a solvent wipe in accordance with <u>Chapter 3</u> of this TO.
- b. Surface temperatures of aircraft, equipment, or components from which the finish system is to be chemically removed shall be maintained to those recommended by product manufacturer or a recommended temperature range of 70 to 90 degrees Fahrenheit (°F) (21 to 32 degrees Celsius (°C)). While chemical removal can be accomplished within the ambient air temperature range of 50 to 100 °F (10 to 38 °C), severe difficulties will be encountered. Above 90 °F (32 °C), the solvents in chemical removers evaporate so rapidly that removal efficiency is severely reduced and its drying on the surface makes it severely difficult to clean the finish system and remover residue from surfaces. Below 70

°F (21 °C), chemical removal is very inefficient because the action of chemical removers is extremely slow. Both situations will increase flow-time, man-hours, and amount of chemical removed required for the chemical removal operations. If these temperatures cannot be maintained in an outdoor environment during the stripping process, the aircraft, equipment or components should be moved into a covered area to maintain proper surface temperatures.

c. For chemical removal operations with chlorinated paint removal materials, masking shall be accomplished with MIL-PRF-131, Class 1, barrier material and SAE AMS-T-23397, Type II, (72 hour protection) aluminum backed, pressure sensitive tape as specified in <u>Table 2-1</u>. These tapes provide adequate protection for the extended time period involved with this type of operation. The engineering support activity for this TO evaluates and approves tapes for this source control listing using the latest issuance of SAE AMS-T-23397. Chemical remover Cee-Bee<sup>TM</sup> R-256 is utilized as the testing materials for remover resistance of the tapes. Chemical remover Cee-Bee<sup>TM</sup> R-256 is the paint removal material being utilized to test tape resistance.



Benzyl Alcohol/Hydrogen Peroxide Activated (BA/HPA) paint removal materials are not approved for removing coating from magnesium substrates/components. Failure to comply could result in damage to, or destruction of, equipment or loss of mission.

- d. For chemical removal operations with BA/HPA paint removal materials, masking shall be accomplished with MIL-PRF-131, Class 1, barrier material, and SAE AMS-T-23397, Type II, (72 hour protection) Aluminum backed, pressure sensitive tape as specified in <u>Table 2-2</u>. These tapes provide adequate protection for the extended time period involved with this type of operation. The engineering support activity for this TO evaluates and approves tapes for this source control listing using the latest issuance of SAE AMS-T-23397. Contact AFCPCO at afcorr@us.af.mil if a copy of the above cited PD is required for reference. Chemical remover PPG Aerospace Eldorado PR-3500 is utilized as the test material for remover resistance of the tapes.
- e. For air and water-driven abrasive removal operations unless otherwise noted, the same materials listed for chemical removal operations shall be used for masking of areas which will not be exposed to direct impingement of the abrasive media to prevent abrasive media intrusion. Impact stripping tape shall be applied with hot glue to mask areas which will be exposed to direct impingement of the bicarbonate of soda and water and plastic blast media as an alternate for masking for EMB subject to the restrictions following.

Part Number	Item Name	NSN	Description
AFL301002560	Tape, Pressure Sensitive Adhesive	7510-01-622-1435	0.25 inch wide by 60 yards long aluminum tape.
AFL30100560	Tape, Pressure Sensitive Adhesive	NSL	0.50 inch wide by 60 yards long aluminum tape.
AFL3010160	Tape, Pressure Sensitive Adhesive	NSL	1.00 inch wide by 60 yards long aluminum tape.
AFL30101560	Tape, Pressure Sensitive Adhesive	NSL	1.50 inches wide by 60 yards long aluminum tape.
AFL3010260	Tape, Pressure Sensitive Adhesive	NSL	2.00 inches wide by 60 yard long aluminum tape.
AFL3010360	Tape, Pressure Sensitive Adhesive	7510-01-621-6206	3.00 inches wide by 60 yards long aluminum tape.
ALF3010460	Tape, Pressure Sensitive Adhesive	NSL	4.00 inch wide by 60 yards long aluminum tape.

Table 2-1.	Aluminum Backed Pressure	e Sensitive Tape for Use with	Chlorinated Chemical Removers
	i indiminum Ducheu i ressure	Sensitive rupe for else with	

PN	Item Name	NSN	Description
3M 425 ALF30000560A	Tape, Pressure Sensitive Adhesive	7510-01-670-5475	0.50 inch wide by 60 yards long aluminum tape
3M 425 ALF300007560A	Tape, Pressure Sensitive Adhesive	7510-01-670-5480	0.75 inch wide by 60 yards long aluminum tape
3M 425 ALF3000160A	Tape, Pressure Sensitive Adhesive	7510-01-670-5481	1.00 inch wide by 60 yards long aluminum tape
3M 425 ALF30001560A	Tape, Pressure Sensitive Adhesive	7510-01-670-5484	1.50 inches wide by 60 yards long aluminum tape
3M 425 ALF3000260A	Tape, Pressure Sensitive Adhesive	7510-01-670-5486	2.00 inches wide by 60 yards long aluminum tape
3M 425 ALF3000360A	Tape, Pressure Sensitive Adhesive	7510-01-670-5489	3.00 inches wide by 60 yards long aluminum tape
3M 425 ALF3000460A	Tape, Pressure Sensitive Adhesive	7510-01-670-5491	4.00 inches wide by 60 yards long aluminum tape
3M 427 (Linered)	Tape, Pressure Sensitive Adhesive	7510-01-153-7976	4.00 inches wide by 60 yards long aluminum tape

 Table 2-2.
 Aluminum Backed Pressure Sensitive Tape for Use with BA/HPA Chemical Removers

2.3.1 <u>Application</u>. Hot glue is used to seal seams, covers and access panel gaps less than 3/16 inch and to seal seams and edges of impact tape for added protection. Fluid wicks fabricated from cotton rope are sealed in place using this material, and are installed at saturated seams prior to sealing with hot glue. Caulking cord is used to fill seams and gaps in excess of 3/16 inch. Impact tape is used to protect areas not to be blasted.

#### 2.3.2 Equipment and Materials Recommended.

Hot Glue Gun Hot Glue - 3M Co. PN 3748 TC, NSN 8040-01-390-9728 or PN AIS 5050, NSN 6850-01-512-7763 Cotton Rope Caulking Cord - More - Tite Putty Impact Stripping Tape 80 mils thick, 20 ounce/inch peel strength, 250 percent to 300 percent elongation, Shore A hardness 70-80 Anchor Continental BT-100 or 3M Co. PN 500 Series (ex. 500, 506, 528, etc.) Impact Stripping Tapes 500 are available in 30 feet long rolls under NSNs: NSN 9390-01-359-7367 (1 inch wide/9 rolls per box) NSN 9390-01-359-7368 (2 inch wide/6 rolls per box) NSN 9390-01-359-7369 (3 inch wide/3 rolls per box)

These are rubberized tapes capable of withstanding a direct nozzle blast from Engineered Media Blasting (EMB) can or bicarbonate of soda and water blast equipment for a maximum of two seconds.

#### 2.3.3 Procedures.

# WARNING

Care must be taken to prevent hot glue from dripping on skin or into eyes. Wear safety goggles. Failure to comply could result in injury to, or death of, personnel or long term health hazards.



Media intrusion into engines, gun assemblies, avionics, or actuators can severely damage these components. Extreme care must be exercised to mask every possible intrusion site. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

Cover all antennas with impact tape. When masking off large areas, such as vents, use hard cardboard, sheet metal or equivalent, reinforced with impact tape over the side that will be exposed to EMB or bicarbonate of soda and water blast media. When placing cover in position, use impact tape to hold in place, and apply hot glue to seal edges. Seal all edges of all impact tape with hot glue to eliminate possibility of tape peeling. In seams or protrusions where slow hydraulic leaks compromise masking integrity, install a fluid wick (cotton rope) with a minimum four inch length and seal in place with hot glue. Aircraft mold line drain holes shall be plugged with rubber stoppers or equivalent and sealed with hot glue.

2.3.3.1 A detailed step-by-step checklist specifying the masking procedure shall be prepared for all finish system removal operations. This checklist shall be used to ensure that all required masking is accomplished prior to removal operations and that all masking is removed afterwards. The following areas shall be masked and/or otherwise protected for chemical and air or water driven abrasive finish system removal operations:



Failure to ensure the plastic-coated side of the MIL-PRF-131, Class 1, barrier material toward the surface to be protected will result in the deterioration of the barrier material by chemical removers, potentially resulting in damage to the surface. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

- a. Close all windows, doors, and hatches on aircraft or equipment; and mask gaps between the structure and these components. For air or water driven abrasive removal operations, these gaps may be stuffed full with sheets of MIL-PRF-131, Class 1, barrier material or heavy duty (0.004 inch thick) polyethylene or vinyl plastic film sheet to prevent abrasive media intrusion.
- b. Mask all transparent plastic and glass surfaces such as windows, canopies, and blisters; because they will be crazed, frosted, or lose transparency if exposed to chemical removers or if air or water-driven abrasive media strikes them. For air or water-driven abrasive removal operations, optional form-fitting metal or wood shields may be fabricated for canopies and blisters in conjunction with 3M Co. PN 510, 3M Co. 500, 510, or Bron Tape, PN 818 material cut to the exact size for windows. These tapes are available in 30 foot long rolls under NSN 7510-01-300-2124 (1 inch), NSN 7510-01-300-2125 (2 inches), NSN 7510-01-300-2126 (3 inches), NSN 7510-01-300-2127 (4 inches), up to 30 inches (special order).



Care should be taken when cutting and trimming of the barrier/tape to prevent damage to the transparent plastic and glass surfaces. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

c. Mask all radomes, antennas, fiber glass and/or composite structure, and rubber boots and/or all other rubber or elastomer surfaces to prevent chemical removers and air or water driven abrasive media from damaging these materials and/or components. (See <u>Paragraph 2.15</u> for composite paint stripping procedure.)

## TO 1-1-8

- d. Mask all engine intake and exhaust openings and all openings or ports leading to interior cavities of structure to prevent entrapment of chemical removers and abrasive media. When masking aircraft pitot static ports and probes, the probe and port openings shall be covered with a disk of barrier material or paper prior to application of pressure sensitive tape to prevent tape adhesive from contaminating the interior and the openings of these probes and ports. The tape shall cover the barrier material or paper completely and overlap onto the aircraft surface approximately one-half inch past the outside diameter of the pitot static port circular hole pattern.
- e. Mask all seams of removable inspection and equipment access panels and personnel doors for chemical removal operations to prevent seepage of the remover into joints.
- f. Mask all edges, repairs, and loose fasteners on honeycomb and metal-to-metal adhesively bonded panels and doors for chemical removal operations to prevent chemical removers from damaging adhesives and disbonding adhesively bonded structure.
- g. Fabric covered control surfaces (rudders, elevators, ailerons, etc.), shall be either completely masked or removed from the aircraft prior to any paint removal operations in the area of these components. Fabric can be damaged by chemical removers and air or water driven abrasive media.
- h. Sometimes, replacements for very detailed or highly specialized decals are very difficult to obtain. Mask these types of decals using barrier material over the decal if directed to save them.
- i. Mask all other areas specified in and as directed by system peculiar aircraft or equipment TOs, such as aircraft -23 corrosion TOs.

#### NOTE

For extensive chemical removal operations such as entire aircraft exterior finish system, some residual stripping will be required. For this limited stripping, it may be more efficient and practical to strip those areas of the finish system which will be covered by masking tape by the hand residual finish system removal procedures in this chapter prior to masking for the overall media removal operation. This is authorized as long as extreme care is taken to prevent damage to areas which require protection by masking, all remover and open finish system residue is thoroughly removed from the stripped areas and areas around them, and surfaces on which masking tape will be applied are solvent wiped with a cotton rag wetted with TT-I-735 isopropyl alcohol followed by wiping dry with a clean cotton rag before the alcohol evaporates.

#### 2.4 ORGANIC FINISH SYSTEM REMOVAL.

There are two methods for removal of organic finishing systems; chemical and mechanical. Each method has its own set of procedures, precautions, restrictions, and limitations; and therefore, each will be explained separately. If confined areas or non-metallic structural materials are involved in the removal operation, specific procedures for these areas are presented in this chapter and shall be used.

#### 2.5 CHEMICAL REMOVAL OF ORGANIC FINISH SYSTEMS FROM METAL SUBSTRATES.

Chemical removal procedures and their sequence of performance are essentially the same for all types of organic finish systems, all types of chemical removers, and either limited or extensive removal operations. However, the type of chemical remover used depends on the type of organic finish system to be removed.

#### 2.6 CHEMICAL REMOVERS.

The type of chemical remover used to remove an organic finish system varies according to the type of system to be removed: alkyd base primer, lacquer or alkyd enamel topcoats over alkyd base primer, epoxy and polyurethane primers, epoxy and polyurethane topcoats over epoxy or polyurethane primers, or polyurethane topcoat over polysulfide primer. The approved types of chemical removers which shall be used to remove each of these organic finish systems are identified below along with precautions to be used for each type:

## NOTE

All chemical removers have a shelf life of 6 months from the date of manufacture unless otherwise specified, if they are stored and maintained under the proper conditions. They should be ordered in quantities and by intervals which allow all chemical removers on hand to be used prior to the shelf life expiration date. Chemical removers shall be stored in a protected area (out of direct sunlight) capable of maintaining a temperature of 40 to 100 °F (4 to 38 °C), to prevent them from freezing or being exposed to excessively high temperatures. Chemical removers rapidly deteriorate at temperatures exceeding 100 °F (38 °C), and many of them become corrosive. Exposure to freezing temperatures causes them to separate in such a way that the components cannot be remixed to a homogeneous solution. In either case, they become totally ineffective. While not necessarily unsatisfactory after six months of age, chemical removers do deteriorate and lose removal efficiency on aging beyond six months; and some start to become corrosive. A definite age control program shall be established for chemical removers by the using activity, and any material which is questionable due to improper storage and/or exceeding its shelf life shall be laboratory tested and updated in accordance with Department of Defense (DoD) 4140.27-M and DoD Shelf-Life Program website (www.shelflife.dla.mil) prior to use. Particular attention shall be given to the corrosiveness of chemical removers during testing.

2.6.1 Remover for Epoxy and Polyurethane Primers and Epoxy and Polyurethane Top-Coats Over Epoxy or Polyurethane Primers. There are no United States Air Force (USAF) approved specification removers for these finish systems, but proprietary removers of two different types, phenolic and non-phenolic/non-cresylic, have been tested and approved by the AFCPCO for use on USAF aircraft, missile or equipment metal surfaces. Each remover is chemically unique and not necessarily interchangeable with others for a particular task. Production variables affecting the choice of removers include the brand and age of the finish system, type of surface to which it is applied (metal type, large/small area, horizontal/vertical surface), local climate, capabilities of local industrial waste treatment facilities, Environmental Protection Agency (EPA) and local environmental restrictions on remover and paint residue disposal, and local medical and bioenvironmental authority concerns for worker contact with the more reactive type products. Phenolic type removers are much more efficient than the nonphenolic/non-cresylic type removers for removal of these finish systems, but they present waste disposal problems and require treatment facilities capable of handling them. Each activity is authorized and encouraged to service test the listed removers to evaluate effectiveness for their own particular situation and to select a preferred remover and one or two alternates, if possible, to promote competition. These removers are heavy bodied or very viscous liquids, usually yellow or brown in color, designed to remove these finish systems by solvent action. These removers shall be applied full strength with no dilution in a smooth even coat by either a brush or a non-atomizing type sprayer. Removers authorized to remove epoxy and polyurethane finish systems from USAF aircraft, missiles, and equipment metal surfaces are identified by PN and source of supply.

2.6.1.1 Phenolic Type Removers, NSN 8010-01-023-0343 (55 gallon drum), NSN 6850-01-512-6620 Cee-Bee<sup>™</sup> R-256 (8 ounces), NSN 6850-01-555-9124 Crest Stripper 18 (8 ounces).

2.6.1.2 Non-Phenolic/Non-Cresylic Type Removers, NSN 8010-00-348-7716 (5 gallon), NSN 8010-01-167-9692 (1 gallon).

2.6.2 <u>Remover for Polysulfide Primer with a Polyurethane Topcoat</u>. There are no USAF approved specification removers for this finish system, but proprietary removers of two different types, phenolic and non-phenolic/non-cresylic, have been tested and approved by the AFCPCO for use on USAF aircraft, missile, and equipment metal surfaces. While they will remover military specification polyurethane topcoats, it is much more efficient to remove polyurethane topcoats with one of the removers listed for epoxy and polyurethane finish systems first and then to remove the polysulfide primer with one of the removers listed in this paragraph. This method is highly recommended to avoid excessive use of materials, man-hours, and flow time in removal of this finish system. These removers are heavy bodied or very viscous liquids designed to remove polysulfide primer with a polyurethane topcoat by solvent action; preferably after the polyurethane topcoat has been removed with one of the removers listed for epoxy and polyurethane finish systems. These removers shall be applied full strength, with no dilution, in a smooth even coat by either a brush or a non-atomizing type sprayer. The removers authorized to remove polysulfide primer with a polyurethane topcoat from USAF aircraft, missiles, and equipment metal surfaces are identified below by PN and source of supply, NSN 8010-01-270-3637 (55 gallon drum).

2.6.3 <u>Removers for Environmental Compliance</u>. In addition to removers listed in preceding paragraphs, removers based on benzyl alcohol and alternate alkaline materials have been tested and approved for use on USAF aircraft, missile, or equipment metal surfaces by the AFCPCO. These products offer the advantage of reduced hazardous waste generation and contain ingredients not currently listed as hazardous materials for occupational health or environmental contamination. However, skin and eye protection is still required. Consult the local Bioenvironmental Engineer (BEE) for minimum personal protection requirements and the local environmental coordinator to establish proper handling and disposal procedures for the removers and the process waste. These products have flash points ranging from 150 °F (66 °C) to over 200 °F (93 °C) so they are not classified as flammable materials, but as combustible materials. Their use should be coordinated with the local

fire department. These products do not afford the same production rates as the traditional methylene chloride and phenolic type removers, and removal efficiency on each type of coating varies for each product. They are chemically unique and not necessarily interchangeable for a particular task. The products are generally effective for topcoat removal but have differing degrees of effectiveness with primers. The following removers are authorized to remove organic finishes from USAF aircraft, missiles and equipment metal surfaces:

2.6.3.1 Removers for epoxy/polyurethane primer and polyurethane topcoats NSN 6850-01-523-0007 (8 ounces).

**2.6.3.2** Removers for polysulfide primers are the following: NSN 6850-01-495-0150 (55 gallon drum), NSN 6850-01-495-0235 (1 gallon), and NSN 6850-01-679-6523 (one box containing twelve 8 ounce cans).



Not to be used on metallic magnesium or non-metallic surfaces. Use of these materials will cause degradation and destroy the integrity to the structure. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

**2.6.3.3** Removers for Epoxy and Polyurethane Primers and Epoxy and Polyurethane Top-Coats to include a sprayable polysulfide sealant type coating within the coating stack up. Benzyl Alcohol/Hydrogen Peroxide removers, performance of these depaint materials is slower than chemical depaint materials listed within <u>Paragraph 2.6.1</u> when the sprayable polysulfide sealant coating is included. NSN 6850-01-584-9119 (300 gallon TOTE), NSN 6850-01-584-9124 (50 gallon drum).

2.6.4 <u>Chemical Depaint Materials Authorized for Air Force Use</u>. Chemical depaint materials, while meeting the AF Qualification Source Document criteria, can vary from manufacturer to manufacturer. The AFCPCO maintains a current list of manufacturers that have been tested and meet AF requirements and first article requirements of chemical depaint materials. These materials are authorized for use on aerospace and non-aerospace structures (where authorized by the cognizant System Program Office (SPO)). Contact the AFCPCO at afcorr@us.af.mil to obtain a current list of qualified depaint materials manufacturers.

#### 2.7 GENERAL OVERALL CHEMICAL REMOVAL PROCEDURES.

Chemical removal of organic finish systems shall be performed in accordance with the following sequential steps:



Chemical removers are toxic to skin, eyes, and respiratory tract. Skin and eye protection required. Contact Bioenvironmental Engineering for determination of need for and selection of proper respiratory protection. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

- a. Ensure that all facility safety, health, and disposal requirements and all personnel safety and health requirements in <u>Paragraph 2.2</u>, <u>Step a</u> and <u>Step b</u>, are met.
- b. Determine the type of organic finish to be removed in accordance with <u>Paragraph 2.2</u>, <u>Step c</u>. Select and obtain the proper chemical remover for the finish system involved in accordance with <u>Paragraph 2.6.1</u>, <u>Paragraph 2.6.2</u>, or <u>Paragraph 2.6.3</u>.
- c. Ensure that the removal operation has been properly planned and that all personnel understand the operation as required by Paragraph 2.2, Step d.
- d. Ensure that the aircraft, equipment or component has been properly cleaned, dried, and masked in accordance with <u>Paragraph 2.3</u> through <u>Paragraph 2.3.3.1</u>, <u>Step i</u>.
- e. Ensure that the aircraft, equipment, or component has a surface temperature defined in Paragraph 2.3, Step b.
- f. Mix the chemical remover well with a mechanical mixer or a wooden paddle immediately before use as chemical removers tend to separate on standing. Do not mix by rolling a drum of chemical remover as this will not mix the material adequately.

- g. Apply a light to medium thick, uniform coat of chemical remover to the area of the aircraft, equipment, or component from which the finish system is to be removed with a long handled, non-metallic brush, specification MIL-B-23958, (type and style are optional) or a non-atomizing type sprayer wand fitted to a barrel pump. Never use an atomized spray to apply chemical removers. Do not apply thick coats of chemical removers as this actually slows down the removal rate, creates a more extensive waste disposal operation, and wastes expensive chemical removers. Efficient removal requires maintaining a wet film of remover on the surface. Active ingredients in chemical removers listed in Paragraph 2.6.1 are highly volatile and evaporate rapidly: so after about one hour dwell time, they begin to dry out and no longer react on the finish system as most of the active ingredients have evaporated. Environmentally compliant removers listed in Paragraph 2.6.3 have a maximum dwell time of 24 hours before they become non-reactive. For an effective removal operation chemical removers must be applied progressively and in a planned logical sequence. Apply removers to areas no larger than can be effectively worked by the personnel on hand to perform the operation. Removers should not be applied to a second area prior to completion of the removal operation in an area being worked. This is particularly important for extensive removal operations such as removal of the entire exterior finish system from an aircraft. Preferably, application of chemical removers should begin at the highest point of a vertical or sloping surface to prevent removers from running down onto surfaces from which the finish system has already been removed; but this is an optional decision to be made by local management.
- h. Allow a chemical remover listed in Paragraph 2.6.1 to dwell on the surface undisturbed for 15 minutes, and one listed in Paragraph 2.6.2 and Paragraph 2.6.3 for 4 hours and then agitate several spots on the surface with Commercial Item Description (CID) A-A-58054, Type I, Grade C abrasive mat, or a MIL-B-23958, Type I or III brush to determine if the finish system has been loosened down to bare metal. If the finish system has loosened down to bare metal at this point, proceed to next step; if not, repeat the 15 minute or 4 hour dwell and spot agitation procedure until loosening of the finish system down to bare metal is indicated or a maximum of one hour or 24 hour dwell time has elapsed and then proceed to the next step.
- i. When the finish system has loosened to bare metal or exceeds a reasonable dwell time, thoroughly agitate the entire area on which the chemical remover has been applied with a MIL-B-23958, Type I or Type III brush while exerting as much pressure with the brush as possible.



- Never allow a chemical remover to dry on the surface to which it is applied as it is extremely difficult to remove after it dries. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- Never rinse surfaces with water between chemical remover applications as this stops the removal action and tends to set up the remaining finish system on the surface making it very difficult to remove. Schedule removal operations so that once started on an area, they proceed without interruption through the entire sequence to complete removal to bare metal. If the operation must be interrupted due to some scheduling problem or the work-day ending, scrape off all chemical remover with a rubber bladed squeegee and rinse the area with water as directed below prior to stopping work. When a chemical removal operation is interrupted in this fashion, extreme difficulty will be encountered in removal of the remaining finish system from the area where work was stopped requiring increased amounts and applications of chemical removers, increased man-hours for the operation, and significant flow time delays. If the area is exposed to direct sunlight during the interruption, even more difficulty will be experienced in removal of the remaining finish system. Never restart chemical remover application until the area is completely dry. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

#### NOTE

A MIL-B-23958, Type I, Style 1, brush is available through GSA under NSN 7920-00-054-7768 (round, nylon bristles). A MIL-B-23958, Type III, Style 1, brush is available through GSA under NSN 7920-00-051-4384 (round, nylon, and Tampico bristles).

j. Immediately after agitation, scrape all loosened finish system residue and chemical remover from the surface with a rubber bladed squeegee; and immediately reapply fresh chemical remover in accordance with Paragraph 2.7, <u>Step g</u>, on spots where the finish system has not been removed down to bare metal in the area being worked, and repeat Paragraph 2.7, <u>Step h</u>, and <u>Step i</u>.



Only those aluminum wools and brushes specified shall be used to agitate metallic surfaces during finish system removal operations. Other types of metallic wools and brushes, such as steel, copper, brass, beryllium copper, etc., shall not be used as they will either embed in or smear on the metallic surface and cause severe galvanic corrosion problems. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

#### NOTE

If a polysulfide primer/polyurethane topcoat finish system is being removed and the first application of chemical remover takes off the topcoat but not the primer, the second and subsequent applications shall be with one of the chemical removers specified in this manual for removing polysulfide primer.

k. Repeat the removal sequence, Paragraph 2.7, <u>Step g</u> through <u>Step j</u>, in the area being worked as necessary to remove the finish system down to bare metal up to a maximum of three times. For the second and all subsequent applications of chemical remover, agitate the surface with CID A-A-58054, Type I, Grade C nylon abrasive mat; CID A-A-1044, Type II, Class 1, Form A, aluminum wool; and/or CID A-A-3118, Type I, Class A7 aluminum wire brushes to assist in the removal operation.

#### NOTE

- CID A-A-58054, Type I, nylon abrasive mat is available under NSN 5350-00-967-5092 for 10 sheets of Grade C (medium) material.
- CID A-A-1044, Type II, Class 1, Form A, (PN CID A-A-1044-B-1-A), aluminum wool is available under NSN 5350-00-286-4851 for a one-pound roll or NSN 5350-00-312-6129 for 25 one-pound rolls.
- CID A-A-3118, Type I, Class 7, (PN CID A-A-3118/A7) aluminum wire brushes are available under NSN 7920-01-067-6192 for one brush.
- As soon as the finish system has been removed down to bare metal or the final attempt at overall chemical removal has been completed and the chemical remover and finish system residue has been scraped from the surface with a rubber bladed squeegee in the area being worked, flush the area thoroughly with hot water at a temperature of 100 to 120 °F (38 to 49 °C) and a pressure of 150 to 250 Pound-force per Square Inch (PSI). Start at the lowest point and work upward using care to keep the water off adjacent areas from which the finish system will be removed.

### NOTE

- If hot water is not available, fresh tap water at hydrant pressure may be used for the flush operation. However, it should be well understood that this will make the final cleaning/washing step much more difficult and require additional man-hours and flow time to accomplish, because cold water tends to gel waxy compounds used in chemical removers and redeposit them on the surface.
- With prior written aircraft SPO approval, Medium Pressure Water (MPW) methods in <u>Paragraph 2.13</u> (water only-no baking soda) may be used instead of Paragraph 2.7, <u>Step i</u> through <u>Step 1</u>, to enhance paint removal with environmentally compliant removers in <u>Paragraph 2.6.3</u> after their required dwell time is reached.
- When removing alkyd base primer having no topcoat, flush the area with water as soon as possible after it has been loosened by the chemical remover and scraped from the surface as it tends to readily redeposit on the surface if the surface becomes dry thus requiring another application of chemical remover.
- m. After the area being worked has been thoroughly flushed with water, remove tape used for masking within the area by hand; or, as an alternate, remove it with the hot water at the same time the area is being flushed.



AIRCRAFT COATING THINNER, MIL-T-81772

- n. Remove any residual finish system from very stubborn spots and areas covered with tape during the general removal operation using care to prevent chemical removal materials from entering into and becoming entrapped in confined areas and/or causing damage to structure, components or materials. Apply either the same chemical removers used for the general removal operation, or MIL-T-81772, Type I or II thinner, by dabbing them on the spots with a small non-metallic bristle brush. Agitate the spots with the same materials listed for agitation during the general removal operation and/or nonmetallic/plastic scrapers while the chemical remover or solvent is on the surface. Wipe the loosened finish system and chemical remover off the surface with a cotton rag; and if necessary, abrade the remaining finish system off the surface in accordance with the mechanical removal procedures in Paragraph 2.10 with materials in <u>Table 2-3</u>, <u>Table 2-4</u>, and <u>Table 2-5</u>. Wipe the area from which the finish system was removed with a cotton rag wetted with fresh water, and then dry with a clean cotton rag.
- o. If the area just completed is the final area from which the finish system is to be removed, proceed directly to the next step. If other areas are to be worked, repeat Paragraph 2.7, <u>Step g</u> through <u>Step n</u>, on the next area. Application of chemical remover on a new area may begin as soon as the flushing operation is completed and while the residual finish system removal operation is in progress on an area being worked as long as enough personnel are on hand to work both areas effectively.
- p. Immediately after finishing the chemical removal operation on the last area from which the finish system is being removed, thoroughly wash all areas of the aircraft, equipment, or component from which the finish system has been removed and those adjacent areas which may have been exposed to or contaminated with chemical remove in accordance with TO 1-1-691, the aircraft -23 TO, and/or the equipment system specific TO. Inspect all areas where chemical remover may have become entrapped, and clean these areas as required. The aircraft, equipment or component shall not be removed from the coating removal facility until this washing operation is completed.

## 2.8 <u>CHEMICAL REMOVAL PROCEDURES FOR CONFINED LOCATIONS.</u>



AIRCRAFT COATING THINNER, MIL-T-81772



17

- MIL-T-81772, Type I or II thinner is flammable. Avoid all sources of ignition. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- Chemical removers are toxic to skin, eyes, and respiratory tract. Skin and eye protection required. Contact Bioenvironmental Engineering for determination of need for respiratory protection and selection of proper type when required. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- Use extreme caution when using MIL-T-81772, Type I or II thinner in areas where liquid oxygen storage and transfer equipment are located. Never use these materials on valves, flanges or other components where they may come in direct contact with liquid oxygen or pure oxygen vapor. Failure to comply could result in injury to, or death of, personnel or long term health hazards.



Do not allow these materials to spread to adjacent areas not being worked or to splash, overspray, or spill onto adjacent rubber, synthetic rubber, plastic, or composite materials, or components as damage to the finish system on adjacent areas and these materials and components will result. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

#### NOTE

If this chemical method does not remove the finish system, proceed to one of the mechanical methods in this TO.

When use of the chemical removers listed in <u>Paragraph 2.6.1</u> through <u>Paragraph 2.6.3</u> of this TO is impractical because of assembly complexities and/or rinsing difficulties, remove the finish system from metal surfaces using MIL-T-81722, Type I or II thinner in accordance with the following procedures:

- a. Apply a solvent selected from the list above to the area from which the finish system is to be removed with a small nonmetallic bristle brush or a clean cotton rag.
- b. Allow the solvent to dwell on the surface until all the finish system to be removed has softened and/or lifted from the surface. It may be necessary to keep a rag saturated with solvent on the surface in order to keep the surface wet for the time required to lift the finish system.
- c. Agitate the surface at frequent intervals using the same abrasive materials and scrapers listed for agitation and residual finish system removal in Paragraph 2.7 <u>Step k</u> and Paragraph 2.7 <u>Step n</u>. Wipe loosened finish system residue from the surface with clean cotton rags wetted with the same solvent being used for removal.
- d. Repeat Paragraph 2.8 <u>Step a</u> through Paragraph 2.8 <u>Step c</u> as necessary until all finish system and residue have been removed from the metal surface, including recesses around rivets, bolts, etc.
- e. Wipe the area clean with a clean cotton rag wetted with fresh tap water, and then wipe the area dry with a clean cotton rag.

#### 2.9 CHEMICAL DIP TANK MATERIALS AND PROCEDURES.

Dip tank chemical removal procedures are used for the removal of coatings from aircraft wheels, landing gear components and other aircraft and support equipment parts small enough to be submerged in a dip tank.

2.9.1 <u>MIL-PRF-83936</u>, Heated Tank Type for Aircraft Wheels, Landing Gear Components, and Other Aircraft and <u>Support Equipment</u>. MIL-PRF-83936 are non-phenolic removers that can be used on steel, aluminum, and magnesium. There is a Qualified Products Database (QPD) for this specification listing approved materials. These paint removers require heated tanks with ventilation. The remover shall be heated and used at the manufacturer's recommended operating temperatures.

**2.9.1.1** MIL-PRF-83936 removers have an inhibitor which prevents corrosion. The lack of inhibitors will have a rapid and most serious effect on magnesium parts. Removal solutions that have inhibitor breakdown will not attack SAE AMS-M-3171 coatings on magnesium parts but will corrode the exposed metal where the coating is damaged. Evidence of inhibitor breakdown will be initially observed as a white powder residue around any scratches or pits on the surface of metal after removing the part from the solution. Inhibitor breakdown will be initially observed on aluminum parts when they are removed from the solution and surfaces appear to be dull or stained. When either of these conditions is observed, one of the two following actions must be taken. The tank can be replenished with the appropriate amount of inhibitors, determined through chemical laboratory analysis or replace the used chemical remover with new MIL-PRF-83936 chemical remover.

2.9.2 <u>Chemical Dip Tank Procedures</u>. Chemical dip tank removal of organic finish systems shall be performed in accordance with the following steps:

- a. Parts shall be cleaned in accordance with TO 1-1-691 prior to removal operation to ensure removal effectiveness. Parts shall be thoroughly dry before immersing in chemical dip tank solutions.
- b. Prior to placing part in the dip tank, mask all openings to its interior such as lightening and drain holes and all dissimilar metals such as steel helicoil inserts in magnesium and aluminum using procedures and materials in <u>Paragraph 2.3</u> through Paragraph 2.3.3.1, <u>Step i</u>.
- c. Immerse part in chemical dip tank. Ensure parts to be stripped are completely immersed. Do not allow them to extend into seal layer or to protrude above surface of solution.
- d. After soaking for a maximum of four hours, scrub parts with non-metallic bristle or fiber brushes. If required to remove stubborn areas of paint, procedure can be repeated up to a maximum of six times. For two tank/material remover, place in first tank for two hours, remove and rinse and place in second tank for two hours.
- e. After removal from tank, pressure spray and rinse parts thoroughly with water (warm water preferred).
- f. Allow parts to dry. Parts may be wiped with towels, rags, or forced-air dried to remove excess moisture.
- g. Remove all masking materials applied prior to placing part in dip tank.

## 2.10 MECHANICAL REMOVAL OF ORGANIC FINISH SYSTEMS.

WARNING

- Reference <u>Table 3-1</u> for the minimum recommended PPE for paint removal operations using hand held or motor driven abrasives (sanding and grinding). Reference <u>Table 2-6</u> for the minimum recommended PPE for abrasive blasting paint removal operations. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- Abrasive blasting, motor-driven wire brush and motor-driven abrasive disc operations create airborne particles that are hazardous to the eyes, skin, and respiratory tract. Do not stand above, below or directly next to other workers. Avoid being "downwind" from others using mechanical sanders and grinders. Do not use compressed air to remove dust. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- The dust created by either of these methods is hazardous to the respiratory tract, and noise produced by abrasive blasting is hazardous to the hearing. Coveralls with full-length sleeves and gloves with gauntlets shall be worn by personnel performing either of these removal methods. Protective clothing should be removed prior to leaving the work area. Personnel using motor-driven abrasives shall wear dust/particulate type respirators, goggles, and/or full face shields. Personnel performing dry abrasive blasting shall wear an abrasive blasting airline/hood respirator meeting the requirements of AFI 48-137 and hearing protection. Hoods or helmets should be cleaned prior to storage in dust-free environment. Contact the Base BEE for specifics on required protective equipment. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- Dust generated from abrasive, metal, and finish system particles during dry abrasive blasting, motor-driven wire brush, or motor-driven abrasive disc finish system removal operations creates the potential for a dust explosion. Use only pneumatic type motor-driven equipment. Properly electrically ground all motor driven equipment, abrasive blasting equipment, work stands, and work pieces when engaged in these operations. Avoid all sources of ignition where these operations are in progress, and provide adequate ventilation in the area. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- Dry abrasive blasting, motor-driven wire brush, or motor-driven abrasive disc finish system removal on steel and titanium alloy surfaces may cause sparking. Perform these operations in a well ventilated area, and take proper fire safety precautions. If these methods are being used in a large operation involving other types of metals, remove the finish system from the steel and titanium surfaces first; and then proceed to the other areas. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- AFMAN 91-203 should be reviewed to ensure all safety, fire and environmental safety requirements are accomplished prior to performing mechanical removal of organic finish systems. Failure to comply could result in injury to, or death of, personnel or long term health hazards.



- Low-carbon steel brushes shall not be used on aluminum, magnesium, copper, stainless steel, or titanium alloy surfaces as steel particles will embed in these surfaces and later rust or cause galvanic corrosion of these surfaces. Copper, brass, or beryllium copper brushes shall not be used on aluminum, magnesium, stainless steel, steel, or titanium alloy surfaces as they will smear on these surfaces and cause galvanic corrosion. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- Mechanical methods shall be used only long enough to remove the finish system and not abrade the underlying metal surface. Speed of removal is not the most important factor. Removal without damage to the surface or creating a condition which can lead to future corrosion damage and providing a surface suitable for finish system reapplication are the most important factors. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- EMB may be used on composite materials in accordance with procedures in <u>Paragraph 2.12</u>, providing its use has been approved by the specific aircraft's SPO. In all cases, use EMB to remove only the topcoat from composite surfaces. The underlying primer must be used as a "flag" to signal the EMB operator that the topcoat has been removed. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness. When the primer begins to show during the stripping operation as the topcoat is slowly removed, the

EMB blast should be directed elsewhere on the surface being stripped. This technique is essential to avoid damaging the composite material. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

• When using mechanical methods, abrasive blast media and pieces of broken brushes and discs can escape from the work area. These methods shall not be used in areas under conditions that allow escaped particles to enter into and damage or contaminate any system, engine, or other component. Barriers shall be erected around the work area and masking of the surrounding area and masking or plugging of all holes leading to the interior of systems and equipment shall be accomplished to prevent damage and contamination of systems and equipment by dust, abrasive blast media, and pieces of broken brushes and discs. The system specific aircraft corrosion manual (-23) or the specific equipment manual shall be consulted for proper masking requirements. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

Mechanical removal methods include the use of hand-held wire brushes, bonded abrasive papers or cloths, and abrasive mats; motor-driven wire brushes, bonded abrasive paper or cloth discs, and abrasive mat discs and flap brushes; and abrasive blasting. Mechanical removal is recommended when use of chemical removers is impractical due to structural complexities and/or rinsing difficulties in an area being worked and/or local environmental restrictions. While these methods are very effective for finish system removal, they can cause severe damage to structure and equipment in a very short time if improperly used. Consult with weapons system specific TOs prior to performing work in fracture critical/no-work areas.

#### 2.11 <u>MECHANICAL REMOVAL METHODS OTHER THAN PLASTIC MEDIA OR MEDIUM PRESSURE WATER</u> <u>BLASTING FOR METAL SUBSTRATES.</u>

WARNING

Protective clothing worn during abrasive blasting operations shall remain in the work area and shall not be taken home for cleaning. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

For any and all mechanical finish system removal operations, approval for the operation shall be obtained from the responsible ALC as directed in <u>Paragraph 2.10</u>. The area involved in the operation shall be thoroughly cleaned to remove all oil, grease, and hydraulic fluid in accordance with TO 1-1-691. Masking shall be accomplished per instruction in <u>Paragraph 2.3</u>, Step e and the applicable system or equipment specific manual prior to starting the operation. Precautions listed in the cautions and warnings in this manual, the applicable system or equipment specific manual, and TO 1-1-691 shall be strictly followed. Mechanical removal methods consist of hand abrasive or motor-driven abrasive removal of organic coatings from various substrate materials and abrasive blasting.

2.11.1 <u>Abrasive Blasting</u>. Iron and Steel Alloys (other than Stainless Steel) may be abrasive blasted with aluminum oxide grit, steel grit, glass, or sand at a maximum air pressure of 80 PSI for a pressure type machine to remove paint. This is very effective on low-carbon steels and iron as it also removes rust/corrosion leaving a bright metal surface. Use TO 1-1-691 as control for this type of abrasive blasting, and never use on steel less than 0.0625 inch thick.

2.11.2 <u>Hand or Motor-Driven Abrasive Removal</u>. These methods for mechanical removal of a finish system are basically the same for all substrates. The primary difference is the type of abrasives used, which vary depending on the underlying surface. <u>Table 2-3</u>, <u>Table 2-4</u>, and <u>Table 2-5</u> shall be used to determine the abrasive material to be used for topcoat or primer removal and the substrate metal it may be used on.

## 2.11.3 Hand Held Abrasive Removal.



- Damage to clad/Alclad or anodize surfaces will reduce the corrosion protection in those areas. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- Motor-driven wire brushes and discs and abrasive blasting shall not be used on flexible, braided copper wire, cables, hoses, and lines as these methods can cause severe damage to these components. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- Magnesium particles, powder, or dust are extreme fire hazards. Motor-driven wire brushes and abrasive flap brushes and abrasive blast media other than those listed in <u>Table 2-3</u>, <u>Table 2-4</u>, and <u>Table 2-5</u> shall not be used for finish system removal from magnesium alloy surfaces. Keep work area clean. Do not permit flammable materials or any source of ignition into the area. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- Finish system removal using motor-driven abrasives can generate airborne particles that are hazardous to the skin, or respiratory tract. Work pieces and motorized equipment shall be properly electrically grounded, and personnel shall wear dust/particulate respirators, goggles, gloves, and full sleeved shirts when using motor-driven abrasives. Do not stand above, below or directly next to other workers performing these operations. Avoid being "downwind" from others using mechanical sanders. Consult Bioenvironmental Engineering Services for respiratory and ventilation requirements. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

Abrade the finish system topcoat from the surface down to the primer with hand-held metallic wool, abrasive mat, abrasive cloth, or wire brushes as specified in <u>Table 2-3</u> and <u>Table 2-5</u>. If required, change the abrasive being used and abrade the primer from the substrate material, taking care not to damage the metal substrate.

### 2.11.4 Motor Driven Abrasive Removal.



Do not mount an abrasive on a motor driven tool having an operational speed higher than the maximum Revolutions Per Minute (RPM) rating of the abrasive. This can result in disintegration of the abrasive. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

Abrade the finish system topcoat from the surface down to the primer with motor driven wire brushes, or either a random orbital tool or pneumatic drill motor fitted with a Roloc<sup>TM</sup> or hook and loop mounted surface conditioning disc, a disc fabricated from an abrasive cloth sheet, a Roloc<sup>TM</sup> Bristle disc, or Radial Bristle disc. Select the abrasive for use per <u>Table 2-4</u> and <u>Table 2-5</u>. Use sanders and grinders attached to high efficiency vacuum systems for dust recovery. Use of a random orbital sander or a pneumatic drill motor fitted with the surface conditioning disc is preferable. This method provides the fastest removal rate with the least possibility of damage to the metal substrate and the longest abrasive life due to the non-loading characteristics of this type of disc. Keep sander heads flush against the surfaces being sanded and apply the least amount of pressure necessary to effectively remove the finish system topcoat and not go through the primer and gouge or abrade the metal substrate. Abrade the primer from the surface with the same methods used for the topcoat, but with finer grade abrasives per <u>Table 2-4</u> and <u>Table 2-5</u>. Again, the motor-driven surface conditioning disc is preferred, and only enough pressure to remove the primer without gouging and abrading the metal substrate shall be applied. Always use high efficiency vacuum systems attached to the tools for dust recovery.

2.11.5 <u>Stainless Steel Corrosion Resistant Steel (CRES) and Nickel Based Alloys</u>. After completing mechanical removal using materials per <u>Table 2-3</u>, <u>Table 2-4</u>, and <u>Table 2-5</u>, polish the surface with hand held aluminum oxide/nylon mesh abrasive mat (very fine) or either a random orbital tool or pneumatic drill motor (12,000 RPM max) fitted with a (very fine) grade "Scotch-Brite" aluminum oxide/nylon mesh Roloc<sup>TM</sup> or hook and loop mounted surface conditioning disc.

2.11.6 <u>Cold Spray Repairs</u>. Low pressure cold spray systems may be used in accordance with drawings 201995835 and 201995836 if approved by the cognizant engineering authority within the weapon SPO or whomever they've delegated the engineering authority to. This low pressure cold spray system can be used to remove corrosion from 2024-T3, 6061-T6, and

7075-T6 aluminum alloys, as well as ZE41A magnesium alloys, and subsequently build up material where corrosion was present on aircraft parts that are not considered by the weapon system chief engineer to have an airworthiness implication in event of their failure. Repairs that have an airworthiness implication are required by the weapon system program office to submit a package in accordance with Airworthiness Bulletin (AWB) 1015. Drawings 201995835 and 201995836 are general non-structural repair and use criteria for the low pressure cold spray system: however, other technical details specific to parts repair are provided in the technical data package or technique sheet by the SPO. Once the repair has been approved by the SPO, low pressure cold spray repairs shall be performed only by certified cold spray operators that have completed both the in-class and hands-on training requirements mandated by the AF Rapid Sustainment Office. For information on training, or to be linked with the appropriate SPO's cognizant engineering authority, please e-mail the AF Rapid Sustainment Office at AFLCMC.RSO.workflow@us.af.mil.

2.11.7 <u>Dust Removal</u>. After the finish system has been removed, use High-Efficiency Particulate Air (HEPA) vacuums with appropriate attachments to vacuum dust from aircraft and facility floors. Do not use compressed air unless absolutely necessary to remove dust from very narrow cracks and crevices.

2-18

coonting augodings																								1
Fiber Glass, Arranged Biber (Kevlar®)/Epoxy and Graphite or Boron Fiber/Epoxy Composite Surfaces		ΕI	٩I		ΗI	٩I									ଦା	ΗI								
syollA muinstiT		ы	٩I		н	<u>م</u> ا			<u>T, P</u>						ଦା	н							<u>T, P</u>	
Copper and Copper Based Alloys		ы	<u>م</u> ا		н	۹I				<u>T, P</u>					ଦା	ΗI				<u>T, P</u>	<u>T, P</u>			
Stainless Steel (CRES) and Nickel Based Alloys		нI	<u>م</u> ا		нI	۵1			<u>T, P</u>				T, P		<u>م</u> ا	н							<u>T, P</u>	
Iron and Steel Alloys (Other Than Stainless Steel)		T, P	<u>م</u> ا		ы	<u>م</u> ا		<u>T, P</u>														<u>T, P</u>		
muisəngaM Aşnesium syollA		нI	<u>~</u> 1		н	۹I					ы				리	Η								
Von-Clad and Unanodized Alumimum Alloys		н	<u>م</u> ا		н	<u>م</u> ا					H				리	Η			<u>T, P</u>				<u>T, P</u>	
Clad/Alclad and Anodized Aluminum Alloys		нI	<u>م</u> ا		нI	٩I					H				<u>م</u> ا	Η								
Hand Held Abrasives	Abrasive Cloth	120 grit ANSI B74.18 Type II, Class 1	240 grit ANSI B74.18 Type II, Class 1	Abrasive Paper	120 grit ANSI B74.18/CID A-A-1047 silicon carbide paper	240 grit ANSI B74.18/CID A-A-1047 silicon carbide paper	Metallic Wool	CID A-A-1043, Type I, Class 1, low carbon steel wool	CID A-A-1043, Type I, Class 1, stainless steel wool	CID A-A-1044, Type I, Class 1, Form A, copper wool	CID A-A-1044, Type II, Class 1, Form A, aluminum wool	Abrasive Mats	CID A-A-58054, Type I, Class 1, Grade A (very fine)	aluminum oxide/nylon mesh	CID A-A-58054, Type I, Class 1, Grade B (fine) aluminum	CID A-A-58054. Type I. Class 1. Grade C (medium)	aluminum oxide/nylon mesh	Wire Brushes	Aluminum wire brushes <u>1</u>	Brass wire brushes <sup>2</sup>	Copper wire brushes <sup>2</sup>	Low carbon steel wire brushes <sup>2</sup>	Stainless steel wire brushes <u>-</u>	T for topcoat removal

for primer removal Ч

Stainless steel or aluminum wire brushes shall be used on non-clad and unanodized aluminum alloys only when the structure is 0.0625 inch thick or greater. 0 -

Never use brass, copper, or low carbon steel brushes on any aluminum or magnesium alloys.

ainless steel or aluminum
e brass, copper, or le

의 너 너 해 너 해	<u>T</u>	ΗI	ы	<u>4</u> 1			Fiber Glass, Arranged Fiber (Kevlar®)/Epoxy and Graphite or Boron Fiber/Epoxy Composite Surfaces
	μI	<u>T, P</u>	ы	۹I			muinstiT RollA
의 비 비 비 비 비 비 비 비 비		T	ΗI	ЧI			Alloys Copper Based Copper and
	Η	<u>T, P</u>	н	сI	₽I		Stainless Steel (CRES) and Nickel Based Alloys
	<u>T, P</u>	<u>T, P</u>	<u>T, P</u>	ЧI			Iron and Steel Alloys (Other Than Stainless Steel)
		<u>T, P</u>	ы	۹I			syollA muisəngaM
	<u>T, P</u>	$\overline{\mathrm{T,P}}$	ΗI	۹I			Non-Clad and Unanodized Aluminum Alloys
	ΗI	$\overline{\mathrm{T}}, \overline{\mathrm{P}}$	нI	41		discs	Clad/Alclad and Anodized Aluminum Alloys
Fine grade "Scotch-Brite" aluminum oxide/nylon mesh Medium grade "Scotch-Brite" aluminum oxide/nylon mesh Roloc <sup>TM</sup> Bristle discs and Radial Bristle discs Grade 120 Abrasive Flap Brush/Wheels Aluminum oxide coated nylon mesh Abrasive Disks 120 grit ANSI B74.18 Type II, Class 1 240 grit ANSI B74.18 Type II, Class 1 240 grit ANSI B74.18 Type II, Class 1 Brasive Disks Aluminum wire brushes <sup>1</sup> Brass wire brushes <sup>2</sup> Copper wire brushes <sup>2</sup> Low carbon steel wire brushes <sup>2</sup>	Abrasive Flap Brush/Wheels Aluminum oxide coated nylon mesh	<sup>TM</sup> Bristle discs and Radial Bristle discs Grade 1	Medium grade "Scotch-Brite" aluminum oxide/nylon	Fine grade "Scotch-Brite" aluminum oxide/nylon mesh	Very fine grade "Scotch-Brite" aluminum oxide/nylon mesh	Roloc <sup>TM</sup> or hook and loop mounted surface conditioning di	Motor Driven Abrasives

Table 2-4. Motor Driven Abrasives

for topcoat removal H 4

Item	Specification	NSN	Unit of Issue
Roloc <sup>™</sup> Plastic Holder	Roloc <sup>™</sup> No. 1 Plastic Holder	3460-01-509-1784	Case
Roloc <sup>™</sup> Plastic Holder	Roloc <sup>™</sup> No. 7 Plastic Holder	3460-01-509-1812	Case
Roloc™ Bristle Disk	Roloc <sup>™</sup> Bristle Disk 2 inches x 5/8 tapered	5345-01-432-3027	Case
Roloc™ Bristle Disk	Roloc <sup>™</sup> Bristle Disk 3 inches x 5/8 tapered	5345-01-432-3292	Case
Roloc™ Bristle Disk	Radial Bristle Disk (Thick Bristle 3 inches	3460-01-509-1789	Case
Surface Conditioning Disk	Scotch-Brite Surface Conditioning Disk 2 inches	5345-01-367-7680	Box
Surface Conditioning Disk	Scotch-Brite Surface Conditioning Disk 3 inches	5345-01-397-5256	Box
Metallic Wool carbon steel	CID A-A-1043, Type III, Class 1	5350-00-242-4404	1 each, 1 pound roll
Metallic Wool stain. steel	CID A-A-1043, Type IV, Class 1	5350-00-440-5035	1 each, 1 pound roll
Metallic Wool aluminum	CID A-A-1044 Type II, Class 1 Form A	5350-00-286-4851	1 each, 1 pound roll
Metallic Wool aluminum	CID A-A-1044 Type II, Class 3 Form A	5350-00-312-6129	1 each, 1 pound rolls
Metallic Wool copper	CID A-A-1044, Type I, Class 1, Form A	5350-00-255-7736	1 each, 1 pound roll
Abrasive Mat	CID A-A-58054, Type I, Class 1, Grade A	5350-00-967-5089	10 each, 9 inch x 11 inch sheets
Abrasive Mat	CID A-A-58054, Type I, Class 1, Grade B	5350-00-967-5093	10 each, 9 inch x 11 inch sheets
Abrasive Mat	CID A-A-58054, Type I, Class 1, Grade C	5350-00-967-5092	10 each, 9 inch x 11 inch sheets
Abrasive Cloth silicone carbide	120 grit ANSI B74.18/GGG-C-520, Type II, Class 1	5350-00-865-5689	25 each, 9 inch x 11 inch sheets
Abrasive Cloth flint/emery	240 grit ANSI B74.18/GGG-C, 520, Type II, Class 1	5350-00-174-0999	25 each, 9 inch x 11 inch sheets
Abrasive Paper silicone car	120 grit ANSI B74.18/CID A-A-1047	5350-00-721-8115	50 each, 9 inch x 11 inch sheets
Abrasive Paper silicone car	240 grit ANSI B74.18/CID A-A-1047	5350-00-224-7207	50 each, 9 inch x 11 inch sheets

 Table 2-5.
 Abrasive Materials

## Table 2-6. Recommended Controls and PPE for Abrasive Blasting Operations<sup>a</sup>

	Engineering		Personal Protective Equipment								
Operation	Controls	Respiratory	Hand	Ear	Eye	Body	Foot				
Masking	None	None	None	None <sup>b</sup>	None	None	Safety toe boots				
Refilling of blast media	None	None	None	None <sup>b</sup>	Safety goggles or face shield	Tyvek™ or cotton coveralls	Safety toe boots				
Abrasive blasting	Abrasive blast enclosure	Blasting helmet with supplied-air	Leather and disposable nitrile gloves	Ear Plugs	None	Tyvek <sup>™</sup> or cotton coveralls; leather shoulder cover <sup>c</sup>	Safety toe boots				

	Engineering		]	Personal Pro	tective Equip	nent			
Operation	Controls	Respiratory	Hand	Ear	Eye	Body	Foot		
Dust removal (compressed air)	Abrasive blast enclosure	Blasting helmet with supplied-air	Leather and disposable nitrile gloves	Ear Plugs	None	Tyvek <sup>™</sup> or cotton coveralls	Safety toe boots		
Dust removal (vacuum)	HEPA vacuum	None	None	Ear Plugs <sup>d</sup>	None	Tyvek <sup>™</sup> or cotton coveralls	Safety toe boots		
Media clean-up	HEPA vacuum	None	None	Ear Plugs <sup>d</sup>	None	Tyvek <sup>™</sup> or cotton coveralls	Safety toe boots		
<sup>a</sup> Local BEE may recommend more or less restrictive controls.									
<sup>b</sup> Hearing protectio	<sup>b</sup> Hearing protection may be required in locations where hazardous noise is produced.								
<sup>c</sup> A Powered Air-Pu	<sup>c</sup> A Powered Air-Purifying Respirator (PAPR) with hood is the best choice.								

## Table 2-6. Recommended Controls and PPE for Abrasive Blasting Operations<sup>a</sup> - Continued

<sup>d</sup> Not required if a full-face piece or hooded respirator is worn.

## 2.12 ENGINEERED MEDIA BLASTING REMOVAL METHOD.



Engineered Media Blasting (EMB) can peen or smear soft metals therefore it shall not be used to remove paint from aluminum or magnesium components requiring subsequent fluorescent penetrant inspection unless specifically directed by the component engineering authority. Distortion caused by EMB could result in limited crack/flaw detection. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

EMB is an excellent and rapid method for finish system removal, but it can cause severe damage to structure and injury to personnel if not done properly with the right type of equipment in an approved facility. In addition, proper waste management must be ensured for economic and environmental reasons. Some materials and material thicknesses cannot be EMB blasted under any circumstances. Therefore, EMB is authorized at depot and field level operations contingent upon SPO approval of facilities, personnel training, and processes as specified in system or item specific technical data. These instructions are not intended to be all inclusive, but are general requirements to be used in conjunction with additional instructions in applicable system peculiar aircraft or equipment manuals. All EMB finish removal operations shall conform to the following requirements:

Media Type. Media used in EMB shall be fabricated from plastic or biopolymer stocks which are free from high-2.12.1 density particle contamination and other impurities. The materials used shall be of a specific, non-changing chemical composition as specified in MIL-DTL-85891, Engineered Media, For Removal of Organic Coatings, and paragraphs below. Media used shall have a particle size of U.S. screen 20 to 40 mesh; however, 12 to 16 mesh may be added as makeup media. The media shall have a particle shape which is irregular with sharp, angular edges. Engineered media is classified by type which specifies the hardness and the material, and therefore the performance characteristics. The following are the definitions of media types as specified by MIL-DTL-85891.

2.12.1.1 <u>Type II</u>.



The Type II media is more aggressive than the Types V, VII, and VIII and will induce greater residual stresses in the underlying metals if used improperly. Increased residual stresses can cause warping and increased crack growth rates in aircraft skin materials and ground equipment enclosures. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

Type II media is a urea formaldehyde based plastic with a 3.5 MOH (54 to 62 Barcol) hardness. This media may be used on aerospace components with approval from the specific item manager engineering authority. Parameters for the proper use of Type II media on aerospace components are also listed in <u>Paragraph 2.12.1</u>. Type II media is recommended for use on non-aerospace equipment such as SE.

2.12.1.2 <u>Type III</u>. Type III is a melamine formaldehyde based plastic with a 4.0 MOH (64 to 74 Barcol) hardness. This media is not authorized for use in stripping aircraft structures, unless blended within Type VIII media. Type III media is very aggressive and is recommended only for stripping iron based equipment where residual stress problems will have no consequences. This material is authorized for use on SE and other non-aerospace applications. See <u>Table 2-7</u> for blast parameters and limitations.

2.12.1.3 <u>Type V</u>. Type V media is an Acrylic Plastic with a 3.5 MOH (46 to 54 Barcol) hardness. This media is authorized for use on aerospace systems as well as non-aerospace applications. See <u>Table 2-7</u> for blast parameters and limitations.

2.12.1.4 <u>Type VII</u>. Type VII media is a starch polymer with a 72 to 79 Shore D hardness. This material is authorized for use on aerospace systems and non-aerospace equipment applications. This media is very moisture sensitive and the air flow shall be dry and oil free. See <u>Table 2-7</u> for blast parameters and limitations.

2.12.1.5 <u>Type VIII</u>. Type VIII media is a Urea/Melamine Formaldehyde blend with a 3.5 MOH (54 to 62 Barcol) hardness. See <u>Table 2-7</u> for blast parameters and limitations.

2.12.2 <u>Media Authorized for Air Force Use</u>. EMB, while meeting the military specification criteria, can vary from manufacturer to manufacturer. The AFCPCO maintains a current list of manufacturers that have been tested and meet AF requirements of MIL-DTL-85891. These materials are authorized for use on aerospace and non-aerospace structures where authorized by the SPO. Contact the AFCPCO at afcorr@us.af.mil to obtain a current list of qualified EMB manufacturers.

2.12.2.1 All media shall be tested for contamination in accordance with <u>Paragraph 2.12.12</u>.

2.12.3 <u>Operational Parameters for Metallic Surfaces</u>. All EMB operations on metallic surfaces shall conform to the parameters and limitations list in <u>Table 2-7</u> and <u>Table 2-8</u>.

Media Type	Min. Pressure (PSI) <sup>*</sup> -	Max. Pressure (PSI) <sup>*</sup> -	Min. Stand Off Dist. (inch)	Max. Stand Off Dist. (inch)	Angle (degrees) <sup>***</sup>
Type II	20	30	18	30	0-60
Type III	-	40	12	-	-
Type V	25	40	12	24	0-60 (clad and composites) 30-90 (non-clad)
Type VII	-	45	12	24	0-60
Type VIII	25	30	10	12	0-80

\* Il pressures are to be measured at the nozzle.

\*\* SE and vehicles may be blasted at any angle.

Media Type	Min. Pressure (PSI) <sup>*</sup>	Max. Pressure (PSI)	Min. Stand Off Dist. (inch)	Max. Stand Off Dist. (inch)	Angle (degrees) <sup>*</sup>
Type II	20	30	18	30	0-60
Type III	-	40	12	-	-
Type V	25	40	12	24	0-60 (clad and composites) 30-90 (non-clad)
Type VII	-	45	12	24	0-60
Type VIII	25	30	10	12	0-80

<b>Table 2-8.</b>	<b>Blast Parameters</b>	for Walk-In Booths
-------------------	-------------------------	--------------------

\* All pressures are to be measured at the nozzle.

\* SE and vehicles may be blasted at any angle.

2.12.4 <u>Usage Restrictions</u>. The following limitations apply for EMB use:

**2.12.4.1** <u>Type II</u>. For non-aerospace use on metallic structure(s) having a minimum substrate thickness of 0.040 inches. Nozzle pressures and stand-off distances in <u>Table 2-7</u> and <u>Table 2-8</u> shall be observed during operations.

2.12.4.2 <u>Type III</u>. For non-aerospace use on metallic structure(s) having a minimum substrate thickness of 0.0625 inches. Nozzle pressures and stand-off distances in <u>Table 2-7</u> and <u>Table 2-8</u> shall be observed during operations.

**2.12.4.3** <u>Type V</u>. For aerospace use on metallic structure(s) having a minimum substrate thickness of is 0.032 inches. Nozzle pressures and stand-off distances in <u>Table 2-7</u> and <u>Table 2-8</u> shall be observed during operations.

## NOTE

When blasting close to masking on the work surface, the nozzle shall be held as close as possible to 90 degrees with respect to the work surface to prevent undercutting of the masking materials.

2.12.5 <u>Operational Parameters for Non-Metallic (Composite) Surfaces</u>. All EMB operations on non-metallic surfaces (fiberglass, Kevlar®/epoxy, graphite/epoxy, boron/epoxy, etc.) shall conform to the following parameters:

## NOTE

EMB shall not be utilized on composite structures unless approved by the cognizant engineering authority for the system, or item, that is to be blasted.

**2.12.5.1** Pressure at the nozzle shall be within the range of 25 to 40 PSI for the 3.5 MOH hardness media (Type II, V, VII, and VIII).

**2.12.5.2** The stand-off distance of the blast nozzle with respect to the work surface shall be within the range of 12 to 24 inches.

**2.12.5.3** The angle of incidence between the blast nozzle and the work surface shall be within the range of 40 to 60 degrees.



- When using the EMB method of paint removal on non-metal (composite) surfaces, it is important to limit the length of time the surface is exposed to the EMB blast. To limit this "dwell time" and still allow paint to be removed, operators should use the primer coat as a "flag". That is, when the primer begins to become visible, the EMB blast should be aimed at another section of the surface to be stripped. This results in all paint being removed and only a portion of the primer. Most importantly, limiting the dwell time prevents damage to the composite material being stripped. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- To minimize dwell time, avoid "low pressure-long stand-off distance/shallow angle" combination of parameters. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

2.12.5.4 To maintain a constant removal rate and limit the amount of time which the EMB blast impinges on any given surface (dwell time), the following relationships are important to remember:

2.12.5.5 As stand-off distance increases (decreases), pressure should increase (decrease) to maintain a constant removal rate.

**2.12.5.6** As the angle of incidence decreases towards zero degrees (increases towards 90 degrees), the pressure should increase (decrease) to maintain a constant removal rate.

2.12.6 <u>Operation Safety Requirements</u>. Refer to the operation safety requirements for the proper type of equipment as follows:

2.12.6.1 Walk-In Blast Booth. Proceed as follows.

- Keep all sources of ignition a minimum of 50 feet away from the area when EMB is in progress.
- All blasting equipment, work stands, and the aircraft, equipment, or components being blasted shall be properly electrically grounded in accordance with TO 00-25-172 and the applicable aircraft or equipment manual during the entire EMB operation.
- All power shall be removed from the aircraft or equipment while EMB is in progress.
- Titanium and steel alloy surfaces will spark when subjected to EMB. When an EMB operation involves a combination of these and other metals, the titanium and steel alloy surfaces shall be blasted first and then the other metal surfaces.
- The facility used for EMB shall have adequate air flow and ventilation to prevent buildup of an explosive dust mixture. The Base BEE shall be consulted for proper ventilation requirements.
- Personnel involved in EMB operation other than blasting cabinets shall wear the required PPE required by the Base Safety Office and Bioenvironmental. Hood shall be put on prior to entering the blasting area and shall not be removed until after exiting the blasting area. Hoods shall be stored in a clean dust free area and shall be cleaned to remove all dust accumulation on them prior to storage after use. All personnel entering the blasting area while EMB is in progress, even though not involved in the operation, shall comply with these personnel protection requirements. The Base BEE and Base Fire Department will define the EMB blasting area when the EMB equipment is located within a larger facility and is not segregated from other areas. Protective clothing worn during EMB shall remain in the work area and shall not be taken home for cleaning.
- Blast nozzle operators shall never direct a nozzle at other personnel. If more than one blast nozzle operator is involved in an operation at the same time, they shall be located on opposite sides and/or ends of the aircraft or equipment being blasted to ensure safe separation of personnel.
- Dust and media residue generated during EMB operations create very slippery conditions. Walking on top of aircraft or equipment during EMB operations shall be avoided if at all possible and shall be done with extreme caution by personnel wearing fall protection devices if it is absolutely required by the operation. All work stands shall be equipped with guard rails to prevent falls.

## 2.12.6.2 EMB Blasting Cabinets. Proceed as follows.

- Keep all sources of ignition a minimum of 50 feet away from the area when EMB blasting is in progress.
- All blasting equipment, work stands, and the equipment or components being blasted shall be properly electrically grounded in accordance with TO 00-25-172 and the applicable equipment manual during the entire EMB operation.
- Titanium and steel alloy surfaces will spark when subjected to EMB. When an EMB operation involves a combination of these and other metals, the titanium and steel alloy surfaces shall be blasted first and then the other metal surfaces.
- The facility where the EMB cabinet is located, and the EMB cabinet shall have adequate air flow and ventilation to prevent buildup of an explosive dust mixture. The Base BEE shall be consulted for proper ventilation requirements.
- The Base Bioenvironmental and Safety Office shall be consulted for specific PPE requirements. The PPE requirements may vary based on media type. Protective clothing worn during EMB shall remain in the work area and shall not be taken home for cleaning.

2.12.7 <u>Personnel Qualifications</u>. EMB shall be performed only be personnel thoroughly trained in the operation of EMB equipment and thoroughly indoctrinated in EMB requirements and techniques specified in this TO and any other system peculiar aircraft or equipment TO applicable to the job to be performed.

#### 2.12.8 Pre-blast Preparation. Proceed as follows.

- Prior to masking for EMB, thoroughly clean the aircraft, equipment, or component in accordance with TO 1-1-691 to remove all grease, oil, hydraulic fluid, and dirt from surfaces to be blasted. Every effort shall be made to stop all fluid leaks noted at this time. Surfaces shall be allowed to fully dry prior to masking and input of the item into the blasting facility. Water and other fluids contaminate blasting media and may damage separation equipment.
- Prior to starting EMB, properly mask the aircraft, equipment, or component to prevent blast media and dust from penetrating into interior areas and causing contamination or damage to equipment, systems, or structure susceptible to damage by media impingement. Masking shall be accomplished in accordance with instruction in <u>Paragraph</u> 2.3 <u>Step e</u> of this TO and the applicable system specific aircraft or equipment TO for the item being blasted such as the aircraft system specific -23 manual.

2.12.9 <u>Post-blast Cleaning</u>. When the finish system has been completely removed by EMB, thoroughly vacuum all surfaces of the aircraft, equipment, or component with a heavy duty, pneumatic type, wet/dry HEPA filtered vacuum cleaner to remove all finish system dust and media residue. As an alternative, compressed air or water wash may be used to remove dust and media residue. However, avoid the use of compressed air to remove dust and media residue, unless absolutely necessary. Masking shall be removed, and interior areas and crevices which were masked or plugged to prevent dust and media entry shall be inspected for presence of dust and media particles and vacuumed clean as necessary.

#### NOTE

EMB media has an anti-static additive that tends to contaminate the blasted surface and inhibit paint adhesion. Solvent wiping is required in addition to washing to completely remove this residue.

2.12.10 <u>Specific Technical Data and Work Directives</u>. Prior to initiating any EMB finish system removal operation on any aircraft, component, or piece of equipment, each aircraft SPO or equipment item manager (XX-ALC/XX) shall prepare detailed work specifications or project directives that outline masking instructions and blasting instructions. These instructions shall conform to all requirements in this TO and the applicable system specific aircraft or equipment TO. Finally, a detailed step by step process order or work control document that complies with all the technical data and work specification or project directive requirements shall be prepared by the maintenance organization or contractor for each separate EMB finish system removal operation.

2.12.11 <u>Disposal of Engineered Media Used in Paint Removal Operations</u>. Disposal of used media must be coordinated with the proper local base agency due to the contamination of the media. The resulting contamination from most paint removal operations makes the engineered media a hazardous waste that must be disposed of properly.

## TO 1-1-8

2.12.12 <u>Contamination Testing of Engineered Media</u>. The engineered media shall be tested for contaminates as specified in the following paragraphs. The media used in EMB equipment for paint removal of aircraft and aircraft components shall be sampled and tested every 80 hours of equipment operation time or after each aircraft or large piece of aerospace equipment is blasted (whichever is longer). The engineered media that is being used to blast steel/ferrous items for paint removal or other coatings removal shall not be used on aluminum aircraft surfaces or components. Media found to have a high-density particle contamination level greater than that specified in <u>Paragraph 2.12.12.1</u> shall be purged from the system and replaced with new media. Testing at the ALCs shall be accomplished in the physical sciences laboratory (XX-ALC/MAD). Testing at contractor and field level activities shall be accomplished locally in a designated area adequately equipped to run the test for contamination. Organizations using EMB coatings removal processes in small walk-in or cabinet-type booths are given an option to either test media as specified in the paragraphs that follow, or forego EMB testing and purge the used media and replace it with new media at intervals not to exceed 80 hours of equipment operation when used on aircraft components. This option is not applicable to large-scale EMB coatings removal operations where entire aircraft or large sub-assemblies, such as wings or horizontal/vertical stabilizers, are completely stripped.

2.12.12.1 Equipment and Materials Recommended.

One 500 Milliliter (mL) separatory funnel

Rod stand, for separatory funnel

Holding rings, for funnels

Perfluorohexane, (Specific Gravity (SG) 1.68), 3M Company PN PF-5060TM or equivalent

ASTM D1836 N-Hexane (Adhesive Thinner), SG 0.66

One glass funnel, 3 inch nominal diameter

One glass powder (large stem) funnel, 4 inch nominal diameter

Whatman number 42 (or equal) filter paper, 12.5 centimeters, to fit above funnel

Scales, 1000 grams capacity/0.1 gram sensitivity such as:

Ohaus E4000, 0 to 4000 grams/0.1 gram Sartorius U3600, 0 to 3600 grams/0.1 gram Ohaus GT2100, 0 to 2100 grams/0.01 gram

Analytical balance, 100 grams capacity/0.001 gram sensitivity such as:

Ohaus E120G, 0 to 120 grams/0.001 gram Sartorius H120, 0 to 120 grams/0.001 gram Mettler AB-160, 0 to 160 grams/0.0001 gram Mettler PM200, 0 to 210 grams/0.001 gram Mettler AT200, 0 to 205 grams/0.0001 gram

Special dual range balances offering bulk weighing and precision weighing in a single instrument may be substituted for the above instruments, but usually they have limited capacity and significantly higher prices. Two are:

Mettler PM480 Delta Range, 80 grams/0.001 gram, 410 grams/0.01 gram Mettler AT460 Delta Range, 62 grams/0.0001 gram, 405 grams/0.001 gram

500-600 mL tall form Pyrex beaker

250 mL Pyrex beaker

500 mL graduated glass cylinder

Two jug-type glass storage bottles, gallon with screw caps

Hydrometer, 1.60 to 1.80 SG

Pyrex watch glass, 75 to 90 millimeters diameter

Nalgene polyethylene wash bottles, 250 mL

Bar magnet

Spatula, stainless steel

Glass stirring rods, 10 inches

Neoprene gloves, size as required such as: Playtex neoprene

## NOTE

Laboratory equipment may be purchased from national laboratory supply firms such as Fisher Scientific, VWR Scientific, Curtin Matheson Scientific, or from local laboratory supply firms found in most large cities.

2.12.12.2 <u>Sampling Procedure</u>. Collect approximately two liters of used media, preferably from the blast pot or hose.

2.12.12.2.1 <u>Used Media</u>. The best representative sample is obtained by collecting media directly from the blast nozzle; but if this is not feasible, collect the sample from media hoppers located after separation equipment in recovery/ reclamation system.

2.12.12.3 <u>Contamination Test Procedure</u>. Proceed as follows:

a. Ensure all glassware is clean and dry.

WARNING

Keep solvents away from heat and open flame. Keep containers closed. Use only with adequate ventilation. Avoid prolonged or repeated contact with skin and swallowing. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

- b. Prepare a mixture of 95 percent by volume Perfluorohexane (SG 1.68), 3M Company PN PF-5060TM, and 5 percent by volume ASTM D1836 N-Hexane (SG 0.66). To make mixing easier, pour the N-Hexane into the container first, and then add the Perfluorohexane (PF-5060TM) fluid. Using a hydrometer, measure the SG of the mixture to ensure it is within the range of 1.60 to 1.66. If the SG is below 1.60 add a small amount of PF-5060TM until the SG is within range; if the SG is above 1.66, add very small amounts of N-Hexane until the SG of this fluid mixture is high enough to float the light media particles while allowing high density particles to separate and settle out. A quantity of this test fluid mix may be prepared in advance and stored until needed in small necked, tightly capped bottles. These bottles shall be marked in accordance with AFI 90-821, <u>Chapter 3</u>, and with the value of the SG of the fluid they contain.
- c. Add approximately 300 to 350 mL (bulk dry volume) of sample media to 500 mL beaker. Weigh beaker and media to the nearest tenth gram (0.1 gram) and record (Weight No. 1) gross weight. Pour media into 500 mL separatory funnel (stopcock closed) and ensure there is no spillage. Obtain tare weight of 500 mL beaker and record (Weight No. 2) to the nearest tenth gram (0.1 gram).
- d. Add the fluid to separatory funnel leaving some air space in the funnel for ease of agitation. Swirl the mixture. A swirling motion is better than shaking to reduce entrapment of air and suspension of particles due to energy of motion of the moving fluid. Media samples may contain some dust-sized particles, which may be suspended in the fluid after agitation and adhere to the sides. Tapping the side of the funnel should dislodge any particles adhering to the sides. Place the separatory funnel on the rod stand using the holding ring. Allow 10 minutes for the suspended dust to settle or rise. Higher density particles will accumulate in the bottom of the separatory funnel on top of the stopcock.

## TO 1-1-8

- e. Fold the filter paper in a standard filter fold and place it in a funnel. Position the funnel in a holding ring on the rod stand beneath the separatory funnel and place a beaker beneath this funnel to catch the test fluid. Use short duration opening of stopcock in order to drain higher density particles settled out in the bottom of separatory funnel (on top of stopcock) into filter funnel. Tapping the side of the separatory funnel may help to remove the high-density particles. Do not allow fluid level to get too low, because it might allow some floating media to be deposited with the high-density contaminants. Additional fluid may be added to separatory funnel taking care not to agitate mixture. If agitation occurs, allow 10 minutes for suspended dust particles to float/settle prior to continuation. To separate all of the high-density particles, the process has to be repeated until no particles will separate out of the media. One attempt will not extract them all.
- f. Place the filter and filtrate in a vented, dust free location (preferably, a laboratory hood) to dry for one hour. Weigh the filter paper and filtrate to 0.001 gram precision. Allow the filter paper to dry an additional 30 minutes and reweigh. If there is a change greater than 0.001 gram, continue to dry the sample, checking the weight every 30 minutes until the weight between intervals does not change. Obtain the tare weight of a watch glass, or on an electronic balance so equipped, and reset the balance to 0 with the watch glass on the pan. Carefully remove the filtrate from the filter paper onto the watch glass by tapping. Unfold the filter paper and remove the remaining particles with a hard instrument, such as a metal spatula, until no visible sign of particles remain. Do not use a brush. Fine particles or dust may have impregnated the filter paper. This residue is not a major concern and may be disregarded because fine particles (less than 80 mesh, US Standard Sieve) are not damaging to aircraft materials or structure. Depending upon the balance used, weigh or calculate the weight of the dense particles to 0.001 gram precision and record as Weight No. 3. (Gross weight minus weight of watch glass). After weighing use a magnet to determine if any steel/ferrous material is in the dense particles. This information may help in determining the source of the contamination and facilitate process troubleshooting. However, the 0.02 percent dense particle contamination level in <u>Paragraph 2.12.12.3</u>, <u>Step i</u>, is the basis for acceptance or rejection of the media regardless of the contamination composition.
- g. Filter the used test fluid mixture through a funnel with clean filter paper, and retain for reuse. Store in a separate, smallneck, tightly closed and properly labeled container. Recheck specific gravity with a hydrometer to assure it is in the proper range prior to reuse.
- h. Calculations: Gross weight of media and 500 mL beaker (Weight No. 1) minus tare weight of 500 mL beaker (Weight No. 2) equals net weight of media, and (Weight No. 3) is the dense particle weight. The dense particle weight divided by the media weight equals the weight fraction of dense particles in the sample. Multiply the weight fraction by 100 to find the weight percent of dense particles in the sample.

Weight No. 3=Dense Particulate Wt.x 100 = Heavy Particulate PercentWeight No. 1 - Weight No. 2Sample Wt.

i. Sand, concrete, and glass particles tend to cause pitting and the most fatigue life degradation while steel/ferrous particles will pit and embed in softer aluminum and magnesium substrates. The high density particle contaminant level shall not exceed 0.02 percent for all used media employed in aerospace equipment stripping operations. For nonaerospace equipment (SE, vehicles, etc.) stripping operations, the high density particle contamination level shall not exceed 2.0 percent for used media.

## 2.13 MEDIUM PRESSURE WATER (MPW) REMOVAL METHOD.

This removal method requires the use of a MPW and bicarbonate of soda injection system with control, hoses, and handheld nozzles of various configurations. The injection system shall consist of a positive feed control system, such as an auger/ computer controlled system. This MPW removal system, with or without abrasives, is an excellent method for finish system removal but can cause severe damage to structure and injury to personnel if not done properly. MPW paint removal is authorized at depot and field-level operations subject to SPO approval of facilities, equipment, personnel training, and technical data. These instructions are not intended to be all inclusive, but are general, necessary guidelines to be used in conjunction with additional instructions in applicable system-peculiar aircraft or equipment manuals and a definitive process order. All MPW removal operations shall conform to the following requirements:

#### 2.13.1 <u>Preparation</u>. Proceed as follows:

a. Prior to masking for MPW paint removal, the aircraft and other equipment shall be defueled and purged. In addition, if deemed necessary, the aircraft or extremely contaminated areas on the aircraft shall be washed in accordance with TO 1-1-691.



ACETONE, ASTM-D329



ISOPROPYL ALCOHOL, TT-I-735

- b. Before starting the MPW paint removal operations, the aircraft, equipment, or component shall be properly masked and sealed to prevent water or bicarbonate of soda blast media from penetrating into interior areas and causing contamination or damage to equipment, systems, or structure. All surfaces where tape is to be applied shall be wiped down with isopropyl alcohol, TT-I-735 or acetone, ASTM D 329. The solvent used during the wipe down operation shall not be allowed to evaporate from the surface, but shall be wiped from the surface with a dry, clean cloth. Masking shall be accomplished in accordance with instructions in <u>Paragraph 2.3</u>, Step e of this TO and the applicable system-peculiar aircraft or equipment TO for the item being stripped, such as the aircraft system-peculiar -23 corrosion manual or the definitive process order. In addition to masking and sealing such areas as fiberglass components, windows, radomes, and composite structures, drain holes shall be plugged prior to stripping.
- c. Areas which are covered by the barrier tape may be hand stripped with an environmentally compliant chemical remover prior to masking for the complete paint removal operation provided the procedures in this TO are strictly followed. Narrow seams around emergency doors, hatches, entry doors, and other doors on the aircraft shall be protected from the blast stream.
- 2.13.2 Paint Removal Operations. All MPW paint removal shall conform to the following parameters:



- Bicarbonate of soda blast media shall not exceed 1/2 pound per minute on the exterior of any aircraft. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- It is very important to prevent intrusion of the bicarbonate of soda blast media in areas where it can become entrapped in the aircraft structure. It may become corrosive if left within the aircraft structure. A thorough inspection for media intrusion shall be performed and a thorough rinsing with hot water after blasting shall be accomplished to prevent media from being retained in the aircraft. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- a. The MPW equipment shall have the following operating parameters: MPW will not exceed 15,000 PSI and not utilize a rotating head; water flow rate of 3 gallons per minute, bicarbonate of soda blast media flow rate 1/4 to 1/2 pound per minute.
- b. The nozzle stand-off distance shall be within the range of 2 to 4 inches from the tip of the nozzle to the working surface.
- c. The angle of incidence between the nozzle and the work surface shall be within the range of 40 to 60 degrees (measured from the surface being stripped).
- d. In order to limit the amount of time the MPW and abrasive strikes or hits any given surface (dwell time) and prevent possible damage, the nozzle shall be moved across the surface at a minimum rate of 4 inches every second.
- 2.13.3 Post-Paint Removal Cleaning. Proceed as follows:
  - a. When the finish system has been completely removed by the MPW method, all surfaces of the aircraft, equipment or component shall be rinsed with hot water (not to exceed 140 °F (60 °C)) to remove all media residue.

8

## TO 1-1-8

- b. Remove masking and sealing materials and, if necessary, hand clean protected areas. Allow entire area to thoroughly dry. Open and flush all covers and/or crevices to eliminate media residue. The aircraft, equipment, or component shall be thoroughly washed in accordance with TO 1-1-691.
- 2.13.4 Operational Safety Requirements. The following is required for safety.
  - All sources of ignition shall be kept a minimum of 50 feet away from the area when MPW paint removal is in progress.
  - All MPW equipment, work stands, and the aircraft, equipment, or components being stripped shall be electrically grounded in accordance with TO 00-25-172 and the applicable aircraft or equipment manual during the entire paint removal operation.
  - All power shall be removed from the aircraft or equipment while MPW paint removal is in progress.
  - The facility used for MPW paint removal shall have adequate air flow/ventilation. The Base BEE shall be consulted for proper ventilation requirements.
  - Personnel involved in MPW paint removal shall wear ear plugs, ear muffs, goggles, or full face shield, wet-weather suit, water-resistant hoods, chemical-resistant boots, and shin and instep guard assemblies. The shin and instep guard assembly shall be puncture resistant aluminum with a 5 inches wide by 6 inches long instep section attached by a hinge assembly to a shin section of at least 20 inches in length. Ellwood Safety Appliance Co. Model Number (No.) 3235P is one product that meets these requirements. All personnel entering the removal area while MPW stripping is in progress, even though not involved in the operation, shall also comply with these personnel protection requirements. The local Base BEE shall define the MPW paint removal area when the MPW equipment is located within a larger facility and is not segregated from other areas. Protective clothing worn during water stripping shall remain in the work area and shall not be taken home for cleaning.
  - MPW nozzle operators shall never direct a nozzle at other personnel. If more than one MPW nozzle operator is involved in an operation at the same time, they shall be located on opposite sides and/or ends of the aircraft or equipment being stripped to ensure safe separation of personnel.
  - Water and media residue generated during paint removal operations can create a slippery condition. Walking on top of aircraft or equipment during paint removal operations shall be avoided, if at all possible, and shall be done with extreme caution by personnel wearing fall protection devices. All work stands shall be equipped with guardrails to prevent falls.

2.13.5 <u>Personnel Qualification</u>. Several methods of training may be used for initial and follow on MPW training.

2.13.5.1 <u>Equipment Manufacturer's Training</u>. This training may consist of on-site training or video training. Regardless of the method, it is essential the individual receives and understands the training given through a practical, locally developed certification method.

2.13.5.2 <u>Air Force Supplied Local Training</u>. A unit level training program can be developed to include general instructional information on operation and safety. This should be followed by hands on practical training in performing MPW using all appropriate safety equipment. This would be the minimum requirements for operator certification.

## 2.14 REMOVAL OF THERMOPLASTIC POWDER COATING.

2.14.1 <u>Removal Procedures</u>. Thermal spray coating resins are difficult to remove by medium pressure abrasive grit blasting; but grit blasting, scrapers, and other manual tools may be used to remove coating that have deteriorated or are substantially cross-linked. Intentionally inducing cross-linking by overheating the powder coating during application or degrading by excessive heating after coating application results in easier removal. Conventional abrasive blasting at 60 PSI will remove these coatings. For areas requiring Non-Destructive Inspections (NDI) on bare metal, brush a release agent, NSN 9150-00-443-9003, on the specific NDI site after each inspection prior to coating or re-coating. When removal is required, carefully score the site and peel the coating off. Reapply the release agent after the inspection clean up before re-coating. Small areas may also be reheated with a hot air gun or small propane torch to soften the thermoplastic and then manually scrape the area requiring removal while the coating is still soft. For coatings that are still serviceable with a low degree of cross-linking, or if induced cross-linking is not feasible, MPW blasting in accordance with <u>Paragraph 2.13</u> is an effective method for removal. MPW blasting augmented with sodium bicarbonate is more effective in removing the powder coatings.

## 2.15 PAINT REMOVAL ON NON-METALLICS.

2.15.1 <u>Removal Requirements</u>. Non-metallics are defined as Fabric Covered Surfaces, Fiber Glass, Arranged Fiber (Kevlar®)/Epoxy, and Graphite or Boron Fiber/Epoxy Composite Surfaces. Non-metallics are susceptible to severe damage by any of the paint removal processes if improperly used. Therefore, these limited and specific procedures for removal of organic coatings shall be used only when the responsible ALC, aircraft SPO or equipment or component item manager, with the full knowledge of the ALC Corrosion Program Manager, approves the procedure to be used.



- Chemical removers used for finish system removal from metal surfaces shall not be used on any non-metallics identified in this chapter, unless approved within weapon system specific TOs. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- Sharp-edged and sharp-cornered tools shall not be used as scrapers for removal of the finish system from fabric covered surfaces, as they can easily puncture or tear the fabric. Scrapers shall not be pushed across the surface, but shall be held with the blade angled away from the body and pulled across the surface toward the body to prevent gouging of the fabric. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

2.15.1.1 EMB may be used for paint removal on Fiber Glass, Arranged Fiber (Kevlar®)/Epoxy, and Graphite or Boron Fiber/Epoxy Composite Surfaces in accordance with <u>Paragraph 2.12.5</u>; but if unavailable or unauthorized, use the mechanical methods in <u>Paragraph 2.15.2</u>, <u>Step a</u>, <u>Step b</u>, and <u>Step c</u>, below. If repairs require the total removal of the topcoat and primer, refer to TO 1-1-690 for additional procedures and precautions.

#### 2.15.2 <u>Mechanical Paint Removal on Fiber Glass, Arranged Fiber (Kevlar®)/Epoxy, and Graphite or Boron Fiber/</u> Epoxy Composite Surfaces.

WARNING

Do not mount an abrasive on a motor driven tool having an operational speed higher than the maximum RPM rating of the abrasive. This can result in disintegration of the abrasive. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

#### NOTE

The following procedures are not applicable to radomes. Finish system removal from radomes shall be accomplished per instructions in TO 1-1-24.

- a. Abrade the finish system topcoat from the surface down to the primer with hand held abrasives per <u>Table 2-3</u> and <u>Table 2-5</u>, or either a random orbital tool or pneumatic drill motor (12,000 RPM maximum) fitted with a Roloc<sup>™</sup> or hook and loop mounted surface conditioning disc or a cloth abrasive disc per <u>Table 2-4</u> and <u>Table 2-5</u>. Use sanders attached to high efficiency vacuum systems for dust recovery. Use of a random orbital tool or a pneumatic drill motor fitted with the Scotch-Brite medium grade, aluminum oxide, surface conditioning disc (3M Co.) is preferable. This method provides the fastest removal rate with the least possibility of damage to the composite substrate and the longest abrasive life due to the non-loading characteristics of this type of disc. Keep sander heads flush against the surfaces being sanded and apply the least amount of pressure necessary to effectively remove the finish system topcoat and not go through the primer and gouge or abrade the composite substrate.
- b. Abrade the primer from the surface using the same methods as used for the topcoat but with finer grade abrasives per <u>Table 2-3</u> and <u>Table 2-5</u> using the same methods as specified for the topcoat in paragraph above. Extreme caution is to be used to avoid any damage to the composite materials. Re-coating of exposed composite materials should be accomplished at the earliest opportunity as composite materials degrade when exposed to Ultra Violet (UV) light.
- c. After all topcoat has been removed, use HEPA vacuums with appropriate attachments to vacuum dust from aircraft and facility floors. Do not use compressed air unless absolutely necessary to remove dust from very narrow cracks and crevices. Refer to AFMAN 91-203 for additional safety and health program guidance.

# CHAPTER 3 SURFACE PREPARATION AND CHEMICAL PREPAINT SURFACE TREATMENT

## 3.1 SURFACE PREPARATION FOR PAINTING AND CHEMICAL PREPAINT SURFACE TREATMENT.

The life of an organic coating system, its effectiveness, and the appearance of organic finishes depend more on the condition of surfaces receiving them than any other factor. Most surfaces can be expected to present adverse painting conditions due to either the inherent nature of the material, the environment in the presence of foreign materials, contamination, or corrosion. Presence of any of these factors will require treatment or removal action to make possible the proper application of organic coatings. The life and effectiveness of organic coatings are an integral part of corrosion prevention and control for aerospace equipment. These procedures are for preparation of interior or exterior surfaces that have existing coating systems to be recoated or repaired. These procedures are also for surface preparation after complete depainting prior to the complete repainting of an aircraft. All Technical Order (TO) requirements and procedures for preparation of metal surfaces other than aluminum and magnesium, which may be used on aircraft exterior surfaces, shall be complied with in addition to requirements of this TO.

#### 3.1.1 Surface Preparation for Painting.

WARNING

- Refer to <u>Table 3-1</u> for minimum Personal Protective Equipment (PPE) required for all paint preparation operations. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- Provide adequate ventilation when using solvents. Avoid prolonged breathing of vapors and avoid skin contact. Use appropriate protective gloves and eye protection. Contact Bioenvironmental Engineering to determine need for respiratory protection. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

Surface preparation for painting is the most important requirement for ensuring proper adherence and performance of a paint system. For the purposes this manual, there are two types of surfaces requiring preparation for painting; bare unpainted surfaces (metal or composite material) and surfaces with organic coatings currently applied. In either case, an exceptionally clean surface is necessary whether painting over an existing paint system, painting newly fabricated aircraft or components, or after complete removal of an existing paint system or to overcoat an existing paint system must be thoroughly prepared before the reapplication of new organic coatings.

3.1.2 <u>Surface Preparation for Repair or Over Coating of Damaged Organic Coating</u>. Closely inspect candidate areas for the extent of damage and maintenance painting required. If inspection reveals major paint failure or damage, such as chipped or peeled paint from the center of a skin panel, the involved skin section should be prepared and maintenance painted from seam to seam. If only minor damage is found, i.e., paint chipped or missing from screw/rivet heads and on outer edges of skin panel(s), the specific area may be prepared and maintenance painted. Prepare damaged area(s) as follows:

**3.1.2.1** Thoroughly clean the area to be prepared in accordance with TO 1-1-691, or using solvent wipe procedures in accordance with <u>Paragraph 3.1.4</u>.

# WARNING

- Sanding of finish systems using motor driven abrasives can generate airborne particles and toxic dust that can injure personnel and create a possible dust explosion from paint and abrasive material dust. Work pieces and motorized equipment shall be properly electrically grounded. When using motor driven abrasives the minimum required personnel protective equipment shall be dust/particulate respirator, goggles/face shield, disposable nitrile rubber gloves, and cloth coveralls with paint sock or hooded Tyvek<sup>™</sup> coveralls and non-slip rubberized foot coverings. Do not stand above, below, or directly next to other workers. Avoid being "downwind" from others using mechanical sanders. Consult Bioenvironmental Engineering Services for respiratory and ventilation requirements. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- Do not mount an abrasive on a motor driven tool having an operational speed higher than the maximum Revolutions per Minute (RPM) rating of the abrasive. This can result in disintegration of the abrasive. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- AFMAN 91-203 should be reviewed to ensure all safety, fire and environmental safety requirements are accomplished prior to performing surface preparation and chemical prepaint surface treatments. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

3.1.2.2 Feather the edges of damaged coating adjacent to the peeled section. Use 120 grit or finer abrasive paper or nylon abrasive matting material specification CID A-A-58054 medium grade or finer for sanding. When using the coarser grit sizes down to 120, use care not to score the metal surfaces. Sanding to feather out the damaged coatings may be done by hand or with the use of either a random orbital tool or pneumatic drill motor (12,000 RPM max) fitted with a Roloc<sup>TM</sup> or hook and loop mounted surface conditioning disc, or a disc fabricated from an abrasive cloth sheet. Use sanders and grinders attached to high efficiency vacuum systems for dust recovery. Keep sander heads approximately flush against the surfaces being sanded and apply the least amount of pressure necessary to accomplish feathering of the paint.

## NOTE

It is essential that a formal maintenance/repair schedule be instituted for the high efficiency vacuum units. Replace bags in vacuum units after each aircraft or large part has been sanded. Do not use vacuums when the hoses have holes or tears. Use the minimum length of hose attached to vacuum units to ensure the highest airflow rates through the vacuum. Use the vacuum at the manufacturers recalls compressed air pressure.

**3.1.2.3** Scuff sand the surface of other area(s) adjacent to the damaged coatings that are to be coated using abrasive paper no coarser than 120 grit, 3M Corp. medium grade aluminum oxide surface conditioning disc, or CID A-A-58054, Type I, Class 1, Grade C abrasive mat. Use of a random orbital sander or a pneumatic drill motor fitted with the surface conditioning disc is preferred.

**3.1.2.4** After the finish system has been sanded, use High-Efficiency Particulate Air (HEPA) vacuums with appropriate attachments to vacuum dust from aircraft and facility floors. Do not use compressed air unless absolutely necessary to remove dust from very narrow cracks and crevices. Refer to AFMAN 91-203 for additional safety and health program guidance.

3.1.3 <u>Scuff Sanding for Overspraying Existing Coating Systems on Aircraft</u>. It is always better to start a paint system from bare metal, however, when authorized in <u>Chapter 8</u>, it is feasible to overspray existing paint systems.

#### NOTE

Adhesion failure between coatings will require complete removal of the non-adhering coating. When intercoat adhesion failure occurs over large areas, overcoating shall not be accomplished and complete strip/repaint is required.

3.1.3.1 Aircraft exterior painted surfaces shall initially be cleaned in accordance with TO 1-1-691 and thoroughly inspected to determine the soundness of the paint film. Areas of severely deteriorated paint, as indicated by loose or peeling paint; contamination from hydraulic oil, engine oil, fuel, or other fluids; or where bare metal is showing, shall be stripped in accordance with <u>Chapter 2</u> of this TO.

**3.1.3.2** Mask all areas which may be damaged by entry of fluids or paint dust generated during the cleaning and scuff sanding operations in accordance with <u>Chapter 2</u> of this TO.

#### 3.1.3.3 Prepare the surface for overcoating by scuff sanding as follows:



- Sanding of finish systems using motor driven abrasives can generate airborne particles and toxic dust that can injure personnel and create a possible dust explosion from paint and abrasive material dust. Work pieces and motorized equipment shall be properly electrically grounded. When using motor driven abrasives, the minimum required PPE shall be dust/particulate respirator, goggles/face shield, disposable nitrile rubber gloves, and cloth coveralls with paint sock or hooded Tyvek<sup>TM</sup> coveralls and non-slip rubberized foot coverings. Do not stand above, below, or directly next to other workers. Avoid being "downwind" from others using mechanical sanders. Consult Bioenvironmental Engineering Services for respiratory and ventilation requirements. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- Do not mount an abrasive on a motor driven tool having an operational speed higher than the maximum RPM rating of the abrasive. This can result in disintegration of the abrasive. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- AFMAN 91-203 should be reviewed to ensure all safety, fire and environmental safety requirements are accomplished prior to performing scuff sanding. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

#### NOTE

Requirements for vacuuming of sanding dusts may be waived by local Bioenvironmental Engineering, Industrial Hygienists, or the Office of Coordinating Responsibilities (OCR) for corporate safety/health only after approval of alternative measures for personnel protection.

3.1.3.3.1 Completely scuff sand the entire exterior surface of the aircraft, excluding bare metal areas, using abrasive paper no coarser than 120 grit, 3M Corp. medium grade aluminum oxide surface conditioning disc, or CID A-A-58054, Type I, Class 1, Grade C abrasive mat. Scuff sanding shall include roughing up 100 percent of the painted surface, removal of oxidized paint, and feather-edging of all flaked paint. It is not intended to remove a sound paint system. Light scuffing is sufficient for adhesion of the primer tie-coat to a sound topcoat. Do not sand through to bare metal as damage to the aircraft may occur. All areas where the paint system is nicked, scratched, or chipped and any edges of the paint system around areas where paint removal was done are to be feathered-out (blended smooth) during the sanding operation in accordance with Paragraph 3.1.2. All sanding operations should be accomplished using either a random orbital tool or pneumatic drill motor (12,000 RPM max) fitted with a Roloc<sup>™</sup> or hook and loop mounted surface conditioning disc, or a disc fabricated from an abrasive cloth sheet. Use sanders and grinders attached to high efficiency vacuum systems for dust recovery. Keep sander heads approximately flush against the surfaces being sanded and apply the least amount of pressure necessary to accomplish feathering of the paint.

#### NOTE

It is essential that a formal maintenance/repair schedule be instituted for the high efficiency vacuum units. Replace bags in vacuum units after each aircraft or large part has been sanded. Do not use vacuums when the hoses have holes or tears. Use the minimum length of hose attached to vacuum units to ensure the highest airflow rates through the vacuum. Use the vacuum at the manufacture's recommended compressed air pressure.

**3.1.3.3.2** After the finish system has been sanded, use HEPA vacuums with appropriate attachments to vacuum dust from aircraft and facility floors. Do not use compressed air unless absolutely necessary to remove dust from very narrow cracks and crevices. Refer to AFMAN 91-203 for additional safety and health program guidance.

3.1.3.3.3 Complete all remaining operations for preparation of the aircraft for painting as required in <u>Chapter 4</u> of this TO.

3.1.4 <u>Solvent Wiping for Surface Preparation</u>. Solvent wiping may be used for general cleaning prior to surface preparation or for final cleaning prior to coating application. A clean surface is one of the most critical process requirements that must be met to ensure coating adhesion. Depending on the process requirement, solvent selection should be made from the approved solvents in <u>Table 3-2</u>. The necessity for having an exceptionally clean surface to receive the new paint system requires that a solvent wipe be done: 1) if the surface becomes contaminated after chemical treatment, 2) after all scuff sanding operations, and 3) if required for reactivation of coating. Given these requirements, a hand solvent wipe shall be performed each time the coating sequence of an aircraft is broken and the surface has been vulnerable to the accumulation of

soils such as dust, shop dirt, fingerprints, overspray, leaks, etc., either after conversion coating application, priming, or between topcoats. This will be accomplished immediately prior to application of further paint coats to assure cleanliness and the adhesion of the paint film to the surface. The hand solvent wipe-down shall be accomplished using materials per <u>Table 3-2</u>. The solvent will be applied and the surface wiped using wiping cloths. Wiping cloth (CID A-A-59323) shall be lint free, 100 percent cotton cloth conforming to CID A-A-2522, Grade A, color 1: cotton gauze/cheese cloth conforming to CCC-C-440, Type II or III, which are unbleached or white cleaning cloths conforming to AMS 3819, Class 2, Grade A, and have not been exposed to any other chemical solution. When accomplishing the solvent wipe, always pour fresh solvent onto the cloth and dispose of them as they accumulate soils. The solvent wipe must be performed in this manner in order to prevent simply smearing soils or transferring them back to the surface from a pail of contaminated solvent. This operation must be accomplished when required and always just prior to application of the primer or subsequent paint topcoats.

	Engineering	Personal Protective Equipment					
Operation	Controls	Respiratory	Hand	Ear	Eye	Body	Foot
Masking	None	None	None	None <sup>b</sup>	None	None	Safety toe boots
Corrosion removal (acid etch)	General dilution ventilation	Air-purifying with HEPA filter	Butyl rubber gloves	Ear plugs <sup>c</sup>	Safety goggles or face shield <sup>d</sup>	Rain suit	Safety toe boots
Conversion coating (Alodine)	General dilution ventilation	Air-purifying with HEPA filter	Butyl rubber gloves	Ear plugs <sup>c</sup>	Safety goggles or face shield <sup>d</sup>	Rain suit	Safety toe boots
Alodine Sempen	General dilution ventilation	None	Disposable nitrile gloves	None <sup>b</sup>	None	None	Safety toe boots
Alodine "wipe on/blot-off"	General dilution ventilation	None	Disposable nitrile gloves	None <sup>b</sup>	Safety goggles or face shield	Tyvek <sup>™</sup> or cotton coveralls	Safety toe boots
Sanding	HEPA- ventilated sander	Air-purifying with Organic Vapor (OV)/HEPA cartridges <sup>e</sup>	Disposable nitrile gloves	Ear plugs	Safety goggles <sup>d</sup>	Tyvek <sup>™</sup> or cotton coveralls	Safety toe boots
Dust removal	HEPA vacuum	None	Disposable nitrile gloves	Ear plugs <sup>c</sup>	None	Tyvek <sup>™</sup> or cotton coveralls	Safety toe boots
Solvent wiping	General dilution ventilation	Air-purifying with OV cartridges <sup>f</sup>	Disposable nitrile gloves	None <sup>b</sup>	Safety goggles or face shield <sup>d</sup>	Tyvek <sup>™</sup> or cotton coveralls	Safety toe boots

## Table 3-1. Recommended Controls and PPE for Surface Preparation Operations<sup>a</sup>

<sup>a</sup> Local Bioenvironmental Engineer may recommend more or less restrictive controls or PPE based on exposure monitoring.

<sup>b</sup> Hearing protection may be required in locations where hazardous noise is produced from other sources.

<sup>c</sup> Ear plugs required when the noise levels exceed 85 Decibels (dB).

<sup>d</sup> Safety goggles not required if a full-facepiece or hooded respirator is worn.

<sup>e</sup> Powered Air-Purifying Respirator (PAPR) with hood is the best choice for scuff sanding.

<sup>f</sup> PPE required when chemical exposure levels exceed occupational exposure limits.

3.1.4.1 Solvent-Wipe, Aircraft Prepaint for Environmental Compliance.



These solvents should not be used on polycarbonates or acrylics. These solvents will cause most rubber products to swell, however, the rubber will return to its original shape when the solvent evaporates. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

## NOTE

Low vapor pressure National Emission Standards for Hazardous Air Pollutants (NESHAP) compliant solvents are slow to evaporate and must be wiped dry before paint application. These are the preferred solvents.

Environmental requirements have placed restrictions on use of some solvents. When using any solvents that are being restricted by environmental regulations, minimize consumption by using only a small amount of solvent on a wiping cloth; do not saturate the cloth. Wipe the surface being cleaned and then wipe with a dry wiping cloth. When the cloth becomes soiled, dispose of it in a closed container. This operation must be accomplished when the surface to be painted has become contaminated and always just prior to application of primers or subsequent topcoats. Always check with the local base Environmental authorities for restrictions and full compliance requirements. <u>Table 3-2</u> lists approved alternative solvents that will meet many environmental regulatory requirements.

3.1.5 Surface Preparation for SAE AMS-C-27725 Integral Fuel Cell Coating.



SOLVENT COMPOUND, CID A-A-59281



CHEMICAL CONVERSION COATING, MIL-DTL-81706



- CID A-A-59281 is flammable and toxic to eyes, skin, and respiratory tract. Eye and skin protection required. Good general ventilation is normally adequate. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- MIL-DTL-81706 is toxic to eyes, skin, and respiratory tract. Eye and skin protection required. Consult Bioenvironmental Engineering Services to determine need for respiratory and ventilation requirements. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

The integrity of fuel tank coatings is critical to all aircraft, and surface preparation requirements are specific and not to be wavered from. Clean surfaces to be coated with SAE AMS-C-27725 using only CID A-A-59281, Type I cleaning compound. CID A-A-59281, Type I is a solvent blend designed for this application. Apply CID A-A-59281, Type I, to a lint-free cleaning cloth. Wipe dry. Do not allow the solvent to evaporate. Change cleaning cloths regularly as required to ensure soils are not spread or transferred. Immediately follow the solvent wipe with application of conversion coating conforming to MIL-DTL-81706 in accordance with Paragraph 3.1.19.

9

11


Table 3-2. Wipe Solvents

	Metals	Organic Coatings FL 6	Coated Solvent Resistant Finishes FL 6		Composite Materials Reactivation of Painted Surface	Regulated By NESHAP FL 1		Meets Requirements of NESHAP FL 2
Solvent Selection			Coated		L L			Meets
	Surface to	be Cleaned				Compliance		
Alcohols			-					$\neg$
Ethyl alcohol, denatured FL 4	G	G	G	G			X FL 5	$\neg$
Isopropyl alcohol FL 4	G	G	G	G			X FL 5	
Napthas/Petroleum Distillates				1		•		
P-D-680, Type II, III, Dry								
Cleaning Solvent	G	G	G				X FL 5	
TT-N-95, Aliphatic Naptha	G	G	G	G			X FL 5	
CID A-A-2904, Mineral Spirits	G	G	G				X FL 5	
Ketones								
Acetone	GF		GF	GF	X		X FL 3	
Methyl Ethyl Ketone (MEK)	F	F	F	F	X	X		
MPK	G		G	G	X		X #	
Specialty Solvents				-				
Parachlorobenzotrifluoride			_					
(PCBTF)	G		G	G	X		X FL 3	$ \longrightarrow $
	Solvent Blends							
MIL-T-81772, Type II	GF		_	_		X		
1:1 MEK Toluene	F	F	F	F	X	X		
1:1 MEK Acetone	GF		GF	GF	X		X #	
1:1 MPK Naptha	G	G	G	G			X #	
1:1 Acetone: PCBTF	GF		GF	GF	X		X FL 3	
CID A-A-59231	F					X		
DS-104, Dynamold Solvents,	CE	<b>C</b> E	CE	<b>CE</b>			X *	
Inc.	GF	GF	GF	GF			$\Lambda^{+}$	
DS-108, Dynamold Solvents, Inc.	GF	GF	GF	GF			X *	
NAVSOLVE (R)	GF	GF	GF	GF			X FL 2	
SD 1291, Brulin Corp.	G	01	G	G			X *	
Super 140, LPS Industries	G		G	G			X *	
Terpenes								
Citra Safe, Inland Technology	GF	F	GF	GF			X *	$\neg$
De-Solv-It, Orange-Sol, Inc.	G		G	G			X *	
$C = U_{00}$ for Conoral Cleaning in		non-onotion fo				und for Einal (		

G = Use for General Cleaning in surface preparation for painting (General cleaners not approved for Final Cleaning leave a residue and must be followed by Final Cleaning before painting.).

F = Use for Final Cleaning before paint.

#### Table 3-2. Wipe Solvents - Continued

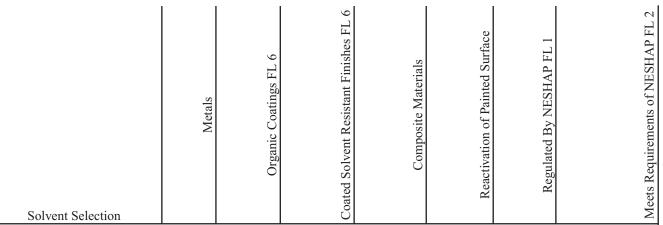

FL 1 = If the requirements of the National Emission Standards for Hazardous Air Pollutants (NESHAP) must be complied with, these solvents maybe restricted from use or have very specific limitations applied to their use.

FL 2 = These solvents meet the requirements of the NESHAP for compliance. This only applies where the requirements of the NESHAP are being enforced.

# = These solvents have a vapor pressure not exceeding 1.77 inches of mercury at 68 °F (45 millimeters of mercury at 20 °C) and will have reporting and other requirements under the NESHAP.

\* = These solvents are composed of a mixture of photo-chemically reactive hydrocarbons and oxygenated hydrocarbons and have a maximum vapor pressure of 0.28 inches of mercury at 68 °F (7 millimeters of mercury at 20 °C). There are no reporting requirements or containment controls on the use of these solvents.

#### NOTE

These solvents evaporate slowly and must be completely dried prior to application of coatings.

FL 3 = These organic compounds have been determined to have negligible photochemical reactivity and is not to be included in volatile compound calculations per 400 CRF 51.100(s) (1). Not all local state authorities have granted these exemptions.

FL 4 = Alcohols contain water and are not compatible with polyurethane coatings. Ensure all alcohol solvents have completely evaporated prior to applying polyurethane coatings.

FL 5 = Most vendor's products which meet specifications are NESHAP compliant, but some are not. Check vendor's Safety Data Sheets (SDS) to determine if composite vapor pressure is 1.77 inches of mercury (45 millimeters of mercury) or less and therefore compliant.

FL 6 = See Glossary for definitions of "Organic Coatings" and "Solvent Resistant Coatings".

3.1.6 <u>Reactivation of Newly Applied Primer or Tie Coat</u>. All standard organic coating systems consist of an approved primer and topcoat or tie coat and topcoat. In the application process, many times it is critical that topcoats be applied to the primer before the primer completely cures. Specific coating cure times are listed in <u>Chapter 6</u>. When the cure time is exceeded, the primer or tie coat must be reactivated to assure adhesion of the topcoat. Reactivation may be accomplished either through a solvent wipe or by scuff sanding. Solvent wipe for reactivation is normally allowed within a specified window during the curing process and is not effective for fully cured coatings. When solvent wipe is permitted, wipe the entire aircraft surface with a white lint-free, cotton cloth (CID A-A-59323) conforming to CID A-A-2522, Grade A, color 1 (Part Number (PN) AA 522-A1) or cotton gauze/cheese cloth conforming to CCC-C-440, Type II or III wetted with one of the solvents approved for this process in <u>Table 3-2</u>. Ensure surfaces are completely wetted to soften the coating and promote reaction between the solvents and binders in the topcoat with the primer or tie coat for adhesion, scuff sanding for reactivation shall be accomplished using 320 - or 400 grit sandpaper, CID A-A-58054, Type I, Class 1, Grade B abrasive mat, or hook and loop or Roloc<sup>TM</sup> mounted surface condition discs, "very fine" grade (3M Co.), to reactivate the primer or tie coat for adhesion of the topcoat. Surfaces shall be scuff sanded 100 percent using procedures in <u>Paragraph 3.1.3</u> followed by a solvent wipe in accordance with <u>Paragraph 3.1.4</u>.

3.1.7 <u>Surface Preparation, Unpainted Surfaces</u>. The final step in surface preparation for coatings application is the inspection and treatment of unpainted metal surfaces, i.e., areas of peeled or damaged coatings, depainted surfaces, or new repairs or fabricated components. A thorough inspection for corrosion shall be conducted over the entire surface to be painted. All areas requiring mechanical and chemical corrosion removal will be identified and marked.

3.1.8 <u>Corrosion Removal, Chemical and Mechanical.</u> All chemical and mechanical corrosion removal required for treatment of corrosion damage shall be accomplished in accordance with the system specific corrosion control TO and TO 1-1-691. All corrosion removal and treatment shall be accomplished prior to performing prepaint processes in this manual.

#### NOTE

All work requirements, repairs, mechanical corrosion removal, and sealing requirements (sealant cured completely) shall be completed, inspected, and have all defects corrected prior to prepaint cleaning and surface preparation. Failure to comply with the above requirement will cause paint adhesion problems and severe delays in painting operations.

3.1.9 <u>Preparation for Prepaint Treatment, Unpainted Surfaces</u>. Prior to application of corrosion removal compounds on aluminum or magnesium, all surfaces to be treated shall be thoroughly cleaned of dirt, grease, and contamination. Immediately prior to prepaint treatment, evaluate surfaces and clean as follows:

**3.1.9.1** Conduct a thorough inspection over the complete surface to be treated to ensure all foreign matter that may have been retained in seams, or oily deposits that may have accumulated during or after cleaning, have been removed. Also, all corrosion that is to be chemically treated during the prepaint surface preparation must be identified.

**3.1.9.2** All surfaces shall be regarded as dirty even if there is no visible dirt. Carefully wash the aircraft or surfaces to be treated in accordance with TO 1-1-691 and spot clean using solvent wipe in accordance with <u>Paragraph 3.1.4</u>.

**3.1.9.3** Water break tests shall be conducted on representative areas to be treated immediately prior to application of corrosion removal prepaint solutions.

3.1.10 <u>Water Break Inspection</u>. The following procedures shall be used to comply with the water break inspection. A Water Break Free Kit, NSN 6850-01-524-8291, is available, which contains all the items needed to complete the test. A mist of distilled or clean tap water is atomized on the surface to be coated employing any convenient small atomizing spray device. If the water gathers into discrete (separate) droplets within 25 seconds, that is, if the surface shows a water break within this time, the surface shall be considered as failing the test. If the water forms a continuous film by flashing out suddenly over a large area, it shall be considered as failing the cleanliness test. If the water drops coalesce (go together) into a continuous film of water without a sudden flash out and form a lens, then the surface shall be considered as having satisfactorily passed the water break test. Any areas that fail the test shall be cleaned in accordance with TO 1-1-691 and reinspected.

3.1.11 <u>Evidence of Inadequate Cleaning</u>. During prepaint operations of acid-etch and chromate conversion coatings, surfaces should also be monitored for evidence of undetected soiled areas. When accomplishing the rinse of etch or conversion coating solution and a rapid flash off or breaking of the rinse water occurs, this indicates an unsatisfactorily cleaned area not detected during the random sample of the water break test. Areas that show evidence of inadequate cleaning during rinsing require recleaning and reaccomplishment of prepaint surface preparation.

3.1.12 Corrosion Removal Prepaint Compound, Aluminum.



- Exposure of magnesium surfaces to aluminum prepaint chemicals will initiate corrosion which will continue even under a new paint system and ultimately cause severe damage. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- All magnesium surfaces, steel/high strength steel and cadmium plated surfaces shall be protected from SAE AMS-1640 solutions. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

Masking of all lap joints, hinges, faying surfaces, access doors, air scoops, and other openings that would allow SAE AMS-1640 to enter or be entrapped is required prior to beginning the required prepaint process. Also, masking of unprotected mag-

10

11

12

nesium, steel, and cadmium-plated components shall be done at this time. Masking will be accomplished in accordance with <u>Chapter 2</u> of this TO using masking procedures for chemical paint removal.

3.1.13 <u>Prepaint Chemical Corrosion Removal Materials</u>. Corrosion removal compound, prepaint specification SAE AMS-1640, is used for removing oxidation and corrosion products from aluminum alloys which are not required to be Liquid Oxygen (LOX) compatible. SAE AMS-1640 is available in two types.

- Type I, liquid concentrate, which is diluted with an equal amount of water before use.
- Type II, powdered concentrate kit, materials will be dissolved in the volume of water specified on the kit.

#### 3.1.14 Application of SAE AMS-1640 Solution/Not LOX Compatible.



CORROSION REMOVING COMPOUND, SAE AMS-1640



CHEMICAL CONVERSION COATING, MIL-DTL-81706



IRIDITE NO. 14-2 CHEMICAL FILM, MIL-DTL-5541



SAE AMS-1640 is moderately toxic to the skin, eyes, and respiratory tract. Eye and skin protection is required. Good general ventilation is normally adequate. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

Apply solution by flowing, mopping, sponging, brushing, or wiping. The solution is more effective if applied warm (120 to 140 °F) (49 to 60 °C), followed by vigorous agitation with a non-metallic, acid-resistant brush or aluminum-oxideabrasive nylon mat (CID A-A-58054, Type I, Grade A). When applying the solution to large areas, start at the lowest surface working upward. Applying the solution with a circular motion to disturb the surface film will assure proper coverage. Allow the solution to remain on the surface approximately 12 minutes, then rinse away with potable water. Corroded areas identified for treatment during the prepaint process may require additional agitation beyond that specified above. Corroded areas being treated during the prepaint may also require more than one application and rinse. Examine the areas being treated with a 4 to 10 power magnifying glass to determine if another application is required. MIL-DTL-5541/MIL-DTL-81706 chemical conversion coating shall be applied immediately after the final rinse and before the surface dries.

#### NOTE

When a large area/aircraft is being treated with SAE AMS-1640, start applying solution to lowest point first and work upward.

3.1.15 <u>Surface Treatment Materials for Aluminum</u>. There are two specifications which cover formation of Chromate Conversion Coatings with its attendant process application and the Chemical Conversion Materials. These two specifications and their scope are as follows:

#### NOTE

Chromate Conversion coating specification MIL-DTL-5541 should be applied after the manufacture of new aluminum alloy repair parts.

**3.1.15.1** Chromate Conversion coating specification MIL-DTL-5541 covers two classes of chemical conversion coatings formed by the reaction of chemical conversion materials and the surfaces of aluminum and aluminum alloys. It is designed to provide corrosion protection and better paint adhesion than uncoated aluminum. It is used on aluminum alloys as a prepaint treatment for most approved paint systems, repair of damaged anodic coatings, and treatment of corrosion rework areas on clad and unclad aluminum alloys. This specification covers the preparation and application of chemical conversion materials, and film formation or consistency. These coatings are not as abrasion-resistant as anodized coatings conforming to specification MIL-PRF-8625, even though they do provide an effective means for reestablishing the corrosion resistance of mechanically damaged anodic coatings in the field. Specification MIL-DTL-5541 covers two classes of films as follows:

- Class 1A For maximum protection against corrosion
- Class 3 For protection against corrosion where low electrical resistance is required

**3.1.15.2** Specification MIL-DTL-81706, Chemical Conversion Materials for Coating Aluminum and Aluminum Alloys, covers the chemicals used in the formation of conversion coatings. These are available under this specification in three forms:

- Form I Concentrated Liquid
- Form II Powder
- Form III Premixed liquid (ready for use touch-up brush application)

**3.1.15.3** Each form of MIL-DTL-81706 can be applied by spray, brush, or immersion. Materials for Class 1A chemical films are available in iridescent yellow or light brown, or dyed in specific colors. The prepaint treatment of aircraft surfaces prior to repainting will be accomplished using specification MIL-DTL-5541, Class 1A coatings, using specification MIL-DTL-81706, color iridescent yellow.

3.1.16 <u>Touch-Up of Damaged Aluminum Surface Treatment MIL-DTL-5541</u>. The touch-up of damaged MIL-DTL-5541 coatings due to maintenance or surface preparation for maintenance painting can be accomplished using one of three methods:

- MIL-DTL-81706, mixed (if required) in accordance with <u>Paragraph 3.1.18</u> and applying to affected areas in accordance with <u>Paragraph 3.1.19</u>.
- MIL-DTL-81706, mixed (if required) in accordance with <u>Paragraph 3.1.18</u> and applying to affected areas per the "NO-RINSE PROCESS" in <u>Paragraph 3.1.17</u>.
- Touch-N-Prep<sup>™</sup> (TNP) pens (Alodine 1132), NSN 8030-01-460-0246, for minor repair of damaged MIL-DTL-5541 chemical conversion coatings on aluminum alloys can also be accomplished by applying Alodine 1132 using the TNP pens. These pens also conform to MIL-DTL-81706, Class 1A, Form VI, Method D. The solution applied with TNP pens doesn't require rinsing or wiping off following application, thus minimizing hazardous waste generation. Empty pens can be returned to manufacturer for disposal. However, check with Bioenvironmental Engineering and Environmental Management for proper disposal of used applicators. To use the TNP pen, remove the cap and charge the tip by pressing the tip against a flat surface for 10 to 15 seconds. The conversion coating solution will saturate the tip. Do not oversaturate the tip. Refresh solution often during use in a similar fashion.

#### NOTE

Acrylic tip of TNP pen can be modified or altered to form any shape to allow touching up hard to reach areas.

- a. It is necessary to ensure the surface to be treated is thoroughly cleaned before application. Immediately following cleaning, use the TNP pen to apply a chemical conversion coating solution in overlapping parallel strokes. Do not over apply the solution which would allow puddles, drips, or runs to form.
- b. Apply one coat of solution and allow coating to dry for 5 to 10 minutes before next application.
- c. Apply a second coat perpendicular to the first coat and allow it to dry. The treated surface does not require rinsing or wiping off, and it can be air dried at ambient temperature or force air dried with hot air. Once completely dried, the coating is ready for priming and/or painting.

d. Use of TNP pen will be limited to 1 square foot.

**3.1.16.1** After processing, if bare surface areas still exist, repeat Step a through Step c. Also, if the treated surface does not turn to an iridescent yellow color shortly following application, re-clean the surface and reapply per Step a through Step c.

3.1.17 <u>"No-Rinse Process" for Surface Treatment of Aluminum</u>. This process is for applying conversion coating using a "wipe-on and blot-off" method. This procedure can be used in order to minimize hazardous waste water generated from the application of MIL-DTL-81706 solutions. This process is for use on repaired areas and where coatings have been damaged or removed. Application of this process is not to exceed 4 square feet per occurrence.



CORROSION REMOVING COMPOUND, SAE AMS-1640

- a. Apply corrosion removal solution (SAE AMS-1640) diluted with an equal amount of water) by sponging, brushing, or wiping. The solution is more effective if applied warm (120 to 140 °F) (49 to 60 °C), followed by vigorous agitation with a non-metallic, acid-resistant brush or aluminum-oxide-abrasive, nylon mat (CID A-A-58054, Type I, Grade A), or scouring pads. Applying the solution with a circular motion will disturb the surface film and assure proper coverage. Allow the solution to remain on the surface approximately 12 minutes. Keep the surface wet during the entire 12 minutes. Rinse, using a clean cloth dampened with cold potable water. After rinsing with cold water, allow the water to evaporate until a thin film of water exists on the surface. Corroded areas identified for treatment during the prepaint may require more than one application and rinse. Examine suspect areas being treated with a 4 to 10 power magnifying glass to determine if another application is required.
- b. All requirements of <u>Paragraph 3.1.18</u> through <u>Paragraph 3.1.18</u>, <u>Step b</u>, shall be complied with prior to the "wipe-on and blot-off" method.



CHEMICAL CONVERSION COATING, MIL-DTL-81706



IRIDITE NO. 14-2 CHEMICAL FILM, MIL-DTL-5541

- c. MIL-DTL-5541/MIL-DTL-81706 chromate conversion coating shall be applied immediately after the evaporation period. After allowing the aluminum part to dry to a damp surface, dampen a white cotton wiping rag with MIL-DTL-81706, Class 1A, Form III, corrosion conversion coating. Dampen the rag by slowly pouring the liquid onto the rag (this will keep the material uncontaminated and minimize the amount of material being used). The rag will have a yellowish color.
- d. Wipe-on the conversion coating to the still wet aluminum part. Apply the coating in a manner such that streaking is minimized and a thin uniform coat is developed. On areas where difficulty is experienced in getting the conversion coating to react with the aluminum, light abrading with a very fine or fine aluminum oxide nylon abrasive mat, specification CID A-A-58054 dampened with MIL-DTL-81706, will help overcome the difficulty. If dark brown spots or streaking occurs, lightly rub the area with fingers of your glove.
- e. Allow the conversion coating to react with the aluminum until the aluminum turns a brassy iridescent yellowish tint. The reaction time should be at least 3 minutes, but not longer than 5 minutes.
- f. Dampen a white rag in clean water and hand ring out the rag so it is not dripping with water. Blot all of the areas that have been conversion coated with the clean wet rag. The rag should become contaminated with the conversion coating, giving the rag a yellowish color. Repeat this procedure (starting with a clean rag) at least two more times so the surface has been blotted off at least three times. No visible coating residue (yellowish color) should be on the rag after the last blotting action.

10

12

11

- g. Areas not properly coated (including those that are powdery) shall be recoated by reapplying fresh coating solution allowing it to react with aluminum until the aluminum turns a brassy iridescent yellowish tint.
- h. Contaminated rags, abrasive mats, and other materials shall be disposed of by placing them in an appropriate hazardous waste container.
- i. The coating should be allowed to air dry for 2 hours minimum or, if required, force dried by blowing dry with warm, clean air (140 °F maximum (60 °C maximum)) for 1 hour prior to overcoating with primer coating.

#### NOTE

Check with Bioenvironmental Engineering and Environmental Management for proper disposal of excess solution.

j. The final protective primer or primer/topcoat system shall be applied only on a completely dry surface and within 48 hours after completion of the MIL-DTL-81706 conversion coating application. The reapplication of SAE-AMS-1640 corrosion removal compound and MIL-DTL-81706 chromate conversion coating is mandatory if more than 48 hours has elapsed since the previous application.

3.1.18 <u>Mixing MIL-DTL-81706 Solution</u>. The use of MIL-DTL-81706 requires that the following precautions be observed.

11



CHEMICAL CONVERSION COATING, MIL-DTL-81706

## WARNING

- MIL-DTL-81706 chemical conversion coating materials are toxic and require the use of rubber gloves and eye protection (goggles and face shield) by personnel mixing or applying. If the material (which is an acid) accidentally contacts the skin or eyes, flush immediately with plenty of clean water. Report to dispensary and/or consult a physician if eyes are effected or skin is burned. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- Mixing and application shall be done in an adequately ventilated area. Avoid prolonged breathing of vapors. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- Do not permit MIL-DTL-81706 materials to come into contact with paint thinner, acetone, or other combustible material; fire may result. Also, any absorbent materials, i.e., rags, sponges, paper or nylon matting, etc., used in or exposed to these materials shall be rinsed in water before discarding. They are an extreme fire hazard if allowed to dry otherwise. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

# EAUTION

- Do not use MIL-DTL-5541 or MIL-DTL-81706 treatment on magnesium alloy, high strength steel, or on cadmium or zinc plated surfaces. If these materials are present in adjacent areas, they must be protected. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- Conversion coating material should not be allowed to enter faying surface areas or other areas where the solution cannot be adequately removed by rinsing. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

#### NOTE

- The solution will usually turn green during application if dirt or corrosion is present on the surface. The color green will not have the iridescent quality that a properly applied and dried solution will display.
- Select an area for mixing so spillage or splatter from solution will not cause damage to other equipment. Use only a stainless steel, plastic, or rubber container to mix solution. Mix only enough solution to coincide with the immediate job requirements in order that fresh materials will be available for each use.
- a. If MIL-DTL-81706, Form II Powder, is being used and it is not finely divided, crush by rolling on a clean piece of paper. This will improve mixing efficiency.



CHEMICAL CONVERSION COATING, MIL-DTL-81706

### WARNING

Nitric acid is highly toxic to skin, eyes, and respiratory tract. Eye and skin protection is required. Use only in a well-ventilated area. In case of eye or skin contact, flush immediately with water and report to dispensary. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

b. Preparation and use of MIL-DTL-81706, Form II - Powder, will be done in accordance with vendors technical instructions. This solution should be analyzed prior to use for pH value and hexavalent chromium content by the base chemical laboratory at depot facilities. Solutions used in field operations can be analyzed using pH paper or a pH meter and visual performance characteristics. Solution matter should be retested every 5 days and the chemical laboratory should be consulted should difficulties arise. Field operations prepare solutions as per vendor's instructions and test per example below. Mix three ounces of MIL-DTL-81706 powder to one gallon of clean water in an approved container. Add nitric acid, Federal Specification O-N-350, and check pH for range of 1.6 to 1.9. Five mL will usually adjust pH to this range, however, it could require up to 15 mL. Mix solution well with a clean plastic or aluminum paddle. Check the time it takes to form an iridescent yellow to brown color on a sample of the same alloy the solution will be used on. If the time is more than 5 minutes, retest the pH and make the following adjustments:

(1) A pH greater than 1.9 will require addition of 2 mL portions of nitric acid until desired pH is achieved.

(2) A pH less than 1.6 will require addition of 2 mL portions of ammonium hydroxide until the desired pH is achieved. After pH adjustment, the solution reaction time should fall within the range of 1 to 5 minutes.

c. If powder material is being used, allow the solution to stand approximately 1 hour prior to application. A small amount of powder may not dissolve; however, this is not objectionable.

#### 3.1.19 Application of MIL-DTL-81706 Solutions.



#### CHEMICAL CONVERSION COATING, MIL-DTL-81706

- a. Apply the coating solution with a fiber brush, clean rag, sponge, applicator bottle (plastic), or low pressure stream (flow-on, do not atomize). The method used for application should be selected depending on the specific job requirement. If pumping is required, pumps, valves, and fittings shall be manufactured from 18-8 stainless steel, polypropylene, or Polyvinyl Chloride (PVC). Flow on MIL-DTL-81706 solution immediately after rinsing the SAE AMS-1640 compound from aircraft surfaces which are to be painted and while these surfaces are still wet. Allow the gross amount of rinse water to run off the aircraft, but do not wait for completed drying before applying MIL-DTL-81706 solution. The oxide film just removed by SAE AMS-1640 compound will reform during this time period and prevent a proper formation of the MIL-DTL-5541 conversion coating from the MIL-DTL-81706 solution.
- b. Wet or flood the surface to be treated and keep the surface completely wet with the solution until coating is formed. This will take from 1 to 5 minutes depending on the surface condition, the particular manufacturer's product being used, and the temperature. Begin application at the lowest surface then apply sideways and upward to prevent streaking.
- c. On areas where difficulty is experienced in getting the coating to take (coating formation), light abrading with a very fine or fine aluminum oxide nylon abrasive mat, specification CID A-A-58054, Type I, Grade B, soaked with the solution will help overcome the difficulty. If the surface is dirty, remove the dirt with the nylon mat or sponge. The mat or sponge used to remove the dirt should be rinsed in clean water and squeezed almost dry before wetting with stock coating solution for reapplication.

11

11

- d. It will be noted during the initial coating application that there will be a tendency for dark (brown) spots to form on some areas. The formation of these spots can be prevented to some extent by lightly rubbing with the fingers (gloves on). If the spots are allowed to form, the applicable areas shall be abraded with the nylon mat to remove the stain and a fresh coating shall be reapplied.
- e. After controlling the stain formation, discontinue agitation, apply additional solution to keep all surfaces wet and observe the aluminum surface for a color change. The aluminum will turn a brassy yellow or iridescent greenish tint, which is easily detected through the overlying solution.
- f. Do not let the coating over develop or surface powdering will be experienced. Disturb such areas by rubbing with fingers (gloves on) or nonabrasive nylon mat as necessary.
- g. When coating formation shows on all areas, stop the reaction by rinsing or flooding the area with fresh clean water. The reaction of the solution is stopped by diluting the acid component. Be careful not to flush the solution into areas where it cannot be removed or further diluted by water. Accidental spills in confined areas can be neutralized using baking soda followed by rinsing with clean water.
- h. Allow the surface to drain or pick up the excess water by absorbing in a sponge by blotting action; do not rub. Excess rubbing will remove the coating since it is soft.
- i. Areas not properly coated (including those that are powdery) shall be recoated by reapplying fresh coating solution, abrading lightly with a nylon mat (nonabrasive or fine abrasive), allowing normal time for coating to develop, rinsing, and drying.
- j. The coating should be allowed to air dry for 2 hours minimum or, if required, speed dried by blowing dry with warm clean air (140 °F maximum (60 °C maximum)) for 1 hour prior to using a part or painting.

#### NOTE

- Check with Bioenvironmental Engineer (BEE) and Environmental management for proper disposal of excessive solution.
- The final protective paint system or primer shall be applied only on a completely dry surface and shall be applied within 48 hours after application of MIL-DTL-5541/MIL-DTL-81706 conversion coating. The reapplication of SAE AMS-1640 corrosion removal compound and MIL-DTL-81706 chromate conversion coating is mandatory if more than 48 hours has elapsed since the previous application.

#### 3.1.20 Alternate Surface Preparations for Aluminum Surfaces (PreKote SP).



PreKote SP is for exterior mold line applications only. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

#### NOTE

- PreKote SP requires specific System Program Office (SPO) approval prior to use.
- PreKote SP will only be used with chromated primers.
- PreKote SP is not a direct drop-in replacement for current chromated conversion coating processes. Unlike the
  application process for MIL-DTL-5541/MIL-DTL-81706, which produces a visible indication that the chromate
  conversion film has formed, PreKote SP does not provide any type of visible indicators. Therefore, it is absolutely critical that all steps of the PreKote SP application process be precisely followed.

PreKote SP is a non-chromic, non-hazardous and non-toxic alternative to chromate conversion coatings for surface painting preparation operations. The PreKote SP formulation is a non-chromic alkali soap with a saline adhesion promoter and inorganic inhibitor package. The PreKote SP application cleans the surface and deposits a very thin layer of adhesion-promoting organic molecules on the surface of the substrate.

**3.1.20.1** <u>Surface Preparation</u>. Preparation for aircraft cleaning shall be accomplished in accordance with TO 1-1-691 and any weapon system specific cleaning instructions. Rinse exterior of aircraft with hot water 100 to 120 °F (38 to 49 °C) to remove any residue left in seams or on surface.

## WARNING

Finish system removal using motor driven abrasives may generate airborne particles and toxic dust, which may injure personnel and create a possible dust explosion. All aerospace and motorized ground equipment shall be properly electrically grounded. Personnel shall wear dust particle masks, goggles, gloves and long sleeved shirts when using motor driven abrasives. Consult Bioenvironmental Engineering Services for respiratory and ventilation requirements. Refer to AFMAN 91-203 for additional instructions. Failure to comply could result in injury to, or death of, personnel or long term health hazards.



Avoid excessive pressure or repeated passing over the same area while sanding. Excess sanding can cause damage to the surface of the aircraft. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

#### NOTE

Some residual amounts of old coating system may be left after stripping (i.e., fastener heads, seams, hinges, surface porosity, etc.). These areas are acceptable as long as they are feathered into the surrounding surface.

- a. Lightly sand aircraft and feather sand the rough areas of the aircraft with 240 grit sandpaper.
- b. Remove all tape adhesive residue using solvent, denatured alcohol, or isopropyl alcohol.

#### NOTE

If rinse facilities are not available, solvent wipe using denatured (CID A-A-59282) or isopropyl alcohol (TT-I-735) on clean lint-free cotton rags (CID A-A-59323) is an acceptable substitute process.

#### 3.1.21 Application of PreKote SP.

### WARNING

Personnel shall wear full rain gear, face shield, and rubber gloves to remain dry during the application of PreKote SP. Failure to comply could result in injury to, or death of, personnel or long term health hazards.



- PreKote SP shall be applied when temperature is maintained between 65 to 110 °F (18 to 43 °C), and humidity
  is between 10 percent and 90 percent. Coating system failure may result if these conditions are not met. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- Use only aluminum oxide pads. Use of any other pad type may contaminate surface and prevent adhesion of primer. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effective-ness.

Apply PreKote SP using the following procedures:

a. Mask aircraft in accordance with the weapons system requirements for preparation of surfaces prior to painting.

- b. Apply PreKote SP liberally to the surface being prepared for paint by creating a "flood type coating." PreKote SP may be applied by pressure sprayer, spray bottle, or fluid feed attached to sander.
- c. Completely scrub the surface with a 180 grit aluminum oxide scrub pad (CID A-A-58054, Type I, Class 1, Grade B) to generate a rich lather. A pneumatic power buffer (preferred method) or pole may be used. Start from the top and work down. Pay particular attention to leading edges and other high-erosion areas.
- d. Let PreKote SP dwell for approximately 2 minutes. Do not rinse.
- e. Flood surface again with PreKote SP.
- f. Completely scrub surface again with a 180 grit aluminum oxide scrub pad (CID A-A-58054, Type I, Class 1, Grade B) to generate a rich lather. Start from the top and work down.
- g. Thoroughly rinse the surface with deionized or fresh water.
- h. Allow to dry.

#### NOTE

- Deionized water is preferred for the final rinse but is not mandatory. Purity standards for water conforming to ASTM D1193-06, Type IV, Grades A, B, or C are sufficient for this process.
- The maximum time allowed prior to paint application is 48 hours. Excess time prior to paint application will cause degradation of surface condition. If more than 48 hours has passed or exposure to significant contamination has taken place, wipe the surface down with a clean, PreKote SP moistened, lint-free cloth.
- To avoid damage to the PreKote SP and surface of the aircraft, all personnel shall wear cotton booties when on aircraft from this point forward.

3.1.22 <u>Use of PreKote SP on Exterior Surfaces Where Paint and Primer Have Been Removed during Scuff</u> <u>Sand, Touch-up, or Repair</u>. PreKote SP may be used on exterior aluminum parts as an alternative surface preparation for MIL-DTL-5541 chemical conversion coating, and corrosion removal treatment requirements (SAE AMS-M-3171, SAE AMS-1640) prior to prime and paint.

a. Prepare exterior surfaces in accordance with Paragraph 3.1.19.



Finish system removal using motor driven abrasives may generate airborne particles and toxic dust, which may injure personnel and create a possible dust explosion. All aerospace and motorized ground equipment shall be properly electrically grounded. Personnel shall wear dust particle masks, goggles, gloves, and long sleeved shirts when using motor driven abrasives. Consult Bioenvironmental Engineering Services for respiratory and ventilation requirements. Failure to comply could result in injury to, or death of, personnel or long term health hazards.



Avoid excessive pressure or repeated passing over the same area while sanding. Excess sanding can cause damage to the surface of the aircraft. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

#### NOTE

Some residual amounts of old coating system may be left after stripping (i.e., fastener heads, seams, hinges, surface porosity, etc.). These areas are acceptable as long as they are feathered into the surrounding surface.

b. If area to be prepared is adjacent to old paint system, lightly sand entire bare metal area and feather edges where required using 240 grit sandpaper.



CHEMICALS, ANALYTICAL, CID A-A-59282



ISOPROPYL ALCOHOL, TT-I-735

- c. Solvent wipe sanded area with denatured alcohol (CID A-A-59282) or isopropyl alcohol (TT-I-735).
- d. Mask area where PreKote SP is to be applied so as to avoid contact with surrounding paint. Masking should extend to the outside edges of the feathered area or to the edge of the part being treated.

#### NOTE

- PreKote SP may be applied by pressure sprayer, spray bottle, or fluid feed attached to sander.
- The first coat of PreKote SP may be hand or pneumatic scrubbed using 180 grit scrub pads.
- All coats of PreKote SP may be removed using a clean, lint-free cotton rag moistened with isopropyl or denatured alcohol instead of rinse with water.
- e. Follow procedures outlined in application of PreKote SP, Paragraph 3.1.21.
- 3.1.23 Corrosion Removal Solution for Magnesium.



CHROMIUM TRIOXIDE, CID A-A-55827



- Do not allow rags, brushes, abrasive mats, or any other item soaked with CID A-A-55827 chromic acid or the chromic acid pickle solution prepared with it to come in contact with any organic solvent (MEK, acetone, paint thinner, CID A-A-59601/MIL-PRF-680 dry cleaning solvent, MIL-PRF-32295, etc.); fire will result. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- CID A-A-55827 chromic acid and the chromic acid pickle solution prepared with it are highly toxic to the skin, eyes, and respiratory tract. Chemical splash proof goggles and/or face shield, chemical resistant rubber gloves and apron are required. Good general ventilation is usually adequate. Ensure this operation has been reviewed by local Bioenvironmental Engineer. In case of eye or skin contact, flush with water immediately and report to the base medical facility. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

Chromic acid pickle solution, which is a mixture of CID A-A-55827 chromic acid in water, may be used to remove surface oxidation and light corrosion from magnesium alloy surfaces. It is not adequate for removal of deep pitting, heavy corrosion, sand or other blast media residue, or the effects of blasting which will require use of one of the mechanical methods described in this chapter. If properly used, this chemical method removes much less metal causing much less reduction of sectional thickness than mechanical methods, but it shall not be used on parts containing copper or steel inserts unless they are completely masked off. Do not allow excessive amounts of anions such as chlorides, sulfates, or fluorides to build up in the solution; they tend to coat or etch the metal surface rather than removing corrosion products. Do not reuse old solutions; prepare fresh solutions for each separate removal operation.

20

18

22

- a. Mix 24 ounces of CID A-A-55827 chromium trioxide in enough water to make 1 gallon for each gallon of solution being prepared in a container fabricated from lead lined steel (any alloy), stainless steel (any CRES alloy), or 1100 aluminum alloy. For depot level operations only, a removable part that is being treated can be completely immersed in the solution with an immersion time ranging from 1 to 15 minutes at an operating temperature ranging from 190 to 202 °F (88 to 94 °C). For hand application with the solution at room temperature, the dwell time for the solution on the surface is 15 minutes minimum to 30 minutes maximum. Paragraph 3.1.21, Step b through Step d, are for hand application. Paragraph 3.1.21, Step e through Step f, apply to both the immersion and hand application methods.
- b. Mask off the surrounding areas, in particular to include all nearby operating mechanisms, joints, crevices, copper and/or steel inserts, and plated steel, to keep the solution from attacking them.
- c. Apply the chromic acid pickle solution carefully to the corroded area with a CID A-A-289 acid brush.
- d. Allow the solution to remain on the surface for approximately 15 minutes for a solution at room temperature. Agitate the area with a CID A-A-289 acid brush having half the bristle length cut off or a CID A-A-58054, Type I, Grade B or C abrasive mat.
- e. Thoroughly rinse the solution from the surface with plenty of fresh tap water.
- f. Repeat the preceding sequence as necessary until all corrosion products have been removed and the metal is a bright metallic color.

#### 3.1.24 Surface Treatment Process for Magnesium.



CHROMIUM TRIOXIDE, CID A-A-55827

22

## WARNING

Chromic acid solution is highly toxic to the skin, eyes, and respiratory tract. Avoid all contact. Skin and eye protection and vapor controls are required. Ensure this operation has been reviewed by local Bioenvironmental Engineer. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

Chemical pretreatment solution provides a passive surface layer with an inhibitive characteristic that resists corrosive attack and also provides a bond for subsequent coatings. The solution consists of the following materials and must be mixed in the ratio specified:

Water to make Chromic Acid Solution (Also known as Dow 19) Chromium Trioxide (CID A-A-55827 Type III) (99.5 percent pure) Calcium Sulfate (CaSo4<sub>4</sub>•2H<sub>2</sub>O) Operating Temperature Container

WARNING

1 gallon 1 and 1/3 ounce 1 ounce 70 to 90 °F (21 to 32 °C) Stainless steel, aluminum, vinyl polyurethane or rubber

Rubber gloves, acid apron, and eye protection shall be worn by personnel during all mixing operations. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

- a. Add chemicals to the water in the order shown, stirring the solution vigorously, either mechanically or by air agitation, for at least 15 minutes.
- b. Apply the solution to a properly prepared surface using a brush, clean rag, sponge, applicator bottle, or a low pressure stream (flow-on, do not atomize). Apply the solution to the surfaces treated with the acid pickle solution while these surfaces are still wet. Allow the gross amount of rinse water to run off the aircraft, but do not wait for complete drying be-

fore applying Chromic Acid Solution, as the oxide film just removed by the acid pickle solution will reform during this time period and prevent a proper formation of the conversion coating. When applying solution to large areas, start at the lowest surface working upward, applying the solution with a circular motion to disturb the surface film and assure proper coverage. Agitation shall be accomplished using a non-metallic acid resistant brush or aluminum oxide abrasive nylon mat (CID A-A-58054, Type I, Class 1, Grade A). Solution works best when applied at 70 °F (21 °C) or above. Leave solution on the surface 1 to 20 minutes, until a dark brown coating is produced. Rinse with cold running water while ensuring complete flushing of any residual materials.

3.1.25 <u>Surface Preparation for Steel</u>. It is essential to remove rust, scale, oil, or other contaminants from steel surfaces to be painted. The organic or inorganic zinc rich primers require good electrical contact with the steel (these primers provide galvanic protection). To enable this, the steel surfaces shall be solvent wiped in accordance with <u>Chapter 3</u> of this TO, phosphoric acid treated (reference TO 1-1-691), or sandblasted. Sandblasting to white metal is preferred. Where sandblasting is not practicable or possible, clean surfaces by means of powered wire brushes, disc sanders, grinding wheels or needle scalers (reference TO 1-1-691). Grind sharp edges to a rounded contour. Remove dust, sand, or grit by vacuuming with a HEPA filtered vacuum. Follow this with a solvent wipe in accordance with <u>Chapter 3</u> of this TO. Clean galvanized surfaces with power tools.

3.1.26 <u>Masking</u>. Masking off areas is almost invariably required in painting operations on large assemblies or structures either for protective reasons, as in the precautionary note below, or for purposes of delineation. In spray application of coatings, masking operations may consume more man-hours than the actual painting.

#### NOTE

To prevent overspray or paint drift of one color or material onto another, untreated Kraft paper may be used to mask or cover areas not specifically described below where protection of an area against overspray is the prime consideration.

3.1.26.1 Mask areas such as windows, canopies, and large openings with combinations of tapes and barrier materials:

- Specification MIL-PRF-121, usually a treated paper which is oil and moisture resistant.
- Specification MIL-PRF-131, usually a laminated foil and cloth or foil and paper with good water vapor resistance.

#### NOTE

Both types above are heat sealable.

**3.1.26.2** Pressure-sensitive masking tape conforming to SAE AMS-T-21595, Types I (creped paper backing), II (flat paper backing), and III (plastic backing), or commercial equivalent tapes.

# CAUTION

Care should be taken when cutting and trimming of the barrier/tape to prevent damage to any transparent plastic and glass surfaces. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

#### NOTE

For general large area masking, use either Type I or Type II. For operations involving sharp, fine line color separation such as aircraft markings and two-tone gloss color schemes, use Type III tape only. This tape is designed to prevent edge bleeding and is more flexible for masking shapes, curves, etc.

- a. Cover small or irregular shaped parts with tape alone. Use pressure-sensitive masking tape conforming to SAE AMS-T-21595, Types I and II, or commercial equivalent tapes.
- b. In repetitive spraying of the same or similar structures, it is advisable to have available predesigned bandages, socks, etc., of barrier paper or cloth. Locally manufactured foam plugs or inserts may be used to protect aircraft inlet areas (e.g., scoops, air intakes, engine intakes, etc.) from painting as a replacement for masking and barrier paper. It is

recommended that MIL-PRF-26514, protective ion material, be used in the making of foam plugs/inserts. One side of the plug should be covered in replaceable plastic or barrier material for easy clean up.

#### NOTE

Care should be taken to ensure that paint is not applied to certain surfaces where paint will interfere with a function. The following should be masked or otherwise protected during painting: machined surfaces that move with respect each other such as threads, bearing contacts, and gear teeth; electrical parts, such as contacts, relays, insulators, sockets, plugs, connectors, wiring, and terminals; plastic and rubber (natural and synthetic) mounts, spacers, etc.; and lubrication fittings, cups, oil holes, etc.

- c. Avoid using tape in such a way as to leave a paint edge on aerodynamic surface unless feathering by sanding can safely be done.
- d. Use only approved masking tapes in varying widths required by the job. A complex curved area is better masked initially at the paint edges with narrow (1/4 inch or 1/2 inch) tape. Wider tape may then be applied over the narrow, if required.
- e. Use only approved masking paper for large area masking. Coating solvents may dissolve and deposit printing ink from newspapers, etc., on surface of the area being masked.
- f. When spray painting, mask or cover surfaces at a distance from the area being painted which might receive overspray or paint drift.
- g. Masking tapes should be removed as soon as possible after coating application to allow edges of coating to heal and draw down as much as possible.
- h. Press tape firmly when applying it to prevent paint bleeding under it by capillary action.

#### 3.1.27 Tack Ragging.



Exercise extreme caution in applying protective finishes to parts and equipment which may contact propellants directly or by accidental spillage. Critical areas may have to be masked. The guidance of applicable equipment technical manuals or engineering drawings shall be followed concerning use of protective finishes on parts or equipment used in or near propellant storage and transfer systems. Failure to comply could result in injury to, or death of, personnel or long term health hazards.



Commercial rental wiping cloths, laundered shop cloths, or disposable fiber or chemically treated paper wiping materials shall not be used. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

To ensure that all primed surfaces are free from foreign matter, they should be tack ragged immediately before applying the topcoat. Do not tack rag an entire large structure at one time. Each area to be painted should be tack ragged immediately prior to the application of finishing material to that area. Surfaces are gently wiped with the tack rag, removing accumulations of dust and other foreign matter. One form of tack rag in common use to CID A-A-2522, Grade A, Color 1 dampened with an approved solvent per <u>Table 3-2</u>. Other commercially available forms of tack rag which are designed for the purpose of removing surface contamination from an area receiving paint may also be used. Do not use a tack rag to clean more than 10 square feet at a time to prevent spreading any contaminants on the rag over a large surface.

## CHAPTER 4 PAINTING APPLICATION METHODS

#### 4.1 <u>GENERAL</u>.

Spray application is the standard for painting Air Force (AF) aircraft and most other equipment. It is fast and, in the hands of skilled operators, produces films of good uniformity and quality. When application is described in this technical manual without specifying the method, High Volume Low Pressure (HVLP) spray application is implied. Methods other than spraying are useful in special cases, particularly in non-aeronautical or less critical applications. Brush or roller applications have their place and should be considered as alternate methods when used with suitable materials. The painter's discretionary use of brush or roller for painting aerospace equipment should be based on local circumstances such as health or fire hazards. Additionally, there are some requirements which demand brush application, such as painting porous surfaces which require brushing-in for adequate coverage and penetration.

#### 4.2 SPRAY METHODS.

The AF uses several hand-operated spray methods: hot spray, cold and/or hot airless, air assisted airless, HVLP spray, and any of these methods in conjunction with electrostatics. The HVLP method is now the standard spray method used in the AF and meets the requirements of environmental regulations.

4.2.1 <u>HVLP Spray</u>. In this method, the coating material is atomized by a high volume of low pressure air through the spray gun nozzle. The HVLP spray equipment generally utilizes low pressure (below 20 Pound-force per Square Inch (PSI)) gun cups to assist in delivery of the coating material to the gun nozzle. Low pressure air between 1 and 10 PSI is used to atomize the coating material at the spray head. A high volume of air is used to push the coating material and form a very soft, low-velocity pattern. This soft spray generally provides more consistent coverage and a better overall finish. The HVLP gun should be held closer to the surface (6 to 10 inches) than a conventional air spray gun because of the lower speed of the paint particles. The film thickness generated in a single coat is often greater than that of conventional air spray systems. This equipment shall not be used above 10 PSI at the nozzle. Pressure should be checked regularly with a nozzle pressure gauge. (See Figure 4-1.)



Figure 4-1. Nozzle Pressure Gauge

4.2.1.1 <u>HVLP Touch-Up Spray Gun</u>. For minor touch-up and application of insignias and markings, a small HVLP spray gun may be used. While designed for applying quantities less than a quart, it has all of the advantages of the full size HVLP. It is also preferred over other aerosol power pack spray units for touch-up if an air source is available.

4.2.2 <u>Hot Spray</u>. Hot spraying is the application of coatings with HVLP or airless spraying equipment using heat as a substitute for all or a portion of the thinner ordinarily used to reduce coating materials to spraying viscosity. Hot spray is most frequently and effectively used with the airless spray system. Also, the hot paint, while cooled rapidly when atomized, retains sufficient heat to still be close to the ambient air temperature when it reaches the work surface. This reduces the possibility of blushing due to moisture condensation and allows spraying under conditions of relatively high humidity. However, a disadvantage is that heating the paint reduces its pot life.

4.2.3 <u>Airless Spray</u>. The term airless comes from the fact that no air pressure is used with this paint application method. Instead, hydraulic pressure is used to deliver the coating material, heated or unheated, to the gun head and atomize it by ejecting it from special spray nozzles. These nozzles increase the pressure by a factor of approximately 100. Atomization of the

coating material and formation of the spray pattern are created by the gun nozzle. The droplets move toward the work surface by their momentum and are appreciably slowed down by air resistance. There is less bounce of the coating material on arrival at the work surface and, therefore, less overspray. The cooling effect of expanding air associated with conventional spray is not present, so the only heat loss in the cold airless method is through solvent evaporation. In the hot airless method, the material arrives at the work surface warmer than with other methods of spraying, usually at or above ambient air temperatures.

4.2.4 <u>Air-Assisted Airless Spray</u>. In this method, the coating material is atomized by hydraulic pressure the same as airless spray but at a much lower pressure. Low pressure air is added at the gun head and directed at the paint mist to control and form the spray pattern. While the coating can be atomized at lower hydraulic pressure through the spray nozzle, proper spray pattern formation requires the assistance of the low pressure air through jets at the nozzle. This allows the operator control of the atomized coating pattern that cannot be done with standard airless. It offers almost equivalent advantages in spraying as the airless spray method, while being safer and requiring lower maintenance on pumps. These advantages are due to the lower hydraulic pressures used. In addition, the appearance of coatings applied by this method is better as the tendency to orange peel is lessened.

#### 4.2.5 Electrostatic Spray.



Electrostatic spray painting of Jet Propellant 8 (JP-8) fueled aircraft constitutes a significant hazard when the onboard fuel temperature exceeds 100 °F (38 °C). Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

This method is a variation of the spray methods previously described which adds the feature of electrostatic charging (60,000 volts at about 200 microamperes ( $\mu$ A) of the paint material which is then attracted to the grounded work piece. Charging of paint material can occur either inside the gun or at a fine metal probe at the gun nozzle exit (the most common method). Typically, this requires specially designed paint guns as most HVLP, airless, or air-assisted airless guns cannot be modified to add this feature. This method is more effective with airless or air-assisted airless as the combination of low-particle velocity of the airless spray and the electrostatic attraction to the work piece produces an excellent transfer efficiency rate. Electrostatic spray painting equipment can be powered by an external electrical source or a self-generating electrical source contained within the spray gun. Overspray is greatly reduced and hard-to-coat areas such as edges or geometric shapes are more effectively painted. The work piece (aircraft, etc.) is not charged electrically, but is grounded as in normal painting practices. This method has limited effectivity in coating interior corners, crevices, and cavities due to the Faraday Effect, that causes charged paint particles to be repelled from the deepest points, and on some aircraft exterior surfaces, due to aluminum components being insulated by anodize, or due to composite materials that cannot be grounded. The safety precautions, operational parameters, and equipment maintenance for this method in <u>Paragraph 5.5.3</u> must be strictly followed.

#### 4.3 SPRAY PAINTING EQUIPMENT, GENERAL.

4.3.1 <u>HVLP Spraying Systems</u>. All HVLP spray systems have certain basic components necessary for their efficient operation. There must be an adequate source of compressed air, a supply of the finishing material from a reservoir or feed tank, a spray gun, and a device for controlling the combination of air and finishing material. Other refinements, such as an air-pressure transformer (regulator), air filter, water drain, hose cleaner, etc., are incorporated in the system to provide more efficient and satisfactory results. Figure 4-2, Figure 4-3, and Figure 4-4 are diagrams of complete spray systems.

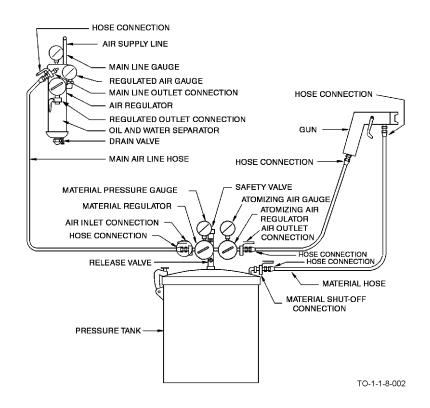


Figure 4-2. Simple Spray System Setup

4.3.2 <u>Spray Gun, General</u>. Spray guns are mechanical devices for atomizing or breaking-up coating materials into a spray and applying it under control, to a surface to form a continuous film. <u>Figure 4-5</u> illustrates a sectional view of a typical spray gun. It is a precision instrument and must be treated as such. Its daily care and maintenance determine the effectiveness of spray painting. It should not be used by untrained personnel.

4.3.3 <u>Classes of Spray Guns</u>. HVLP spray guns are classed in three general types: suction feed, gravity feed, and pressure feed. Each type is further subdivided by having either external or internal mix air caps. For the most part, the AF uses the external mix type.

4.3.3.1 The suction feed (or siphon) cup gun is usually fitted with a fluid cup. Its nozzle assembly is designed to feed paint into the air-stream by the vacuum created from the air flowing past the fluid tip which protrudes into the air stream beyond the air cap. The amount of spraying at one time is limited to the contents of the cup. This gun is most commonly used in painting smaller areas, usually within the confines of a spray booth. (Figure 4-4, Detail 2, illustrates suction feed hookup.)

4.3.3.2 The pressure feed gun is designed to fluid feed to the gun under pressure from an external tank through a hose. The air cap and fluid tip are flush with each other, and no siphoning effect is necessary. It is suitable for high volume painting. (Figure 4-4, Detail 1, illustrates pressure feed hookup.)

**4.3.3.3** The gravity feed gun is designed with the cup located on the top of the spray gun. This allows paint to completely drain, minimizing paint waste. Gravity feed guns supply paint to the orifice solely by means of gravity. The air pressure at the orifice of these guns is typically 40 to 50 Pound-force per Square Inch (PSI).

4.3.4 <u>Material Containers</u>. Two types of containers serve as material reservoirs for spray guns, the cup and the tank. Both cups and tanks are available with agitators to provide constant mixing to keep materials in suspension during application. Agitators are mechanically operated by either an air or an electrical powered motor. See <u>Chapter 6</u> to determine which coatings require agitators.

**4.3.4.1** Cup containers are used when small quantities of paint are to be sprayed. They are generally of the suction type with a small vent on top of the container through which atmospheric pressure operates to force material up to the fluid tip when a compressed air stream creates a vacuum at the spray opening.

**4.3.4.2** Pressure feed tanks are used for high volume painting. Pressure feed tanks are tightly closed metal containers of varying size (2 to 120 gallons) that provide material at a uniform pressure and a constant rate of flow. Compressed air is directed into the tank to force the material out. Air pressure must be increased or decreased to change the rate of flow.

4.3.5 <u>Air Compressors</u>. Air compressors provide a continuous supply of compressed air at a predetermined maximum pressure and a minimum volume in Cubic Feet per Minute (CFM). There are two general types of air compressors, single stage and two stage. These can be further subdivided into many types such as portable or stationary, electric motor or gas engine driven, unloader or pressure switch controlled, and air or water cooled.

4.3.6 <u>Air Regulators or Transformers</u>. A regulator is a device equipped with indicator gages which reduces the main line air pressure to a lower regulated pressure. It also provides outlets to which spray guns and other air operated equipment may be connected. It must be capable of providing 15 CFM of air at 80 PSI (supply line pressure) with a maximum pressure drop of 10 PSI.

4.3.7 <u>Air Condensers</u>. An air condenser is similar to the air transformer and separates oil and moisture from the air. A condenser is usually equipped with pressure gages, but may be found without gages where a regulated supply of air is available.

#### NOTE

Air condensers and transformers shall be drained at least daily and more frequently in humid weather.

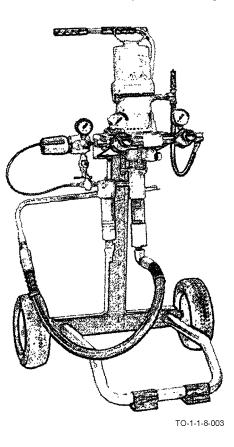


Figure 4-3. Airless Spray System


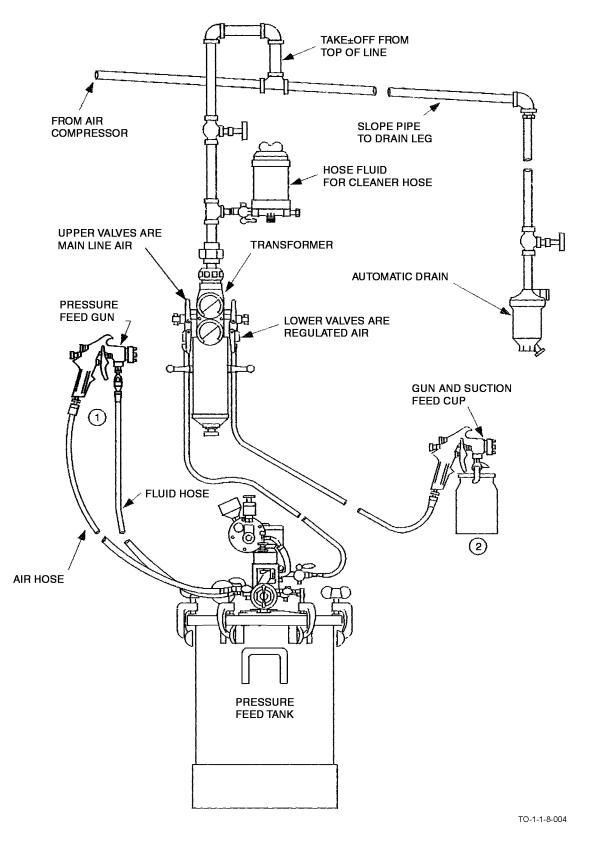


Figure 4-4. Complete Spray System

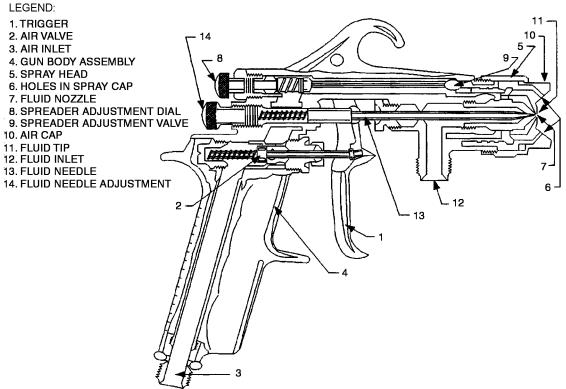

TO-1-1-8-005



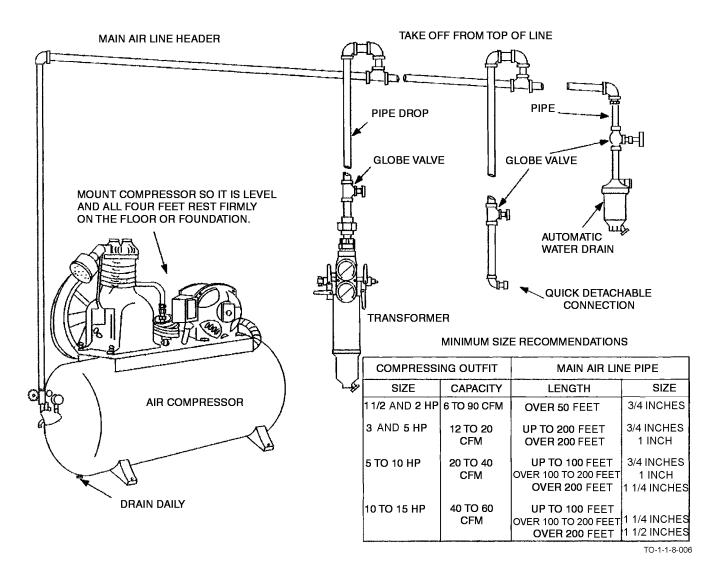


Figure 4-6. Proper Installation of Air Compressor, Piping

4.3.8 <u>Air Supply</u>. Figure 4-6 illustrates proper installation of an air supply for paint spraying.

4.3.9 <u>Hose</u>.



Hoses shall always be thoroughly cleaned by flushing with solvent appropriate for the coating material used. When the material is a catalyzed (two-component) system (epoxy or polyurethane), this must be done immediately after use to prevent the material from curing in the hose. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

Because of friction losses in hose, it is essential that the proper size and length be used. Do not use hoses longer than 50 feet. High-pressure air hose leading from the air source to the regulator or tank which may be a maximum of 150 feet if required to reach the tail surfaces of exceptionally large aircraft. Extra lengths of hose may be attached for this use but shall be removed as soon as no longer needed. The high-pressure air hose shall have a minimum Inside Diameter (ID) of 7/16 inch. The fluid hose from the tank to the gun shall be no less than 3/8 inch ID and the air hose from the regulator to the tank and from the tank to the gun shall be no less than 5/16 inch ID. Any reduction in size or increase in length may produce unsatisfactory results. Air and paint hoses are furnished in various standard lengths.

#### 4.4 SPRAY PAINTING.

4.4.1 <u>Gun Techniques</u>. Spray guns are designed to be used with certain spraying techniques. The quality of finish that is applied will depend on how well these techniques are used by the painter. Spraying techniques include the following:

4.4.1.1 <u>Distance</u>. Distance depends on the desired width of the paint fan and the type of gun used (<u>Figure 4-7</u>, Detail A). When all adjustments to the spray gun are correct and the spray gun is held at too great a distance from the surface, it will result in a dry spray (dusting) and excessive overspray. Conversely, if the spray gun is too close to the surface, it will result in too heavy a coating with a tendency for sags or runs to develop.

4.4.1.2 Stroking. The essence of proper stroking is to maintain as near as possible the same distance to the work, the same speed, and the same perpendicularity of the gun to the surface throughout the pass. The natural tendency for spray painters, particularly when fatigued or in an uncomfortable position is to arc or wave the gun (Figure 4-7, Detail B). This practice must be avoided at all costs. In general, wrist movement must be eliminated in stroking as almost inevitably it causes the gun to describe a curve instead of remaining perpendicular to the surface. This results in a thicker coating in the middle of the stroke than at the end. An exception to the rule is spotting in for touch-up. In this case, it is permissible to fan the gun to produce an area which is thinner at the edges in order to blend into the surrounding painted area. When applying coating materials with poor flow characteristics (such as vinyl paints), special efforts must be taken to hold the gun perpendicular to all surfaces (flat or contoured). If this is not done, the irregular spray pattern formed will produce an uneven thickness and cause uneven drying. Protrusions such as screw heads, etc., present surfaces that will require facing the gun in several directions to completely coat them. It may be advisable to spot paint these in advance. The rate of the stroke should be uniform to produce a full wet coat of material. Stroking should be in parallel passes with each stroke aimed for a 50 percent overlap, or so that the middle of the spray pattern strikes the wet bottom edge of the previous stroke (Figure 4-8). In order to ensure good coating integrity and coverage, the technique of cross coating is best (Figure 4-9). Cross coating should always be used when applying multiple coats of a coating system. This is done by applying each layer using the 50 percent overlap and cross coating with each alternate layer of the coating system, usually after a drying or curing period between coats. The crosscoating technique is also the standard for applying a single coat finish system by applying a thin, wet coat followed immediately with another thin cross coat to obtain one full wet coat. When applying high solids primers and topcoats, with HVLP, airless, or air assisted airless equipment, a single coat using 50 percent overlap without a cross coat may be used. The process control must be adequate to prevent holidays or other finish defects that may result from a single heavy application.

4.4.1.3 <u>Triggering</u>. Proper triggering of the gun is difficult to learn. The variations of triggering technique which may be called for in special situations can only be developed by practice. It is a matter of judgment and experience. In general, the painter should begin his stroke before triggering the gun and release the trigger before stopping the stroke. It can be compared to the follow-through in swinging a golf club. This tends to feather out the end of a stroke so that the end of a succeeding overlapping stroke blends into it. Examples of correct techniques are shown in Figure 4-7.

#### NOTE

- A reasonable amount of care will maintain spray guns and spray equipment in top operating condition and prevent a majority of spraying difficulties. Thorough cleaning immediately after use and appropriate lubrication are essential.
- This manual provides only general spray gun information. See specific manufacturer's booklet or manual for detailed operating and maintenance instructions.


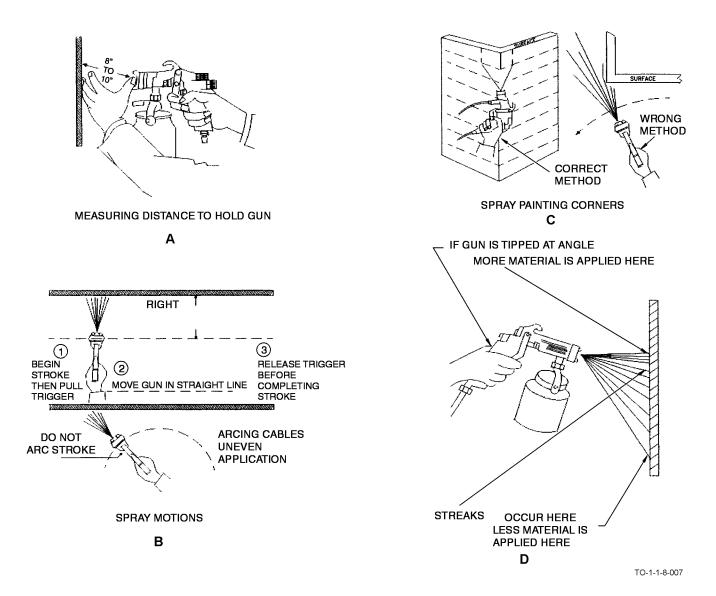


Figure 4-7. Right and Wrong Methods of Spraying

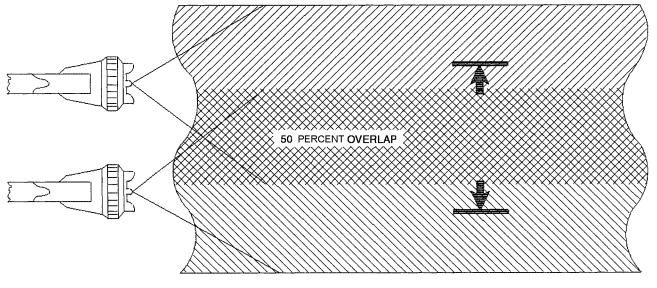

TO-1-1-8-008



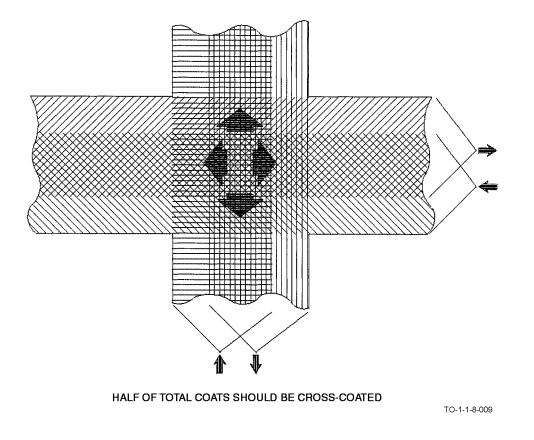


Figure 4-9. Cross Coating

4.4.2 <u>Gun Adjustments</u>. The flow of air and fluid at the gun must be adjusted or balanced to obtain proper atomization and other desired spraying characteristics.

4.4.2.1 The first consideration in obtaining this balance is the proper combination of air cap and fluid tip for the particular material being sprayed as recommended by the equipment manufacturer and the coating material manufacturer.

4.4.2.2 After the air cap and fluid tip have been selected, there are several adjustments which may be made with the gun controls to properly adjust the air and fluid relationship. These adjustments are necessary to obtain proper atomization and other desired spraying characteristics required for the job and conditions. The fluid adjusting screw on the gun (Figure 4-10, B) permits restriction of fluid flow relative to the volume of air being used, but is limited since it puts additional tension on the gun trigger and tends to discourage feathering at the beginning and end of the stroke.

4.4.2.3 For pressure feed spraying, adjustment of tank pressure and adjustment of the atomization air supply to the gun is more effective for obtaining the proper air to fluid balance.

4.4.2.4 The air adjustment screw (Figure 4-10, A) can be changed to spread the atomized fluid out over a greater area, which, in combination with the increased air flow, is equivalent to reducing the flow of fluid.


#### NOTE

Do not thin the paint excessively to increase the flow of fluid.


4.4.2.5 The correct atomizing pressure depends on the type of coating and the length and diameter of the air line from the regulator to the gun. The pressure must be sufficient to completely atomize the material being sprayed but no greater. For HVLP paint guns, the regulator pressure shall be adjusted to a lower level to ensure the nozzle pressure does not exceed a maximum of 10 PSI in accordance with Paragraph 4.2.1. An excessive amount of air may give a split pattern in which the material deposited is light in the middle of the pattern; too little air may give a heavy centered pattern. Pressure on the paint pot is usually adjusted to a range of 25 to 40 PSI but may vary more widely, depending on the density of the paint and the elevation of the surface being painted above the pressure tank. In normal operation, the wings on the nozzle are in the horizontal position which provides a vertical fan-shaped pattern for maximum coverage as the gun is moved back and forth parallel to the surface being painted. The spray pattern is variable from round to flat with all patterns in between and can be adjusted to obtain the pattern which produces the best results.

#### NOTE

As the width of the spray is increased, more paint must be allowed to pass through the gun to get the same coverage.

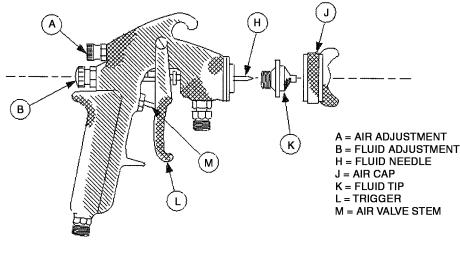

TO-1-1-8-010



4.4.3 <u>Painting Difficulties and Remedies</u>. Coating troubles may be divided into five groups: inadequate surface preparation, incorrect methods or techniques of application, unusual climatic or atmospheric conditions, unusuable equipment, and

faulty finishing material. Inadequate surface preparation is self-explanatory and is discussed in <u>Chapter 3</u>. Incorrect methods of application should be discontinued upon discovery of the discrepancy. Remedying incorrect techniques of application, however, calls for training. The practice of allowing inadequately trained personnel to apply coatings, particularly to aeronautical surfaces, is unauthorized and dangerous. Conditions such as adverse weather and humidity may cause the application method chosen to be unworkable. Unusual climatic and atmospheric condition can to some extent be remedied or compensated for by temperature and humidity controls, shielding from elements, etc. Consideration should always be given to alternative methods such as hot spraying or even brushing and roller coating on certain surfaces. Unsuitable or faulty equipment can only be remedied by obtaining proper equipment or repair. An experienced painter may be capable of compensating for faulty materials to obtain proper results, but this is an emergency measure only and must be with the cognizance and authority of the quality control facility. Table 4-1 and Figure 4-14 through Figure 4-22 lists common troubles of spray coating operations with suggested remedies or methods of avoidance.

Trouble	Possible Causes	Preventive Measures or Remedies
Sags and Runs	1. Dirty air cap and fluid tip (distorted spray pattern).	1. Remove air cap and clean tip and air cap carefully.
	2. Gun stroked too close to the surface.	2. Maintain 6 to 10 inches for HVLP gun distance from surface.
	3. Trigger not released at end of stroke (when stroke does not go beyond object).	3. Release the trigger after every stroke.
	4. Gun stroked at wrong angle to surface.	4. Keep gun at right angle (perpendicular) to surface during stroke.
	5. Coating material too cold.	5. Heat material by approved methods.
	6. Coating applied on too heavily.	6. Develop ability to apply correct thicknesses by panel practice.
	7. Coating material thinned excessively.	7. Add the correct amount of solvent by measure or determine by viscosity test.
Streaks	1. Dirty air cap and fluid tip (distorted spray pattern).	1. Remove air cap and clean tip and air cap carefully.
	2. Insufficient or incorrect overlapping of strokes.	2. Follow the previous stroke accurately. Deposit a wet coat.
	3. Gun stroked too rapidly (dusting of the paint).	3. Avoid whipping. Make deliberate, slow strokes.
	4. Gun stroked at wrong angle to surface.	4. Keep gun at right angle (perpendicular) to surface during stroke.
	5. Stroking too far from surface.	5. Maintain 6 to 10 inches for HVLP gun from surface.
	6. Too much air pressure.	6. Use least air pressure necessary.
	7. Split spray.	7. Clean the fluid tip and air cap.
	8. Coating material too cold.	8. Heat material to get good flow-out.
Paint will not come from Spray Gun	1. Out of paint (gun begins to sputter).	1. Add paint, correctly thinned out and strained.
	2. Settled, cake pigment blocking gun tip.	2. Remove obstruction, stir paint thor- oughly.
	3. Grit, dirt, paint skins, etc., blocking gun tip, fluid coat valve or strainer.	3. Clean spray gun thoroughly and strain the coating material. Always strain materials before using.
Paint will not come from Pressure Tank	1. Lack of proper air pressure in the pressure tank.	1. Check for leaks or lack of air entry. Set correct pressure.
	2. Air intake opening inside of pressure tank lid, clogged by dried-up material.	2. This is a common trouble. Clean the opening periodically.
	3. Leaking gaskets on tank cover.	3. Replace with a new gasket.
Paint will not come from Suction Cup	1. Dirty fluid tip and air cap.	1. Remove air cap and clean tip and air cap carefully.

Table 4-1. Spray Coating Troubles, Possible Causes, and Remedi	Table 4-1.	<b>Spray Coating Troubles</b>	Possible Causes.	and Remedies
--	------------	-------------------------------	------------------	--------------

Trouble	Possible Causes	Preventive Measures or Remedies
	2. Clogged air vent on cup cover.	2. Remove the obstruction.
	3. Using wrong air cap.	3. Ascertain and use correct setup.
	4. Leaky connections on fluid tube or nozzle.	4. Check for leaks under water and repair.
Excessive Material Loss	1. Not triggering the gun at each stroke.	1. It should be a habit to release trigger after every stroke and retrigger to begin the next stroke.
	2. Stroking at wrong angle to surface.	2. Gun should be stroked at right angles to surface and the stroke parallel to the surface.
	3. Stroking gun too far from the surface.	3. Stroke the gun 6 to 10 inches for HVLP gun from the surface.
	4. Wrong air cap or fluid tip.	4. Ascertain and use correct setup.
	5. Depositing a film of irregular thickness.	5. Learn to calculate the depth of wet film of finish and develop control. Measure wet film thickness.
	6. Air pressure too high.	6. Use the least amount of air necessary.
	7. Fluid pressure too high.	7. Reduce pressure. If pressure keeps climbing, clean regulator on pressure tank.
	8. Coating material too cold.	8. Heat to enable reduced air pressure.
Excessive Spray Fog (Figure 4-11)	1. Too high air pressure.	1. Use the least amount of air pressure necessary.
	2. Spraying past surface of the product.	2. Release trigger when gun passes target.
	3. Wrong air cap or fluid tip.	3. Ascertain and use correct setup.
	4. Gun stroked too far from the surface.	4. Stroke the gun 6 to 10 inches for HVLP gun from surface.
	5. Material thinned out too much.	5. Add the correct amount of solvent by measure or test.
Paint Leaks from Spray Gun (Figure 4-12)	1. Fluid needle packing nut too tight.	1. Loosen nut, lubricate packing.
·	2. Packing for fluid needle dry.	2. Lubricate this part daily.
	3. Foreign particle blocks fluid tip.	3. Remove tip and clean.
	4. Damaged fluid tip or needle.	4. Replace both tip and needle.
Gun Sputters Constantly (Figure 4-13)	1. Fluid nozzle not tightened to the spray gun.	1. Tighten securely, using a good gasket.
	2. Leaking connection of fluid tube or needle packing (suction cup).	2. Tighten connections; lubricate packing.
	3. Fluid pipe not tightened to the pressure tank lid.	3. Tighten. Check for defective threads.
Orange Peel (Figure 4-14)	1. Coating material not thinned out sufficiently.	1. Add the correct amount of solvent by measure or viscosity test.
	2. Coating material too cold.	2. Heat material to get flow-out.
	3. Insufficient air pressure.	3. Increase air pressure or reduce fluid pressure.
	4. Using wrong air cap or fluid nozzle.	4. Select correct air cap and nozzle for the material and feed.
	5. Gun stroked too far from the surface.	5. Stroke the gun 6 to 10 inches for HVLP gun from surface.
	6. Overspray striking a previously sprayed surface.	6. Spray detail parts first. End with a wet coat.

Table 4-1.	Spray Coating Troubles, Possible Causes, and Remedies - Continued
------------	---

Trouble	Possible Causes	Preventive Measures or Remedies
Sandpaper Finish ( <u>Figure</u> <u>4-15</u> )	1. Unsatisfactory primer.	1. Laboratory analysis to verify acceptabil- ity of the material; check primer applica- tion procedures.
	2. Excessive dirt contamination from painting area.	2. Provide cleaner painting areas.
	3. Insufficient scuff sanding of primer.	<ol> <li>Scuff sand primer using Number (No.)</li> <li>and No. 400 wet or dry sandpaper.</li> </ol>
	4. Improperly cleaned paint lines.	4. Flush paint lines frequently with solvent.
	5. Dried overspray, gun too far from surface.	5. Sand the complete finish until smooth to the fingertips. Stroke gun 6 to 10 inches for HVLP gun from the surface.
Wrinkling ( <u>Figure 4-16</u> )	Caused by applying too thick a coating, this prevents uniform drying of the coat and thus results in formation of ridges and furrows.	Material should be applied in thin uniform coats. If a thick coating is necessary, it should be applied by spraying several thin coats until the desired thickness is obtained. Allow each coat to set before applying the next.
Crazing, Mud Cracking, Checking ( <u>Figure 4-17</u> and <u>Figure 4-18</u> ).	1. Painting over a hard glossy coat. A base coat of this condition offers a poor surface adhesion of subsequent coats. In drying, the topcoat slides over the base coat, breaking out in cracks.	1. Remove all previous coats of paint using paint remover or scuff sand, solvent wipe, and apply a primer tie coat before overcoating.
These three defects are all very similar in that they all consist of surface cracks in	2. Excessive amount of catalyst in paint causing brittleness.	2. Drier should be used only as recom- mended by manufacturer of material being used.
varying degrees. Crazing is a fine surface crack while cracking and checking often	3. Excessive heat employed in drying operation.	3. Exercise caution in placement of heat lamps to assure uniform heat distribution over the entire painted area.
extend to the metal surface.	4. Insufficient drying times between coats.	4. Allow sufficient drying times.
Pinhole Cavities, Solvent Pop	Improper surface treatment or lack of surface treatment; entrapped oils and/or solvents; insufficient primer drying times; use of improper thinner.	Apply manual surface treatment and ensure complete coverage with surface chemical film, before primer application; check mixing instructions to eliminate use of improper thinners.
Excessive Blushing of Topcoats.	Excessive humidity; insufficient quantity of Specification blush-retardant thinner ASTM D330.	Check humidity control equipment where employed and/or increase quantity thinner ASTM D330.
Peeling	Failure to remove moisture, oil or grease from the surface before the finish is applied.	Refinish surface.
Blistering (Figure 4-19)	1. Oil or grease on surface.	1. Strip and clean; or sand down and repaint.
	2. Moisture in lines.	2. Drain lines periodically.
	3. Trapped solvents.	3. Use proper thinner.
Inconsistent Coloring	Pigment not evenly distributed as a result of settling or insufficient mixing.	Apply additional coats after thoroughly mixing the finish material.
Defective Spray	1. Setting too low on fan adjustment.	1. Adjust fan adjusting valve.
Patterns	2. Air cap; atomizing pressure too low.	2. Adjust atomizing pressure.
(Heavy Center)	3. Pressure feed: Fluid pressure too high for normal capacity of air cap.	3. Adjust fluid pressure.
	4. Nozzle too large for fluid used.	4. Replace nozzle with correct size.


 Table 4-1.
 Spray Coating Troubles, Possible Causes, and Remedies - Continued

Trouble	Possible Causes	Preventive Measures or Remedies
Defective Spray Patterns (Split Spray)	Air and fluid feeds not properly balanced.	Reduce width of spray pattern by means of the spreader adjusting valve, and if condition is not remedied, increase fluid pressure. The latter increases rate of material flow. Readjust atomizing pressure, fluid pressure, and spray width until desired spray is obtained.
Defective Spray Patterns (Heavy Top or Bottom) (Heavy Right or Left)	1. Horn holes partially clogged. Obstruction on top or bottom side of nozzle.	1. Determine location of obstruction by rotating air cap one-half turn and spray a new pattern. If defect is reversed, obstruc- tion is in air cap; if not reversed, it is on the nozzle of fluid tip.
	2. Dirt on air-cap seat or nozzle fluid tip seat.	2. Clean. Check for burrs and dried paint in opening.
Starving the Spray Gun	1. Insufficient air because of waste filter in transformer too tightly packed or clogged.	1. Repack or replace filter.
	<ol> <li>Air cocks, hose or pipelines too small.</li> <li>Inadequate air supplies from too small a compressor or a break in the system.</li> </ol>	<ol> <li>Replace with units of adequate size.</li> <li>Obtain a compressor of adequate size or repair leakage.</li> </ol>
Failure of Wet Tape Test	Insufficient drying time for primer; insufficiently cleaned surface; cleaning compound residue, etc. Oil seepage through inspection doors or fasteners; entrapped oils and soil in shop applied temporary primer; insufficient removal of shop primer and/or previous coatings; use of final finishes incorporating wax ingredients; use of laundered rags in- stead of new lint free cotton rags; seepage of water containing cleaning in compound residues from between faying surfaces.	Employ solvent wipe down, in accordance with <u>Chapter 2</u> of this TO; remove any shop primers to provide a clean aluminum surface prior to any painting; employ solvent-dampened cloths in lieu of dry cloths for removal of oil contamination (especially along jet engine inspection doors); conduct laboratory analysis to determine primer acceptability; allow aircraft to stand for sufficient time to permit drainage of effluent before final cleaning; note the type of failure, such as to bare metal intercoat failure, and select the applicable remedy according to the cause of failure.
Fish-Eyes and Poor Wetting, Crawling, Poor Flow out. (Figure 4-20)	Use of waxes or sealants and adhesives contain- ing silicones. Presence of other types of oils, greases, or hydraulic fluids on the surface.	Solvent wipe with silicone-removing compounds.
	NOTE	
	Minute quantities of silicones can cause this film.	
Lifting ( <u>Figure 4-21</u> )	1. Absorption of solvents by previous partially dried film.	1. Allow coats to dry/cure for the proper dry to over-coat time before recoating for epoxies, polyurethanes, and lacquers; with enamels either allow first coats to dry completely, or apply second coats immediately.
	2. Second coats apt to lift if surface is poorly prepared.	2. Begin with properly prepared surface.
	3. Use of lacquer over enamel.	3. Use compatible coatings and thinners. Enamel may be applied over lacquer but lacquer may not be applied over enamel.

Table 4-1.	Spray Coating Troubles, Possible Causes, and Remedies - Continued
------------	---

Trouble	Possible Causes	Preventive Measures or Remedies
	4. Use of lacquer thinner in enamel.	4. Use compatible coatings and thinners. Enamel may be applied over lacquer but lacquer may not be applied over enamel.
Pitting or Cupping ( <u>Figure</u> <u>4-22</u> )	1. Rust under surface.	1. Strip and clean; or sand down and repaint.
	2. Oil or grease on surface.	2. Strip and clean; or sand down and repaint.
	3. Moisture in lines.	3. Drain lines periodically.
	4. Trapped solvents.	4. Use proper thinner proportions and allow proper cure times.

 Table 4-1.
 Spray Coating Troubles, Possible Causes, and Remedies - Continued

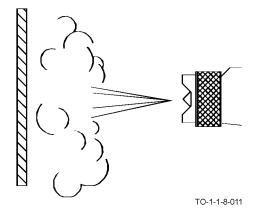



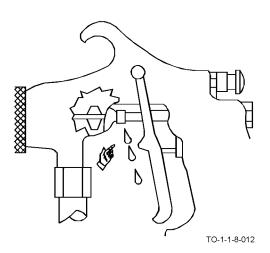


Figure 4-12. Paint Leaks From Spray Gun

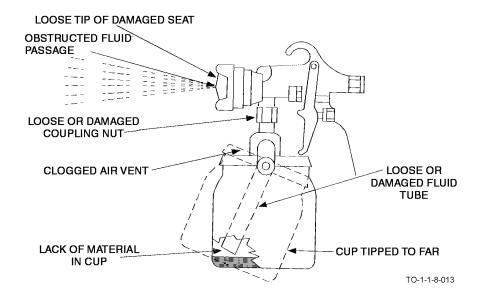


Figure 4-13. Gun Sputters Constantly

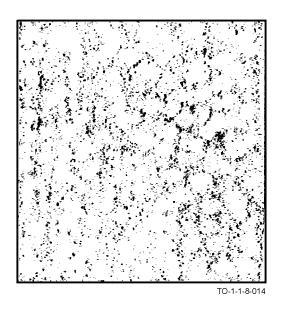


Figure 4-14. Orange Peel

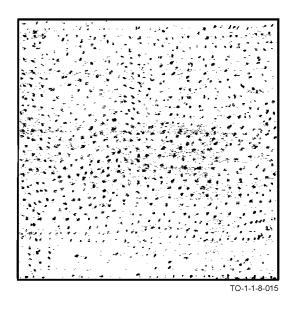
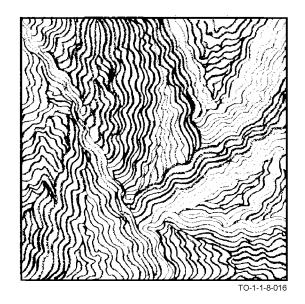



Figure 4-15. Sandpaper Finish





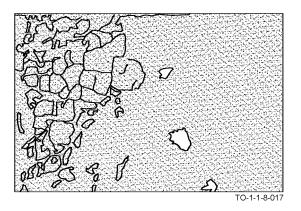


Figure 4-17. Crazing

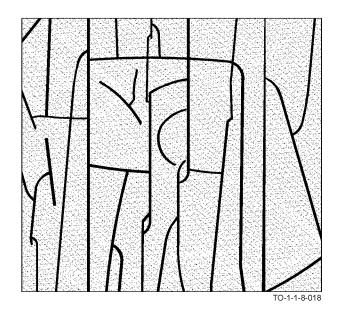


Figure 4-18. Cracking


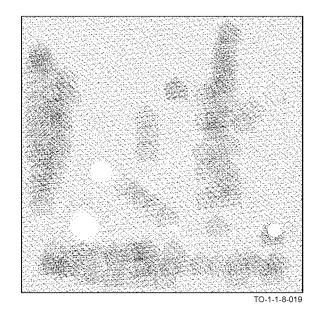


Figure 4-19. Blistering

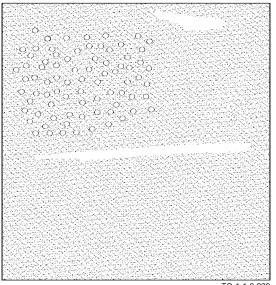

TO-1-1-8-020

Figure 4-20. Fish Eyes

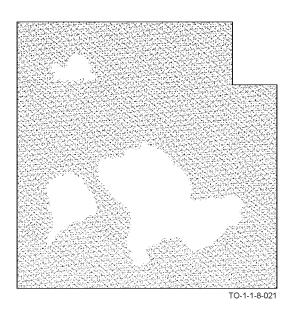


Figure 4-21. Lifting

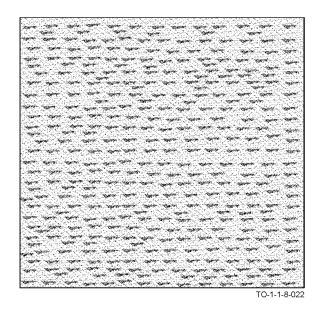


Figure 4-22. Pitting or Cupping

# 4.5 CLEANING AND MAINTENANCE.

Proper maintenance of spray guns is necessary to preserve the life of the gun and ensure high quality results. The gun requires little other maintenance if kept clean.

a. Basic maintenance consists of occasional lubrication. The packing surrounding the air valve stem shall receive a few drops of light oil to maintain easy movement of the air valve. The packing enclosed in the packing nut around the fluid needle shall be lubricated for easy movement of the fluid needle assembly. The spring for the fluid needle assembly shall be coated with petrolatum (Vaseline®). In addition to lubrication, parts that experience wear, such as air nozzles, fluid nozzles, and needle assemblies, should be periodically replaced.

# NOTE

Excessive tightening of the packing nut will damage the packing and the needle valve assembly.

b. After each paint job, the gun shall be thoroughly cleaned with thinners/solvents listed in <u>Paragraph 4.6</u>. If cleaning is delayed, the time needed to clean the gun is greater and there is a potential for damage to the equipment.

# WARNING

When using solvents, keep away from heat and open flame, keep container closed, use only with adequate ventilation, and use gloves to avoid skin contact. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

(1) To clean a siphon-feed gun, unscrew the air cap and release the paint cup from around the siphon tube at least a distance of 1 or 2 inches. Hold a cloth over the air cap and trigger the gun. Air will be sent into the passageways, forcing any excess paint back down the siphon tube and into the loosened paint cup.



PURGING THINNER, TT-T-2935



AIRCRAFT COATING THINNER, MIL-T-81772

17

17

1

(2) Remove the paint container and clean the inside using MIL-T-81772, Type I or II thinner or TT-T-2935 purging thinner or one of the lower vapor pressure solvents listed as preferred alternatives for these in Paragraph 4.6.



Abrasive materials and chemical strippers shall not be used to clean spray gun parts, as damage to the gun will result. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

- (3) Fill a quarter of the clean container/cup with the same type of thinner or solvent (fresh/unused) used to clean it.
- (4) Remove the air nozzle and carefully lower it into the container/cup of thinner or solvent.
- (5) Using a nonmetallic bristle brush, clean the fluid nozzle openings and other parts of the gun that are difficult to reach, such as around the packing nuts and controls.



Do not submerge the gun in thinner or solvent as they can dry out the packing around the fluid and air stems. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

- (6) Dampen a rag with thinner or solvent and wipe the entire gun and cup until they are free of paint.
- (7) Using the bristle brush, clean the air nozzle and its openings.



AIRCRAFT COATING THINNER, MIL-T-81772



When lower vapor pressure solvents are used to clean paint guns and their paint supply lines/hoses, the paint guns must be blown out with clean, compressed air and the lines/hoses must be flushed with MIL-T-81772, Type I thinner immediately after they are removed from the paint gun washer and prior to use to eliminate all traces of these solvents from the guns and lines/hoses. These solvents are not compatible with the paints and primers used on AF equipment, and failure to remove them will contaminate the next paint system applied with the paint gun and supply lines/hoses and cause fish eyes and other paint curing problems. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

- (8) Put the gun back together and spray clean MIL-T-81772, Type I thinner only through the gun until a fan of clear thinner is produced. Do not use the lower vapor pressure solvents listed in <u>Paragraph 4.6</u> for this final flushing procedure.
- (9) Remove any excessive thinner, and wipe the cup and gun with a clean dry rag.

### NOTE

A spray gun contains parts that must work together. Dismantling a spray gun after each paint operation will cause excessive damage to the gun and its seals. A spray gun should only be dismantled when a proper spray pattern cannot be produced.

#### 4.6 MECHANICAL PAINT GUN WASHER.



When lower vapor pressure solvents are used to clean paint guns and their paint supply lines/hoses, the paint guns must be blown out with clean, compressed air and the lines/hoses must be flushed with MIL-T-81772, Type I thinner immediately after they are removed from the paint gun washer and prior to use to eliminate all traces of these solvents from the guns and lines/hoses. These solvents are not compatible with the paints and primers used on AF equipment, and failure to remove them will contaminate the next paint system applied with the paint gun and supply lines/hoses and cause fish eyes and other paint curing problems. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

#### NOTE

It is highly recommended that an initial hazardous waste collection container be located as near as possible to the paint gun cleaner so that any contaminated sludge, solvents, and filters may be immediately placed in the container without having to transport the waste to the collection container.

The most effective method for cleaning paint spray guns, paint fluid hoses, and paint pots/cups is by using a mechanical paint gun washer. These washers use either MIL-T-81772, Type I or II thinner, TT-T-2935, Parachlorobenzotrifluoride (PCBTF) purging thinner, or other low vapor pressure solvents that contain some Volatile Organic Compounds (VOC) but no Hazardous Air Pollutants (HAP). The solvents are contained in a closed-loop system consisting of a cover, reservoir, sump, pneumatic pump, spray nozzles, pneumatic controls, and either a filtration or a distillation system. The container has devices installed inside of it for connecting paint guns for cleaning of internal as well as external surfaces. Since these washers are closed-loop systems, their use reduces hazardous waste, VOC emissions, solvents required to manually clean the paint equipment, and hazards to the personnel. Use of paint gun washers is required to comply with NESHAP rules when applicable.

a. Equipment fitted with a filtration system reutilizes the solvent until it is so soiled that it must then be replaced, and it also requires periodic change out of the filters. These units are recommended for paint shops with a medium to low production rate and a high personnel turnover rate such as many field level maintenance organizations. The filtration type paint gun cleaners are relatively simple to operate and require only a minimum amount of personnel training for safe and effective operation. There should be at least two people in each paint shop that are proficient in the operation of the shop's paint gun cleaner so that personnel turnover will not result in a situation where there are no trained operators present in the shop. Operation of this equipment shall be in accordance with the manufacturer's instructions.

#### NOTE

- For proper disposal of contaminated solvent, contact local civil engineering authorities for instructions.
- Solvent replacement shall be done in accordance with manufacturer's instructions.
- Contaminated filters are considered hazardous waste and shall be placed in a hazardous waste collection container immediately after removal from the paint gun cleaner.
- b. Equipment fitted with a distiller recycles the solvent and separates out the waste and does not require solvent disposal. These units are recommended for paint shops with a medium to high production rate and a relatively stable work force such as found in most depot level maintenance organizations. The distillation type paint gun cleaners are relatively difficult to operate and require a higher degree of personnel training than the filtration type units for their safe and effective operation. There should be at least two people in each paint shop that are proficient in the operation of the shop's paint gun cleaner so that personnel turnover will not result in a situation where there are no trained operators present in the shop. Operation of this equipment shall be in accordance with the manufacturer's instructions.

# CHAPTER 5 PAINTING OPERATIONS FOR AIRCRAFT AND EQUIPMENT

# 5.1 GENERAL.

This chapter describes coating application procedures for aircraft and equipment used by the Air Force (AF). Except when otherwise directed by this Technical Order (TO) or by local requirements or limitations, protective organic coatings may be applied by spraying, brushing, or any other approved method which results in continuous adherent films. The method selected or directed for application of coatings to aerodynamic surfaces shall be developed and adjusted to provide film integrity, optimum adherence, smoothness and good appearance. Achieving acceptable finishes on airframe surfaces requires trained personnel plus certain disciplines of operation. Pre-planning for painting is an absolute requirement to provide a logical schedule of operations, arrange for a cleared working area, and have available painting aids such as scaffolding and clean up materials and equipment, etc. Correctly preparing coating materials and maintaining painting equipment in good operating condition are as important as knowing the techniques of applying coatings.

#### 5.2 SAFETY AND HEALTH ASPECTS OF PAINTING.

**CAUTION** 

Measures shall be taken to prevent paint waste from contaminating air, water, or soil. Some of the chemicals used in painting require treatment or other special control prior to disposal. Disposal of materials shall be accomplished under the direction of the Base Civil Engineer (BCE), Safety Office, Bioenvironmental Engineer, and Environmental Management Office in a manner that will not result in violation of local, state, or federal pollution criteria. Detailed information for disposal is cited in Air Force Instruction (AFI) 32-7001, AFI 32-7040, AFMAN 32-1067, and AFMAN 32-7002. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

Painting operations are hazardous and require control or preventive measures. Vapors produced, particularly in spray painting, are usually highly flammable, as are the accumulated dried coating materials deposited on walls, floors, and equipment in the painting area. Also, coating materials and their thinners very often contain toxic substances which are injurious to health by inhalation and, to a lesser degree, by skin contact. Painting operations also involve hazards of physical injury due to improper use of work stands, ladders, hoists, etc. As directed by the local Safety and the Bioenvironmental Engineers, all painting personnel shall observe all safety precautions regarding toxicity, other health, and flammability hazards specified by existing instructions and regulations. AFMAN 48-146 and AFI 48-137; Air Force Policy Directive (AFPD) 91-2; AFMAN 91-203; and National Fire Protection Association (NFPA) 10, 13, 33, and 91 apply, and all safety precautions in these documents regarding personnel health, fire prevention, ventilation, handling of equipment, electrical grounding, storage of coating materials, area preparation, use of vapor-proof lights, etc., are mandatory. Refer to <u>Table 5-1</u> for the minimum recommended personal protective equipment. The following measures are minimum required practices for personal safety:

- a. Wear approved respiratory protective devices.
- b. Wear protective clothing to prevent contamination of ordinary clothing. When painting, use cloth coveralls with a head covering (sock hat) or hooded Tyvek<sup>TM</sup> coveralls, disposable rubber gloves, and non-slip foot coverings for walking on aircraft. Do not store protective clothing in the painting area. Store protective clothing in ventilated metal lockers in some other convenient location.
- c. After painting, wash hands thoroughly before eating. Do not carry food into spraying areas.
- d. Spray paint only in areas approved by Fire, Safety, and Bioenvironmental Engineering.

	Engineering	Personal Protective Equipment					
Operation	Controls	Respiratory	Hand	Ear	Eye	Body	Foot
Mixing	General dilution ventilation	None	Disposable Nitrile gloves	None <sup>b</sup>	Safety goggles or face shield	Tyvek <sup>™</sup> or cotton coveralls	Safety toe boots
Thinning	General dilution ventilation	None	Disposable Nitrile gloves	None <sup>b</sup>	Safety goggles or face shield	Tyvek <sup>™</sup> or cotton coveralls	Safety toe boots
Spray application	Paint spray booth/facility	Air-purifying with Organic Vapor (OV)/N95 cartridges <sup>c</sup>	Disposable Nitrile gloves	None <sup>b</sup>	Safety goggles <sup>d</sup>	Tyvek <sup>™</sup> or cotton coveralls	Safety toe boots
Curing	General dilution ventilation	None	None	None <sup>b</sup>	None	None	Safety toe boots
Sempen usage	General dilution ventilation	None	Disposable Nitrile gloves	None <sup>b</sup>	None	None	Safety toe boots
<sup>a</sup> Local Bioenvironmental Engineer (BEE) may recommend more restrictive controls or PPE based on exposure monitoring. <sup>b</sup> Hearing protection may be required in locations where hazardous noise is produced from other sources.							

# Table 5-1. Minimum Recommended Controls and Personal Protective Equipment (PPE) for Priming and Painting Operations<sup>a</sup>

<sup>c</sup> Powered air-purifying respirator (PAPR) with hood is the best choice for spray paint application.

<sup>d</sup> Safety goggles are not required if a full-facepiece or hooded respirator is worn.

# WARNING

Spray gun nozzles are sources of very high pressure. During operation and cleaning of paint spray guns, the nozzle shall never be pointed towards any person in close proximity. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

e. Spray painting equipment presents hazards of which painters should be aware. Consult manufacturers' instructions for proper handling, cleaning, operation, and precautionary procedures.

5.2.1 <u>Respiratory Protection</u>. Many toxic materials are found in spray painting shops which may impair the health of personnel if control measures are not provided. Harmful concentrations of these materials may be reduced to a safe level by an efficient mechanical exhaust system supplemented with personal respiratory protection. At a minimum, it is recommended that powered air purifying respirators with hood be used (see <u>Table C-1</u>); however, always contact Bioenvironmental Engineering for selection of proper respiratory protection. It should be understood that a respirator is not a substitute for a proper exhaust system, but is a supplement to existing ventilation methods (refer to NFPA 91, AFMAN 48-146, and AFI 48-137).

# NOTE

This manual provides only general information for respiratory safety devices. See the manufacturer's technical data for detailed operating and maintenance instructions. See the DO43 System for National Stock Numbers (NSNs) and to convert specification and Part Numbers (PN) s to NSNs. Equipment Authorization Inventory Data (EAID) authorization for equipment type items must be established in accordance with AFH 23-123.

# 5.3 SPRAY BOOTHS AND PAINTING AREAS, GENERAL.

Spray painting shall be conducted in a properly ventilated spray area such as in a spray booth which confines and exhausts vapors and mists and overspray during painting operations. Paint booths are available in various sizes for small parts painting, or for larger wheeled equipment, and can be large enough for complete aircraft. Air flow design shall provide adequate velocity at the face of the booth. Basic airflow criteria for a specific type paint booth is available from the Bioenvironmental Engineer. Also, see NFPA 91, "Industrial Ventilation, A Manual of Recommended Practices", published by the American Conference of Government Industrial Hygienists (ACGIH), and AFMAN 91-203. For additional reference criteria, see the Air Force Corrosion Facility Reference Guide on the AFCPCO's SharePoint. Doors and windows in the area should be kept closed to exclude dust and dirt. Air should enter a booth at a rate which will not cause turbulence or excessive air currents but be sufficient to keep dried overspray from settling on surfaces which have been painted and are still tacky. Humidity and temperature indicators shall be installed and kept in proper operation so that the temperature and humidity for correct spraying can be checked and maintained. Lighting shall amply illuminate all surfaces being painted, and all lighting and connecting electrical switching shall be explosion proof. Spray room surfaces shall be cleaned frequently to ensure good housekeeping.

# 5.4 PAINT BOOTH TYPES.



Prior to spraying of paint, rigidly comply with all safety regulations regarding to electrical grounding, fire prevention, vapor and explosion-proof lights, etc. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

Two types of paint spray booths are in general use, the dry type and the air-water wash type. Traditional spray booths are generally effective at removing particulate matter such as solid and liquid particles of overspray, but they do not remove solvent vapors from exhaust air. Removal of solvent vapors for air quality emissions compliance requires supplemental equipment to collect the organic vapors on activated charcoal filters or to destroy them by combustion or catalytic reaction. These special process capabilities are matters to be addressed by local civil engineering and environmental planning functions.

5.4.1 <u>Dry-Type Booth</u>. Dry-type spray booths draw contaminated air through a series of baffles or filters before exhausting it to the outside. Care should be taken to minimize air currents in the spray booth that will interfere with removal of spray dust or with the health and comfort of personnel. These booths are available with varying types of filter material, and local environmental regulations may specify the numbers of filter banks required. In most cases, the filter material will be considered a hazardous waste and disposal should be coordinated with local civil engineering and environmental management.

5.4.2 <u>Air-Water Wash Type Booth</u>. In addition to the baffles used in the dry-type booth, this type of spray booth has a series of water curtains to trap and remove overspray solids and liquids from contaminated air before it is exhausted. An airwater wash type booth will remove up to 95 percent of paint residue before it is exhausted when working properly. Many areas today have greater restrictions than 95 percent efficiency. Fire hazards are greatly reduced when the airwater wash booth is used. A deflocculating material or water wash compound is added to the water to prevent residue from adhering to the working portion of the booth and also serves to prevent rusting. A paint sludge removal system may be installed in these booths to decrease the frequency of changing the water. Disposal of paint sludge may be considered a hazardous waste and should be coordinated with local civil engineering and environmental management.

5.4.3 <u>Cleaning and Maintenance</u>. A suitable coating should be applied to all dry interior surfaces of a booth to facilitate cleaning. Paint residue which floats on the surface of the water should be removed each day to prevent it from settling to the bottom of the tank. Spray booths should be coated with an approved fireproof material. The applicable equipment manual should be consulted for complete information on paint spray booths. It is very important to keep the spray booth and its immediate vicinity as free from dirt and dust as possible. The strong suction created by the exhaust fan can pull dust from outside into the booth and may deposit it on sprayed surfaces.

5.4.4 <u>Part and Equipment Painting Operations</u>. All parts and equipment painted in spray booths shall be properly positioned in the booth. This is necessary to ensure the painter is not improperly exposed during the painting operation. The parts shall be placed on roll around tables or hung from roll around racks to allow for their repositioning in the paint booth during the painting operation. The painter shall spray into the face of the booth with the air flow from the painters back. When painting complex parts, change the position of the part being painted so that the painter is never spraying into the air flow. Painted parts shall be removed from the spray booth as soon as possible after the spraying has been completed and the vapors have been removed. When painting large equipment, the painter shall begin at the front or exhaust end of the booth and work toward the back or air supply end. This is to ensure the painter remains out of the flow of the paint overspray.

#### 5.5 AIRCRAFT PAINTING OPERATIONS.

5.5.1 <u>Depot Level Aircraft Painting Operations</u>. Depot painting of aircraft shall conform to the following safety and health protection precautions:

# NOTE

Painting of entire aircraft will necessarily be accomplished in a variety of locations including interior areas not primarily designed for painting operations and out-of-doors. Insofar as applicable, all safety precautions and directions on environmental and materials controls pertain in these areas also. Painting in maintenance hangars shall be restricted to the minimum necessary to maintain the integrity of the coating system and shall always be under cognizance of local safety, fire and medical service representatives. Painting in maintenance hangar will be done in accordance with AFMAN 91-203.

- a. Base Fire, Safety, Bioenvironmental, and Environmental Management Offices shall approve locations for spray painting aircraft. Painting of fueled aircraft must be approved by Air Force Materiel Command (AFMC) and the responsible Air Logistics Center (ALC) Fire Protection Engineering Offices, and is authorized only if the following precautions are taken. Aircraft containing Jet Propellant 8 (JP-8) fuel may be electrostatically painted during depot level operations providing the on-board fuel temperature is below the flash point of 100 °F (38 °C) before and during electrostatic painting operations. The aircraft being electrostatically painted must be grounded in two locations to prevent accidental electrical discharge from the electrostatic spray equipment. Each base is responsible for establishing procedures to ensure that the temperature of on-board fuel is below 100 °F (38 °C) before and during applications.
- b. The ventilation system must provide sufficient exhaust to remove the solvent vapors generated by the process. The exhaust stream shall be maintained below 20 percent of the Lower Explosive Limit (LEL) with no more than 500 Parts Per Million (PPM) total solvent vapor concentration as defined in Occupational Safety and Health Act (OSHA) Standard 1910.94. The paint hangar facility shall be equipped with an audible alarm system which activates if the ventilation system fails. Personnel shall wear proper respiratory protection in addition to the ventilation as specified by Bioenvironmental Engineering.
- c. The painting equipment must be used only in the paint hangar and shall be of the High Volume Low Pressure (HVLP), airless, or air-assisted-airless type and may employ electrostatic capabilities in accordance with Environmental Protection Agency (EPA) requirements.
- d. Painters shall be trained in the hazards associated with painting fueled and unfueled aircraft, and the fire and safety problems associated with the process.
- e. All safety and regulating features on associated spray painting equipment and safety equipment shall be operational.
- f. No unauthorized personnel are allowed in the paint hangar during fueled aircraft painting operations.
- g. Any personnel involved in operations in the paint hangar, even those not associated with the painting process, shall be briefed on the hazards of static on ungrounded objects and provided with the appropriate safeguards.
- h. All aircraft, equipment, work stands, solvents containers/buckets, people, and adjacent equipment shall be grounded prior to using the painting equipment.
- i. Prior to cleaning electrostatic paint guns, the operators shall ensure that they and the gun are grounded and that the equipment is deenergized. All spray nozzles and auxiliary equipment being cleaned with flammable solvents shall be done inside the paint hangar facility with the ventilation system operating.
- j. The manufacturers operational/safety procedural criteria is used as a supplement to these procedures.
- k. All electrical equipment within the paint hangar facility must be approved for explosion proof environments. The painting equipment used for this process must have been tested and approved by a recognized laboratory for NFPA 70 Class I, Division I, Groups C and D locations.
- 1. When painting fueled aircraft, the paint hangar facility and aircraft shall be protected with by a fire suppression system. The fire suppression system must be fully operational prior to the start of electrostatic painting. Facility fire suppression required for electrostatic painting is outlined in MIL-STD-3007, Electrical Test Laboratory (ETL) 02-15, and ETL 98-8.
- m. Supervisory personnel must ensure all fire/safety precautions have been implemented prior to the start of the painting operation.

n. LEL readings in the fuel vent areas must be taken prior to the painting of each aircraft. LEL readings must be maintained at or below 20 percent.

5.5.2 <u>Field Level Aircraft Painting Operations</u>. Field level painting of aircraft shall conform to the following safety and health protection precautions:



Electrostatic spray painting of Jet Propellant (JP-8) fueled aircraft constitutes a significant hazard when the onboard fuel temperature exceeds 100 °F (38 °C). Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

- a. Painting of aircraft at field level shall be limited to only maintenance painting operations. Maintenance painting is permitted in designated paint areas identified and approved per requirements in AFMAN 91-203 and approved by the Base Fire, Safety, Bioenvironmental, and Environmental Management Offices. Aircraft containing JP-5, JP-8, or equivalent fuel may be electrostatically painted at field level organizations, providing the on-board fuel temperature is below the flash point of 100 °F (38 °C) before electrostatic painting operations begin.
- b. The requirements for aircraft painting in AFMAN 91-203 shall be strictly followed.
- c. Personnel involved in painting operations of both unfueled and fueled aircraft shall be trained in the fire/safety and environmental hazards associated with the processes.
- d. All safety and regulating features on associated spray painting equipment and safety equipment shall be operational.
- e. Unauthorized personnel will not be allowed in designated paint areas during painting operations.
- f. Prior to starting a paint operation, ground all aircraft, metal solvent containers, flammable waste containers, airless and air-assisted airless paint spray equipment, and adjacent equipment as deemed necessary by the Base Safety Office.
- g. Supervisory personnel must make sure all fire/safety precautions have been implemented prior to the start of the painting operations.
- h. Painting equipment shall be the HVLP or electrostatic type in accordance with EPA NESHAP requirements.

5.5.3 <u>Electrostatic Aircraft Painting</u>. Electrostatic painting of aircraft shall conform to the following safety and health protection precautions:



Electrostatic spray painting of JP-8 fueled aircraft constitutes a significant hazard when the on-board fuel temperature exceeds 100 °F (38 °C). Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

- a. Aircraft to be electrostatically painted shall be defueled and purged. Exceptions: Aircraft fueled only with JP-5 and/or JP-8 are authorized to be painted with electrostatic airless spray equipment approved in SA 480 without being defueled and purged, providing fuel temperature remains below 100 °F (38 °C). Electrostatic spray painting of JP-5 or JP-8 fueled aircraft can only be performed in designated paint hangars that are approved for this function by the local base Fire, Safety, Bioenvironmental, and Environmental Management Offices. The aircraft being electrostatically painted must be grounded in two locations to prevent accidental electrical discharge from the electrostatic spray equipment. Each base is responsible for establishing procedures to ensure that the temperature of on-board fuel is below 100 °F (38 °C) before and during electrostatic painting applications.
- b. Electrostatic coating application equipment shall be used only in paint hangars or other areas designated and approved by the local base Fire, Safety, Bioenvironmental, and Environmental Office.

# TO 1-1-8

- c. The ventilation system is on and operating and must also provide sufficient exhaust to remove the solvent vapors generated by the process. The ventilation shall be sufficient to limit vapor concentration to 500 PPM or 20 percent of the LEL, whichever is lower as defined in OSHA Standard 1910.94. Electrostatic painting equipment powered by an external electrical source requires an interlock system to ensure that equipment can only be operated if the ventilation system is operational. An interlock system is not required for pneumatically operated equipment; however, the paint hangar facility shall be equipped with an audible alarm system which activates in the event of a ventilation system failure.
- d. All painters using the electrostatic equipment shall be trained in its use, the hazards associated with electrostatic painting, and the fire/safety problems associated with the process.
- e. All safety and regulating features on all equipment are operational.
- f. No unauthorized personnel are allowed in the paint hanger during electrostatic painting operations.
- g. Any personnel involved in concurrent operation in the paint hangar, not associated with the electrostatic painting process, shall be briefed on the hazards of static on ungrounded objects and provided the appropriate safeguards.
- h. All aircraft, the electrostatic equipment, work stands, solvent containers/buckets, people, and adjacent equipment shall be grounded prior to using the electrostatic painting equipment.
- i. Prior to cleaning electrostatic paint guns, the operators shall ensure that they and the gun are grounded and that the equipment is de-energized.
- j. The manufacturer's operational/safety procedures are used to supplement these procedures.
- k. All electrical equipment within the paint hangar facility must be approved for explosion-proof environments. The electrostatic painting equipment used for this process must have been tested and approved by a recognized laboratory for Class I, Division I, Groups C and D locations.
- 1. When painting aircraft fueled with JP-5 and JP-8, the paint hangar facility and aircraft shall be protected by a fire suppression system. The fire suppression system must be fully operational prior to the start of electrostatic painting. Facility fire suppression required for electrostatic painting of fueled aircraft is outlined in MIL-STD-3007, ETL 02-15, and ETL 98-8.
- m. Supervisory personnel must ensure all fire/safety countermeasures have been implemented prior to the start of the painting operation.
- n. LEL readings in the fuel vent area must be taken prior to the painting of each aircraft. LEL readings must be maintained at or below 20 percent.

5.5.4 <u>Atmospheric Conditions for Painting</u>. Normally, coatings should not be applied under unfavorable atmospheric conditions such as high humidity, strong drafts or extremes of temperature. Painting should be accomplished whenever possible in an environmentally controlled facility capable of maintaining a range of 30 to 80 percent Relative Humidity (RH) and 60 to 90 °F (16 to 32 °C). Some coatings may be applied outside these ranges without significant adverse effects, but paint personnel should always watch for adverse effects when applying paint outside of these ranges and develop painting decisions based upon local experiences for the particular types of coatings used and the local climate. Factors to be considered are:

- The temperature of surfaces being painted should be considered in any painting decision since it is a major factor in the drying or cure of coatings.
- Low humidity retards the cure of moisture curing coatings.
- High humidity can cause blushing of lacquers and also may result in condensation on the coating if the temperature of the coating drops to the dew point.
- Low temperatures cause slow drying, or cure, longer tack time, and sometimes incomplete cure. If the temperature is 50 °F (10 °C) or lower, painting operations should be suspended.

- High temperatures cause too rapid an evaporation of solvent which leads to premature skinning, pinholes or solvent pop, blisters, cracked finish, or excessive dry spray. If the temperature exceeds 95 °F (35 °C), painting operations should be suspended.
- The aircraft skin temperature must be at least 60 °F (16 °C) prior to any application of coatings. During extremely cold weather, this may require placing the aircraft in a heated paint facility several days in advance to ensure proper skin temperature.

5.5.5 <u>Test Panels</u>. To test suitability of materials, conditions, etc., spray test panels prior to beginning operations. The suitability shall be determined experimentally on a panel approximately 10 x 32 inches in size coated under prevailing conditions with the finish system that is to be applied. If the finish system applied to the experimental panel is satisfactory, then full scale operations may begin. Defects found in the experimental application such as blushing, poor adhesion, excessive orange peel, sagging, etc., shall be corrected prior to large scale application. Application of catalyzed (two-component) coatings having a long drying time usually cannot await inspection of completely cured and dry films, so use the best information available from the test panels at the beginning of the application. Test panels are not required for component/part or maintenance painting (touch-up).

5.5.6 <u>Material Requirements, General</u>. Materials used on AF aircraft and equipment should normally conform to Military or Federal Specifications and shall be applied as directed in this technical manual and other pertinent technical publications.

### NOTE

Unauthorized material shall not be used by AF activities on aircraft and associated equipment.

**5.5.6.1** Proprietary non-specification materials may exist on aircraft and equipment as supplied by the manufacturer, and the maintenance of these may offer special difficulties. Normally, the repair and maintenance of proprietary coatings should be with the same material. However, if a material cited in this TO is determined by the ALC corrosion manager or the weapon/item manager engineering function to be compatible with the proprietary coating, use the cited material for touch-up. In case of complete unit stripping and recoating, only AF authorized specification materials shall be used.

#### NOTE

Avoid the possibility of incompatibility of materials under the same specification but of different manufacture by not mixing them. Primers of different manufacture but under the same specification shall not to be mixed in the same area, but may be applied separately to areas which are to be over coated. Every effort shall be made; however, to assure that an entire topcoat is restricted to the product of a single manufacturer and, where possible, to the same batch in order to maintain uniformity of color, gloss, etc.

#### 5.6 THE AIRCRAFT PAINTING PROCESS SEQUENCE OF EVENTS.

- a. Clean and mask the aircraft in accordance with Chapter 3 of this TO.
- b. Apply conversion coating to bare aluminum surfaces in accordance with Chapter 3 of this TO.
- c. Allow at least 2 hours for the conversion coating to dry and set up. Then, move the aircraft (if required) to the paint hangar with no delay in the outside environment.
- d. After the aircraft is situated in the paint facility, begin application of the primer after 2 hours minimum to 48 hours maximum has elapsed since applying the conversion coating to the aircraft.

#### NOTE

If the aircraft was not prepared in the paint hangar and was moved to the paint hangar the aircraft must be allowed to dry (if necessary) and the aircraft skin to warm to room temperature and solvent wipe the entire aircraft surface in accordance with Paragraph 3.1.4 of the TO.

e. Allow the primer to cure for the time specified in <u>Chapter 6</u> but no more than 8 hours. Apply two coats of the required topcoat in the appropriate paint scheme in accordance with <u>Chapter 8</u> of this TO, aircraft drawings, or -23 manual or equivalent manual. If more than 8 hours elapse (not to exceed 24 hours) between priming and top coating, the

primer must be solvent wiped for reactivation in accordance with <u>Paragraph 3.1.6</u> or scuff sanded with 320 or 400 grit sandpaper or CID A-A-58054, Type I, Grade A, abrasive mat in accordance with <u>Paragraph 3.1.3</u> to reactivate the primer for adhesion of the topcoat. If the primer is scuff sanded, solvent wipe in accordance with <u>Paragraph 3.1.4</u> must be re-accomplished prior to topcoat application. If 24 hours elapse between priming and top coating, solvent wipe only for reactivation is not permitted and scuff sanding is mandatory.

#### 5.6.1 <u>Aircraft Paint Application Sequence</u>.



- Aircraft shall be primed and painted so painter's exposure to the spray mist or cloud is minimized. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- Always spray with painter's back or side upwind, and never direct spray upwind. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- Two or more painters spraying at the same time shall never spray directly at each other and shall be positioned as far apart as possible or on opposite sides of the aircraft. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- When priming, start at the end of the aircraft near the exhaust filter bank and move toward the air supply. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

Application of coatings on aircraft by spraying methods is best accomplished by at least two painters supported by helpers to handle lines, stands, etc., as required. Four painters may be required on larger aircraft. Recommended painting sequences are as follows:

#### 5.6.1.1 Small Aircraft-Tail Toward Hanger/Insert Exhaust.

#### 5.6.1.1.1 Priming.

- a. For "T" tail aircraft, apply a full wet coat of primer to the horizontal stabilizer upper surface starting at the center moving outboard to the tip with a stroke perpendicular to the leading edge. Using this same technique, prime the horizontal stabilizer lower surface and then apply a full wet coat of primer to the outboard edge of the tip and the front of the leading edge working from the tip to the junction with the vertical stabilizer. Apply a full wet coat of primer to each side of the vertical stabilizer(s) starting at the top and leading edge moving down and aft with a vertical stroke. Finally, apply a full wet coat of primer to the front of the vertical stabilizer(s) leading edge starting at the top moving down. For bottom mounted horizontal stabilizer aircraft prime using the same techniques as for a "T" tail aircraft except prime the vertical stabilizer first. Prime vertical stabilizer mounted engine nacelles using the same techniques at this time.
- b. Apply a full wet coat of primer to the aft section of the fuselage starting at the aft end and the top moving forward and down to the junction with the wing trailing edge with a vertical stroke. Prime any aft fuselage mounted engine nacelles using the same techniques at this time.
- c. Apply a full wet coat of primer to the lower surface of the wings starting at the tip moving inboard to the wing root with a stroke perpendicular to the leading edge. Prime all wing mounted pylons, tanks, and nacelles, all main landing gear pods and doors, lower fuselage between the wings on low wing aircraft, the side of the fuselage beneath the wings, and the lower fuselage on high wing aircraft using the same techniques at this time.
- d. Apply a full wet coat of primer to the upper surface of the wings starting at the tip moving inboard toward the fuselage with a stroke perpendicular to the leading edge. Apply a full wet coat of primer to the wing tip outboard edge and the front of the leading edge starting at the tip and moving inboard. For low wing aircraft, prime the fuselage side above the wing and the top of the fuselage using the same techniques at this time.
- e. Apply a full wet coat of primer to the forward section of the fuselage starting at the wing leading edge and the top moving down and forward to the nose with a vertical stroke.

# 5.6.1.1.2 Topcoating.

- a. Topcoats are applied in either a one coat or a two coat system. For a one coat system, apply a mist coat of the topcoat with a stroke in one direction followed immediately be a full wet cross coat with a stroke perpendicular to the stroke of the mist coat working small areas at a time. For a two coat system, apply the first coat with a stroke in one direction and the second coat with a stroke perpendicular to the first coat, but after the first coat "time to overcoat" specified for the coating system has elapsed.
- b. Apply topcoat to the fuselage forward section starting at the nose and leading edge with the initial stroke perpendicular to the fuselage length. Apply the criteria in Step a above.
- c. Apply topcoat to the upper surface of the wings starting at the tip and moving inboard toward the fuselage with the initial stroke perpendicular to the leading edge. Apply the criteria in Step a above. For lower wing aircraft coat the fuselage section above the wings using the same technique at this time.
- d. Apply topcoat to the lower surface of the wings starting at the tip moving inboard toward the fuselage with the initial stroke perpendicular to the leading edge. Apply the criteria in Step a above. Apply topcoat to all wing mounted pylons, tanks, and nacelles, all main landing gear pods and doors, lower fuselage between the wings on low wing aircraft, and the side of the fuselage on high wing aircraft using the same techniques at this time. Finally, apply topcoat to the outboard edge of the tip and front of the leading edge starting at the tip and moving inboard toward the fuselage.
- e. Apply topcoat to the fuselage aft section starting at the wing trailing edge and the top moving aft and down to the aft end with the initial stroke perpendicular to the aircraft length. Apply the criteria in Step a above. Topcoat any aft fuselage mounted engine nacelles using the same techniques at this time.
- f. Apply topcoat to the horizontal stabilizer upper surface on "T" tail aircraft starting at the center and moving toward the tip with the initial stroke perpendicular to the leading edge, and then topcoat the horizontal stabilizer lower surface starting at the tip moving inboard to the junction with the vertical stabilizer. Topcoat each side of the vertical stabilizer(s) on "T" tail aircraft next starting at the top and the leading edge moving down and aft to the junction with the fuse-lage with the initial stroke in a vertical direction. Topcoat the front of the leading edge of the vertical stabilizer(s) starting at the top moving downward. Topcoat any vertical stabilizer mounted engine nacelles using the same techniques at this time. Apply the criteria in Step a above. Bottom mounted horizontal stabilizer aircraft are topcoated using the same techniques except the vertical stabilizer(s) are topcoated first.

#### 5.6.1.2 Large Aircraft-Nose Toward Hanger Exhaust.

5.6.1.2.1 <u>Priming</u>. Apply primer using the same techniques as for small aircraft with tail toward the exhaust except reverse the order of areas being primed, i.e., prime from the nose working toward the tail.

5.6.1.2.2 <u>Topcoating</u>. Apply topcoat using the same techniques as for small aircraft with tail toward the exhaust except reverse the order of areas being topcoated, i.e., topcoat from the tail working toward the nose.

5.6.1.3 <u>Walkway Coatings</u>. Specialty walkway coatings applied to the upper wing main gear pods, upper fuselage, and horizontal stabilizer: surfaces should be applied before topcoating the aircraft. Any masking for walkway areas should then be removed and the aircraft should then be topcoated while the walkway coating is curing. If any anti-slip grit is added to the topcoat material for application to walkway areas, the above does not apply; and the walkway areas should be coated with topcoat material to which anti-slip grit is added as the second topcoat for these areas.

5.6.2 <u>Overspraying Existing Coating Systems on Aircraft and Aerospace Equipment</u>. It is always better to start a paint system from bare metal; however, it is feasible to overspray existing paint systems. For aircraft, this must be authorized by <u>Chapter 8</u> of this TO and the weapon system specific TO.

#### NOTE

Adhesion failure between coatings requires complete removal of the nonadhering coating. When intercoat adhesion failure occurs over large areas, overcoating shall not be accomplished and complete strip/repaint is required. Refer to <u>Chapter 2</u> of this TO for removal.

a. Clean, mask, scuff sand, and vacuum surface to be overcoated in accordance with Paragraph 3.1.3.

- b. Apply conversion coating to repair bare aluminum surfaces in accordance with Chapter 3 of this TO.
- c. Allow at least 2 hours for the conversion coating to dry and set up. Aircraft requiring movement to a paint hangar must be moved with minimal delay in the outside environment.
- d. After the aircraft or equipment is situated in the paint facility, or after 2 hours minimum has elapsed since applying the conversion coating to the aircraft, solvent wipe the entire aircraft surface in accordance with Paragraph 3.1.4.

### NOTE

13

15

If the aircraft was not prepared in the paint hangar and was moved to the paint hangar after scuff sanding, the aircraft must be allowed to dry (if necessary) and the aircraft skin to warm to room temperature before final solvent wipe and before conversion coating application if not already done.



EPOXY PRIMER, MIL-PRF-23377



# POLYURETHANE COATING, MIL-PRF-85285

- e. Begin overcoating within 48 hours after scuff sanding and conversion coating operations and immediately after solvent wipe down and tack rag if available in accordance with Paragraph 3.1.27. Apply one thin/mist coat of MIL-PRF-23377 Type I, Class C1, C2 or N (one full wet coat per Table 5-2 to large bare metal areas) to the entire aircraft or equipment exterior painted surface per instructions in Paragraph 5.6. Allow primer to dry in accordance with Chapter 6 of this TO, but no more than 8 hours. Apply two coats of the required topcoat MIL-PRF-85285 and appropriate paint scheme in accordance with Chapter 8 of this TO, aircraft drawings, -23 manual, or equipment manual. If more than 8 hours elapse (not to exceed 24 hours) between priming and topcoat, the primer must be solvent wiped for reactivation or scuff sanded with 320- or 400 grit sandpaper in accordance with Chapter 3 of this TO to reactivate the primer for adhesion of the topcoat. If the primer is scuff sanded, solvent wipe in accordance with Chapter 3 of this TO must be reaccomplished prior to topcoat application. To achieve a dust and lint free surface prior to topcoat application, it is recommended to tack rag. If 24 hours elapses between priming and topcoating, solvent wipe for reactivation is not permitted and scuff sanding is mandatory.
- f. A non-chromated tiecoat/Primer (Class N) may be used for overcoating of existing coating systems after scuff sanding. This is an alternative to MIL-PRF-23377 Type I, Class C1, C2 or N. All bare metal areas must have primer applied using MIL-PRF-23377, Type I, Class C1, C2 or N before application of the tiecoat. Allow 2 hours for the primer to dry, but not more than 8 hours, prior to application of the tiecoat. Apply the tiecoat and topcoat in accordance with <u>Chapter 5</u> of this TO for MIL-PRF- 23377, Type I, Class C1, C2 or N and MIL-PRF-85285.

#### NOTE

These primers do not provide adequate corrosion protection and shall not be applied over bare metal areas.

5.6.3 <u>Curing of Finishes</u>. After painting, allow aircraft finish system to cure in a dust-free temperature controlled atmosphere for a sufficient time prior to placing in service. In the absence of a temperature controlled facility, the aircraft shall not be flown for at least 72 hours after painting. In general, all painted aircraft should be handled, taxied, etc., as little as possible during the first week after painting.

**5.6.4** Coating Thickness Measurements. Wet and dry film gauges are available as local purchase items from various laboratory supply houses. If paint film thickness measuring instruments are not available, small (2 x 6 inches) anodized aluminum panels will be used for measurement of the paint thickness after drying. Apply these panels to each side of the fuselage with a section of 1 inch wide masking tape doubled back on itself with adhesive contacting the panel and the aircraft surface prior to the painting operation. Mask one end of the panel with tape for a distance of approximately 2 inches to provide a comparison of the original panel thickness and the thickness after painting. Remove the panel after application of the primer so that immediate maintenance painting can be used to cover those areas previously protected by the panel. This procedure

will also permit locating other panels on various portions of the same aircraft to provide a good indication of the overall paint thickness. The location of panels depends upon inspection procedures and may vary throughout the aircraft. Each aircraft should use a set of panels for each different operation employed on the aircraft identified by the name of the painter, aircraft model, and the date of painting, to provide follow-on data during any subsequent service evaluation. Slight errors in paint thickness measurements can be expected when using this method due to thickness tolerances for the basic aluminum sheet. Measure the paint thickness with an ordinary micrometer possessing flat contact surfaces. Micrometers with pointed or rounded contact surfaces are not recommended. At least six readings shall be taken on both painted and unpainted portions of each panel to provide an average paint thickness measurement. When using a wet film gauge or an electronic dry film gauge, a minimum of six readings shall also be taken. Take readings in a 1 square foot area that is representative of the entire area bring painted. Rejection is only if the average of the six readings falls outside of the thickness range for that particular paint system.

5.6.5 <u>Allowable Coating Thickness</u>. Because of the greatly reduced corrosion protection for a dried film thickness of less than 0.6 mils (0.0006 inch), solitary primer films below this thickness shall be avoided. Attaining proper coating thickness by spraying is a matter of technique plus checking. There is a limit to the thickness that can be applied in one pass because of protracted drying time or possible sagging of the film. This must be considered in obtaining the total desired thickness. Also, there is a tendency with coating materials of good hiding power to increase the spreading rate as the work progresses and this must be curbed. Operator fatigue may alter the speed of working, but this should not be allowed to result in applying more or less material to the surface. Changing atmospheric conditions during operations may have to be compensated for in order to continue applying a uniform film. Frequent checks with a wet film thickness gauge shall be made during painting to ascertain and control film thickness. Thickness cannot be gauged accurately without instruments, but lacking these, the best assurance of consistent films is in correct adjustment of the gun for the material being applied and the use of good judgement. See Table 5-2 for dry film thickness ranges of various primers and topcoats.

		Dry Film Thickn	ess Range (inch) <sup>1</sup>
Coating Specification	Number of Coats	Minimum <sup>2</sup>	Maximum <sup>2</sup>
MIL-PRF-23377 and MIL-PRF-85582 Epoxy Primers	One coat	0.0006	0.0009
	To Be Reactivated <sup><math>\frac{3}{2}</math></sup>	0.0004	0.0013
	Mist, "Light Dust Coat" Activation	0.0002	0.0005
	After Reactivation, Total	0.0006	0.0009
	Two coats	0.0008	0.0020
TT-P-2760 Elastomeric Polyurethane Primer	One coat	0.0015	0.0020
	Two coats	0.0017	0.0030
MIL-PRF-85285 Polyurethane Coating	One coat (without cross coat)	0.0017	0.0023
	One or two coats (with cross coat)	0.0016	0.0050
	Three to four coats <sup><math>\frac{4}{2}</math></sup>	0.0048	0.0070
MIL-PRF-22750 Topcoat	One coat	0.0008	0.0020
	Two coats	0.0016	0.0040
SAE AMS-C-27725 Fuel Tank Coating	Two coats	0.0008	0.0012

### Table 5-2. Allowable Coating Thickness for Production Level Finishing (Depot, Original Manufacture, Field)

<sup>1</sup> In most cases the desired coating thickness should be the low to nominal for the range specified unless there is a requirement for thicker coatings. The higher end of the range is not intended to be the mean or average of thickness measurements (unless it is required) but to allow for overlaps, etc., that occur in localized areas or sections of a part or surface. Measurements should not be taken around edges or holes and considerations must be allowed where overlap occurs such as in angles and on irregular surfaces.

- <sup>2</sup> Lower end of thickness range is expected when painting detail parts and small assemblies. Mid to high end of thickness range is often needed when finishing large areas such as the exterior of aircraft.
- <sup>3</sup> A single coat which is to be reactivated with a "light dust coat" before topcoat application after scuff sanding.
- <sup>4</sup> This coating thickness is intended for use only in specific areas where wear or abrasion are a factor, such as leading edges. These unique requirements should be specified in finish documents.

5.6.6 <u>Inspection Control</u>. Inspection shall enforce the requirements of this technical manual.

# TO 1-1-8

- a. Proper and adequate equipment shall be used at all times.
- b. Materials shall be thoroughly mixed with thinners and catalysts properly proportioned.
- c. Ensure that thorough cleaning and proper preparations are taken prior to application of each coat, proper drying times are observed before recoating, and coatings are applied at the proper thickness.
- d. Ensure the general appearance, texture, color, and gloss are acceptable. No sand paper finish to exceed approximately 320 grit coarseness, wrinkling, crazing, blistering, fisheye, lifting, or pitting/cupping as defined in this TO is permissible but not exceed limits of Paragraph 5.6.6.2.6.

5.6.6.1 Certain physical tests shall be made before, during, or after coating operations:

- Water Break Test (refer to <u>Paragraph 3.1.9</u>).
- Spray Test Panel (refer to <u>Paragraph 5.5.4</u>).
- Coating Thickness Measurement (refer to Paragraph 5.6.2).

**5.6.6.1.1** Adhesion (Wet) Tape Test. This method covers a procedure suitable for establishing acceptability of intercoat and total surface adhesion of an organic coating system.

- a. Adhesion tests shall be made on the completed exterior finish system after drying for a period of at least 48 hours in a sufficient number of selected areas to ensure a satisfactory level of adhesion for the overall finish system.
- b. To perform this test, wet a piece of cloth/gauze pad with either tap or distilled water and cover with plastic sheet taped on the area under inspection. The test area shall be soaked for 24 hours minimum and shall have a minimum diameter of 3 inches.
- c. Remove the wet cloth and plastic sheet and blot up the surface water. Immediately apply a 1 inch strip of tape, PN 250, manufactured by 3M Company, NSN 7510-00-283-0612, age of tape not to exceed 3 years, adhesive side down. Press the tape down, using two passes of a 4-1/2 pounds rubber covered roller or employ firm pressure with the hand.

#### NOTE

This tape is the only approved tape (no alternatives or substitutes).

- d. Remove the tape in one abrupt motion and examine the test area for any paint damage such as removal of one of the layers of the finish system or removal of the entire system from metal. Any removal constitutes failure of the wet tape test.
- e. Gloss shall be measured in accordance with the general procedures described in SAE ASTM D523, except that the measurements will be made on flat or approximately flat surfaces of the aircraft instead of a test panel. The test shall be made on the complete exterior finish after drying for a period of at least 24 hours in a sufficient number of areas to assure that the required gloss has been obtained. See <u>Table 5-3</u>.

Fable 5-3.	Gloss	Requirements
------------	-------	--------------

Gloss Meter Degrees	Paint System Reading	Unit
60	Semi-gloss	35 to 45
60	High-gloss	90 Minimum
60	Gloss	80 Minimum
60	Camouflage	7 Maximum
60 and 85 <sup>+</sup> (both)	Gunship <del>*</del>	3 Maximum

\* Both Meters Required

5.6.6.2 Evaluation and classification of discrepancies for complete aircraft painting.

5.6.6.2.1 The paint system, pattern, and markings shall be in accordance with weapon system specific TOs, aircraft drawings, or other applicable directives, and <u>Chapter 8</u> of this TO.

**5.6.6.2.2** Colors of camouflage pattern shall fade and blend into each other with irregular lines of demarcation, with no straight or sharp lines.

**5.6.6.2.3** No color variation in any single color area of the camouflage pattern or paint scheme when the surface is viewed with the unaided eye from a distance of 50 feet is allowed. Touch-up of the paint system to correct minor discrepancies by the paint activity will produce some minor color variation and is acceptable.

5.6.6.2.4 No more than two minor sags or runs per 50 square feet of surface is allowed (a minor sag run is one which does not exceed 2 inches in length).

#### NOTE

Slight orange peel appearance is inherent with the PR-1432 GV polysulfide primer/MIL-PRF-85285 polyurethane paint system and is acceptable.

5.6.6.2.5 The paint system shall pass the paint adhesion wet tape test. Candidate test areas shall include the following (where applicable): Upper center wing, left and right upper inboard and outboard wing, left and right lower wing surface (inboard and outboard), left and right horizontal stabilizer surface (upper and lower), left or right side of vertical stabilizer, cargo door, main landing gear pod, engine pylon, engine nacelle, left and right side of fuselage forward and aft, lower fuselage or belly (multiple sites shall be selected for this area). Failure of this test includes peeling of topcoat to primer as well as primer to bare metal.

**5.6.6.2.6** Fifteen or more individual discrepancies, any combination of discrepancies with a total area of 15 or more square feet, or any one discrepancy with an area of 5 or more square feet wrinkling, crazing, blistering, lifting, or pitting/cupping as defined in this TO, or peeling of topcoat to primer or primer to bare metal shall be reported as a major defect. List all these discrepancies by number found and type, area of each, and total area of all discrepancies.

#### NOTE

Failure of 25 percent of the wet tape adhesion tests prescribed here shall be reported as major defect. List all failures of this test by location on the aircraft.

5.6.6.3 <u>Frequency of Inspection</u>. The quality control plan and frequency of inspection shall be decided by local quality control authority. For large surface painting (e.g., the partial or complete repaint of an aircraft), a predetermined number of tests may be applied to sampled areas of each item. For subassembly and component painting, inspection of paint shop workmanship may be covered by in-process inspection or inspections of representative samples items according to a sampling plan either on a time basis or production count basis. Testing shall be kept to the minimum necessary to determine acceptability of the finished work. System and Item Managers have the option to specify a frequency of test in TOs or work specifications on their equipment.

5.6.7 <u>Soil Barrier Coating</u>. If approved by weapon system TO, this coating may be applied to all newly painted aircraft in the jet engine exhaust, Auxiliary Power Unit (APU) exhaust, and gun/rocket blast exhaust areas to protect the newly painted surfaces. If left unprotected, the above areas will be very difficult to clean after exposure to the aforementioned exhausts. This material and application procedures are called out in TO 1-1-691. If used, the soil barrier coating shall be applied after the topcoat cures at least 24 hours and prior to engine run-up.

#### 5.7 INTERIOR FINISHING PROCEDURES AND OPERATIONS.

5.7.1 <u>Preparation for Coating</u>. Cleaning and anodizing (new parts) or chemical surface treatment of metals and metal parts in accordance with <u>Chapter 3</u> of this TO is a necessary prerequisite on all interior surfaces prior to priming and painting operations.

**5.7.2** <u>Coating Application</u>. Interior surfaces previously primed with TT-P-1757 may be touched up using MIL-PRF-85582, Type I, Class C1, C2 or N. All other interior surfaces shall be finished with MIL-PRF-23377, Type I, Class C1, C2 or N epoxy primer. If appearance is of concern, the epoxy primer may be topcoated. For areas specified to be of a particular color, Sherwin Williams DTM Gloss Latex Enamel or MIL-PRF-85285 polyurethane shall be applied over the primer in the desired SAE-AMS-STD-595 color and in the same manner and with the same precautions and restrictions as are prescribed for ex-

# TO 1-1-8

terior finishing in this TO. The interior colors prescribed by MIL-C-8779 shall be applied in the locations called out in that specification, the aircraft drawings, or the aircraft -23 TO.

- 5.7.3 Refinishing of Fiber Glass Components. Proceed as follows:
  - a. Remove the topcoat in accordance with <u>Chapter 2</u> of this TO.
  - b. Thoroughly solvent wipe in accordance with Chapter 3 of this TO.
  - c. On the epoxy-primed surface:
    - (1) Sand the surface with 280 grit abrasive paper and solvent wipe. Do not sand through the primer.
    - (2) Reactivate the surface in accordance with <u>Chapter 3</u> of this TO.



### EPOXY PRIMER, MIL-PRF-23377

(3) Apply one coat of MIL-PRF-23377, Type I, Class C1, C2 or N epoxy primer.



### POLYURETHANE COATING, MIL-PRF-85285

(4) Apply two coats of MIL-PRF-85285 polyurethane topcoat.

#### 5.8 MAINTENANCE PAINTING.

Closely inspect candidate areas for extent of damage and maintenance painting required. If inspection reveals major paint failure or damage, such as chipped or peeled paint from the center of a skin panel, the involved skin section should be prepared and maintenance painted from seam to seam. If only minor damage is found, i.e., paint chipped or missing from screw/ rivet heads and on outer edges of skin panel(s) the specific area may be prepared and maintenance painted. Prepare damaged area(s) and paint as follows:

- 5.8.1 Epoxy or Polyurethane Primer/Polyurethane Topcoat. Proceed as follows:
  - a. Thoroughly clean area to be repainted.
  - b. Feather edges of coating adjacent to peeled section and scuff sand the other area(s) to be coated in accordance with <u>Chapter 3</u> of this TO. Use 180 grit paper or nylon abrasive matting material CID A-A-58054, Type I, Grade A or B, very fine or fine for scuff sanding. Grit size down to 120 may be used as long as care is taken not to score the metal surfaces.
  - c. Wipe scuffed or sanded areas with approved solvent and repair damages conversion coatings in accordance with <u>Chap-</u> <u>ter 3</u> of this TO.

15

13

2

13

15

16

# 5.8.2 Primer and Polyurethane Touch-Up.



PRIMER COATING, POLYURETHANE, ELASTOMERIC, HIGH SOLIDS, TT-P-2760



EPOXY PRIMER, MIL-PRF-23377



POLYURETHANE COATING, MIL-PRF-85285




WATER BORNE EPOXY PRIMER, MIL-PRF-85582

5.8.2.1 Brush or Spray. Proceed as follows:

- Apply (brush or spray) one thin coat of epoxy primer MIL-PRF-23377, Type I, Class C1, C2 or N; MIL-PRF-85582, Type I, Class C1, C2 or N; or Polyurethane Primer, TT-P-2760, Type I, Class C or N to area being touched up. Thoroughly mix the primer materials per instructions in <u>Chapter 6</u> before use, but the viscosity need not be checked.
- b. Apply one full wet coat of MIL-PRF-85285 polyurethane topcoat in the required color. If required, apply a second coat after allowing 1-4 hours curing period for the first coat.

5.8.2.2 <u>Touch-Up Pen</u>. Proceed as follows:

- a. Touch-up using MIL-PRF-23377, Type I, Class C1, C2 or N, or MIL-PRF-85582, Type I, Class C1, C2 or N epoxy primer and MIL-PRF-85285, Type I high solids polyurethane in the touch-up applicator pen. These self-contained touch up applicators are available by NSN under the coating specification.
- b. The applicator provides two-component pre-measured materials which are separated by a barrier, <u>Figure 5-1</u>. To mix the materials for use, displace the barrier separating the materials by sliding the tube collar all the way to the back of the applicator, <u>Figure 5-2</u>. Shake the applicator vigorously by hand until the materials are thoroughly mixed (approximately 1 minute).

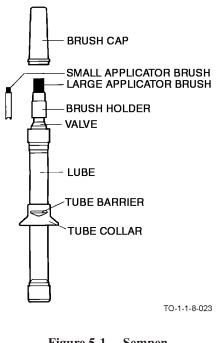






Figure 5-2. Sempen Mixing



After mixing, remove the brush cap and press the applicator against a test article to bleed off any internal pressure that may have formed during storage. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

c. Apply the primer by pressing the applicator brush against the work surface. This opens the spring-loaded valve which allows the coating material to flow when the tube is gently squeezed, <u>Figure 5-3</u>. Use the brush to distribute primer onto the work surface as required. Replace the brush cap when the applicator is not being used.

15

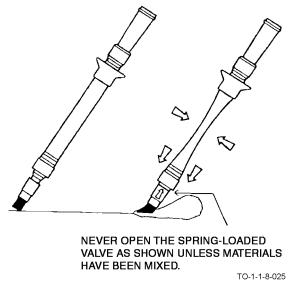


Figure 5-3. Sempen Application



POLYURETHANE COATING, MIL-PRF-85285

d. Apply one full wet coat of MIL-PRF-85285 mixed polyurethane topcoat with a touch-up pen in the same manner. If required, apply a second coat after allowing 1-4 hours curing period for the first coat.

# 5.8.3 Aerosol Touch-Up.

- a. Power Pak Spray Unit NSN 4940-00-803-6444, Specification MIL-S-22805/SAE-AS-22805, Type I, Class 134A (PN M22805-1-134A) may be valuable aid in accomplishing field maintenance painting. (See Figure 5-4.) The kit is designed to be disposable and intended for use in isolated areas when air spray guns cannot be used or are not available. Replacement propellant HFC/Type R134A propellant cans may be obtained under CID A-A-58060, Type R134A, (PN AA58060-R134AW034).
- b. Preval Spray Unit, 8020-01-501-3127, (Preval Sprayer Kit with Power Unit and Glass Bottle), or NSN 8020-01-496-2473, (Preval Power Unit only). Each power unit is capable of spraying up to 16 ounces of liquid.



Figure 5-4. Spray Tool

# TO 1-1-8

- c. Two component aerosol containing mil-spec qualified primer and topcoats, NSN 8010-01-528-XXXX, Figure 5-5. The spray nozzle on the aerosol can has an adjustable fan for vertical and horizontal application. Apply per manufacturer's recommended instructions or by using the following steps:
  - (1) Activate can by removing the red button from cap and attach to pin on the bottom of the can. The pot life of the aerosol after activation is approximately 48 hours.
  - (2) Using the ball of your hand or a hard stable surface, push on the red cap, depressing it into the can until stop is reached.
  - (3) To test activation, the plastic pin should be move easily when pushed after button is removed. To prevent Foreign Object Damage (FOD), discard the red plastic button in trash bin or FOD container.
  - (4) Invert the can and shake vigorously for 2 to 3 minutes to mix hardener and base. Follow can label instruction for appropriate induction time.
  - (5) Clean and prepare the surface per applicable TO instruction. Distance from spray nozzle to surface should be 8 to 10 inches.
  - (6) Rotating spray tip select either vertical or horizontal spray fan.
  - (7) Use overlap stroke pattern for uniform application. Best performance is achieved when can is used in a vertical position. If can must be tilted, it may sputter. To correct, turn nozzle in 90 degree increments to ensure feed tube is immersed.
  - (8) For clean-up and disposal, invert aerosol can and spray until clear. Dispose of can in accordance with hazardous waste disposal regulations.



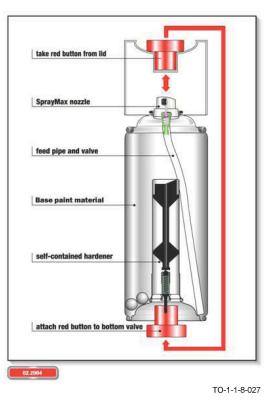


Figure 5-5. Two-Component Aerosol

5.8.4 <u>Brush/Roller Touch-Up</u>. Paint brushes and rollers can be used effectively for touch-up and maintenance painting, but they will not produce the esthetic results of a spray application. Some advantages of brush and roller touch-up over spray application are:

- Masking is minimized, and in most cases, is not required at all.
- More economical for small area and low volume painting because much less paint is required.
- More efficient for application of stencil type markings and grit containing anti-slip walkway coatings.
- Requirements for solvent thinners is very limited.
- Coating transfer efficiency is almost 100 percent with no over spray and very little air pollution that is generated by a small amount of solvent evaporation.
- Hazardous and non-hazardous waste is minimized and limited to used brushes or roller covers and small amounts of excess primer or paint.
- Can be performed in standard maintenance facilities without specialized ventilation and air filtering while other maintenance is being performed.
- PPE is limited to chemical type gloves and eye protection (face shield or chemical type goggles).

**5.8.5** Brush Application. It is very difficult to get a smooth professional appearance without brush strokes with the brush touch-up method on metal surfaces. Therefore, brush touch-up should be limited to areas of 1 square foot or less and preferably to areas of 1 square inch or less, such as fastener heads. Use a fine, flat nylon or nylon/polyester blend bristle brush with a chiseled tip or a triangular tip foam brush having a width appropriate for the job at hand. The application procedure is as follows:

- a. Scuff sand and solvent wipe the touch-up area in accordance with Chapter 3 of this TO.
- b. Mix and thin the primer or paint for brush application in accordance with <u>Chapter 6</u> of this TO and/or the manufacturer's instructions. Mix the least amount possible for the job at hand.

#### NOTE

Pint quantities are more economical than quart or larger quantities to avoid waste of the unused portions when doing small touch-up jobs.

- c. Dip the brush to 1/2 its bristle length into the paint or primer and no more. Remove the brush and press it lightly against the inside of the container to distribute the liquid throughout the thickness of the brush and eliminate any excess. Do not drag the brush over the container rim as this will form bubbles in liquid in the container.
- d. Grasp the brush at the bottom of the handle as if holding a pencil at a 60 degree angle to the surface. Start the brush stroke on one side of the touch-up area with light pressure in the "feathered" paint area, heavier pressure in the bare area, and light pressure again in the opposite "feathered" paint area.
- e. If the area is completely covered, blend the paint into all the "feathered" edges using just the brush tip stroked at several different angles across the initial stroke; and proceed to the next area.
- f. If the area is not completely covered, begin the next stroke parallel to the first stroke with an overlap of about 1/4 of the brush width using the same pressure methods as in Step d and replenishing the paint or primer on the brush per Step c as needed. When the entire area is covered blend the paint or primer as in Step e.
- g. If primer was applied, allow the proper cure time; then apply the topcoat using the same brush techniques as in Step a through Step f.

**5.8.6** <u>Roller Application</u>. While not as good as sprayers for metal surfaces, rollers do provide a smoother and more professional appearance than brushes. Therefore, rollers may be used to touch-up large areas. The most effective roller covers for

application of primer are manufactured from ultra-high-density sponge (Table 5-4). The most effective roller covers for topcoat are manufactured from lint-free, extra-density, high-quality, soft-woven fabric, with a maximum nap length of 1/4 inch (Table 5-5). The core roller center should be resistant to water and solvent. Choose a handle of the proper length and a roller of the right width (3 to 9 inches) for the job at hand, and use one with a splatter shield to prevent the coating from splattering on personnel and other surfaces not being coated. For large areas, power or automatic feed rollers are more efficient and their use eliminates the possibility of spillage from open containers. To minimize spillage when using manual rollers, use coating container grids. Move the roller across the grid to eliminate excess coating material. Polyurethanes and epoxy coatings require a little more paint on the roller during application to achieve a smooth surface and a second cross-coat may be required. The application procedure is as follows:

- a. Scuff sand and solvent wipe the touch-up area in accordance with Chapter 3 of this TO.
- b. Mix and thin the primer or paint for roller application in accordance with <u>Chapter 6</u> of this TO and/or the manufacturer's instructions. Mix the least amount possible for the job at hand. Insert the vertical, portable, metal grid into the container; or pour the liquid into the power/automatic feed roller reservoir.
- c. Dip the roller fully into the primer or paint. Withdraw the roller and move the roller across the vertical metal grid to distribute the liquid throughout the roller pile and eliminate any excess. For power or automatic feed rollers, depress the feed trigger until the roller is full of liquid; and move the roller across a vertical, portable, metal grid mounted in an empty container after the initial filling only to distribute the liquid throughout the pile evenly.
- d. Always start application in a corner of the area being touched up. The maximum area of coverage should be about 9 square feet before moving to an adjacent area. Place the free end of the roller about 3 feet away from where the roller stroke will end so that it covers a small portion of the left or right "feathered" edge of the area being touched up completely and with the roller at an angle to this edge. For horizontal surfaces, always make the first stroke away from you and, without lifting the roller from the surface, make alternate strokes toward and away from you to form a "W" pattern. For vertical surfaces, always make the first stroke upward and, without lifting the roller from the surface, make alternate up and down strokes to form an "M" pattern. Fill in the gaps in the "W" or "M" patterns with crisscrossing strokes of the roller moving back across the "W" or "M" pattern and still not lifting the roller from the surface. Make sure that the entire section is completely covered, including its "feathered" edges, before moving to an adjacent section or finishing the touch-up of an area less than 9 square feet. Always use even pressure on the roller to prevent bubbles and blotches in the primer or paint.
- e. If the touch-up area is not entirely covered, touch-up a section adjacent to the first section making sure it over laps the first section about 2 inches. Application is by the same techniques as in Step d.
- f. If primer was applied, allow the proper cure time and then apply the topcoat using the same roller techniques as in Step a through Step e.

Nomenclature	Specifications/PN	NSN
Roller Kit, Paint (Sponge Roller, Roller	97610 (2 inch Roller)	8020-01-566-8652
Handle and Tray)	97614 (4 inch Roller)	8020-01-566-8654
	97616 (6 inch Roller)	8020-01-566-8655

Table 5-4.	Suggested/Approved	Rollers	for Primer
------------	--------------------	---------	------------

Nomenclature	Specifications/PN	NSN
	99103 (3 inch Roller)	8020-01-566-8650
Woven Nap, Roller Handle and Tray)	99104 (4 inch Roller)	8020-01-566-8653
	99105 (7 inch Roller)	8020-01-566-8651

5.8.7 <u>Temporary Protection</u>. When polyurethane is not available, repair of paint systems with MIL-DTL-85054, Type I or II, CPC sprayed on or brushed on bare metal areas for protection until polyurethane is available, is permissible. (See TO 1-1-691.) Complete painting of aircraft with other than polyurethane MIL-PRF-85285 is not authorized.

5.8.8 <u>Powder Coating</u>. New support equipment is being delivered coated with thermoplastic or thermoset powder coatings. Thermoplastic powder coatings are generally applied to a surface that has been preheated to a temperature significantly higher than melting point of the powder, whereas thermoset powders contain a heat-activated catalyst and are generally applied to a surface at ambient temperature. The surface and the powder are then heated and, as the temperature rises past the melt temperature of the powder, it melts to the surface.

5.8.8.1 <u>Surface Preparation</u>. In situations where complete removal of the thermoplastic/thermoset powder coatings are required, they shall be stripped with EMB, Type II or Type V, using procedures listed in <u>Paragraph 2.12</u>. Chemical paint removal procedures listed in this TO, are very ineffective at removing these coating and, therefore, should not be used.

5.8.8.2 <u>Maintenance Painting</u>. Maintenance painting of thermoplastic/thermoset powder coatings shall be accomplished using epoxy or polyurethane topcoat procedures listed in <u>Paragraph 5.8</u>.

# **CHAPTER 6**

# UNITED STATES AIR FORCE (USAF) STANDARD COATING SYSTEMS FOR AIRCRAFT AND EQUIPMENT

# 6.1 CLASSIFICATION OF ORGANIC COATINGS.

Customarily, finishing materials are classed as paints, enamels, lacquers, and special coatings such as epoxies and polyurethanes. The word "paint" is loosely used to mean all finishing materials. Modern coatings now include quite different components in combinations that do not fall into the old categories. Coating materials used by the AF are generally identified by the basic classifications above. General information on materials in these categories used by the AF is presented here.

### NOTE

- National Stock Numbers (NSN) for specific coatings and related materials are to be obtained from Federal Stock Classes (FSC) (normally FSC 8000). Also, see the current General Services Administration (GSA) Catalog and the DO43 System to convert specification and part numbers to NSNs.
- To determine the proper paint system for specific equipment, refer to -23 technical orders, and aircraft paint drawings, for aircraft; TO 35-1-3 for support equipment; or specific repair TOs.

#### 6.2 CONSTITUENTS OF ORGANIC COATINGS.

Modern paints may be a mixture of many things, but the primary constituents are pigment, vehicle (the film former), and solvents. Secondary components (although they may still be of prime importance) may be extenders, driers, antioxidants, surfactants, light-filtering agents, and/or other additives. When special properties are required such as luminescence, fluorescence, fire retardant, etc., materials to provide these are also added.

#### 6.3 PIGMENTS.

Pigments are finely divided, substantially insoluble, and usually opaque materials incorporated into paints to provide color, hiding power, and specific qualities such as light and heat reflectance (or heat absorption), corrosion-inhibition, and certain flow characteristics. Pigments may be inorganic or organic types and of either natural or synthetic origin. Examples are the metallic compounds such as zinc oxide and titanium dioxide in white and light tinted paints, zinc chromate in primers to give yellow coloration and act as a corrosion inhibitor, chromium oxide for green, iron oxide for red, etc. Synthetic agents or dyes are also widely used. A limited number of pigments are used as corrosion inhibitors in protective primers. The par-ticular pigment used depends upon the metal that is to be protected, steel, aluminum, magnesium, etc., and the environment to which it is to be subjected.

#### NOTE

The theoretical function of a protective paint is to physically exclude environment from the metal surface; but, practically, it rarely succeeds entirely. All organic films are moisture permeable to some degree. Also, tiny physical defects in a film are usually present to some degree or develop in time. General practice is to supplement the physical protective properties of coatings with materials that provide electrochemical protection either by using surface conversion coating treatments (refer to <u>Chapter 3</u>), or by inclusion of corrosion-inhibiting pigments in the primer coatings.

#### 6.4 VEHICLE.

The vehicle is the liquid portion of the coating. It is the most significant part of the coating as it furnishes desired qualities of adhesion, toughness, flexibility, and resistance to various environments. The vehicle consists of non-volatile and volatile portions. The non-volatile includes resins, drying oils, and plasticizers that become the binding agent in the cured film. Upon evaporation of the volatile portion, the non-volatiles form the actual film on the surface together with the pigment, if one is present. Vehicles appear in a multitude of combinations, containing many materials. A varnish vehicle in enamels generally contains an oil-modified alkyd resin, thinners, and driers. A lacquer vehicle consists mainly of resins, solvents, and plasticizers.

# 6.5 PREPARATION OF COATING MATERIALS FOR USE, GENERAL.

# WARNING

Containers of paint may develop internal pressure during storage and should be opened with caution. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

Coating materials shall be prepared for application under clean conditions with clean equipment. Paint shops shall be equipped with mechanical paint agitators of suitable capacity. The proper sequence for preparing packaged materials prior to each use is as follows:

- a. Allow materials to come to room temperature.
- b. Remove lids and inspect paint for skin-over, gelling, lumps, etc. Skins, if present, shall be carefully removed and discarded, retaining liquids which drain from them. Gelled, lumpy, or otherwise deteriorated paints shall not be used.

### NOTE

Cans of pigmented paint with non-resealable lids should not be opened and inspected until after the original mechanical agitation.

- c. Thoroughly agitate all pigmented paints using a mechanical agitator prior to thinning and prior to and during application.
- d. Thinning shall be controlled by weight, volume, or viscosity measurement to obtain and maintain proper and uniform consistency. Thin according to manufacturer's instructions or the specification for the material. When the Volatile Organic Compound (VOC) content of coatings is regulated, thin only with exempt thinner or solvent, and do not use non-VOC compliant thinners or solvents such as MIL-T-81772 to reduce high solids primers and topcoats. Reducing with non-VOC compliant thinners or solvents can cause high solids coatings to exceed the maximum allowable VOC content in violation of air pollution regulations.
- e. Reduction and/or catalyzation of coatings shall be accomplished in accordance with <u>Paragraph 6.6</u>, <u>Paragraph 6.7</u>, and the specific coating paragraph as well as the manufacturer's instructions. If this does not produce the proper spraying viscosity, quality control personnel shall be consulted.
- f. Strain all material to be used in spray equipment through fine-mesh strainers or cheesecloth.

#### 6.6 MIXING AND THINNING OF COATING MATERIALS, GENERAL.

# WARNING

Mixing shall be done in controlled areas that are well ventilated and away from any open flame or other source of ignition and direct sunlight. Forced air ventilation, preferable with air flow from the back of personnel to an exhaust in front of them. For two-component materials, an organic vapor type respirator shall be worn as a minimum, with the air supplied type being preferable. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

Mixing of coating materials may seem too elementary to require lengthy discussion, but it is a very common source of trouble either through negligence or lack of knowledge. All coating materials require preparation prior to application, and problems with color, gloss, hiding power, film application characteristics, adhesion, and curing can be expected if materials are not adequately prepared. For two-component materials, the components must be thoroughly mixed with each other and in the exact specified proportions or curing and adhesion problems will occur. Pigments, which give color and other desirable characteristics to coatings, are generally insoluble and heavier than the liquid portion of the coating material, so they eventually settle out of suspension. The consistency or viscosity of the liquid portion determines the rate of settling; for example, pigments mixed with a thinner alone would settle out in a few minutes; but in a paint vehicle, it might take months. The practice of thinning too much material at a time and pouring unused portions of the material back into the original container with unthinned material lowers the total consistency and increases the rate of settling and should not be done. Settled material

usually re-disperses readily unless the material is over-aged or has become exposed to the atmosphere. In some materials, such as some vinyl based materials, settling may be accompanied by a change in chemical structure after storage of only a few months. Such changes are not reversible; therefore, judgment should be employed whenever using them.

#### NOTE

After a coating materials shelf life has expired, thoroughly test material per Appendix A before using it. If an aged material appears unsuitable after appropriate attempts at mixing and reducing, it should be discarded. If the quantity involved is large, laboratory tests by Robins Science and Engineering Laboratory to determine its continued conformance to specification requirements will be required before its use or its disposal.

- 6.6.1 <u>Method of Mixing</u>. Mixing in containers shall be done per the following methods:
  - a. Hand-mixing of single-component materials and the catalyst component of two-component materials in cans, cups, and drums, per the manufacturer's instructions, using wooden or plastic paddles.
  - b. Mixing of one-component materials and the base component only of two-component materials in containers up to 5 gallons is best accomplished by using mechanical shakers that vibrate or shake the unopened container.
  - c. Accomplish mixing of one-component materials and the base and catalyst components of two-component materials with low speed mechanical paddles.

6.6.2 <u>Mixing Test</u>. A simple test of complete mixing is to flow samples down an inclined piece of glass. Irregularities of color or flow will indicate incomplete mixing. Comparison of materials from the bottom and top of a container may be made by this method.

### 6.7 SOLVENTS, DILUENTS, AND THINNERS.

At ordinary room temperatures, the consistency or viscosity of mixtures of oils, pigments, and resins that make up coating materials is too high to allow spreading them effectively over surfaces in the desired thickness. Also, most resins are solids and need to be dissolved in a liquid before they can be dispersed. A solvent has the essential function of reducing the viscosity of the vehicle portion of the material to the point where it can be managed. Solvents do not react chemically with coating constituents or dissolve pigments; and ultimately, they are lost from the coating by evaporation having served their purpose. Most solvents are organic materials and are classified by their chemical structure as alcohols, esters, ketones, etc. In practice, they must be considered from the standpoint of their powers of solvency as expressed in reference to some material. A liquid may dissolve one substance well, another poorly, and still others not at all. There is no universal solvent in coating technology. A liquid that does not actually dissolve a given substance may, however, be used as a diluent or a thinner for that substance. Solvents and diluents are frequently used together in coating formulations, and the purpose of a liquid determines whether it is "solvent" or "diluent". For example, mineral spirits is a solvent for linseed oil, but not for cellulose nitrate. But solutions of cellulose nitrate in butyl acetate will tolerate substantial amounts of mineral spirits and here the mineral spirits is used as a diluent for the solution. Diluents and thinners are normally less expensive than solvents. Generally, the solvent portion of a coating is itself a blend of solvents, each one chosen for its power to dissolve a particular constituent of the coating, and each present in proper proportion to regulate evaporation to a rate that prevents premature segregation of any single dissolved constituent.

#### NOTE

- Although in practice the terms solvent, diluent, and thinner are often used interchangeably to describe a liquid, it should be understood that the words have different meanings, and the mechanism of solvents and diluents or thinners are different. For example, a solvent will thin incidentally while performing its prime purpose of dissolving something; whereas a diluent or thinner is used to reduce viscosity and/or regulate evaporation and is not required to, and may be unable to, dissolve any constituents of the coating concerned. Of course, thinner must be compatible with the coating. Compatibility is beyond determination in the field; hence, only authorized thinners specifically called out for use with a given coating shall be used to thin it.
- To distinguish between "diluent" and "thinner", the material added by the manufacturer to adjust viscosity is called a "diluent", while the same material added by the painter for the same purpose is called "thinner".

6.7.1 <u>Volatility</u>. Volatility is the rate at which a solvent evaporates, governs the length of time a paint film remains fluid. Thus, it affects performance characteristics of the paint film when deposited, such as smoothness of flow-out, time an edge re-

mains wet to enable blending of overlapped strokes of the spray gun or brush, tendency to sag or run, drying time, etc. Volatility also largely governs the flash point of materials.

6.7.2 Thinners.



The very properties that make a substance a good solvent for organic materials tend to make it harmful to the body. Many are also hazardous due to flammability. Use caution to avoid unnecessary and continued exposure to the volatile constituents of paints either by inhalation or by skin contact. Precautions must be taken at all times to prevent accidental ignition. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

Thinner is the material added to a coating material by the painter to adjust its viscosity. The following specification thinners are among those used in AF painting:

6.7.2.1 CID A-A-3007 is thinner for enamels, such as MPI No. 6 or MPI No. 94, for spray applications.

6.7.2.2 MIL-T-81772, Aircraft Coating Thinner, covers three types of thinners for reducing the standard aircraft coatings. They are suited for, but are not necessarily limited to, the following applications:

6.7.2.2.1 Type I is for thinning MIL-PRF-85285 and SAE AMS-C-83231 polyurethane coatings or other coatings, as authorized.

6.7.2.2.2 Type II is for thinning MIL-PRF-23377 epoxy primer, MIL-PRF-22750 epoxy coating, or other coatings, as authorized.

6.7.2.2.3 Type III is for thinning TT-P-1757 primer or other coatings, as authorized.

6.7.2.3 Special purpose "thinners" are often added to coating materials to provide good drying characteristics under abnormal environmental conditions. High boiling point solvents such as diacetone alcohol (ASTM D2627) and butyl alcohol (ASTM D304) are often added to prevent blushing.

6.7.3 <u>Viscosity</u>. Viscosity is a measure of a liquid's resistance to flow. Very viscous or thick liquids such as molasses flow very slowly, while low viscosity liquids such as water flow very quickly. Maintaining the proper viscosity is very important for proper spray application of primers and paint coatings. Too high a viscosity produces poor spray patterns and poor coverage, while too low a viscosity produces a film that sags and runs easily. Many different methods can be used to measure viscosity, but the easiest and most frequently used methods for primers and paint coatings are flow time measurements from either a Number (No.) 2 Zahn Cup or a No. 4 Ford Cup. Therefore, the acceptable viscosity ranges for each primer and paint coating discussed in this TO are given in flow time in No. 2 Zahn Cup and No. 4 Ford Cup seconds at 75 °F (24 °C). For any of these materials, the viscosity will be somewhat higher at lower temperatures and somewhat lower at higher temperatures. Viscosity is measured as follows:

6.7.3.1 <u>No. 2 Zahn Cup</u>. (See Figure 6-1) After the primer or paint coating is properly mixed, fully immerse the cup in the liquid so it is completely filled, and lift the cup out of the liquid. Using a stop watch, measure the time, in seconds, it takes the material to flow out of the hole in the bottom of the cup from the moment the cup clears the liquid surface to the point where the first break in the flow stream is noted. This time is the viscosity in No. 2 Zahn seconds.

#### NOTE

The No. 2 Zahn Cup doesn't work well for high-solids coatings. The No. 4 Ford Cup is preferable for these high-solids coatings.




Figure 6-1. Zahn Cup

6.7.3.2 <u>No. 4 Ford Cup</u>. After the primer or paint coating is properly mixed, pour the material into the cup mounted in a stand while blocking the hole in the bottom of the cup with a finger. Make sure the cup is completely filled and then scrape away any excess sliding a flat glass plate across the rim of the cup. Leave the glass plate in place and remove the finger blocking the hole in the bottom of the cup. Slide the plate horizontally to remove it from the top of the cup. Using a stop watch, measure the time, in seconds, it takes the material to flow out of the hole in the bottom of the cup from the moment the plate is removed to the point where the first break in the flow stream is noted. This time is the viscosity in No. 4 Ford Cup seconds.

6.7.3.3 <u>Adjustments</u>. If the viscosity measured is not within the specified range, thin the material per the thinning instructions for the primer or paint coating listed in this TO and remeasure the viscosity after cleaning the cup with thinner. Repeat as necessary until the viscosity is within the specified range.

# 6.8 BLUSHING.

Blushing of coatings is the result of moisture condensation from the atmosphere within or on a drying organic film. It occurs when the temperature of the work surface and/or the coating material itself falls below the prevailing dew-point. Always look for it in production coating operations whenever high humidity conditions exist. It shows as a lighter-than-normal or whitish discoloration or increased opaqueness of film. It may occur to the extent that a surface powder results which can be removed by a fingernail or by light rubbing. Rubbing will not cure the condition. It may also be almost imperceptible, and blush-inducing conditions may escape notice on test panels sprayed prior to production coating such as lacquers and only rarely with enamels. It is detrimental in some degree to any coating material and will affect adhesion of any overcoat. Any blushed areas must be stripped and redone. Superficial blushing may occur at borderline temperature and humidity conditions and subsequently disappear. This is not considered harmful and may be ignored.

# NOTE

Slight blushing may sometimes be detected by noting faint dissimilarities of appearance in the film occurring over structural members underlying the surface such as bulkheads, ribs, etc. Skin surfaces in contact with internal structures may be lower in temperature than the surrounding skin, and this may be reflected and outlined in blushing.

# 6.9 <u>RESINS</u>.

Natural resins are solid organic substances of vegetable or animal origin. Synthetic resins are man-made substances physically similar to natural resins. Rosin and shellac are examples of natural resins. Synthetic resins have largely taken over in modern coating formulations because they can be made to order to furnish desired characteristics. Coating materials described in this technical manual are almost exclusively based on synthetics. The following are examples of resins and their special characteristics:

# TO 1-1-8

6.9.1 <u>Alkyds</u>. Alkyds are the backbone of modern enamel in a great many combinations. Specification MPI No. 6 or MPI No. 94 is alkyd or modified alkyd enamel used by the AF. Alkyd is characterized by toughness, flexibility, and durability, and is used in exterior and interior coatings for utility and decorative purposes. It does not have good chemical resistance.

6.9.2 <u>Acrylics</u>. Acrylics have outstanding light resistance and outdoor weather durability, with moderate chemical resistance. Used with nitrocellulose as a hardener, they have better drying properties and increased hardness.

6.9.3 <u>Vinyls</u>. Vinyls have limited aircraft application, but where construction materials, such as metal and wood, must be protected from high humidity, acidic, or caustic environments, vinyls are used.

6.9.4 <u>Phenolics</u>. Phenolic resins are used in varnishes and enamels requiring extra hardness and abrasion resistance. Specification CID A-A-1800 spar varnish is an example.

6.9.5 <u>Silicones</u>. Silicone resins are used primarily in heat resistant coatings. They are not particularly hard surfaced and may craze. They are usually baked to cure.

6.9.6 <u>Epoxies</u>. Epoxies have outstanding adhesion and chemical resistance. In combination with other resins, they become baking enamels. For air drying types, catalysts are mixed with a base material prior to application, starting a chemical reaction that continues after application to develop a film with good performance characteristics. The AF uses MIL-PRF-23377 and MIL-PRF-85582 primers.

6.9.7 <u>Polyurethane</u>. Polyurethane resins are also catalyzed coatings. The AF MIL-PRF-85285 polyurethane coating is characterized by its very high gloss retention in gloss finishes and its flatness in camouflage finishes, its superior toughness and outdoor durability, and good chemical resistance.

#### 6.10 ADHESION.

Good adhesion of organic coatings requires a surface that is mechanically and chemically clean. A smooth or highly polished surface will have very poor coating adhesion and should be roughened to provide "tooth" for physical bonding. Adhesion to smooth materials, such as glass, is difficult and surface etching is essential. With plastics, etching may be augmented by solvent activation to obtain some degree of fusion with the surface. Metal surfaces require an appropriate surface preparation, such as conversion coating, for adequate primer adhesion.

#### 6.11 PRIMERS.

Primers are used to provide an adherent coating to which subsequent coatings will firmly adhere and to provide corrosion protection for metals. The pigment portion of primers for ferrous base metals usually consists of iron oxide, strontium chromate, zinc chromate, zinc oxide, zinc dust, or a mixture of these. Zinc or strontium chromate is the principal pigment in primers used on aluminum, magnesium, and their alloys. Primers are satisfactory for corrosion protection of metals, but are generally not suitable as topcoats. Color, weathering properties, or physical durability may be unsatisfactory; and for these reasons, primers require protection by topcoating.

#### 6.12 COATINGS AND COATING SYSTEMS.

Some examples of specification coatings are as follows:

#### NOTE

Because of the large number of Military and Federal Specifications approved for AF use, no attempt has been made to discuss all of them in this technical manual. In addition, many items of AF equipment and components are coated with proprietary materials making logistic support of such equipment difficult. Every effort should be made by responsible personnel to select standard AF approved specification material for overcoating or replacing these proprietary materials.

6.12.1 <u>USAF Standard Polyurethane Aircraft Coating System</u>. (See <u>Chapter 8</u>, aircraft -23, or other weapon system specific TOs, and paint drawings for schemes, colors, and markings.) Optional standard polyurethane coating systems consist of epoxy primer MIL-PRF-23377, water reducible epoxy primer MIL-PRF-85582, polyurethane primer TT-P-2760, or polysulfide primer PR-1432GV, topcoated with polyurethane coating MIL-PRF-85285. Additionally, a light dust coat may be utilized for the reapplication of MIL-PRF-85285 over an existing coating. Most coatings formulated for these specifications are two-component materials intended for spray application.

13

# NOTE

- Before applying a material, spray it on an aluminum panel to determine its suitability. Observe the panel for blushing, sagging, or other defects detectable during or shortly after application. Correct the cause of any defect found before continuing. This test panel is in addition to the one coated simultaneously with the aircraft and used as a check of the completed job.
- Epoxies and polyurethanes cure (chemically react) rather than dry by evaporation. Use only clean equipment for mixing and applying the system to prevent contamination of the materials. Clean the equipment immediately after use with a suitable solvent before the coatings set up.
- Cure accelerators are not authorized for use in painting aircraft exterior surfaces as they make coatings brittle.
- Inadequate mixing or mixing in the wrong proportions causes poor adhesion, slow or incomplete curing, and poor performance of the coating.

#### 6.12.2 Primer Coating, Epoxy, For Aircraft Application, MIL-PRF-23377.



EPOXY PRIMER, MIL-PRF-23377

6.12.2.1 <u>Characteristics</u>. This is a two-component, low VOC, solvent-borne, lead free, corrosion inhibiting epoxy primer particularly formulated for its adhesion properties. It is compliant with the NESHAP VOC requirements of 336 grams per liter (2.8 pounds per gallon). It is very resistant to chemicals, lubricants, and corrosive atmospheres; but it has only fair weathering characteristics. Because it is an epoxy, this primer is difficult to remove with standard paint removers. This primer is available in two different types each with two different classes.

Type I	Standard pigments (yellow)
Type II	Low infrared reflective pigments (dark green)
Class C1	Barium chromate based corrosion inhibitors
Class C2	Strontium chromate based corrosion inhibitors
Class N	Non-chromate based corrosion inhibitors

# NOTE

Class N shall not be substituted for Class C1 or C2, unless authorization is given by the engineering authority for the system or item on which the primer is used.

6.12.2.2 <u>Uses</u>. A primer for MIL-PRF-85285 polyurethane topcoat for the exterior of aircraft, components, and other aero-space equipment, and as a stand-alone primer on interior surfaces of aircraft and components.

6.12.2.3 <u>Mixing</u>. Thoroughly agitate components (Epoxy Resin Base Component A and Polyamide and/or amine resin curing agent Component B), preferably with a mechanical shaker, prior to mixing and, if required, pour into separate measuring or metering containers. Using manufacturer's instructions, mix proper volumes of the components A and B by pouring B into A and thoroughly agitating. Best mixing results can be achieved with a mechanical shaker. Mix only materials from the same manufacturer and do not mix more material than can be used in a 4 hour period. After mixing, allow the primer to stand 30 minutes before applying. This primer must be agitated continuously during spraying applications to prevent settlement of pigment and ensure uniformity of color. If in-line or in-head proportioning equipment is used to mix base and catalyst (curing agent) as the paint is being used, a 30-minute dwell time is not required before application.

# 6.12.2.4 <u>Thinning</u>.



PARACHLOROBENZOTRIFLUORIDE, PCBTF



AIRCRAFT COATING THINNER, MIL-T-81772



- MIL-T-81772 is flammable and moderately toxic to eyes, skin, and respiratory tract. Eye and skin protection required. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- Parachlorobenzotrifluoride (PCBTF), is combustible and an irritant to eyes, skin, and respiratory tract. Eye and skin protection required. Disposable 8 mil nitrile gloves, splash goggles, Tyvek<sup>TM</sup>/cloth coveralls are the recommended Personal Protective Equipment (PPE). Use in well ventilated areas. Failure to comply could result in injury to, or death of, personnel or long term health hazards.



In areas where air quality regulations restrict volatile emissions, do not add thinner MIL-T-81772 to the primer coating as that addition may raise the VOC content to greater than 336 grams per liter (2.8 pounds per gallon). Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

# NOTE

PCBTF, is exempt as a VOC or Hazardous Air Pollutants (HAP) by the Environmental Protection Agency (EPA) and by 48 states and will not change compliance of high solids coatings to air quality regulations.

The viscosity of the unthinned primer may range up to a maximum of 40 seconds in a No. 4 Ford Cup (56 seconds in a No. 2 Zahn Cup). Strain the primer through clean cheesecloth, per CCC-C-440, Type I, Class 2 or a commercial paint strainer. When required, adjust the viscosity by thinning to a viscosity of 8 to 19 seconds in a No. 4 Ford Cup (17 to 23 seconds in a No. 2 Zahn Cup). Use thinner per MIL-T-81772 Type II or PCBTF, NSN 6850-01-566-2678 (1 gallon). Add MIL-T-81772, Type II thinner as required to achieve the viscosity range above. In areas where air quality regulations restrict volatile emissions, thin with PCBTF using up to 10 percent by volume as a recommended maximum for reduction of viscosity.

6.12.2.5 <u>Application</u>. Apply one coat of primer to a dry film thickness of 0.6 to 0.9 mils, per <u>Table 5-2</u>. Follow manufacturer recommendations for dry to tack-free times. Tack-free is the point of time in drying at which the surface of the film will not fingerprint; yet the film is not dry and hard throughout. If the primer is allowed to hard dry, solvent wipe in accordance with <u>Chapter 3</u> of this TO to reactivate before topcoating. The film is considered hard dry when any mark left by the thumb is completely removed by lightly polishing the contacted area with a soft cloth. Since this epoxy primer has a very high solids content, cross coating may not be required; and the spray gun must be kept moving to prevent excessive film buildup with subsequent reduction of adhesion. Apply a topcoat within 24 hours of primer application. After 24 hours, scuff sand the entire primed surface with CID A-A-58054, Type I, Grade A abrasive mat and solvent wipe the area in accordance with <u>Chapter 3</u> of this TO prior to topcoating. Discard any of this primer mixed for longer than the manufacturer recommended pot life. Higher or lower temperatures shorten or lengthen the pot life proportionally.

6.12.2.6 <u>Drying Time</u>. Drying times will vary by the manufacturer's instructions, temperature, and Relative Humidity (RH) in the painting area. Lower temperatures and higher RH will increase drying times while higher temperatures and lower RH will decrease these drying times.

17

6.12.3 Primer Coating, Epoxy, VOC Complaint, Chemical and Solvent Resistant, MIL-PRF-85582.



WATER BORNE EPOXY PRIMER, MIL-PRF-85582

6.12.3.1 <u>Characteristics</u>. This is a two-component, lead free, water-reducible, corrosion inhibiting epoxy primer formulated to meet most local environmental pollution regulations. This primer is available in two different types each with three different classes.

- Type I Standard pigments (yellow)
- Type II Low infrared reflective pigments (dark green)
- Class C1 Barium chromate based corrosion inhibitors
- Class C2 Strontium chromate based corrosion inhibitors
- Class N Non-chromate based corrosion inhibitors

### NOTE

Class N shall not be substituted for Class C1 or Class C2 unless authorization is given by the procuring activity or engineering authority for the system or item on which the primer is used.

6.12.3.2 <u>Uses</u>. As a primer for MIL-PRF-85285 polyurethane topcoat for aircraft and a stand-alone primer on interior surfaces of aircraft and components.

6.12.3.3 <u>Mixing</u>. See manufacturer's mixing instructions, as different manufacturers may have different mixing ratios and methods.

6.12.3.4 <u>Thinning</u>. Thin with water per the manufacturer's instructions as each manufacturer may have different thinning ratios and methods. Application viscosity will be approximately 14 seconds in a No. 4 Ford Cup (20 seconds in a No. 2 Zahn Cup). Allow the mixed and thinned primer to stand 30 minutes prior to use.

# NOTE

The volume of some primers may increase by 250 percent when properly thinned with water.

6.12.3.5 <u>Application</u>. After thoroughly cleaning, surface treating, and solvent wiping the surface to be primed in accordance with <u>Chapter 3</u> of this TO, and purging spraying equipment lines with a mixture of 25 percent TT-I-735 isopropyl alcohol and 75 percent water, apply the primer to a dry film thickness of 0.6 to 1.8 mils, see <u>Table 5-2</u>. Follow manufacturer recommendations for dry to tack-free times. Tack-free is the point in time in drying at which the surface of the film will not fingerprint; yet the film is not dry and hard throughout. If the primer is allowed to hard dry, the primer shall be lightly scuff sanded with CID A-A-58054, Type I, Grade A abrasive mat, tack ragged and solvent wiped before topcoat application. The film is considered hard dry when any mark left by the thumb is completely removed by lightly polishing the contacted area with a soft cloth. Areas that are not clean will not support the primer film, which will break into droplets; like a water break test. If this happens, the primer can be blotted up, the area wiped clean with a clean cloth dampened with solvent per <u>Table 3-2</u>, and the primer reapplied.

6.12.3.6 <u>Drying Time</u>. Drying times will vary by the manufacturer's instructions, temperature and RH in the painting area. Lower temperatures and higher RH will increase drying times while higher temperatures and lower RH will decrease these drying times.

16

6.12.4 Primer Coating, Polyurethane, TT-P-2760.



PRIMER COATING, POLYURETHANE, ELASTOMERIC, HIGH SOLIDS, TT-P-2760

# WARNING

2

TT-P-2760 is moderately toxic to eyes, skin, and respiratory tract. Eye and skin protection required. Consult Bioenvironmental Engineering to determine need for respiratory and ventilation requirements. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

6.12.4.1 <u>Characteristics</u>. This is a two-component, low VOC, solvent borne, highly flexible elastomeric polyurethane primer. The maximum VOC content of the primer coating is 336 grams per liter (2.8 pounds per gallon). It is available in two different types each with two different classes.

- Type I Standard pigments (yellow or light brown)
- Type II Low infrared reflective pigments (dark green)
- Class C Strontium chromate based corrosion inhibitors
- Class N Non-chromate based corrosion inhibitors

### NOTE


Class N shall not be substituted for Class C unless authorization is given by the procuring activity or engineering authority for the system or item on which the primer is used.

6.12.4.2 Uses. As a primer for MIL-PRF-85285 polyurethane topcoat. It is a suitable alternate for MIL-PRF-23377 and MIL-PRF-85582 primers and can be used as a touch-up primer for both MIL-PRF-23377 and MIL-PRF-85582 on exterior surfaces. Because of this primer's flexibility, it is recommended for high impact areas, such as leading edge slats, and the entire exterior surface on large, flexible cargo and bomber aircraft.

6.12.4.3 <u>Mixing</u>. Shake the base material (component A) for 5 minutes on a paint shaker and stir the catalyst (component B) with a wooden paddle prior to mixing. Pour one volume of catalyst into one volume of base and mix the material thoroughly following manufacturer's instructions. Do not mix more material than can be used in 4 hours.

# NOTE

Some materials are mixed in a three to one by volume ratio. Always mix in accordance with manufacturer's instructions.





AIRCRAFT COATING THINNER, MIL-T-81772



PARACHLOROBENZOTRIFLUORIDE, PCBTF

• MIL-T-81772 is flammable and moderately toxic to eyes, skin, and respiratory tract. Eye and skin protection required. Use in well ventilated areas. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

WARNING

• PCBTF is combustible and an irritant to eyes, skin, and respiratory tract. Eye and skin protection required. Disposable 8 mil nitrile gloves, splash goggles, Tyvek<sup>TM</sup>/cloth coveralls are the recommended PPE. Use in well ventilated areas. Failure to comply could result in injury to, or death of, personnel or long term health hazards.



- All thinners used with this coating must be "urethane grade" with a water content of less than 0.05 percent by weight. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- In areas where air quality regulations restrict volatile emissions, do not add thinner MIL-T-81772 to the primer coating as that addition may raise the VOC content to greater than 336 grams per liter (2.8 pounds per gallon). Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

# NOTE

PCBTF, is exempt as a VOC or HAP by the EPA and by 48 states and will not change compliance of high solids coatings to air quality regulations.

Thinning of this primer is not required, as viscosity as manufactured should be correct for spray application. If thinning is done, it shall be with MIL-T-81772, Type I or PCBTF, NSN 6850-01-566-2678 (1 gallon). Use thinner in the least quantity necessary to get the proper viscosity. The application viscosity will be approximately 14 seconds in a No. 4 Ford Cup (20 seconds in a No. 2 Zahn Cup).

6.12.4.5 <u>Application</u>. After thoroughly cleaning, surface treating, and solvent wiping the surface to be primed in accordance with <u>Chapter 3</u> of this TO, apply one coat of primer to a dry film thickness of 1.0 to 1.5 mils, per <u>Table 5-2</u>. This primer will not adhere to an improperly prepared or contaminated surface. Allow to dry tack-free. Follow manufacturer's instructions for dry to tack-free times. Tack-free is the point of time in drying at which the surface of the film will not fingerprint; yet the film is not dry and hard throughout. The coating must be applied in a RH range of 30 percent to 80 percent. If humidity is below 30 percent, add moisture to the air by wetting the floor of the painting area or by equivalent methods. If the primer is allowed to hard dry, the primer shall be lightly scuff sanded with CID A-A-58054, Type I, Grade A abrasive mat, tack ragged, and solvent wiped before topcoat application. The film is hard dry when any mark left by the thumb is completely removed by lightly polishing the contacted area with a soft cloth. Discard any of this primer mixed for longer than the manufacturer recommended pot life time.

6.12.4.6 <u>Drying Time</u>. Drying times will vary by the manufacturer's instructions, temperature, and RH in the painting area. Lower temperatures and higher RH will increase drying times while higher temperatures and lower RH will decrease these drying times. Higher or lower temperature shorten or lengthen the pot life proportionally.

# 6.12.5 Primer Coating, Elastomeric, Polysulfide Corrosion Inhibiting, PR-1432GV.



POLYSULFIDE PRIMER, PR-1432GV



PR-1432GV is moderately toxic to eyes, skin, and respiratory tract. Eye and skin protection required. Consult Bioenvironmental Engineering to determine need for respiratory and ventilation requirements. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

6.12.5.1 <u>Characteristics</u>. This is a two-component, polysulfide primer, particularly formulated for its corrosion resistance and flexibility. It is a superior material for protection of relatively flexible aircraft structures as it does not crack or peel away from fasteners in highly stressed areas, and it will not crack, peel, or rupture from lap and butt joints. The physical properties of this primer on large flexible aircraft structures will increase the longevity of the paint system as well as decrease maintenance and corrosion rework during the life cycle of the coating system.

6.12.5.2 <u>Uses</u>. As a primer for MIL-PRF-85285 polyurethane topcoat on aircraft exterior surfaces. The Weapon System Manager shall specify when this primer is to be used.

6.12.5.3 <u>Mixing</u>. Adequate curing of sealant and sealant based coatings depend on proper and controlled component mixing by weight. This ensures that the component ratio is as close as possible to that specified by the manufacturer's instructions. When mixing partial kits, an accurate scale is required that will weigh up to 2.6 kilograms to the nearest 0.1 of a gram. One scale meeting these requirements is the Triple Beam 760-W Balance made by Paul N. Gardner Co., Inc., 316 N.E. First St., Pompano Beach FL 33060. Mix the base compound (component A) and the accelerator (component B) in the proportions of 15 to 1 by weight. Always properly mix in the correct proportions by the manufacturer's instructions for optimum results.

#### NOTE

The base compound has a tendency to settle out in storage and should be thoroughly mixed prior to adding the accelerator.

- a. Shake the base compound on a standard paint shaker for 5 minutes.
- b. Mix the accelerator by stirring with a paddle and add to the base compound.
- c. Replace the base compound container lid and shake for 2 to 3 minutes in an upright position followed by 2 to 3 minutes in an inverted position.

#### NOTE

Fast and longer mixing decreases application time (pot life). High humidity (70 percent RH or above) at time of mixing decreases application time (pot life).

6.12.5.4 <u>Thinning</u>.



ACETONE, ASTM-D329



PARACHLOROBENZOTRIFLUORIDE, PCBTF

If thinning is required, follow manufacturer's instructions. Acetone or PCBTF may also be used.

6.12.5.5 <u>Application</u>. The primer can be applied by High Volume Low Pressure (HVLP), airless spray, or air-assisted airless spray. The primer has a 2 hour pot life at 75 °F (24 °C) temperature and 50 percent RH. For every 18 °F (-8 °C) rise in temperature, the application time (pot life) is reduced by half; and for every 18 °F (-8 °C) drop in temperature, the application time (pot life) is reduced by half; and for every 18 °F (-8 °C) drop in temperature, the application time is doubled. The polysulfide primer shall be applied to a wet film thickness of 3.0 to 4.0 mils which results in a dry thickness of 1.0 to 1.2 mils. The polyurethane topcoat, MIL-PRF-85285 can be applied any time after the polysulfide primer is tack-free up to 24 hours if no moisture or dirt is on the aircraft, the aircraft is kept in an environmentally controlled hangar, and no maintenance or walking has been done on the aircraft.

6.12.5.6 <u>Drying Time</u>. At 75 °F (24 °C), the tack-free time is approximately 6 hours, 3 hours at 90 °F (32 °C), and 12 hours at 60 °F (16 °C); however, high humidity at time of application will shorten the tack-free time. Follow manufacturer's instructions for specific drying times.

#### NOTE

- The material shall be applied to test panels as specified in Paragraph 5.5.5 so that any defects can be corrected prior to production spray application. The correct line and pot pressure can be determined at this time.
- Some orange peel appearance in the coating system is inherent with this primer and is acceptable.
- It is mandatory that spray equipment be cleaned immediately after use.

# 6.12.6 Tiecoat, Non-Chromated.



#### TIECOAT, NON-CHROMATED

This coating differs from MIL-PRF-23377 which has requirements directed toward the corrosion protection of and adhesion to bare metal. The tiecoat purchase description requirements are only for adhesion to other coatings. Tiecoats listed here meet all of the requirements for MIL-PRF-23377 Type I, Class N, except for the corrosion protection requirements and are an interim authorization until completion of the purchase description. All test results and certifications for meeting the MIL-PRF-23377 Type I, Class N, with the exception of the corrosion protection requirements must be submitted to AFCPCO at afcorr@us.af.mil for inclusion in this TO. The following coatings are approved as tiecoats for overcoating existing MIL-PRF-85285 paint systems:

NSN 8010-01-482-8620 Aeroglaze 9741 (light gray) U/I gallon

NSN 8010-01-483-4363 Aeroglaze 9743 (red) U/I gallon

NSN 8010-01-483-4365 Aeroglaze 9744 (dark gray) U/I gallon

6.12.6.1 <u>Characteristics</u>. This is a two-component, VOC, solvent-borne, lead and chromate free epoxy coating particularly formulated for its adhesion properties to other coatings. It is compliant with the NESHAP VOC requirements of 336 grams

31

30

#### TO 1-1-8

per liter (2.8 pounds per gallon). It is very resistant to chemicals and lubricants, but it has only fair weathering characteristics. Because it is an epoxy, this coating is difficult to remove with standard paint removers.

6.12.6.2 <u>Uses</u>. As a tiecoat over existing coating systems for the reapplication of MIL-PRF-85285 polyurethane topcoat on the exterior of painted aircraft and other aerospace equipment.

6.12.6.3 <u>Mixing</u>. Thoroughly agitate Component A, preferably with a mechanical shaker, prior to mixing Component B into Component A. If smaller quantities other than an entire kit are required, pour quantity needed into separate measuring or metering containers. Thoroughly mix components utilizing manufacturer's instructions. Best mixing results can be achieved with a mechanical shaker. Mix only materials from the same manufacturer, and do not mix more material than can be used in a 4 hour period. After mixing, allow the primer to stand per manufacturer's instructions for induction time requirements. This primer must be agitated continuously during spraying applications to prevent settlement of pigment and ensure uniformity of color. If in-line or in-head proportioning equipment is used to mix base and catalyst (curing agent) as the paint is being used, a 30 minute dwell time is not required before application.

#### 6.12.6.4 Thinning.



AIRCRAFT COATING THINNER, MIL-T-81772



PARACHLOROBENZOTRIFLUORIDE, PCBTF

WARNING

- MIL-T-81772 is flammable and moderately toxic to eyes, skin, and respiratory tract. Eye and skin protection required. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- PCBTF, is combustible and an irritant to eyes, skin, and respiratory tract. Eye and skin protection required. Disposable 8 mil nitrile gloves, splash goggles, Tyvek<sup>TM</sup>/cloth coveralls are the recommended PPE. Use in well ventilated areas. Failure to comply could result in injury to, or death of, personnel or long term health hazards.



In areas where air quality regulations restrict volatile emissions, do not add thinner MIL-T-81772 to the primer coating as that addition may raise the VOC content to greater than 336 grams per liter (2.8 pounds per gallon). Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

#### NOTE

PCBTF, is exempt as a VOC or HAP by the EPA and by 48 states and will not change compliance of high solids coatings to air quality regulations.

The viscosity of the unthinned tiecoat may range up to a maximum of 40 seconds in a No. 4 Ford Cup (56 seconds in a No. 2 Zahn Cup). Strain the tiecoat through clean cheesecloth, per CCC-C-440, Type I, Class 2 or a commercial paint strainer, and, when required, adjust the viscosity by thinning to a viscosity of 8 to 19 seconds in a No. 4 Ford Cup (17 to 23 seconds in a No. 2 Zahn Cup). Use thinner per MIL-T-81772 Type II or PCBTF, NSN 6850-01-566-2678 (1 gallon). Add MIL-T-81772, Type II thinner as required to achieve the viscosity range above. In areas where air quality regulations restrict volatile emissions, thin with PCBTF using up to 10 percent by volume as a recommended maximum for reduction of viscosity.

6.12.6.5 <u>Application</u>. Apply one coat of tiecoat to a dry film thickness of 0.6 to 1.8 mils. Allow the tiecoat to dry to tack-free. Tack-free is the point of time in drying at which the surface of the film will not fingerprint; yet the film is not dry and

30

hard throughout. If the tiecoat is allowed to hard dry, solvent wipe in accordance with <u>Chapter 3</u> of this TO to reactivate before topcoating. The film is hard dry when any mark left by the thumb is completely removed by lightly polishing the contacted area with a soft cloth. Since this epoxy tiecoat has a very high solids content, cross coating may not be required; and the spray gun must be kept moving to prevent excessive film buildup with subsequent reduction of adhesion. Apply a topcoat within 24 hours of primer application. After 24 hours, scuff sand the entire primed surface with CID A-A-58054, Type I, Grade A abrasive mat and solvent wipe the area in accordance with <u>Chapter 3</u> of this TO prior to topcoating. Discard any of this tiecoat mixed for longer than the manufacturer recommended pot life time. Higher or lower temperatures shorten or lengthen the pot life proportionally.

6.12.6.6 <u>Drying Time</u>. Drying time will vary by the manufacturer's instructions, temperature, and RH in the painting area. Lower temperatures and higher RH will increase dry times while higher temperatures and lower RH will decrease these drying times.

6.12.7 Coating. Polyurethane, Aircraft and Support Equipment, MIL-PRF-85285.



POLYURETHANE COATING, MIL-PRF-85285

15

6.12.7.1 <u>Coating Classifications</u>. MIL-PRF-85285 coatings are divided into the following types and classes:

6.12.7.1.1 <u>Type</u>. The types of coatings are as follows:

- Type I Aircraft application (420 grams per liter (3.5 pounds per gallon) maximum VOC content)
- Type II Support equipment application (336 grams per liter (2.8 pounds per gallon) maximum VOC content)
- Type IV Aircraft application with extended weatherability (420 grams per liter (3.5 pounds per gallon) maximum VOC content)
- 6.12.7.1.2 <u>Class</u>. The classes of coatings are as follows:
- Class H High solids formulation
- Class W Water-borne formulation

6.12.7.2 <u>Uses</u>. Type I and Type IV are intended for use on aerospace weapon systems and other applications. Type II is intended for use on ground support equipment and shall not be used on aircraft due to its very low flexibility.

# NOTE

The AFCPCO will be removing general authorization for the use of MIL-PRF-85285, Type I coating on USAF assets after 31 December 2021. Organizations shall utilize MIL-PRF-85285, Type IV in place of Type I to increase coating system longevity where technical orders and drawings allow. SPO's shall endeavor to update system peculiar technical orders and respective technical drawings to reflect this change.

6.12.7.3 <u>Advanced Performance Coating (APC)</u>. MIL-PRF-85285, Type IV, APC, also known as Extended Life Topcoat (ELT), is a chemically cured, two-component polyurethane topcoat formulated with fluorinated polyol resin to provide a protective coating with exterior durability and cleaning efficiencies superior to MIL-PRF-85285, Type I or Type II. APC, when used over MIL-PRF-23377 or MIL-PRF-85582 epoxy primer, provides fade resistance superior to conventional polyurethane topcoats. Although some degradation in fade resistance will occur if APC is applied over PR-1432 GV elastomeric polysulfide primer, color retention still exceeds MIL-PRF-85285 requirements.

# 6.12.7.4 <u>Mixing</u>.

# WARNING

- The catalyst portion of polyurethane topcoat contains a resin that may contain up to one percent Hexamethylene Diisocyanate (HDI). This material is a sensitizing agent and in low atmospheric concentrations is a strong respiratory and skin irritant. After the catalyst portion containing HDI is mixed with the polyester resin base component, the HDI reacts chemically with the resin base and the potential for generation of HDI is significantly reduced. Personnel mixing the isocyanate catalyst component with the polyester resin base component must avoid the vapors and skin contact of these materials. Mixing shall be done in exhaust ventilated booth or well ventilated area. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- Personnel shall wear plastic or rubber gloves, plastic apron, and a face shield. Requirement for respiratory protection during mixture and application procedures shall be determined by Bioenvironmental Engineering. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- Even after the polyurethane components have been mixed as noted below, painting with the polyurethane paint, Specification MIL-PRF-85285 still may result in a significant health hazard to the painter. Respiratory protection shall be specified by the local medical service based upon the process evaluation by Bioenvironmental Engineering. Also, it is important that all the precautions required for spray painting as outlined in AFMAN 91-203 be rigidly enforced. Personnel with histories of allergies or asthma shall be cleared through the base medical services before using any material containing diisocyanates. Failure to comply could result in injury to, or death of, personnel or long term health hazards.



Since the polyurethane is sensitive to moisture, ketones, and alcohols, use only clean, dry equipment for mixing and keep the mixed material in closed containers. Use adequate oil and water separators between the air supply and pressure pot to exclude water. Water reacts with the catalyst and liberates carbon dioxide, causing bubbles and craters in freshly applied polyurethane paint. In addition, blow down air lines at least every hour to remove water. Reaction of catalyst with water is evident by an accelerated rate of increase in viscosity. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

Thoroughly agitate the resin component (preferably with a mechanical shaker) and stir the catalyst with a wooden paddle in an exhaust ventilated booth or a well ventilated area and pour into separate metering containers. Mix three parts resin (component A) with one part catalyst (component B) by volume, unless otherwise specified by the manufacturer's instructions, and agitate thoroughly. Induction time (dwell time) or a waiting period is not required before applying the coating. Use only catalyst and resin from the same manufacturer and the same lot, and do not mix more material than will be used in a 4 hour period. It is preferable, however, that the amount of material mixed at one time be limited to that usable in 2 hours. This polyure-thane coating requires continuous agitation during spraying application to prevent settlement of pigment and ensure uniformity of color.

6.12.7.5 APC Mixing. Follow mixing instructions in Paragraph 6.12.7.4.

#### NOTE

Do not use catalyst (component B) from MIL-PRF-85285, Type I or Type II, coatings or catalyst from other APC colors.

30

6.12.7.6 Thinning.



PARACHLOROBENZOTRIFLUORIDE, PCBTF



PCBTF, is combustible and an irritant to eyes, skin, and respiratory tract. Eye and skin protection required. Disposable 8 mil nitrile gloves, splash goggles, Tyvek<sup>TM</sup>/cloth coveralls are the recommended PPE. Use in well ventilated areas. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

#### NOTE

PCBTF, is exempt as a VOC or HAP by the EPA and by 48 states and will not change compliance of high solids coatings to air quality regulations.

Cure accelerators are not authorized for use in polyurethane when painting aircraft as they change the cured properties and integrity of the coating. It can be thinned with PCBTF, NSN 6850-01-566-2678 (1 gallon) or the paint manufacturer's recommended EPA exempt product. Thin the coating using up to 10 percent by volume as a recommended maximum for reduction of viscosity. The expected viscosity as thinned will be in the range of 8 to 29 seconds in a No. 4 Ford Cup (17 to 23 seconds in a No. 2 Zahn Cup), but it can be up to 30 seconds in a No. 4 Ford Cup (39 seconds in a No. 2 Zahn Cup) before thinning.

6.12.7.7 <u>Application</u>. MIL-PRF-85285, Type I or Type II, is for application on properly prepared and primed substrates. Surfaces shall be prepared in accordance with <u>Chapter 2</u> of this TO and primed with MIL-PRF-23377, Type I, Class C1, C2 or N; MIL-PRF-85582, Type I, Class C1, C2 or N; or TT-P-2760, Type I, Class C or N. Steel surfaces shall be phosphate treated or coated with MIL-C-8514 and primed with the same primers listed above. Use Type II of these primers if low IR reflectance is required. This coating may be applied by airless, air assisted airless, HVLP, or electrostatic equipment after proper mixing of the base and catalyst. Apply the coating in one wet cross-coat or two coat with the second coat applied crosswise to the first after cure time of 4 hours or as recommended by the manufacturer. The dry film thickness shall be 1.7 to 2.3 mils each coat, per <u>Table 5-2</u>. Air assisted airless is preferable. For air assisted airless, use No. 617 tip for 12 inch fan and No. 517 tip for 10 inch fan. Atomize at 8 to 10 Pound-force per Square Inch (PSI) at the tip with the trigger pulled to conform to the HVLP requirement of the NESHAP.

6.12.7.7.1 <u>APC (MIL-PRF-85285, Type IV) Application</u>. Follow application procedures of <u>Paragraph 6.12.7.7</u>. In addition, maintain a wet edge during each application. After the first coat, the coating should be air dried 15 to 60 minutes at 70 to 80 °F (21 to 27 °C) before application of the second coat. It is normal for occurrences of mottling or "tiger striping". This condition typically disappears after coating has reached full cure. Although the visible gloss of camouflage APC will appear to be greater than conventional MIL-PRF-85285, APC still meets the requirements of the military specification.

6.12.7.7.2 <u>Maintenance Painting</u>. Maintenance painting (touch-up) of APC shall be accomplished using same procedures as described in <u>Chapter 5</u>. Although APC and MIL-PRF-85285, Type I and Type II, coating are compatible, it is recommended to use the same material as the previously applied coating system for maintenance painting. If both materials are used, a significant color mismatch will develop as the two coatings age due to APC's superior color retention.

6.12.8 <u>Curing of Complete Polyurethane System</u>. The preferred cure schedule for polyurethane coatings should be followed. Aircraft should not be operated until 72 hours has elapsed at a temperature of 75 °F (24 °C) or higher after the top-coat application is completed. If the temperature is less than 75 °F (24 °C) at any time during the cure cycle, it is preferable to wait a full 7 days before flying the aircraft.

• Cure time before handling, taping, masking, etc., is 6 hours minimum. Time may be reduced to 4 hours if temperature and humidity reach upper limit of 90 °F (32 °C) and 80 percent RH. Low temperature and low humidity of 60 °F (16 °C) and 30 percent RH retards cure rate to 12 hours minimum.

# TO 1-1-8

- Curing time before movement from controlled hangar environment at a temperature of 75 °F (24 °C) or higher is 6 hours minimum after application of last paint coat. Aircraft may then be moved to another location with a controlled environment of 75 °F (24 °C) or higher to continue its 72 hour cure.
- Curing time before decal application, 8 hours minimum.
- Curing time before engine run up, 30 hours minimum.
- Curing time before wet tape test, 48 hours minimum.
- Curing time before flight, 72 hours minimum.

6.12.8.1 <u>Maintenance Painting for Low Speed Aircraft</u>. This paragraph shall be utilized for maintenance painting of low speed aircraft with polyurethane paint systems. Low speed aircraft is defined as those with maximum speeds of less than 500 knots indicated air speed (KIAS). Maintenance painting of aircraft with maximum speeds of greater than 500 KIAS shall utilize Paragraph 6.12.8.2 of this TO.

- Maintenance painting is related to complete leading edges (All), complete control surfaces (All), major skin panels, and engine intakes. No size restrictions apply.
- Only qualified polyurethane systems, as defined by Paragraph 6.12.1 of this TO, shall be utilized for maintenance painting.
- Temperature and humidity requirements for maintenance painting of polyurethane systems are 75 °F (24 °C) and 50 percent RH and higher (not to exceed manufacturer's recommendations). Lower temperatures and RH will require longer cure times.
- Curing time before flight, 24 hours minimum if temperature/humidity requirements are met.

#### NOTE

Maintenance painting cure times shall not be utilized when accomplishing an aircraft full paint. Personnel shall utilize Paragraph 6.12.8 of this TO to determine procedures and cure times.

6.12.8.1.1 <u>Maintenance Painting for High Speed Aircraft</u>. This paragraph shall be utilized for maintenance painting of high speed aircraft with polyurethane paint systems. High speed aircraft is defined as those with maximum speeds of greater than 500 KIAS. Maintenance painting of aircraft with maximum speeds of less than 500 KIAS shall utilize Paragraph 6.12.8.1 of this TO.

- Curing time for maintenance painting related to complete leading edges (All), complete control surfaces (All), major skin panels 9 square feet (1296 square inches) and over, and engine intakes, 72 hours minimum.
- Curing time for maintenance painting related to skins panels less than 9 square feet (1296 square inches), fasteners, rivet heads, screw heads, and minor chipped and scratched areas less than 9 square feet (1296 square inches), 30 hours minimum.
- Only qualified polyurethane systems, as defined by Paragraph 6.12.1 of this TO, shall be utilized for maintenance painting.
- Temperature and humidity requirements for maintenance painting of polyurethane systems are 75 °F (24 °C) and 50 percent RH and higher (not to exceed manufacturer's recommendations). Lower temperatures and RH will require longer cure times.

6.12.9 Coating, Heat Resisting, TT-P-28.



PAINT, ALUMINUM, HEAT RESISTING (1200 °F), TT-P-28

6.12.9.1 <u>Characteristics</u>. This is heat resistant aluminum paint capable of withstanding temperatures of 1200 °F (649 °C). It is not intended to provide protection against corrosion as a primary function. In high temperature areas on air-craft where other paints will not survive, it will provide limited protection, primarily for steel components.

6.12.9.2 <u>Uses</u>. Can be used on superheated steam lines, boiler casings, boiler drums, superheated headers, other similar high temperature applications, and areas on aircraft where operating temperatures exceed 400 °F (204 °C).

6.12.9.3 Thinning. As recommended by the manufacturer's instructions.

6.12.9.4 <u>Mixing and Application</u>. Because the pigment settles out of suspension and cakes in the bottom of the can, this coating requires thorough mixing on a mechanical paint shaker before application. Apply by brush or by spraying after thinning as recommended by the manufacturer's instructions.

6.12.9.5 <u>Drying Time</u>. When air drying at 75 °F (24 °C), it is tack-free in 1 hour, full hard in 3 hours, and fully cured in 24 hours. Baked at 400 °F (204 °C), it is fully cured in 1 hour. Follow manufacturer's recommended instructions to determine actual cure times.

6.12.10 Enamel, Alkyd, Gloss, Low VOC Content, MPI No. 6/MPI No. 94.



PAINT GLOSS, SEMI-GLOSS ALKYD ENAMEL, MPI NO. 6, MPI NO. 94

6.12.10.1 <u>Characteristics</u>. This is a high-gloss, air-drying, alkyd enamel with excellent weather resistant properties. It is flexible and has satisfactory gloss and color retention. It is lead and chromate free and VOC compliant with a maximum of 420 gallons per liter (3.5 pounds per gallon).

6.12.10.2 <u>Uses</u>. It is used on properly pretreated and primed exterior and interior metal and wood surfaces. Its main use is for refinishing automobiles, construction equipment, machinery, gasoline pumps, trucks, buses, passenger and freight railway cars, metal drums (exterior), metal signs, metal railings and fences, and marine use (above water).

6.12.10.3 <u>Thinning</u>.



THINNER, ALKYD ENAMEL, A-A-3007

Use enamel thinner conforming to CID A-A-3007. Add one pint of thinner per gallon of enamel or the amount recommended by the manufacturer's instructions.

6.12.10.4 Application. Brush-apply as issued. Spray by HVLP methods after thinning.

6.12.10.5 <u>Drying Time</u>. Drying times will vary by the manufacturer's instructions, temperature, and RH in the painting area. Lower temperatures and higher RH will increase dry times while higher temperatures and lower RH will decrease dry times.

19

6-19

6.12.11 Coating, Sprayable, Strippable, Protective, MIL-PRF-6799.



COATING, SPRAYABLE, STRIPPABLE, PROTECTIVE, WATER EMULSION, MIL-PRF-6799

6.12.11.1 <u>Characteristics</u>. This is a water emulsion, protective, strippable, sprayable, multi-coat coating for application over metallic, painted, and plastic surfaces that comes in one type with several classes.

Type II, Class 1	Base coat (black)
Type II, Class 5	Topcoat (white or olive drab)
Type II, Class 6	Topcoat (white)
Type II, Class 7	Topcoat brushable

6.12.11.2 <u>Uses</u>. These materials are used to protect equipment and aircraft during shipment and storage.

6.12.11.2.1 <u>Type II, Class 1</u>. This is a black material intended for use as a strippable, protective coating for acrylic plastic bulk materials and assemblies containing acrylic plastics when the protected item is shipped fully covered or stored under cover; and as a base coat for Type II, Class 5 and Class 6 materials.

6.12.11.2.2 <u>Type II, Class 5</u>. This is a white or olive drab material intended to be used only as a topcoating for Type II, Class 1 material. This combination protective system serves as a sprayable, strippable, protective coating for application on metallic, painted, and plastic surfaces, such as entire aircraft, missiles, rockets, and transportation vehicles, during outdoor storage and overseas deck-loaded shipments. This material should be applied to a dry film thickness of 3±1 mils.

6.12.11.2.3 <u>Type II, Class 6</u>. This is a white material intended to be used only as a topcoating for Type II, Class 1 material. This combination protective system serves as a sprayable, strippable, protective coating for applications on metallic, painted, and plastic surfaces, such as entire aircraft, missiles, rockets, and transportation vehicles, during outdoor storage and overseas deck-loaded shipments. This material should be applied to a dry film thickness of 6±1 mils.

6.12.11.2.4 <u>Type II, Class 7</u>. This material is intended as a brushable coating for patching or repairing damaged Class 5 or Class 6 coatings.

6.12.11.3 <u>Thinning</u>. Thin as required per the manufacturer's instructions.

6.12.11.4 <u>Application</u>. Apply by HVLP spray methods. Class 5 material may be applied at 6 °F (-14 °C), and  $50\pm10$  percent RH. Class 6 material may be applied within a temperature range of 50 to 115 °F (10 to 46 °C), and  $50\pm10$  percent RH, but the pot life and cure time will be much longer at the lower temperature and much shorter at the higher temperature as compared to those at 75 °F (24 °C).

6.12.11.5 <u>Drying Time</u>. Drying times will vary by the manufacturer's instructions, temperature, and RH in the painting area. Lower temperatures and higher RH will increase dry times while higher temperatures and lower RH will decrease dry times.

6.12.12 Resin Coating, Unpigmented, for Engine Components and Metal Parts, MIL-PRF-3043.



RESIN COATING, MIL-PRF-3043

5

7

6.12.12.1 <u>Characteristics</u>. This is a permanent thermosetting resin coating free from drying and non-drying oils and cellulose. The resin coating is baked on and provides a transparent green film on the surface.

6.12.12.2 <u>Uses</u>. The coating is used as a permanent corrosion preventative, oil resistant coating for metallic non-bearing surfaces of engine parts, airframe components, magnesium parts, gun mounts, gear housings, and other components. The ma-

terial is specifically used on the interior surfaces of droppable steel tanks and tubing of methyl bromide or trifluorobromomethane fire extinguishing systems.

6.12.12.3 <u>Thinning</u>. As recommended by the manufacturer's instructions.

6.12.12.4 Application. Apply by dip or spray at room temperature.

6.12.12.5 <u>Drying Time</u>. The coating air dries to handle in 30 minutes at room temperature. Fully cure by baking in oil or by oven baking. Follow manufacturer's recommended instructions for detailed information on dry times.

6.12.12.5.1 <u>Baking in Oil</u>.



LUBRICATING OIL, AIRCRAFT TURBINE ENGINE, SYNTHETIC BASE, MIL-PRF-7808

14

6

Air dry for 16 to 24 hours and immerse in MIL-PRF-7808 hot lubricating oil for 15 minutes.

6.12.12.5.2 <u>Oven Baking</u>. Air dry for 1 hour followed by 30 minutes baking at 325 °F (163 °C). Follow manufacturer's recommended instructions for detailed information on dry times.

6.12.13 Coating Kit, Epoxy, for Interior of Steel Fuel Tanks, MIL-PRF-23236.



COATING KIT, EPOXY, FOR INTERIOR OF STEEL FUEL TANKS, MIL-PRF-23236

6.12.13.1 <u>Characteristics</u>. This is a kit containing a primer and a topcoat, each of which are two-component kits of epoxy coatings. This coating is for protecting interior surfaces of steel tanks used for transportation and storage of fuels. It is lead and chromate free and has a maximum 336 grams per liter (2.8 pounds per gallon) VOC content.

6.12.13.2 <u>Uses</u>. The coating is intended for protection of sand blasted interior surfaces of mobile and stationary mild steel tanks and auxiliary handling equipment used for the storage and transportation of military fuels and oils.

6.12.13.3 <u>Mixing</u>. Thoroughly mix component A, preferably using mechanical agitation, and then add one part component B to four parts by volume of component A.

6.12.13.4 <u>Thinning</u>. Thin as recommended by the manufacturer's instructions.

6.12.13.5 <u>Application</u>. Apply by HVLP spraying methods (hot or cold method) or as recommended by the manufacturer's instructions within the 6 hours at 75 °F (24 °C) pot life of the material.

6.12.13.6 <u>Drying Time</u>. Set-to-touch in 5 hours and dry hard in 18 hours. Follow manufacturer's recommended instructions for detailed information on dry times.

# TO 1-1-8

6.12.14 <u>Coating, Corrosion Preventive, for Aircraft Integral Fuel Tanks for Use to 250 °F (121 °C), SAE AMS-C-27725</u>.



COATING, CORROSION PREVENTIVE, POLYURETHANE, FOR AIRCRAFT INTEGRAL FUEL TANKS (FOR USE TO 250 °F (121 °C)), SAE AMS-C-27725 23

6.12.14.1 <u>Characteristics</u>. This is a polyurethane material available in two types each with two classes. It is fuel resistant and is used to provide protection of aircraft fuel tanks against corrosion from contaminants and water in fuels.

- Type I A one-part formulation polyurethane coating
- Type II A two-part formulation polyurethane coating
- Class A General use (does not comply to most air pollution regulations, may be used only where not prohibited)
- Class B Limited use (for areas requiring regulation of air pollution caused by emissions of certain solvents that produce smog)

6.12.14.2 <u>Uses</u>. This coating is intended for the protection of aircraft integral fuel tanks against corrosion in a service temperature range of -65 to +250  $^{\circ}$ F (-54 to 121  $^{\circ}$ C).

# 6.12.14.3 <u>Mixing</u>.

# WARNING

- SAE AMS-C-27725 is flammable and toxic to eyes, skin, and respiratory tract. Eye and skin protection required. Consult Bioenvironmental Engineering to determine proper respiratory and ventilation requirements. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- The coating material contains harmful solvents and free isocyanates. Inhalation of vapor may cause irritation of the nose, throat, and lungs, and may cause sensitization. Vapors or liquid contact with the eyes or skin may cause severe irritation. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- Safety and health procedures are mandatory and no deviation will be permitted except by written approval of the Office of Safety and/or Bioenvironmental Engineer. It is the responsibility of the immediate supervisor to ensure that all safety and health procedures are followed without deviation. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- Personnel applying the coating by spray or brush or those required to reenter coated fuel tanks before complete cure shall be protected by wearing full-face air supplied respirator with air flowing before tank entry until exiting the tank, white cotton coveralls, cotton booties or cotton socks, rubber chemical resistant gloves or surgical type gloves, and cotton head covering. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- All clothing shall be washed after each use. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- Place all material used to mop up spilled coating or runs in coating into water immediately. A small container of water shall be provided in the immediate area. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- Blowers which are grounded and bonded to the aircraft shall be circulating air in the fuel cells/tanks before and during entry of personnel to perform any operation such as cleaning. Air shall flow so that vapor will be carried away from the operator. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- SAE AMS-C-27725 has a flash point of 266 °F (130 °C) open cup, therefore, can present a fire hazard when heated or atomized. Some materials used in this operation have flash points as low as 20 °F (-7 °C) and will ignite if exposed to a flame or spark. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- If SAE AMS-C-27725 is spilled in the repair area, evacuate the area and call the Fire Department. Neutralize with strong ammonia solution, then flush with water. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

#### NOTE

Do not mix more material than can be used in a 5 hour period.

Mix coating components within an approved ventilated paint booth. If a booth is not available, personnel shall wear an airsupplied respirator and mixing shall be accomplished so that vapors are exhausted to an area as approved by the Bioenvironmental Engineer. Mix and blend the two components of the coating thoroughly for a minimum of 5 minutes. Do not mix in contaminated containers. Stir the material with a metal spatula. Keep empty containers, and those containing mixed and unmixed coating, tightly closed when not in use.



SOLVENT COMPOUND, CID A-A-59281



The dry film thickness of this coating shall be between 0.8 and 1.2 mils, per <u>Table 5-2</u>. Runs and sags shall be mopped immediately to prevent thick spots. Thicknesses over 1.2 mils result in cracking, flaking, and peeling of coating while those less than 0.8 mils do not provide adequate protection. Measure the wet film thickness with a wet film gauge and control the wet film per the manufacturer's requirements. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

After the tank surface is thoroughly dry and immediately prior to application of the coating, gently clean the area to be coated with lint-free cleaning cloth wet with CID A-A-59281 cleaner and wipe dry. Do not allow the cleaner to air dry. Do not abrade the chemical conversion coating film. Clean small areas starting from the top and farthest from the access door and work down and out using clean lint-free cloths/pads. The exception is for large repair areas where there must be alternately cleaning, sealing, and coating of an area and then repeating in the next area while working toward the access door. Use caution not to contaminate a previously cleaned area and reclean immediately if it occurs. Spray all accessible areas when practical; areas that cannot be sprayed shall be coated by brush application. Access doors and removable parts shall be spray coated in a spray booth and cured in an area with circulating fresh air. Personnel entering the curing area shall follow all precautions stated in the "warning" When spraying, apply a light double pass to cover the surface. Take care to prevent runs and puddles; and if they occur, remove them immediately.

**6.12.14.4.1** Prior to starting application of SAE AMS-C-27725 and at each change of painters, spray or brush a small strip of aluminum prepared in the same manner as described above. Properly adjust the flow of material from the spray nozzle to provide the proper coating thickness of 0.8 to 1.2 mils dry film.

#### 6.12.14.4.2 Spray Application.



AIRCRAFT COATING THINNER, MIL-T-81772

Use a HVLP spray gun. Use a pressure feed tank with 5 PSI and an atomizing air pressure of 35 PSI. Pressure tanks shall be equipped with an agitator to provide proper pigment suspension. Immediately after use, the equipment shall be thoroughly cleaned with MIL-T-81772, Type II.

6.12.14.4.3 <u>Brush Coating</u>. A fine camel hair or soft hog bristle brush shall be used when applying this coating by brush. The material shall be stirred with a metal spatula every 3 to 5 minutes.

#### 6.12.14.5 <u>Drying Time</u>.



AIRCRAFT COATING THINNER, MIL-T-81772

Curing SAE AMS-C-27725 coating will be tack-free in 4 hours under normal conditions (75 °F (24 °C) and 50 percent humidity). Cure may be accelerated after a minimum of 4 hours cure at 75 °F (24 °C) by adding heat up to 120 °F (49 °C). The state of cure can be tested by rubbing a test spot with a gauze pad wet with MIL-T-81772, Type II thinner. If bare metal is exposed after 50 double strokes of the pad at moderate pressure, the coating is not completely cured.

17

17

4

6.12.15 Coating Compound, Nonslip (for Walkways), CID A-A-59166.



COATING COMPOUND, NON-SLIP, CID A-A-59166

6.12.15.1 <u>Characteristics</u>. A nonslip compound formulated in a hand brushable consistency that is fuel and fluid resistant. These coatings are available in several colors. This material is compliant with the NESHAP VOC requirements of 420 grams per liter (3.5 pounds per gallon).

- Type I This is a smooth coating without grit formulated primarily for brush application.
- Type II This is a rough material formulated primarily for brush application containing grit as an integral part of the coating.

6.12.15.2 <u>Uses</u>. A nonslip is used on aircraft exterior walkway surfaces to protect personnel from falling while walking on aircraft surfaces. May also be used on vehicles, maintenance ramps, steps, ladders, and similar areas.

- Type I Used along leading edges of aircraft that fly less than 250 mph and on other adjacent surfaces of aircraft where the roughness of the Type II coating is undesirable due to aerodynamic considerations.
- Type II Material used along trailing edges and adjacent surfaces in cases where maximum nonslip qualities are essential and aerodynamics are not affected.

6.12.15.3 <u>Thinning</u>. If thinning is necessary, use the solvent recommended by the manufacturer's instructions. Adjust the viscosity for spray application by thinning 21 to 27 seconds in a No. 2 Zahn Cup (16 to 21 seconds in a No. 4 Ford Cup).

6.12.15.4 <u>Mixing and Application</u>. Walkway coatings are applied to primed surfaces prior to application of final topcoat of aircraft coating systems. The topcoat applied over walkway coating shall be a single mist coat to reduce distinctive difference in color while not causing loss of nonslip features. Only the Type II (rough) coating shall be used under the topcoat of aircraft coating system. Type II walkway coating need not be topcoated on interior walkways, ramps, steps, and doorways in high traffic areas. Before applying the nonslip coating, wipe primed surface with a clean lint-free cloth with solvent per <u>Table 3-2</u>, if necessary. Thoroughly mix the material, preferably with a mechanical shaker. The coating will normally have the proper viscosity for brush application. Application by brushing is recommended as the material is primarily formulated for this. Apply quickly and avoid brushing previously coated areas that are wet. Allow to dry at least 30 minutes but not more than 45 minutes between coats. Apply by spraying only when large areas are involved. Apply the coating (Type I and Type II) to a dry film thickness of 10 to 12 mils on aircraft exterior surfaces which weights 15 to 20 ounces per square yard for a Type I coating, and 20 to 25 ounces per square yard for a Type II coating. A 30 to 40 mil thick coating is recommended for non-aeronautical interior surfaces.

6.12.15.5 <u>Drying Time</u>. Type I and Type II coatings dry tack-free in 15 minutes, for re-coating in 30 minutes, through in 6 hours, and to full hardness in 24 hours. Follow manufacturer's recommended instructions for detailed information on dry times.

6.12.16 <u>Coating, Polyurethane, Rain Erosion Resistant for Exterior Aircraft and Missile Parts, SAE AMS-C-83231</u>.



COATING, POLYURETHANE, RAIN EROSION RESISTANT, FOR EXTERIOR AIRCRAFT AND MISSILE PLAS-TIC PARTS, SAE AMS-C-83231 26

6.12.16.1 <u>Characteristics</u>. This material is available in two types each with two classes. Type I is an electrically nonconductive rain erosion resistant coating, and Type II is an antistatic rain erosion resistant coating. Class A material is not dependent on moisture or high RH for curing and Class B is dependent on them. Primer and topcoat components are furnished together as a kit. Specific aircraft directives specify the area to be coated and the materials to be used. 6.12.16.2 <u>Uses</u>. Classes A and B, Types I and II coatings are intended for protection of exterior laminated plastic parts of high-speed aircraft and missiles from rain erosion while in flight. Classes A and B, Type II coatings also discharge and dissipate static electricity to prevent radio and radar interference.

6.12.16.3 <u>Thinning</u>. Thin as recommended by manufacturer's instructions and/or TO 1-1-24.

6.12.16.4 Application. Apply as recommended by the manufacturer's instructions and/or TO 1-1-24.

6.12.16.5 <u>Drying Times</u>. Drying times are as recommended by the manufacturer's instructions and/or TO 1-1-24.

6.12.17 <u>Coating System, Polyurethane, Non-Yellowing White, Rain Erosion Resistant, Thermally Reflective, SAE AMS-C-83445</u>.



COATING SYSTEM, POLYURETHANE, NON-YELLOWING WHITE, RAIN EROSION RESISTANT, THERMALLY REFLECTIVE, SAE AMS-C-83445 27

6.12.17.1 <u>Characteristics</u>. This material is one type of thermally reflective, non-yellowing white, rain erosion resistant polyurethane coating for glass fabric, reinforced plastic laminated, and other plastic parts used as exterior surfaces of aircraft and missiles.

6.12.17.2 <u>Uses</u>. This coating is intended to protect exterior laminated plastic parts of high speed aircraft and missiles from rain erosion and thermal energy while in flight. This coating cannot be used on radomes and other plastic parts that have a requirement for protection against static electrical charges, because it is not electrically conductive.

6.12.17.3 <u>Thinning</u>. Thin as recommended by manufacturer's instructions and/or TO 1-1-24.

6.12.17.4 Application. Apply as recommended by the manufacturer's instructions and/or TO 1-1-24.

6.12.17.5 Drying Times. Drying times are as recommended by the manufacturer's instructions and/or TO 1-1-24.

6.12.18 Primer Coating, Magnesium-Rich, Non-Chromated.



PRIMER COATING, MAGNESIUM RICH, NON-CHROMATED, AERODUR 2100 MGRP

33

6.12.18.1 <u>Characteristics</u>. Magnesium-Rich (Mg-R) primer is a three component, low VOC, solvent-borne, lead free, non-chromated, corrosion inhibiting magnesium rich epoxy-modified polyamide primer formulated using unique chrome free inhibitors to meet Environmental, Safety, and Occupational Health regulations. It is compliant with the NESHAP VOC requirements of 336 grams per liter (2.8 pounds per gallon). It is very resistant to chemicals, lubricants, and corrosive atmospheres.

6.12.18.2 <u>Uses</u>. A non-chromated primer for MIL-PRF-85285 polyurethane topcoat for the exterior of aircraft, components, and other aerospace equipment, and as a standalone primer on interior surfaces of aircraft and components.

# 6.12.18.3 <u>Mixing</u>.



- The base material (Component A) is flammable and moderately toxic to eyes, skin. Eye and skin protection, along with engineering controls, shall be utilized in accordance with locally developed BEE guidelines. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- The catalyst material (Component B) and the reducer material (Component C) are both highly flammable, is and are seriously toxic to eyes/skin and is carcinogenic. Eye, skin, face, and respiratory protection, along with engineering controls, shall be utilized in accordance with locally developed BEE guidelines. Use in well ventilated areas. Failure to comply could result in injury to, or death of, personnel or long term health hazards.



This high solids epoxy primer is an environmentally compliant product. Use of TR-7005 in place of TR-114 will alter VOC compliance. Ensure compliance with local VOC regulations before proceeding with use of TR-7005 reducer.

Thoroughly agitate the base material (Component A), preferably with a mechanical shaker for no longer than 5 minutes, prior to mixing and, if required, pour into separate measuring or metering containers (base component should be uniform and free of lumps, skins or hard setting). Stir the catalyst material (Component B) separately with a compatible paddle until homogenous. Utilizing manufacturer's instructions, slowly pour the catalyst (Component B) into the base (Component A) and mix the material thoroughly. Continue mixing while slowly adding in the reducer material (Component C) in accordance with manufacturer's instructions. If not mixing the complete kit, mix by weight in accordance with manufacturer's instructions. Do not mix more material than can be used in 3 hours.

6.12.18.4 <u>Thinning</u>. Package viscosity is appropriate for application when following manufacturer's mixing instructions. Thinning shall not be accomplished. The viscosity of the mixed primer may range from 18 seconds to a maximum of 22 seconds in a No. 4 Ford Cup (33-59 seconds in ISO Cup No. 4, 28-30 seconds in No. 2 Zahn Cup).

6.12.18.5 <u>Application</u>. Apply in one even coat to achieve a dry film thickness of 1.0 to 1.4 mils. Follow manufacturer recommendations for dry to tack-free times. Tack-free is the point of time in drying at which the surface of the film, will not fingerprint; yet the film is not dry and hard throughout. The film is considered hard dry when any mark left by the thumb is completely removed by lightly polishing the contacted area with a soft cloth. Since this epoxy primer has a very high solids content, cross coating may not be required; and the spray gun must be kept moving to prevent excessive film buildup with subsequent reduction of adhesion. If primer is allowed to hard-dry, solvent wipe in accordance with <u>Chapter 3</u> of this TO to reactivate prior to topcoating. Apply topcoat within 24 hours of primer application, while not going beyond 48 hours, the surface shall be lightly abraded with CID A-A-58054, Type I, Grade A abrasive mat, solvent wiped, and tack ragged in accordance with this TO. Overcoat time shall not exceed 48 hours. If exceeded, removal and reapplication of the primer shall be accomplished in accordance with manufacturer's instructions.

6.12.18.6 <u>Drying Time</u>. Drying times will vary by the manufacturer, temperature, and RH in the painting area. Lower temperatures and higher RH will increase drying times while higher temperatures and lower RH will decrease these drying times. Refer to manufacturer's instructions and/or <u>Chapter 3</u> of this TO for drying etiquette.

6.12.19 Rare Earth Compound Coating (RECC) System, Non-Chromated.

6.12.19.1 Deoxidizer, Non-Chromated, RECC 1015.



DEOXIDIZER, NON-CHROMATED, RECC 1015

6.12.19.1.1 <u>Characteristics</u>. The RECC deoxidizer is a non-chromated pretreatment for the application of RECC specific non-chrome conversion coating (RECC 3021).

6.12.19.1.2 <u>Uses</u>. RECC 1015 is a non-chromated, single package, aqueous solution, spray pretreatment coating that deoxidizes aluminum surfaces.

6.12.19.1.3 <u>Mixing</u>. Stir to ensure solution is homogenous prior to application.

6.12.19.1.4 Application.



RECC 1015 deoxidizer isn't considered hazardous by OSHA hazard communication standard (29 CFR 1910.1200). However, it shall be treated as mildly toxic to eyes/skin and respiratory system. Eye, skin, face, and respiratory protection, along with engineering controls, shall be utilized in accordance with locally developed BEE guidelines. Application should always be in well ventilated area. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

Clean surface by solvent wipe and perform a water break test in accordance with <u>Chapter 3</u> of this TO. Apply RECC 1015 in accordance with manufacturer's instructions until the surface is saturated. Allow surface to dry in accordance with manufacturer's instructions, ensuring to dab any areas where solution is puddling with a lint-fee cotton disposable rag, or blow dry with clean, dry compressed air. Rinse surface with potable water in accordance with manufacturer's instructions.

6.12.19.2 Conversion Coating, Non-Chromated, RECC 3021.



CONVERSION COATING, NON-CHROMATED, RECC 3021

6.12.19.2.1 <u>Characteristics</u>. The RECC conversion coating is a non-chromated for aluminum surfaces for the application of primer. It provides corrosion protection and properties for better adhesion for primer application.

28

6.12.19.2.2 <u>Uses</u>. RECC 3021 is a non-chromated, single package, aqueous solution, spray conversion coating for aluminum surfaces. It is corrosion inhibiting and provides a surface for paint adhesion.

6.12.19.2.3 Mixing. Stir to ensure solution is homogenous prior to application.

6.12.19.2.4 Application.

# WARNING

RECC 3021 conversion coating isn't considered hazardous by OSHA hazard communication standard (29 CFR 1910.1200). However, it shall be treated as mildly toxic to eyes/skin and respiratory system. Eye, skin, face, and respiratory protection, along with engineering controls, shall be utilized in accordance with locally developed BEE guidelines. Application should always being in well ventilated area with sufficient airflow. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

# NOTE

Between two and four applications of RECC 3021 conversion coating is typical to maintain surface saturation timeframe required by manufacturer's instructions.

Ensure surface has been treated with RECC 1015 deoxidizer in accordance with manufacturer's instructions, and is saturated with water before proceeding. Apply RECC 3021 conversion coating to surface to be treated until saturated. Keep surface saturated for allotted time in accordance with manufacturer's instructions. Allow surface to air dry in accordance with manufacturer's instructions.

29

6.12.19.3 Primer Coating, Epoxy Polyamide, Non-Chromated, 02GN093.



EPOXY PRIMER, NON-CHROMATED, 02GN093

6.12.19.3.1 <u>Characteristics</u>. The RECC system specific primer is a two component, low VOC, lead free, high solids, corrosion inhibiting, chemical/solvent resistant epoxy primer formulated for use on exteriors. It is compliant with the NE-SHAP VOC requirements of 336 grams per liter (2.8 pounds per gallon). It is very resistant to chemicals, lubricants, and weathering but only has fair corrosive atmosphere characteristics.

6.12.19.3.2 <u>Uses</u>. A primer to be utilized in conjunction with RECC 1015 deoxidizer and RECC 3021 conversion coating, and for MIL-PRF-85285 polyurethane topcoat for the exterior of aircraft, components, and other aerospace equipment

6.12.19.3.3 Mixing.

WARNING

The base material (Component A) and the catalyst material (Component B) vapors are highly flammable, are highly toxic to eyes/skin/respiratory system, and are carcinogenic. Keep away from heat, hot surfaces, sparks, open lames, ignition sources. Serious eye damage and skin irritation is possible. The base material (Component A) may cause an allergic skin reaction, cancer, damage fertility, damage unborn child and cause respiratory irritation. Eye, skin, face, and respiratory protection, along with engineering controls, shall be utilized in accordance with locally developed BEE guidelines. Restrict use to well ventilated areas. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

#### NOTE

Both base material (Component A) and the catalyst (Component B) must be allowed to acclimate to the ambient temperature for 24 hours prior to mixing. Ambient temperatures must be between 55° to 95 °F (13° to 35 °C) with the minimum temperature of the paint components being 55 °F (13 °C) prior to mixing.

Thoroughly agitate the base material (Component A), preferably with a mechanical shaker for no longer than 5 minutes, prior to mixing and, if required, pour into separate measuring or metering containers (base component should be uniform and free of lumps, skins or hard setting). Stir the catalyst material (Component B) separately with a compatible paddle until homogenous. Utilizing manufacturer's instructions, slowly pour the catalyst (Component B) into the base (Component A) and mix the material thoroughly, being careful not to mix materials for longer than 10 minutes. Do not mix more material than can be used in 3 hours.

6.12.19.3.4 <u>Thinning</u>. Package viscosity is appropriate for application when following manufacturer's mixing instructions. Thinning shall not be accomplished unless directed by the manufacturer's technical representative and/or cognizant engineering authority.

6.12.19.3.5 Application.

#### NOTE

During coating system application, temperatures must remain within 59 to 86 °F (15 to 30 °C), and the RH is between 20-90 percent.

Apply one coat of primer to a dry film thickness of 0.8 and 0.9 mils. Follow manufacturer's recommendations for dry to tack-free times. Tack-free is the point of time in drying at which the surface of the film, will not fingerprint; yet the film is not dry and hard throughout. If the primer is allowed to hard dry, solvent wipe in accordance with <u>Chapter 3</u> of this TO to reactivate before topcoating. The film is considered hard dry when any mark left by the thumb is completely removed by lightly polishing the contacted area with a soft cloth. Apply a topcoat within 24 hours of primer application. After 24 hours, scuff sand the entire primed surface with CID A-A-58054, Type I, Grade A abrasive mat and solvent wipe the area in accor-

# TO 1-1-8

dance with <u>Chapter 3</u> prior to topcoating. Discard any of this primer mixed for longer than the manufacturer recommended pot life. Higher or lower temperatures shorten or lengthen the pot life proportionally.

6.12.19.3.6 <u>Drying Time</u>. Drying times will vary by the manufacturer, temperature, and RH in the painting area. Lower temperatures and higher RH will increase drying times while higher temperatures and lower RH will decrease these drying times. Please refer to previous sections on in this chapter for drying etiquette. Not required for standard dry time. Induction time of 30 minutes is recommended for applications requiring faster dry times, such as touch up or cold weather.

#### 6.12.20 Primer Coating, Anodic Electrodeposition for Aircraft Applications, SAE AMS-3144.

6.12.20.1 <u>Characteristics</u>. Electrodeposition Coating (E-coat) primer is an environmentally friendly coating technology. The combination of a non-chromated pretreatment with this non-chromated electrocoat primer offers an environmentally friendly alternative to conventional hexavalent chromate-based spray application methods while maintaining corrosion prevention and adhesion performance.

#### NOTE

E-coat primer shall not be utilized unless approved by the cognizant engineering authority for the system, or item, on which the primer is to be applied.

6.12.20.2 Uses. E-coat is a compatible primer for MIL-PRF-85285 polyurethane topcoat for the exterior of aircraft, components, and other aerospace equipment, and as a standalone primer on interior surfaces of aircraft and components. A specification was issued by the AMS G8 Organic Coatings Committee in November 2012 as AMS3144 Primer, Anodic Electrodeposition for Aircraft Applications. E-Coat has met the requirements of Airworthiness Bulletin 1015; Airworthiness Circular (AC) 19-02 was issued in June 2019. 19-02 details what substrates, pretreatments and areas of use are approved anodic E-coat technology. For any additional information on E-Coat requirements or process, please contact the AFCPCO at afcorr@us.af.mil.

#### 6.12.21 Coating Systems, Advanced Performance, For Aerospace Applications, MIL-PRF-32239.

6.12.21.1 <u>Characteristics</u>. MIL-PRF-32239 coating systems are extremely versatile, with multiple system options to address the intended application. Depending on the system chosen, properties vary from superior corrosion resistance to advanced weathering resistance, excellent hydrophobicity, cleanability, flexibility, temperature resistance and quick curing times will be exhibited. MIL-PRF-32239 coating systems consist of a pretreatment, a primer, and a topcoat intrinsic to the selected system. MIL-PRF-32239 systems can be divided into the following types, compositions, classes and grades:

Type 1	Skydrol LD-4 resistance.
Type 2	No Skydrol LD-4 resistance.
Composition 1	Coating system containing chromium compounds.
Composition 2	Coating systems containing magnesium particles.
Composition 3	Coating system containing lithium based compounds.
Composition 4	Coating systems containing magnesium oxide compounds.
Composition 5	Coating systems containing rare earth compounds.
Class 1	Standard flexibility coating system.
Class 2	High flexibility coating systems.
Class 3	Low flexibility.
Grade 1	Standard pigmented coating systems.
Grade 2	Low-Infrared (IR) pigmented coating systems.

# 6.12.21.2 Uses.



MIL-PRF-32239 coating systems shall not be utilized unless authorization is given by the cognizant engineering authority for the system, or item, on which it is to be utilized.

As coating systems qualified for use on the exterior of aircraft, components, and other aerospace equipment.

#### 6.12.22 Leading Edge Polyurethane Rain Erosion Resistant Tape.

6.12.22.1 <u>Description and Use</u>. This tape is used to provide rain erosion protection for the wing, vertical and horizontal stabilizer, and any other leading edges aft of the engine intakes. Material and tools to be used are listed below in <u>Table 6-1</u>.

#### 6.12.22.2 Installation.



- The temperature during application shall be at least 60 °F (16 °C). This may be accomplished with a ground heater for small areas. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- Materials to make repairs or remove the tape must be available in case of errors in application. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- Use only the tapes specified in <u>Table 6-1</u> for application on aircraft exterior surfaces. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- Adhesion promoters in <u>Table 6-1</u> cannot be substituted. If not available, do not apply tape. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- Pre-scored liner material is very critical for proper installation. Without the slit liner, application is very difficult. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- Do not apply tape to bare metal. Surfaces must at least be primed before film is applied. Allow primer to cure for 24 hours minimum before tape application. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.
- a. Feather, sand, prime, and paint the leading edge as required. Feathering chipped/peeled areas is vital for a quality installation. Recommend material be applied to aircraft in conjunction with touch-up painting.
- b. Using the template fabricated per <u>Table 6-1</u>, align its centerline with the centerline of the leading edge. Mark the location of the top and bottom of the tape every 2 feet of the length on the leading edge component receiving tape.

#### NOTE

Varying widths of tape can be used depending of the amount on leading edge to be covered.

c. Mask using above marks as guides.



Final sanding with anything coarser than CID A-A-58054 Type I, Grade A abrasive (very fine 240-320 grit) will adversely affect bond of tape. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

d. Abrade the masked off area to a smooth surface using CID A-A-58054, Type I, Grade B followed by Grade A abrasive mat.



ISOPROPYL ALCOHOL, TT-I-735



Do not use rented or polyester rags to apply TT-1-735 isopropyl alcohol as this may cause contamination of the surface. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

e. Remove residue with cheesecloth moistened with TT-I-735 isopropyl alcohol.



SEALANT, CORROSION INHIBITIVE, MIL-PRF-81733

f. Fill all seams and fastener heads with MIL-PRF-81733, Type II, Class 1, Grade A sealant to eliminate any possible air pockets behind the film, trowel smooth/flush with razor blade or other suitable tool, and allow to cure before proceeding. AMS 3265 sealant can be used as an alternative to MIL-PRF-81733 when approved by the System Program Office (SPO) and when environmental restrictions prohibit the use of chromated sealants.



# ADHESION PROMOTER

- g. Use CCC-C-440, Type I, Class 2 cheesecloth to apply thin, but thorough coat of adhesion promoter per <u>Table 6-1</u> to all application areas, including sealant, in the masked off area used to smooth seams and fastener heads.
- h. Remove masking tape.
- i. Let adhesion promoter dry for 20 minutes.
- j. Cut a length of tape to fit leading edge plus 4 inches. Remove about 3 inches of the edge.
- k. With about 2 inches of the excess against the inboard edge of the component, align the film with the top template line and rub down with a tightly folded piece of CCC-C-440, Type I, Class 2 cheesecloth.

# NOTE

Ensure air bubbles do not build under film.

- 1. Remove another 3 inches of the top liner section and rub film to surface.
- m. Repeat process above removing the next liner section and continue until film is completely bonded.
- n. Inspect work for air bubbles. Pierce bubbles with a needle or pin, and press air out before removing tool.
- o. Trim excess at the beginning and end of chip strip where adhesion promoter was not applied.

r

Material	Source	Use
Tape width and color to match erosion area to be covered	3M Industrial Specialties Division	Leading edge rain erosion protection
	CAGE Code No. 52152	
Polyurethane Tape, Clear, 4 inches	AF Supply	Leading edge rain erosion protection
(NSN 9330-01-288-4346)		
Adhesion Promoter	3M Company	Promote tape adhesion
PN 86A (NSN 8040-01-448-4791),		
Wipes 7 inches x 7 inches or		
(NSN 8040-01-450-9187), Pint		
PN 70 0701-8275-6		
(NSN 6850-01-326-1607), Pint		
Edge Sealer	3M Company AF Supply	Seal tape edges and fill fastener head and other voids
PN Epoweld 8173A (NSN 8040-00-092-2816)		
PN Scotchweld DP-190 (NSN 8040-01-334- 8284)		
Tape, Masking, SAE-AMS-T-21595, Type I	AF Supply	Masking of application area
Abrasive Mat CID A-A-58054, Type I, Class A or B	AF Supply	Smoothing and scuff sanding of area as surface preparation
Cheesecloth, CCC-C-440, Type I, Class 2	AF Supply	Cleaning of area and smoothing of leading edge tape
Exacto Knife or Razor Blade	Commercial	Trimming tape
Isopropyl Alcohol, TT-I-735	AF Supply	Cleaning
Pin or 22 gauge or finer Syringe Needle	AF Supply	Air removal
Scraper, Non-Metallic	Local Manufacture	Tape removal
Template	Local manufacture from heavy paper other suitable material (width: same as tape. Length: same as leading edge. Mark centerline for alignment with leading edge centerline.)	Mark area which leading edge tape will be applied.
Paper Wipers	3M Company	Cleaning
Adhesive Remover	3M Company	Adhesive removal
PN 8098 (NSN 8040-01-318-3668),		
PN 35975 (NSN 8040-01-545-7323), Pint		

Table 6-1.	Leading	Edge Tape	Materials/Tools
	Leading	Euge Iup	

6.12.22.3 Application of Edge Sealer.



# EDGE SEALER

Proceed as follows:

a. Scuff 1 inch on either side of all seams and edges where possible.



# ISOPROPYL ALCOHOL, TT-I-735

- b. Wipe area with TT-I-735 isopropyl alcohol and allow to dry.
- c. Apply heavy coat of edge sealer per Table 6-1 into seams and trowel flush with a non-metallic scraper.
- d. Apply edge sealer to all vertical edges exposed to air stream with an acid brush.
- e. Allow edged sealer to cure 24 hours before painting.

6.12.22.4 Repair of Damaged Area. Proceed as follows:

- a. Measure 2 inches either side of damage and apply masking tape along this line.
- b. Trim loose film from damaged area. Cut new film to fit area to be repaired.
- c. Scuff entire area with a CID A-A-58054, Type I, Grade A nylon abrasive mat.



# ISOPROPYL ALCOHOL, TT-I-735

d. Wipe area thoroughly with TT-I-735 isopropyl alcohol.



# ADHESION PROMOTER

- e. Apply adhesive promoter per Table 6-1 to entire area. Allow to dry in accordance with manufacturer's instructions.
- f. Apply film and rub thoroughly.

#### NOTE

Ensure air bubbles do not build under film.

- g. Inspect repair for air bubbles. Try pressing air out, allowing proper bonding. If not successful, insert needle or pin into the air bubble and press out air before removing pin/needle.
- 6.12.22.5 <u>Tape Removal</u>. Remove tape by either of the following methods:

#### 6.12.22.5.1 Removal Disc.

- a. Using a pneumatic drill and 3M Adhesive Removal Disc, NSN 3460-01-447-8021, remove both tape and adhesive from damaged area.
- b. Trim edges as required.

36



# ISOPROPYL ALCOHOL, TT-I-735

c. Wipe work area with CCC-C-440 Type I, Class 2 cheesecloth moistened with TT-I-735 isopropyl alcohol, turning cheesecloth frequently. Continue until cloth no longer shows residue.

# 6.12.22.5.2 Scraping and Solvent Removal.

- a. Remove the tape by peeling it off. For repairs, remove tape 1/2 inch on either side of damage.
- b. Remove residual edge sealer by chipping with a plastic scraper.
- c. Mask work area.



# ADHESIVE REMOVER

- d. Apply adhesive remover per manufacturer's instructions.
- e. Allow to dwell long enough to soften adhesive.
- f. Remove old adhesive with plastic scraper. Repeat as necessary.



ISOPROPYL ALCOHOL, TT-I-735

- g. Using a CID A-A-58054, Type I, Grade A abrasive mat soaked with TT-I-735 isopropyl alcohol, scrub area to remove all adhesive.
- h. Wipe work area with CCC-C-440 Type I, Class 2 cheesecloth moistened with TT-I-735 isopropyl alcohol, turning cheesecloth frequently. Continue until cloth no longer shows residue.

6.12.22.6 Painting Instructions. Proceed as follows:

a. Scuff tape surface with CID A-A-58054, Type I, Grade B nylon abrasive mat.



#### ACETONE, ASTM-D329

- b. Saturate a clean, lint-free, cotton rag with ASTMD-329 acetone and lightly wipe the tape surface.
- c. Wipe surface dry with a clean, lint-free, cotton cloth before the acetone evaporates.

20

38



POLYURETHANE COATING, MIL-PRF-85285

- d. Paint tape surface with MIL-PRF-85285, Type I or Type IV, color to match area, in accordance with <u>Chapter 5</u> of this TO.
- e. Air dry paint a minimum of 72 hours at (75  $^{\circ}$ F (24  $^{\circ}$ C)) before flying the aircraft.

# CHAPTER 7 APPLICATION AND REMOVAL OF DECALS AND SILK SCREENING

# 7.1 <u>DECALS - GENERAL</u>.

### NOTE

National Stock Numbers (NSN) for specific decals and related materials are to be obtained from Federal Supply Classes (FSC) 7690, 9330, 9905, and others as found in Illustrated Parts Breakdowns (IPB) or -4 manuals for specific aircraft. Also, see the current Federal Logistics Data (FED Log) and the DO43 System to convert specification and Part Numbers (PN) to NSNs. See <u>Chapter 8</u> for requisitioning procedures and other related decal information.

Decals are specially prepared plastic film containing designs, words, numerals, or colored marking stripes, which may be applied or attached to Air Force equipment as a method of marking or identification. Decals can be used in lieu of paint for internal and external markings and insignia as authorized in <u>Chapter 8</u>. Decals shall conform to CID A-A-59485 or commercial equivalent and are available in solid or perforated film. Decals with perforations shall only be applied over fully painted surfaces. For application to pressurized areas on aircraft exteriors, prepared (factory) perforated film shall be used to prevent blistering due to leaking rivets, seams, etc. Non-perforated, premasked decals may be applied directly to the primer prior to applying the topcoat. Decals applied prior to the topcoat must be premasked with low tack translucent application/mask tape, leaving a 1/16 inch uncovered lip around the decal edge. This lip will allow the topcoat paint to seal the edge of the decal, eliminating the need for edge sealer. The mask is removed after the topcoat paint is allowed to cure. Decals are not authorized on unpainted surfaces.

#### 7.1.1 Surface Preparation.



Do not apply decals when the temperature is below 45 degrees Fahrenheit ( $^{\circ}F$ ) (7 degrees Celsius ( $^{\circ}C$ )) as early failure or peeling will occur. Failure to comply could result in damage to, or destruction of, equipment or loss of mission effectiveness.

#### NOTE

If application of decals is required at temperatures of 45 to 60 °F (7 to 16 °C), the pressure sensitive adhesive must be activated per instructions supplied by the manufacturer.

The integrity of a decal installation is largely dependent upon proper preparation of the surface to which the decal is applied. Therefore, the following must be accomplished prior to application of decals to aircraft surfaces.

- a. Remove exceptionally oily or greasy contaminants using wipe solvents listed in Table 3-2.
- b. In areas where the decal will be applied, buff very lightly with very fine aluminum oxide abrasive mat per CID A-A-58054, Type I, Grade A.



CLEANING COMPOUND, AIRCRAFT EXTERIOR, MIL-PRF-85570



CLEANING COMPOUND, AEROSPACE EQUIPMENT, MIL-PRF-87937

- c. Clean the entire application surface thoroughly with alkaline cleaner MIL-PRF-87937 or MIL-PRF-85570, in accordance with TO 1-1-691, on all old painted surfaces. This is not required on newly painted surfaces.
- d. Perform final cleaning of the application area with a lint-free cotton cloth.
- e. Optional use of a gloss MIL-PRF-85285 polyurethane clear-coat applied to the area to be covered by aircraft decals for adhesion purposes on camouflage aircraft is authorized.

7.1.2 <u>Application Procedures for Decals and Colored Marking Stripes</u>. Application of decals authorized by <u>Chapter 8</u> or system specific equipment or aircraft TOs is accomplished per the basic methods detailed below. These methods refer generally to simple shapes of the approximate sizes noted. Application of intricately cut shapes require the use of detailed application instruction supplied with the decal.

#### 7.2 SMALL DECALS AND MARKING STRIPES.

7.2.1 <u>Decals Up to  $12 \times 2$  Inches</u>. Remove entire backing from adhesive, align decal, and press on one edge to surface with the finger. Hold the remainder of film taut and slightly away from surface until pressed down with plastic squeegee using firm, overlapping strokes. (See Figure 7-1.)



Figure 7-1. Applying Small Decal

7.2.2 <u>Film for Striping</u>. Pull off backing for approximately 12 inches, exposing the adhesive. Press end in position and apply the striping as the backing is removed. Press firmly to surface with a plastic squeegee. Be sure all edges are firmly adhered (See Figure 7-2.)



Figure 7-2. Applying Marking Stripe

21

#### 7.3 LARGE EMBLEMS AND LETTERS USING HINGE APPLICATION METHOD.

Apply these decals using a "Hinge" method as outlined below.

a. Tape decal into position with small pieces of masking tape. (See Figure 7-3, Step 1.)




Figure 7-3. Applying Large Emblems (Step 1)

b. Apply 1 inch or 2 inch wide tape over one edge to serve as a hinge. Whenever possible, hinge narrow edge. (See Figure 7-4, Step 2.) If the surface requires that the longer edge be hinged, it may be necessary to use the carrier method. Bending the decal back at the hinge, peel the liner off of the decal. For large decals, it may be more convenient to peel the liner back a few inches at a time as the application progresses. (See Figure 7-5, Step 3.)




Figure 7-4. Applying Large Emblems (Step 2)




Figure 7-5. Applying Large Emblems (Step 3)

c. Hinge back and squeegee or roll the emblem to surface with firm, overlapping strokes. Hold sheeting away from the surface with one hand and allow adhesive to touch only as pressure is applied. Be sure the edges are firmly adhered. (See Figure 7-6, Step 4.)



Figure 7-6. Applying Large Emblems (Step 4)

#### 7.4 DECALS APPLIED USING APPLICATION TAPE.

This method is particularly useful with large or intricately shaped emblems or for hot weather applications. Steps 1, 2, and 3 under <u>Figure 7-7</u>, <u>Figure 7-8</u>, and <u>Figure 7-9</u> are not necessary when decals are supplied premasked (cut to same shape as decal with application tape).

a. Place a piece of application tape with the adhesive side up on a flat, rigid surface. (See Figure 7-7, Step 1.)

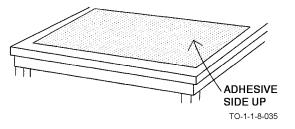


Figure 7-7. Use of Application Tape (Step 1)

b. Align emblem or letter with film side down and drop onto the adhesive. (See Figure 7-8, Step 2.)

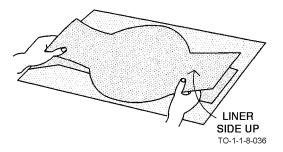


Figure 7-8. Use of Application Tape (Step 2)

c. Starting in the middle of the decal, squeegee to application tape with firm strokes of the plastic squeegee. (See Figure 7-9, Step 3.)


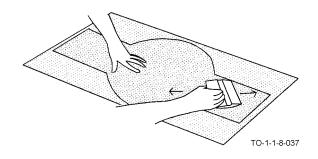


Figure 7-9. Use of Application Tape (Step 3)

- d. Tape into position and follow application steps under hinge method.
- e. Remove tape by pulling directly back upon itself at 180 degrees. Re-squeegee decal, especially the edges. (See Figure 7-10, Step 4.)



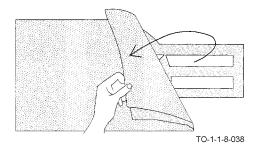

# 7.5 EDGE SEALING



```
EDGE SEALER
```

37

Seal all edges of decals applied over the topcoat on the exterior of the aircraft. Decals that have been applied premasked over primer coat and subsequently top coated do not require edge sealing.

# NOTE

Seal decal edges when required with 3M Co. (Commercial and Government Entity (CAGE) Code 34360) Edge Sealer, PN 4150 under NSN 8030-00-195-7660, or PN 3950 under NSN 8030-00-936-9940. Use of other edge sealers will cause early failure of 4000-series decal ink and CID A-A-59485 polyester film decals.

- a. Use the felt wick applicator attached to screw top can or use small narrow striping brush.
- b. Apply sufficient sealer to effect a feather edging along the entire decal edge (See Figure 7-11.)



Figure 7-11. Edge Sealing

# 7.6 APPLICATION OF PREMASKED DECALS.

Decals that have application tape (cut to the same shape as the decal) applied to the film side are supplied specifically for application on the primer coat (MIL-PRF-23377, MIL-PRF-85582, or TT-P-2760 only).

- a. Tape the decal into position and follow application steps under hinge method (Paragraph 7.3).
- b. After the paint topcoat has cured, remove the masking in the same manner shown in Figure 7-10 Step 4, except do not re-squeegee.

#### 7.7 DECAL REMOVAL.



AIRCRAFT COATING THINNER, MIL-T-81772

# WARNING

- MIL-T-81772 thinner is flammable and toxic. Keep away from heat and open flame. Keep container closed when not in use. Use only with adequate ventilation. Avoid prolonged or repeated contact with skin. Avoid swallowing. Failure to comply could result in injury to, or death of, personnel or long term health hazards.
- Eye protection must always be used when operating these tools. Power tools can cause flying particles which can cause injury. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

Remove perforated decals, listed in <u>Chapter 2</u>, conforming to CID A-A-59845, Type I, with paint remover. The film is a highly solvent resistant polyester, so the paint remover must penetrate through the perforations to soften the adhesive. It may be necessary to use repeated applications of remover to remove the film from adhesive. Another application of remover on the adhesive may then be required. Scrape off the bulk of the softened adhesive with a non-metallic scraper. Wipe off any remaining adhesive residue with thinner conforming to MIL-T-81772 on a cotton cloth. Non-perforated CID A-A-59845 type film can only be removed by applying steam or dry heat to the decal and physically removing film. Wipe off any remaining adhesive with thinner conforming to MIL-T-81772 on a cotton cloth.

7.7.1 <u>Mechanical Removal</u>. Use a pneumatic drill and one of the Adhesive Removal Disc Systems to remove both decal material and adhesive from the area (See <u>Table 7-1</u>.) Non-perforated decals can only be removed by mechanical methods listed below or by applying steam or dry heat to the decal and physically removing the film. Wipe off any remaining adhesive residue with thinner conforming to MIL-T-81772 on a cotton cloth until cloth no longer shows residue.

Table 7-1.	Adhesive	Removal	Disc	System
------------	----------	---------	------	--------

System	PN/NSN	Description	Source of Supply
MBX Vinyl Zapper Tool and Eraser	USSP-01-Blue	MBX Vinyl Zapper Removal Tool (Pneumatic)	AeroSafe Products, Inc. P.O. Box 4755 Marietta, GA 30061 888-666-7885/770-590-8863 CAGE Code: 1LPF0
3M Aircraft	USZU-010	Vinyl Decal Eraser	3M Center
Adhesive and Decal	NSN 3460-01-447-8021	Wheel, Buffing	Saint Paul, MN
Removal Disk			55144-1000
			CAGE Code: 52152

#### 7.8 APPLICATION OF MARKINGS WITH SILKSCREEN.

This method can be used for painting internal and external markings and insignias.

#### 7.8.1 Materials and Equipment for Silkscreening.

Equipment:

Locally fabricated or commercially procured silkscreens are both authorized.

Screen should be polyester monofilament (220-280 mesh).

Silkscreen, squeegee, commercially procured.

Materials:

Colored marking paint, MIL-PRF-81352, Type I - Acrylic, Type II - Alkyd, Type III - Polyurethane.

Thinner, MIL-T-81772, Type I and III.

Topcoat, MIL-PRF-81352, Type I, II, or III, clear.

7.8.2 <u>Surface Preparation</u>. Prior to silk-screening, wipe area being marked with one of the ketones or non-terpene solvent blends in <u>Table 3-2</u>. Freshly painted surfaces require no cleaning.

7.8.3 Application. Mount the silkscreen securely on the aircraft or equipment being marked.

# WARNING

MIL-PRF-81352 Types I, II, or III are flammable and toxic to eyes, skin, and respiratory tract. Eye and skin protection required. Good general ventilation is normally adequate. Failure to comply could result in injury to, or death of, personnel or long term health hazards.

#### NOTE

- The silkscreen paint being used may be either acrylic, alkyd, or polyurethane, unless otherwise specified in the system specific TO.
- If the silkscreened marking requires a clear topcoat, ensure it is compatible with the silkscreen and the base paint materials.
- a. Place just enough paint on the top of the silkscreen, just above the design, to completely cover the design when drawn. Using a square edge squeegee, draw the paint across the silkscreen design using firm constant pressure. When complete, remove the screen from equipment.
- b. Clean screen, squeegee, and other equipment using applicable thinner.

7.8.4 <u>Topcoat Application</u>. Silkscreened markings applied over a base coat of MIL-PRF-85285 polyurethane paint may also have a topcoat of clear MIL-PRF-85285 polyurethane, applied using an air spray gun, to improve the abrasion resistance of the silkscreen design. To avoid blurring of the silkscreen ink, apply a light coat of the clear polyurethane initially. Follow with heavier coats and allow to cure dust free.

#### TO 1-1-8

#### 7.9 APPLICATION OF MARKINGS USING STENCILS.

This method can be used for painting internal and external markings and insignias. The use of locally fabricated or commercially procured stencils is authorized. Use of stencils cut from a vinyl material on a computerized stencil machine is preferable.

7.9.1 <u>Surface Preparation</u>. Prior to stenciling, wipe area to be stenciled with one of the ketones or non-terpene solvent blends in <u>Table 3-2</u>. Freshly painted surfaces require no cleaning.

7.9.2 <u>Mounting Stencil</u>. Stencil may be taped into position using SAE AMS-T-21595, Type 2, Masking Tape or alternatively use 3M Co. (CAGE Code 34360) Repositionable Spray Adhesive 75, PN 3M-75. This adhesive will securely hold the stencil but will not leave any residue when removed. The adhesive is sprayed on the back of the stencil prior to mounting and will remain tacky enough to be reused several times. For the vinyl stencil mask material cut on the computerized stencil machine, peel the protective backing off the self-adhesive side, mount on the surface being marked, remove the cut out sections, and make sure all edges are adhering to the surface. This stencil mask material is easily peeled off the surface after stenciling and leaves no residue.

7.9.3 <u>Painting of Stencils</u>. Stencils shall be applied by using spray, brush, or roller application methods. Use the same type of paint as the topcoat.

#### NOTE

Single-component aerosol paint is authorized for instructional markings on off-equipment components, temporary markings required for Functional Test Flights (FTF)/Functional Check Flights (FCF), and wing-level organizational insignia or emblems. Approval is contingent on the existing coating system being intact (primer and topcoat), with no bare metal where the temporary marking is applied, except for the FTF/FCF application during periodic depot maintenance when the aircraft has been depainted before being repainted. Single-component aerosols are not authorized for any other application. These materials are not as durable as Mil-Spec qualified coatings and should not be used if schedules support the use of Mil-Spec qualified materials.

7.9.4 <u>Adhesion Promoters</u>. When the time between topcoat applications and paint stenciling has been exceeded the use of the following adhesion promoters is authorized. These materials chemically reactivate the topcoat in lieu of scuff-sanding, and improve the paint stencil's adhesion properties. Follow the manufacturers recommended instructions for application and use. (See <u>Table 7-2</u>.)

Material	Source/Cage Code	PN/NSN	Unit of Issue (UI)
Sur-Prep	ANDPAK, INC. ZIP-CHEM PRODUCTS/25873	AP-1/8010-01-600-1533	Twenty-four 4 ounce aerosol cans Box
Sur-Prep	ANDPAK, INC. ZIP-CHEM PRODUCTS/25873	AP-1/8010-01-600-2254	Twelve 11 ounce aerosol cans Box
PreKote SP Presaturated wipes	PANTHEON CHEMICAL/ 0F5L5	065-1080/6850-01-602- 6827	Roll of wipes W/O container EA
PreKote SP Presaturated wipes	PANTHEON CHEMICAL/ 0F5L5	065-1081/6850-01-602- 6830	Container with roll of wipes EA

Table 7-2.	Adhesion	Promoters

# **CHAPTER 8**

# EXTERIOR FINISHES, INSIGNIA, AND MARKINGS APPLICABLE TO UNITED STATES AIR FORCE (USAF) AIRCRAFT

# 8.1 GENERAL.

8.1.1 <u>Purpose</u>. The purpose of this chapter is to standardize the painting, marking, and exterior configuration of all Air Force (AF), AF Reserve, and Air National Guard aircraft. This chapter describes AF policy on the painting, marking, and exterior configuration of aircraft. Also described in this chapter are common internal markings and standardized international markings. In the event of a technical conflict between this chapter and the weapon system specific manuals, the weapon system specific manuals shall take precedence. Conflicts concerning safety, health, or environmental issues shall be resolved locally and through the Major Command (MAJCOM) headquarters. Only the types of finishes and insignia described in this chapter shall be applied to USAF aircraft. Refer to DAFI 21-101, equivalent MAJCOM supplements, weapon system manuals, and weapon system drawings for specific paint schemes and marking applications.

8.1.2 <u>Responsibilities</u>. The MAJCOM/A4 Commanders, MAJCOM/Fabrication Functional Managers, affected Weapons System Managers (WSM), and weapon system specific SPOs are responsible for coordinating AF painting and marking policy with the various international organizations, and are the focal points for painting and marking issues. The MAJCOM logistics and maintenance function is responsible for implementing the policy once developed. SPOs are responsible for maintaining accurate technical data depicting approved paint schemes and markings for their assigned aircraft. SPOs shall be responsible for assuring compliance with DAFI 21-101 and AF policy.

**8.1.3** <u>Maintenance and Application</u>. The MAJCOMs and using organizations are responsible for the application and maintenance of coatings and markings for all assigned aircraft listed in TO 00-25-4. Air Force Materiel Command (AFMC) shall be responsible for the overcoating or strip and repaint of aircraft listed in TO 00-25-4.

**8.1.4** <u>Major Command Instructions</u>. Each MAJCOM shall prepare a supplement for DAFI 21-101, or equivalent, pertaining to painting and marking of aircraft. The supplement will be limited to distinguishing insignia, markings, and finishes as authorized in this Chapter and other AF directives.

8.1.5 <u>Authorized Deviations</u>. All requests for deviations from the standard exterior paint and marking configuration in this TO shall be submitted to the respective MAJCOM Fabrication Functional Manager and Weapons System Manager (WSM).

8.1.6 Paint Scheme and Marking Approval Process. All changes to approved paint schemes and marking configurations shall be submitted to the respective MAJCOM Fabrication Functional Manager, Weapons System Manager (WSM), and weapons system specific SPO. The MAJCOM Fabrication Functional Manager/WSM shall coordinate the proposed changes with the weapons system specific SPO, and garner final approval from MAJCOM/A4 Commander to ensure survivability analysis is completed as necessary. The Fabrication Functional Manager/WSM will work with the SPO to ensure the applicable technical documents are changed and develop a method to implement the changes. A copy of the approved change package shall be retained by the weapons system specific SPO and respective MAJCOM/A4. Exceptions are as follows:

8.1.6.1 <u>89th AW, 201AS, and the 1st Helicopter Squadron</u>. Deviations from standard paint schemes and markings are authorized and shall be approved by the respective MAJCOM/A4.

8.1.6.2 <u>USAF Aerial Demonstration Squadron "The Thunderbirds"</u>. Paint schemes and markings shall be approved by HQ Air Combat Command (ACC).

**8.1.6.3** <u>76th Airlift Squadron</u>. Aircraft assigned are authorized radio call numbers on each side of the vertical stabilizer, American flag, and United States of America markings with no other external USAF markings authorized (i.e., USAF, stars and bars, organizational markings, fuel grade markings under pilot's window) Painting and marking of these aircraft will be as specified by United States Air Force in Europe (USAFE)/Command Center (CC). Information copies of all approved paint schemes and markings will be forwarded to HQ USAF/A4.

**8.1.6.4** <u>Low Observable Aircraft</u>. The Lead Command, as listed in Department of the Air Force Policy Directive 10-9, Paragraph 3.2, is responsible for developing paint schemes and markings for their respective MDS.

# TO 1-1-8

8.1.6.5 <u>Aircraft Received from Other Services</u>. When types and models of aircraft not previously in the AF inventory are acquired from other military departments, the MAJCOM and SPO will develop paint schemes and marking patterns for the aircraft. The SPO will be responsible for developing special purpose markings for servicing and personnel safety.

8.1.7 <u>Service Tests</u>. Approved service test programs will be implemented by coordinated effort, monitored by the appropriate engineering function, SPO, Air Force Research Laboratory (AFRL), and the requesting MAJCOM.

8.1.8 <u>Decals</u>. Decals are special prepared film containing designs, words, letters, or numerals and are intended to be permanently affixed to the aircraft. Decals may be used in lieu of paint for all external markings and insignia where the contact surfaces are of sufficient smoothness to permit good adhesion. Decals used shall meet specification CID A-A-59485 or 3M Scotchcal 220.

8.1.9 <u>Applicable References</u>. The application of North Atlantic Treaty Organization (NATO) code numbers cited in TO 42B1-1-15 shall supplement the applicable service points prescribed in this TO. The codes will be applied immediately adjacent to the symbol as considered most practical. NATO code numbers may be omitted when not reflected in TO 42B1-1-15 or may be omitted on training type aircraft and other aircraft not subject to being serviced at overseas location. Additional instructions and directives applicable or allied to the application and maintenance of the finishes and markings of aircraft are contained in the following Standardization Agreement (STANAG):

CENTO STANAG No. 3230	Emergency Marking on Aircraft.
NATO STANAG No. 3109	Servicing and Ground Handling Codes.
NATO STANAG No. 3230	Emergency Marking on Aircraft.

# 8.2 STANDARD EXTERIOR FINISHES, MARKINGS, AND INSIGNIA FOR USAF AIRCRAFT.

Standard finishes are applied as either glossy or camouflage topcoats. All topcoats, painted markings, and painted insignia will be applied using high-solid polyurethane, MIL-PRF-85285.

8.2.1 <u>Metal Exterior Finishes</u>. Metal exterior finishes other than titanium and Corrosion Resistant Steel (CRES) require surface protection from corrosive elements and, therefore, will be painted.

8.2.2 <u>Titanium and Corrosion Resistant Steel</u>. These materials usually make up a small portion of the exterior surface. Titanium and CRES will be painted to match the rest of the exterior of the aircraft providing temperatures permit.

**8.2.3** <u>Treatment of Metal Exteriors</u>. Treatment of metal exteriors and corrosion control are specified in TO 1-1-691 and weapon system specific manuals.

8.2.4 <u>Policy Guidance</u>. It is a general policy that all AF aircraft will be painted equally as a prime means of corrosion protection and prevention, appearance, and survivability. Painting for professional appearance is an integral part of a wellmanaged corrosion control program (DAFI 21-101). The requirement to paint must be tempered with good judgment. Mission requirements, environmental concerns, and resources must be considered prior to painting. Aircraft will be painted in accordance with a service life program. A coordinated paint/depaint program will be established and kept current for each weapon system. Where possible, a scoring system should be used to determine painting requirements. The scoring system should account for paint condition, local corrosion severity index (Refer to TO 1-1-691), and calendar time. The MAJCOM and SPO will determine when an aircraft is to be stripped and repainted. Maintenance painting will be used to enhance and preserve coating systems.

#### NOTE

Aircraft Structural Maintenance Sections will score assigned aircraft. All other equipment scoring programs will be scored and managed by owning work center.

**8.2.4.1** In determining the requirements for sectional overcoating, total overcoating, or strip and repaint, the following general technical criteria should be considered in the development of the weapon system paint plan.

**8.2.4.1.1** Sectional or total overcoat if the paint is oxidized, discolored, stained, chipped, scratched, or peeled from the primer and the primer remains adhered to the aircraft surface. If the condition is extensive, consider a total overcoat.

**8.2.4.1.2** Strip and repaint if the following defects or combination of defects exists: areas which have been overcoated (primer plus topcoat) at least three times; primer is not adhering to the substrate; or the paint system is peeled to the substrate.

**8.2.4.2** When applying the above criteria to determine painting requirements and a combination of defects for strip and overcoating exists, the following general economic guidelines should be considered in the development of the weapon system paint plan.

**8.2.4.2.1** When determining sectional or total overcoat and a combination of defects exist, overcoating may be accomplished if the time or man-hour requirements for surface preparation (mask, sand, or clean) do not exceed 70 percent of the time or man-hours for a complete strip/repaint.

**8.2.4.2.2** Sectional stripping may be required, as determined by deteriorated areas, on aircraft designated for complete overcoat. Complete overcoating may be accomplished if the combined time or man-hours for sectional stripping and surface preparation for overcoat do not exceed 70 percent of the time or man-hours required for complete strip/repaint.

**8.2.4.2.3** Complete strip/repaint should be accomplished in lieu of overcoating whenever the time or man-hours for masking, sanding, and cleaning for the total or sectional overcoating exceed 70 percent of those to accomplish strip/repaint.

8.2.4.3 In the absence of a tailored weapon system paint plan, the above criteria will apply to all aircraft.

8.2.5 <u>Camouflage</u>. Camouflage is used for the purpose of deception, to conceal material from undesired observation, or to confuse and mislead observers as to the identity and number of assets available. Camouflage may be either pattern or non-pattern. Pattern camouflaging is based on optical principals that dictate certain non-reflective colors, color configurations, and color portions. Arbitrary application of markings and color schemes other that those approved will defeat the purpose of the camouflage and is not authorized.

8.2.6 <u>Special Purpose Exterior Solar Resistant Finishes</u>. For the purpose of this TO, solar resistant finish is defined as a white cap painted on the top surface of the aircraft to reduce interior temperature. The solar resistant finish is only authorized on aircraft used primarily as troop carriers or those that carry heat sensitive equipment. In either case, the MAJ-COM supplement to DAFI 21-101, or equivalent MAJCOM instruction, will authorize the application of a solar resistant finish.

8.2.7 <u>Paint Facility/Finish Identification Block</u>. (See Figure B-4.) All aircraft receiving a new paint finish shall have a contrasting color or black (color 37038) block of no less than 2-1/2 inches, applied to the right side fuselage on the underside even with the leading edge of the horizontal stabilizer or wing by the activity that applied the paint. Stencils or decals may be used for the paint block. Figure B-4 shows an example of a typical paint block, MAJCOMs may allow different designs. The block will contain:

- The name of the activity, plus the Commercial and Government Entity (CAGE) code
- Date of completion (DD, MMM, YY)
- Identification by specification, type, class, manufacturer part number and CAGE Code of all pretreatments and coatings utilized

## NOTE

All full scuff sanded and overcoated aircraft require an additional paint identification block for each coating system applied (in addition to the original paint identification block). It shall contain the same information as required above and will be placed adjacent to the original paint identification block.

### 8.3 MARKINGS AND INSIGNIA FOR USAF AIRCRAFT.

8.3.1 <u>General</u>. The markings and insignia contained in the manual shall be applied to all USAF aircraft. Markings and insignia will vary depending on the paint system being applied and the MAJCOM to which the aircraft is assigned. Standard Markings are as listed in <u>Table 8-1</u>. The above standard insignia and markings will not be altered in location, dimension, or configuration to accommodate any other insignia or marking.

Item	General Location	
National Star Insignia	Aircraft Wing and Fuselage	
"USAF" Marking	Aircraft Wings	
"U.S. AIR FORCE" Marking	Aircraft Fuselage	
Serial Number	Aircraft Fuselage	
Aircraft Radio Call Number	Aircraft Vertical Fin	
American Flag	Aircraft Vertical Fin	

Table 8-1.Standard Markings

**8.3.1.1** <u>National Star Insignia</u>. The National Star shall be installed on all aircraft. Specific instructions for installing the National Star and approximate dimensions are shown in Figure B-1 and in Paragraph 8.3.1.3.

8.3.1.2 <u>The National Star Insignia on Aircraft Fuselage</u>. The star insignia will normally be applied to the aircraft fuselage midway between the wing trailing edge and the leading edge of the horizontal stabilizer.

8.3.1.3 <u>The National Star Insignia on Fixed Wing Aircraft</u>. The star shall be applied to the upper surface of the left wing and the lower surface of the right wing. (See Figure B-2.)

8.3.1.4 <u>The National Star Insignia on Helicopters</u>. The star shall be applied on the fuselage. The insignia shall be located so that it is visible from each side, above and below. Because of helicopter design configuration, the insignia shall be located so as to provide maximum identification. Such locations shall be standardized on like Mission-Design Series (MDS) helicopters.

8.3.2 <u>"USAF" Wing Marking</u>. On aircraft identified by the MAJCOM requiring USAF wing markings, the USAF marking shall be applied to the lower surface of the left wing and upper surface of the right wing. The height and location of the USAF will correspond with the National Star insignia. The top of the letters shall be towards the leading edge of the wing.

8.3.3 <u>American Flag Marking</u>. The display of the American Flag on aircraft exteriors is intended for specific uses which have national significance or U.S. diplomatic connotations. The use of the flag will be restricted and approved only by MAJCOM/A4. Routine or occasional overseas flight of aircraft, assignment of aircraft to foreign soil, or intra-theater travel of overseas based aircraft are not sufficient reasons for use of the American Flag marking. The National Star insignia and USAF markings painted upon aircraft exteriors will adequately identify USAF aircraft. <u>Table 8-2</u> lists all aircraft authorized the American Flag marking.

**8.3.3.1** The American Flag shall have a height, width ratio of 0.52 to 1, and be located on each side of the vertical fin above all other markings of significance. The flag shall be positioned horizontally such that the union shall be uppermost with the bars appearing to be trailing at all times. (See Figure B-5.)

**8.3.3.2** The flag or emblem of other countries (non-AF) organizations shall not be displayed on USAF aircraft for any reason.

<b>Table 8-2.</b>	Aircraft Authorized American Flag Markings
-------------------	--

Aircraft Authorized American Flag Markings				
Air Attaché				
Military Assistance Advisory Group (MAAG)				
USAF Mission				
Apollo Range Instrumentation Aircraft, EC-135 (AFMC-ARIA) and NKC-135A Serial Number (SN) 53-3132 (BIG CROW)				
89th Airlift Wing/201AS				
AF Section Mission (U.S. Military Group Aircraft in Latin America)				
Air Mobility Command (AMC)/ACC Airlift Forces Aircraft				
76th Airlift Squadron, USAFE				
Air Force Reserve Command (AFRC) and Air National Guard (ANG) Airlift Aircraft for which ACC/AMC are the				

## Table 8-2. Aircraft Authorized American Flag Markings - Continued

Aircraft Authorized American Flag Markings Gaining Command EC/RC-135 E-4 Aircraft All Transport and Tanker Aircraft

8.3.4 <u>United States of America Marking</u>. The words "UNITED STATES OF AMERICA" are authorized to be painted on the fuselage exteriors of aircraft authorized the American Flag listed in <u>Table 8-3</u>. When authorized, the marking "UNITED STATES OF AMERICA" will be applied on both sides of the aircraft fuselage, parallel to and above the top of the cabin windows (See <u>Figure B-5</u>.) The fuselage marking "U.S. AIR FORCE" shall be removed from the aircraft.

<b>Table 8-3.</b>	Aircraft Authorized United States of America Markings
-------------------	---

Aircraft Authorized United States of America Markings				
Air Attaché				
MAAG				
AFMC-ARIA				
USAF Mission				
89th Airlift Wing				
AF Section Mission (U.S. Military Group Aircraft in Latin America)				
76th Airlift Squadron, USAFE				
E-4 Aircraft				

8.3.5 <u>Aircraft Radio Call Numbers</u>. The radio call number shall be applied to each side of the vertical stabilizer. On aircraft with multiple vertical stabilizers the radio call number will be applied to the outboard side of the outer most vertical stabilizer. AMC and ACC each use a different method to mark the vertical stabilizer with the radio call number.

**8.3.6** <u>AMC Standard Radio Call Numbers</u>. The radio call number consists of five numbers usually derived from the aircraft SN. The first numeral of the contract number and the hyphen will not be used (e.g., SN 63-545134A will be 35134 and 62-3467 will be 23467). (See Figure B-5.)

**8.3.6.1** In the event five numerals are not available, the radio call number will include the second numeral of the contract year followed by a sufficient number of zeros to provide five numerals (e.g., SN 73-23A will become 30023).

**8.3.6.2** All radio call number placards within the aircraft, including helicopters, shall reflect the same radio call number as applied to the aircraft exterior.

8.3.7 <u>ACC Standard Radio Call Numbers</u>. ACC uses a distinctive two-place alphanumeric in conjunction with the first two and last three numbers of the aircraft serial number. When duplicate last three digits exist among aircraft with the same distinctive unit designator, the last four numerals of the serial number shall be used (See Figure B-6).

8.3.7.1 <u>Distinctive Unit Identifiers</u>. The identifier is two numbers, two letters, or one number and one letter. Any MAJ-COM may authorize the use of the identifier. HQ ACC will be the approving authority and maintain a registry of the identifiers. When the identifiers are no longer required, the respective Command will notify HQ ACC at ACCA4.Workflow@us.af.mil. Distinctive identifiers shall not be removed or installed without the expressed knowledge and approval of HQ ACC. Similarly, only ACC may authorize changes in the identification code assignments.

### 8.4 ORGANIZATION INSIGNIA OR EMBLEMS.

All proposed organizational emblems and insignia will be in accordance with DAFI 21-101, or equivalent MAJCOM instruction. The MAJCOM or ANG will be the approving authority for these insignia and emblems. Only ANG aircraft are authorized the state name and ANG Minuteman emblem. Application location and size will be in accordance to the MAJCOM supplement to DAFI 21-101, or equivalent. Standard markings/insignia shall not be altered to accommodate any organizational markings/insignia. When the aircraft is being transferred, the transferring unit will remove its markings and insignia. Aircraft being processed for storage are exempt from the requirement to remove markings/insignia.

8.4.1 <u>Outstanding Unit Award Marking</u>. A replica of the "Outstanding Unit Award" ribbon earned by an organization may be installed on the sides of the fuselage in accordance with the MAJCOM supplement to DAFI 21-101, or equivalent MAJCOM instruction. The marking shall not exceed 12 inches in length. The size ratio shall be 4:1.

8.4.2 <u>Crew Names</u>. The names of the pilot, crew chief, or other members of the flight or ground crew shall be applied to the aircraft in accordance with the MAJCOM supplement to the DAFI 21-101, or equivalent MAJCOM instruction.

### NOTE

Transient aircraft, as defined by TO 00-20-1, crew names shall be applied in accordance with the respective MAJ-COM's supplement to DAFI 21-101, or equivalent MAJCOM instruction.

8.4.2.1 <u>Combat Deployment Requirements</u>. Aircraft deployed to combat zones are not authorized to have any crew markings. All exterior crew markings shall be completely removed from the aircraft prior to deployment to combat zones. No visible outline (shadowing) or glue shall remain on the aircraft. Names shall be reapplied as soon as practical following redeployment from the combat zone.

### NOTE

Crew name background blocks may need to be completely repainted to ensure the names are not recognizable, distinguishable, or visible in any form on the exterior of the aircraft.

8.4.3 <u>Aircraft Names</u>. All requests for applying aircraft names to the exterior of aircraft shall be coordinated through the respective MAJCOM/A4 Commander for approval. Exception: Units may transfer a previously approved name from one aircraft to another (same MDS within their unit) when transferring aircraft to another unit. Information on approved names, colors, sizes, and locations shall be included in the DAFI 21-101, or equivalent MAJCOM supplement.

8.4.4 <u>Local Station Numbers and Markings</u>. Where aircraft may have a duplication of the last three digits of the aircraft serial number or atmospheric conditions may hinder visibility at a station, the MAJCOM may authorize local station numbers.

8.4.4.1 <u>Station Numbers</u>. Station numbers shall be located on the nose section of fixed wing aircraft and on the deflector shields or other forward component of rotor wing aircraft. Numerals will not be more than 8 inches tall and proportionate to the aircraft size. Station numbers shall be removed prior to transfer of the aircraft.

**8.4.4.2** <u>Tail Stripe</u>. MAJCOMs may authorize a distinguishing colored horizontal stripe for application to both sides of the vertical fin. The stripes shall not be applied over apex antenna.

8.4.5 <u>Propeller Markings</u>. All AF propeller blade tips will be painted in a contrasting color. All blades will be checked for balance after application of blade markings. For blades less than 15 feet in diameter (measured from the tip of the blade to the hub center) the stripe will be 4 inches wide. Larger diameter blades will have 6 inch stripe.

**8.4.5.1** Propeller tips may be marked with light reflective yellow or a contrasting color when it is necessary to define the blade track in the dark.

**8.4.5.2** Aircraft whose primary mission is transportation of Very Important Person (VIP) are authorized to have red, white, and blue stripes applied to the propeller tips. Approval authority for this marking is the MAJCOM. The occasional transport of VIPs in not sufficient justification for multicolored blade tips. Each blade will be painted red, white, and blue in this order with red being the color closest to the blade tip. For blades 15 feet in diameter and less each stripe will be 1-1/2 inches wide; larger diameter blades will have a 2 inch stripe. Table 8-4 lists aircraft authorized multicolored blade tips.

#### Table 8-4. Aircraft Authorized Multi-Colored Blade Tip Markings

	Aircraft Authorized Multi-Colored Blade Tip Markings
Air Attache	
MAAG	

### Table 8-4. Aircraft Authorized Multi-Colored Blade Tip Markings - Continued

Aircraft Authorized Multi-Colored Blade Tip Markings			
USAF Mission			
89th Airlift Wing			

8.4.6 <u>Helicopter Main Rotor Blade Markings</u>. Classification numbers shall be stenciled on the inboard (butt end), flat surface of the ground side of each main rotor blade by facilities authorized to balance and alter the rotor blades. Three numbers in decimal format shall be utilized: the first shall be weight in pounds; the second shall reflect the distance in inches from the center of rotation to the center of gravity of the blade; and the third number shall be the distance in inches from the lead-ing edge of blade to the center of gravity for the blade chord-wise (e.g., 57.2-75.2-5.2 indicates the blade weighs 57.2 pounds, with a center of gravity 75.2 inches from the center of rotation and chord-wise center of gravity is 5.2 inches from the lead-ing edge.). Contrasting coloring stenciling shall be 3/4 inch in height. Color bands installed by the contractor on the tip of the blade shall be maintained along with matching colors on the housing. Different colors are required on the blades for tracking purposes.

8.4.7 <u>Helicopter Tail Rotor Blade Markings</u>. To promote safety, all tail rotor blades, except Sikorsky blades utilizing B and B bonding or having vinyl plastic tape installed, shall be marked using MIL-PRF-85285 and a compatible primer coat as follows:

- a. Prime surface with a light coat of primer.
- b. Apply a 6 inch band of red (color 31136) to the tail rotor tip followed by a 6 inch band of white (color 37925) followed by another 6 inch band of red (color 31136).
- c. Following the second band of red, apply a black band (color 37038) to within 6 inches of the hub. Paint the remaining 6 inches of the tail rotor red (color 31136).
- d. Identifying color bands painted by the contractor shall be maintained and an identifying dot, approximately 1/2 inch in diameter of the same color as appears on the housing, shall be painted on the butt end of the blade for matching purposes.
- e. Balance the blades as necessary.

8.4.8 <u>Identification Markings of Jettisonable Aircraft Components</u>. All jettisonable components will be stenciled using MIL-PRF-85285. The color will be selected to provide the greatest contrast with the surrounding base color of the component.

8.4.8.1 <u>Canopies</u>. The radio call number shall be stenciled in 1 inch letters, 6 inches from the forward left-hand end, on either the inside or outside of the canopy frame.

8.4.8.2 <u>Ejection Seats</u>. All ejection seats shall have the radio call number stenciled on the seat back near the top edge. If the aircraft is equipped with more than one seat, the flight crew position (i.e., pilot, NAV, GUNNER, etc.) shall be stenciled under the radio call number. The numbers and letters shall be 1 inch high and positioned to avoid contact with parachute gear.

8.4.8.3 <u>Jettisonable Components</u>. Where jettisonable components, such as external tanks, are interchangeable and are frequently removed and create a problem of stockpiling components for a specific aircraft, the base supply account number will be applied to the component. The stencil will be 1 inch high and applied near the component center on both sides.

8.4.9 <u>Markings for Servicing, Ground Handling, and Hazard Warning</u>. (See Figure B-7 through Figure B-12.) The markings shall be in contrasting colors. Lettering shall be in accordance with <u>Appendix B</u> of this TO. Symbols for the identification of service points, ground handling, and hazard warnings shall be applied to the required locations on all USAF aircraft. Location is dependent on the amount of available space. The marking may be on or adjacent to the equipment or service point. Symbols and markings may be applied using paint or decals. Symbols shall be approximately 4 inches in size but may be smaller depending on the area or item being marked. The markings provide:

• Rapid identification of servicing points

- Identification of the type of ground servicing required
- Hazard warning or safety precautions which will prevent injury to personnel or damage to equipment
- Rapid exit from air vehicle under emergency conditions

8.4.10 <u>Markings for Engine Compartment Fire Access Panel</u>. The fire access panel or doors in the engine compartments shall have contrasting color boarder and identifying text.

8.4.11 <u>Ejection Seats</u>. A contrasting color equilateral triangle with the sides up to 9 inches long, with the apex pointing downward, shall be applied on each side of the fuselage adjacent to the explosive device.

8.4.12 <u>Identification of Ballistic Hose Assemblies</u>. Ballistic hose or tubing assemblies leading to the ejection seat or catapults shall be marked for ground rescue purposes. The area selected shall be easily visible and readily accessible and as close as possible to the catapult. (See <u>Appendix B</u>.)

8.4.13 <u>Markings for Tank Filler Areas</u>. Fuel filler caps shall be painted red. A red band, 1 inch wide, around and 2 inches away from the fuel fill cap or over the cover door is optional.

8.4.14 <u>Marking of Emergency Lighting (Flashlight) for Cargo and Transport Aircraft</u>. Aircraft which have flashlights adjacent to natural or emergency exits will have a 1/2 inch yellow band around the base of the flashlight mount. The band may be applied to the sides of the light holder if the material cannot be applied around the base. The band may be formed from 3M retro reflective or 6900 photo luminescent paint (TT-P-54), or reflection tape (ASTM D4956).

8.4.15 <u>Markings for Walkways and Steps</u>. In cases where walkways don't contrast with surrounding areas, the walkway will be bounded by a contrasting color line. The word "WALKWAY" shall be stenciled at sufficient intervals. Step areas shall be indicated at all points on the aircraft.

8.4.16 <u>Markings for Composite/Honeycomb Panels</u>. Composite or honeycomb panels on upper surfaces shall be distinctly marked by contrasting color 1-1/2 inch wide hash marks. Each hash mark shall be 2 inches long and separated by 2 inches. The marks shall slope 45 degrees.

### 8.4.17 Removable Escape Panels.

8.4.17.1 <u>Internal Markings</u>. Marking for the identification of escape hatches, doors, and exits on the interior of the aircraft shall be painted orange-yellow (color 13538). Use black (color 17038) on yellow surfaces. Use MIL-PRF-85285, 3M retro reflective or 6900 photo luminescent paint (TT-P-54), or reflection tape (ASTM D4956).

- a. Apply an intermittent band to mark the periphery of the personnel escape exit. The segments of the band will have a minimum width of 1 inch and a length of 2 inches, divided equally, possible and practical between the door mounting and the escape door itself. Where the lining will cover the identification marking band inside of the aircraft, continue the marking onto the lining.
- b. The words EMERGENCY EXIT shall be applied on the escape hatch door or exit or any covering thereof in the most readily visible location. Letters should be approximately 2 inches high.
- c. Paint handles, releases, catches, and knobs for inside hatches and exit doors. Where lettering or marking areas are covered by lining, the lining shall also be appropriately marked. Suitable descriptive wording, readily visible, shall be applied to the door or structure of the aircraft, whichever is nearest the emergency release, to identify and explain its operation. This wording should be approximately 1 inch high. Use Standard English terminology such as PULL, TURN, SLIDE, or PUSH.

8.4.17.2 External Markings. Markings for the identification of escape hatches, doors, and exits on the exterior of the aircraft shall be painted orange-yellow (color 13538) or a contrasting color. Use MIL-PRF-85285. The words EMT RE-LEASE, shall be applied on the outside of the aircraft to facilitate quick identification. Suitable descriptive wording shall be applied to the door or structure of the aircraft, whichever is nearest the emergency release, to identify and explain its operation. This wording should be approximately 1 inch high. Use Standard English terminology such as PULL, TURN, SLIDE, or PUSH. Letters should be approximately 2 inches high.

### 8.4.18 Markings for Unmanned Aerial Vehicles.

8.4.18.1 <u>Target Drones</u>. Target drones for crew training, weapons evaluation, etc., shall be painted International Orange (color 12197) using MIL-PRF-85285.

8.4.18.2 <u>Other Unmanned Aerial Vehicles (UAV)</u>. All other UAVs, Remotely Piloted Vehicles, and drones may be painted with a color scheme to suit the mission requirement. The schemes and markings shall be approved in accordance with the MAJCOM supplement to DAFI 21-101, or equivalent. MIL-PRF-85285 shall be the standard topcoat.

8.4.19 <u>Conspicuity Markings</u>. Conspicuity Markings (MIL-PRF-85285, color 12197) may be used under special conditions on non-camouflaged aircraft and are intended to enhance air-to-air visual detection for safety purposes. Conspicuity markings will be approved by the respective MAJCOM/A4 for aircraft engaged in special missions. Aircraft required to have conspicuity markings:

- Aircraft used primarily as target
- Aircraft specifically designated by the MAJCOM due to special requirements of research and development. Included may be director and drone aircraft
- Special conspicuity markings are authorized only when 75 percent or more of the mission flying hours are utilized en route/on facility time

8.4.20 <u>Arctic Markings</u>. The use of arctic markings (MIL-PRF-85285, color 12197) is intended to facilitate the location of aircraft downed in regions covered by ice and snow. Aircraft in the following categories are exempt from compliance with arctic markings:

- Air Attaché
- Aircraft scheduled for short periods of duty, less than 180 days, in Arctic or Antarctic regions
- Active strike force and combat support aircraft assigned offensive missions for less than 180 days in Arctic or Antarctic regions

### 8.5 <u>ESTABLISHING REQUIREMENTS FOR MISSION ACTIVITY, CREW ACCOMPLISHMENT, AND ESPRIT</u> DE CORPS INSIGNIA AND MARKINGS.

Markings which reflect mission activity, crew accomplishment, and esprit de corps are allowed at the discretion of the respective MAJCOM/A4.

# APPENDIX A SHELF-LIFE EXTENSION PROCEDURES

## A.1 GENERAL TESTING PROCEDURES.

802 MXSS/MXDT is the Air Force (AF) executive agent for the Shelf-Life Extension System (SLES) program, reference Department of Defense (DoD) 4140.27-M and the DoD Shelf-Life Program website (www.shelflife.dla.mil). The SLES program is managed by 802 MXSS/MXDTD at Robins AFB, GA (DSN 468-8590, COM (478) 926-8590, or FAX (478) 926-1276 or FAX DSN 468-1276. Under their authority, the following test procedures are provided for the testing of the most commonly used coatings in this Technical Order (TO) under the 8010 NSC.

- a. These procedures are authorized for use to supplement the test requirements of DoD 4140.27-M and the DoD Shelf-Life Program website (www.shelflife.dla.mil) for MIL-PRF-23377, TT-P-2760, MIL-PRF-85582, and MIL-PRF-85285. When any of the above materials have reached their established shelf-life, they must be tested per the requirements of DoD 4140.27-M and the DoD Shelf-Life Program website (www.shelflife.dla.mil) at Air Force Materiel Command (AFMC) Laboratories, commercial laboratories, or at bases with the means to test these materials using the procedures established here.
- b. The information contained in the SLES program is advisory in nature; however, it may be used to assist in the management of shelf-life extension for MIL-PRF-23377, TT-P-2760, MIL-PRF-85582, MIL-PRF-85285 (and other 80 Federal Supply Group (FSG) materials not discussed here, reference DoD 4140.27-M and the DoD Shelf-Life Program website (www.shelflife.dla.mil). This information may be used to extend the inspection and test date for material under the same National Stock Number (NSN) and manufacturer's batch and lot number. Additionally, condemning material shall be per the requirements of DoD 4140.27-M and the DoD Shelf-Life Program website (www.shelflife.dla.mil) or results of testing of local stocks, either by a laboratory or the tests provided here.
- c. Testing shall be accomplished on or before the initial expiration date and on or before each extension expiration date. Initial shelf life extensions is for full period of the original shelf-life (i.e., Original shelf-life 1 year, initial extension 1 year). Subsequent shelf-life extensions will be for one-half of the original assigned shelf-life (i.e., Original shelf-life 1 year, second and subsequent shelf-life extensions will be for 6 months). Reference DoD 4140.27-M and the DoD Shelf-Life Program website (www.shelflife.dla.mil) for further instruction. This is the maximum allowable update for each retest.
- d. To perform base level tests where laboratories are not available or sending the material for laboratory testing is not economically feasible, the following are necessary: an approved paint spray booth, disposable volume measuring containers either fluid ounces or mLs (these may be available from medical organizations), a powered stirring device of 140 Revolutions Per Minute (RPM), and either Number (No.) 2 Zahn or No. 4 Ford viscosity measuring cup. Each material must be accurately mixed and sprayed on test panels to perform the test. Each coating must be evaluated for its condition in the container, viscosity, pot life, curing (drying) time, and surface appearance.
- e. These materials chemically react when mixed and they are temperature sensitive. The coating components must always be allowed to warm to room temperature for up to 24 hours, as necessary. Tests shall not be performed at temperatures below 70 °F (21 °C), or above 80 °F (27 °C), as the temperature will impact viscosity, pot life, and curing time. The components must be mixed accurately. When the manufacturer's instructions are to mix by ratio, such as 3 to 1 (3 parts component A to 1 part component B) and the quantity to be mixed for testing is 16 fluid ounces, mix 12 fluid ounces of part A to 4 fluid ounces of part B. Manufacturer's instructions for mixing ratios of these materials is always by volume and not by weight; therefore, quantities to be measured for mixing can always be determined by using disposable measuring cups.

## A.2 MIL-PRF-23377 EPOXY PRIMER.

A.2.1 <u>Condition in the Container</u>. Using a kit of material from each batch or lot number to be tested, allow both components A and B to stand until reaching room temperature, and open each container and examine. Mix each component vigorously by hand (using a paddle) or with a mechanical shaker. Each component shall be capable of being mixed within 5 minutes. Each component shall be smooth, homogenous, and pourable. The material shall be free of grit, skins, seeds, lumps,

## TO 1-1-8

abnormal thickening, or livering. In addition, it will reincorporate into a smooth, homogeneous state by mixing with a hand paddle without exhibiting pigment flotation or excessive settling. The containers shall not exhibit deformation due to internal pressure.

A.2.2 <u>Viscosity and Pot Life</u>. To test the viscosity and pot life, mix an adequate quantity of the primer per the manufacturer's instructions (measuring each component). Check viscosity of the unthinned coating with either a No. 2 Zahn or No. 4 Ford cup for conformance with the maximum viscosity ratings given in <u>Table A-1</u> at the times specified in the table.

A.2.3 <u>Drying Time</u>. Mix an adequate quantity of the coating for spray application of test panels per the manufacturer's instructions (measuring each component) and spray the primer on the test panels. Test panels shall be aluminum measuring approximately 3 x 6 inches. The primer coating shall be set-to-touch (when touched, no material transfers to finger) within 5 hours, and dry-hard (finger applied with reasonable force and turned with no deformation of coating) within 8 hours after spray application.

A.2.4 <u>Surface Appearance</u>. When sprayed on a vertical surface to a thickness of 0.0006 to 0.0018 inch, the primer coating shall not sag, run, or streak, and shall dry to a smooth, uniform surface free from grit, seeds, craters, blisters, and other irregularities.

## A.3 MIL-PRF-85582 WATERBORNE EPOXY PRIMER.

A.3.1 <u>Condition in the Container</u>. Using a kit of material from each batch or lot number to be tested, allow to stand until reaching room temperature, and open each container and examine components A and B. Mix each component by hand or mechanical shaker. Each component shall be capable of being mixed within 5 minutes. Each component shall be smooth, homogenous, and pourable. The material shall be free of grit, skins, seeds, lumps, abnormal thickening, or livering. In addition, it will reincorporate into a smooth homogeneous state by mixing with a hand paddle without exhibiting pigment flotation or excessive settling. The containers shall not exhibit deformation due to internal pressure.

A.3.2 <u>Viscosity and Pot Life</u>. To test the viscosity and pot life, mix an adequate quantity of the coating per the manufacturer's instructions (measuring each component). Thin the coating as required per the manufacturer's instructions. When the mixed primer is diluted to application viscosity with water, there shall be no evidence of incompatibility and the material shall be suitable for spray application. Measure the viscosity and record the results. Place the mixed coating in container and stir at 140±30 RPM for 4 hours. After 4 hours, the viscosity shall not increase more than 8 seconds through a No. 4 Ford cup or 9.5 seconds through a No. 2 Zahn cup.

A.3.3 <u>Drying Time</u>. Mix an adequate quantity of the coating for spray application of test panels per the manufacturer's instructions (measuring each component), and spray the primer on the test panels. Test panels shall be aluminum measuring approximately 3 x 6 inches. The primer coating shall be set-to-touch (when touched, no material transfers to finger) within 1 hour, and dry-hard (finger applied with reasonable force and turned with no deformation of coating) within 6 hours after spray application.

A.3.4 <u>Surface Appearance</u>. When sprayed on a vertical surface to a thickness of 0.0006 to 0.0018 inch, the primer coating shall not sag, run, or streak, and shall dry to a smooth uniform surface free from grit, seeds, craters, blisters, and other irregularities.

## A.4 TT-P-2760 POLYURETHANE PRIMER.

A.4.1 <u>Condition in the Container</u>. Using a kit of material from each batch or lot number to be tested, allow to stand until reaching room temperature, and open each container and examine components A and B. Mix each component vigorously by hand (using a paddle) or with a mechanical shaker. Each component shall be capable of being mixed within 5 minutes. Each component shall be smooth, homogenous, and pourable. The material shall be free of grit, skins, seeds, lumps, foreign contaminants, abnormal thickening, or livering. In addition, it will reincorporate into a smooth, homogenous state by mixing with a hand paddle without exhibiting pigment flotation or excessive settling. The containers shall not exhibit deformation due to internal pressure.

A.4.2 <u>Viscosity and Pot Life</u>. To test the viscosity and pot life, mix an adequate quantity of the prime per the manufacturer's instructions (measuring each component). Check viscosity with either a No. 2 Zahn or No. 4 Ford cup for conformance with the maximum viscosity ratings given in <u>Table A-1</u> at the times specified in the table.

A.4.3 <u>Drying Time</u>. Mix an adequate quantity of the coating for spray application of test panels per the manufacturer's instructions (measuring each component), and spray the primer on the test panels. Test panels shall be aluminum measuring approximately 3 x 6 inches. The primer coating shall be set-to-touch (when touched, no material transfers to finger) within 5 hours, and dry-hard (finger applied with reasonable force and turned with no deformation of coating) within 8 hours after spray application.

A.4.4 <u>Surface Appearance</u>. When sprayed on a vertical surface to a thickness of 0.0012 to 0.0025 inch, the primer coating shall not sag, run, or streak, and shall dry to a smooth, uniform surface free from grit, seeds, craters, blisters, and other irregularities.

## A.5 MIL-PRF-85285 POLYURETHANE COATING.

A.5.1 <u>Condition in the Container</u>. Using a kit of material from each batch or lot number to be tested, allow to stand until reaching room temperature, and open each container and examine component A and B. Mix component A vigorously by hand using a paddle or with a mechanical shaker. It shall mix to be smooth, homogenous, and pourable condition. The material shall be free of grit, seeds, lumps, abnormal thickening, or livering. In addition, it will not show pigment flotation or excessive settling which cannot be easily reincorporated to a smooth, homogenous state. Component B shall be homogeneous, clear, and free from gelation or detectable particulate matter either suspended in solution or settled on the inner surface of the container.

A.5.2 <u>Viscosity and Pot Life</u>. To test the viscosity and pot life, mix an adequate quantity of the coating per the manufacturer's instructions (measuring each component). Check viscosity with either a No. 2 Zahn or No. 4 Ford cup for conformance with the maximum viscosity ratings given in <u>Table A-1</u>.

A.5.3 <u>Drying Time</u>. Mix an adequate quantity of the coating for spray application of test panels per the manufacturer's instructions (measuring each component), and spray the coating on the test panels. Test panels shall be aluminum measuring approximately 3 x 6 inches.

### NOTE

For this coating, test panels must be primed with either MIL-PRF-23377 or MIL-PRF-85582 primer applied to a thickness of 0.0006 to 0.0009 inch. The coating shall be set-to-touch (when touched, no material transfers to finger) within 4 hours, and dry-hard (finger applied with reasonable force and turned with no deformation of coating) within 12 hours after spray application.

A.5.4 <u>Surface Appearance</u>. When sprayed on one vertical and one primed horizontal mounted panel to a thickness of 0.0017 to 0.0023 inch, the coating shall dry to a smooth, uniform surface free from runs, sags, bubbles, streaks, hazing, seeding, dusting, floating, mottling, or other defects and irregularities.

	Check Time After Mix	Maximum Time		
Coating and Primer	(Minimum)	No. 4 Ford Cup	No. 2 Zahn Cup	
	Initial	40	48	
MIL-PRF-23377	4 hours	70	84	
	Initial	30	36	
TT-P-2760	4 hours (closed container)	60	72	
	Initial	30	36	
MIL-PRF-85285	4 hours	60	72	
Type I	8 hours	shall not gel	shall not gel	

# APPENDIX B STANDARD AIR FORCE AIRCRAFT MARKINGS

## B.1 NATIONAL STAR INSIGNIA.

- a. Dimensions. (Figure B-1) The dimensions of the insignia shall be determined by the diameter of the circumscribed circle which is standardized in multiples of 5 inches.
  - (1) The width of each end of the rectangle shall equal 1/2 the radius of the circle; the length shall equal one radius (excluding border).
  - (2) The width of the horizontally centered stripe at each end of the rectangle, shall equal 1/6 of the radius of the circle (excluding border).
  - (3) The width of the insignia outer bar shall equal 1/8 the radius of the circle (excluding border).
  - (4) Construction of the five-pointed star may be accomplished by marking off five equal distant points on the circumscribed circle and connecting each point to the non-adjacent points.
- b. National Star Insignia on Aircraft Wings. Each insignia will be positioned at a point inboard from each wing tip equal to 1/3 the distance from the wing tip to the wing-fuselage mating point. The border of the insignia will be tangent to the movable control surface cutout.
  - (1) The wing insignia may be moved in the minimum required distance to avoid structures which would alter the insignia pattern. However, symmetry will be maintained with the United States Air Force (USAF) marking on the opposite wing surface.
  - (2) Normally, the wing insignia shall be positioned so that in normal flight attitude the top point of the star points forward and a line through the center of the insignia and the top star point is parallel to the direction of flight.
  - (3) On swept wings or wings of variable sweep aircraft, the National Star Insignia shall be positioned as illustrated in <u>Figure B-2</u>. The insignia or any part thereof shall not extend to movable flight control surfaces. The insignia shall be applied so that the line through the center and the top point of the star is perpendicular to the constant 50 percent chord line of the wing.
  - (4) The National Star Insignia selected for the wing shall not exceed a maximum diameter of 60 inches nor have a minimum diameter of less than 20 inches (excluding border). The diameter of the circumscribed circle will be the standard size closest to but not exceeding 75 percent of the distance between the wing leading edge and the moveable surface cutout at the point of application.
- c. National Star Insignia on Aircraft Fuselage. The insignia may be moved forward or aft the minimum distance required to avoid transparent material or areas exposed to extreme heat or fluids which would scorch, deteriorate, or otherwise damage the insignia. The insignia may extend over doors and emergency exits, but the insignia shall not extend over the window areas or other such openings which would change the design of the insignia.

## NOTE

The insignia will be the standard size closest to, but not exceeding, 75 percent of the fuselage height at the point of application. The diameter of the blue circle will not exceed 50 inches nor be less than 15 inches. Symmetry will be maintained when applying the insignia on each side of the fuselage.

d. National Star Insignia on Helicopters. The National Star Insignia will be applied on vertical surfaces so that in normal flight attitude the top point of the star points upward; on horizontal surfaces the top point of the star will point forward in the direction of flight.

## TO 1-1-8

## B.2 U.S. AIR FORCE MARKING.

- a. Letter width shall be equal to 2/3 the letter height except that the width of the letter "I" shall be equal to 1/6 of the letter height.
- b. Letter stroke and spaces shall be equal to 1/6 the height, except that the space between "period" and "A" shall be 1/3 letter height.
- c. The space between AIR and FORCE shall be one letter width.

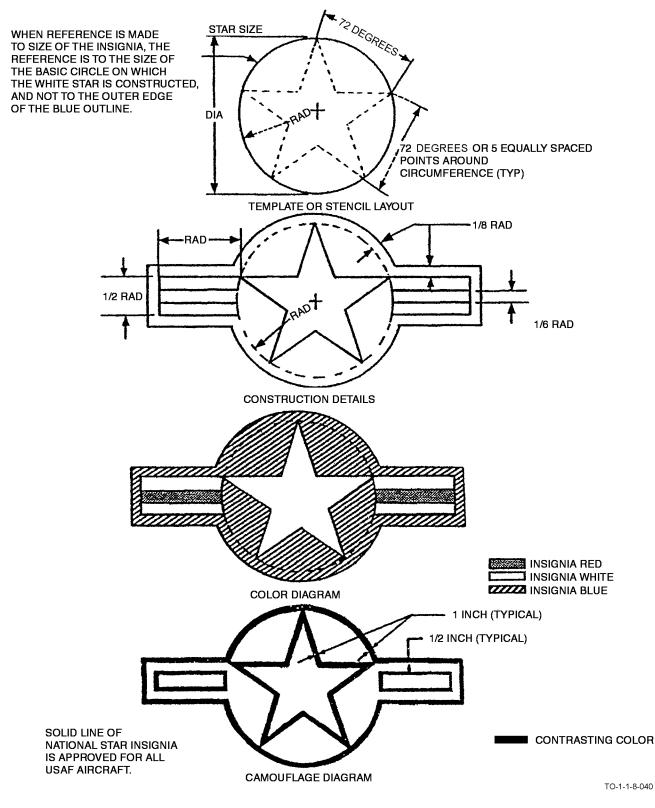


Figure B-1. Dimensions of National Star Insignia


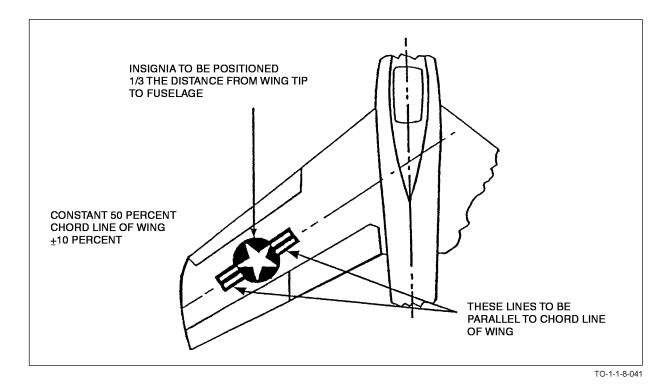


Figure B-2. National Star Insignia on Swept Wings

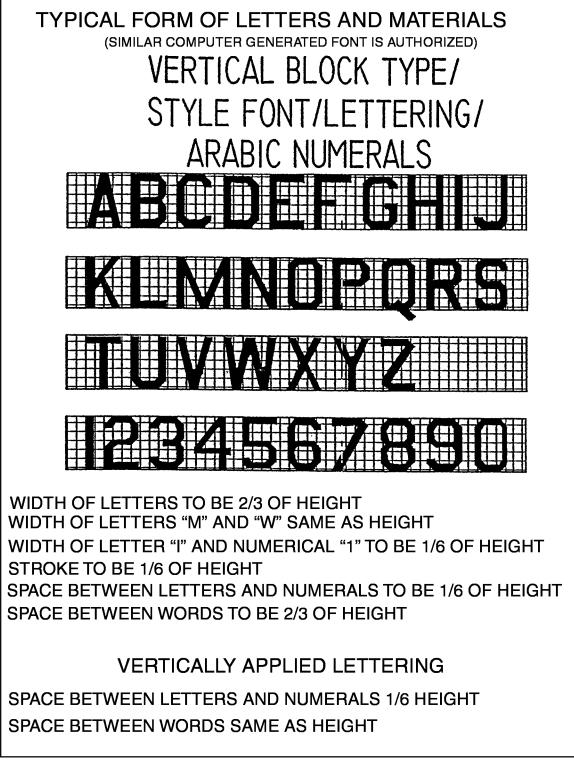

TO-1-1-8-042

Figure B-3. Form of Letters and Numerals

P/	AINTED:
Date: Activity & Cage Code:	(DD, MM, YY)
Pretreatment: Primer: Topcoat:	
	TO-1-1-8-043

Figure B-4. Typical Marking For Paint Facility/Finish Identification Block

NOTE

For non-standard and unique coatings, add manufacture product code.



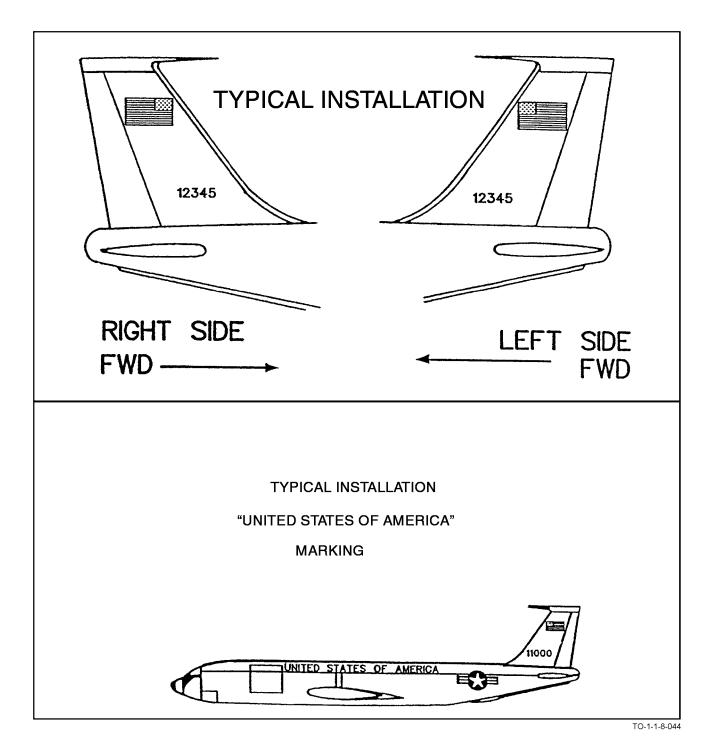


Figure B-5. "UNITED STATES OF AMERICA" and AMC Standard Marking Sample

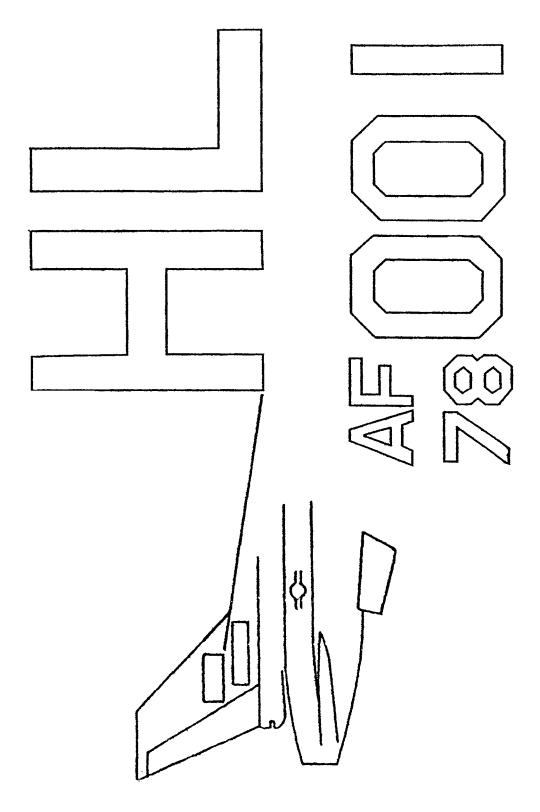

TO-1-1-8-045

Figure B-6. Distinctive Unit, Serial Number, and ACC Standard Sample

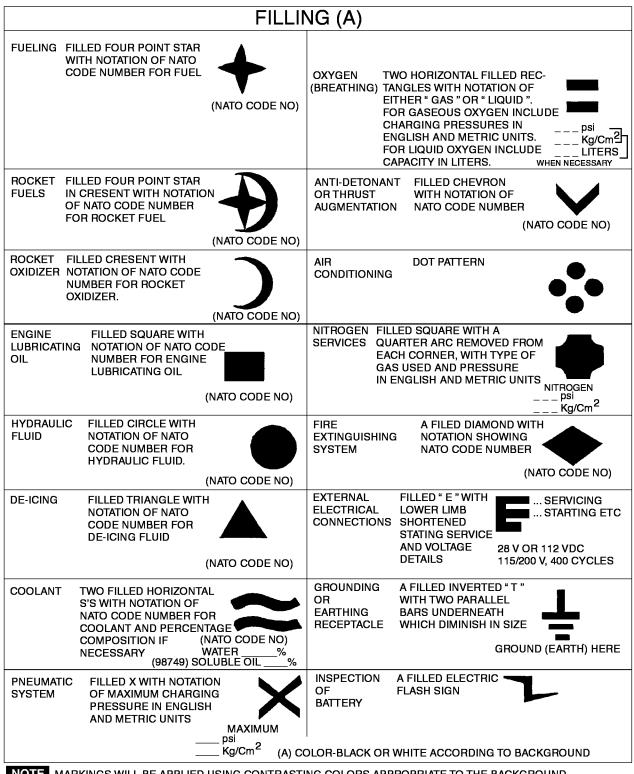


**NOTE** MARKINGS WILL BE APPLIED USING CONTRASTING COLORS APPROPRIATE TO THE BACKGROUND. FOR ADDITIONAL REFERENCE GUIDANCE TO THE BACKGROUND, SEE ALSO TO 42B1-1-15 (NATO/ASCC INTERCHANGEABILITY AVIATION FUELS, LUBRICATES, AND ALLIED PRODUCTS)

TO-1-1-8-046

Figure B-7. Aircraft Markings, Servicing, and Precautioning (Sheet 1 of 2)

	FILLING	GROUND HANDLING		
	A FILLED X CIRCUMSCRIBED BY A FILLED RING	JACKING POINT	$\mathbb{R}$	
		SLINGING OR HOISTING POINTS	2	
REFRIGERANT REPLENISHMENT	TWO FILLED TRIAN- GLES WITH APEXES JOINED ON HORIZON- TAL CENTER LINE.	MOORING OR PICKETING	Ţ	
	HAZARD		$\sim$	
EXPLOSIVE RE ACTUATED TF DEVICES TH SIJ SIJ EX AL DE TC SL	MARK BOTH SIDES OF FUSELAGE ED FILLED EQUILATERAL NANGLE APEX DOWN, OF IE LARGEST PRACTICABLE ZE UP TO A 9 INCH (23cm) ZE TO BE APPLIED TO THE TTERNAL PART OF AIRCRAFT DJACENT TO THE EXPLOSIVE EVICE. THE WORD " DANGER " D BE WITH ITS TOP TO A JRROUNDING PERIPHERAL ED LINE.	AIRBORNE AUXILLARY TURBINE POWER PLANT INLET AND OR EXHAUST.		
NOTE M	IARKINGS WILL BE APPLIED USING CONTR	ASTING COLORS APPROPRIATE TO THE E	BACKGROUND.	



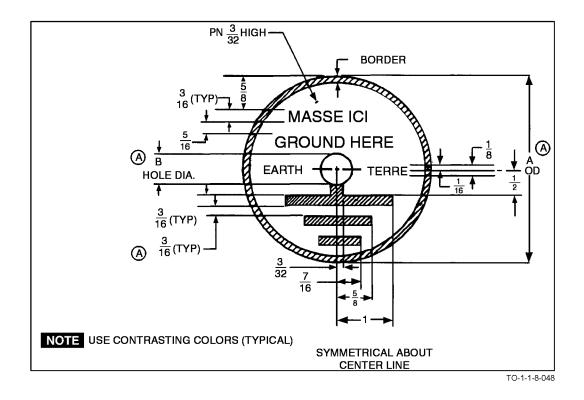


Figure B-8. Ground Here, International Symbol

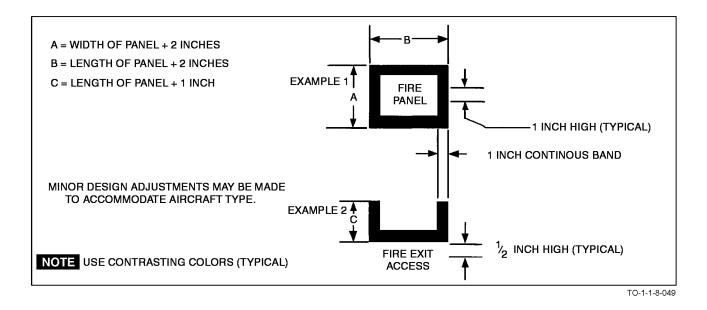


Figure B-9. Markings For Fire Access Panel

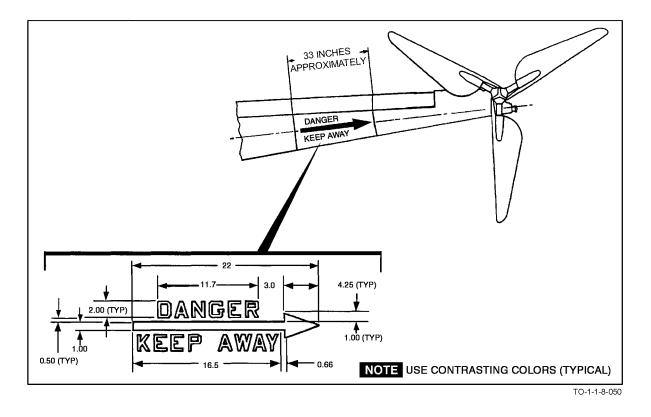


Figure B-10. Helicopter Tail Boom Markings


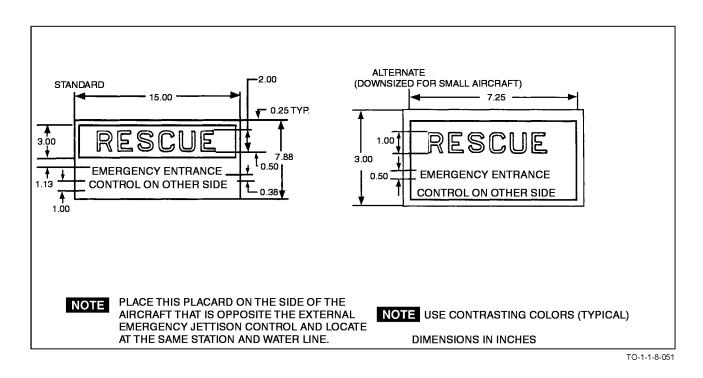


Figure B-11. Typical Emergency Instruction Markings

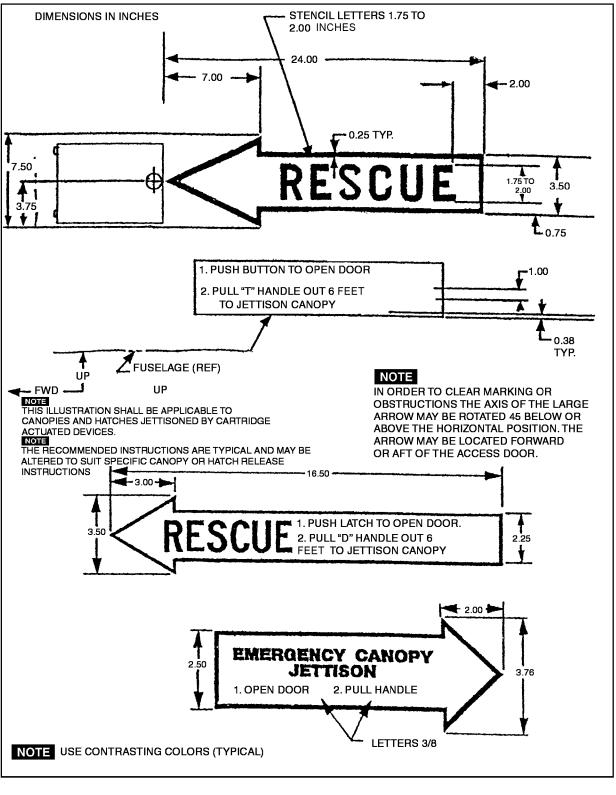

TO-1-1-8-052

Figure B-12. Typical Emergency Entry Markings

# APPENDIX C RESPIRATOR PROTECTION EQUIPMENT

## C.1 INTRODUCTION.

<u>Table C-1</u> provides a list of respirator equipment and related materials for use in aircraft, missile, and equipment corrosion prevention and control processes. This table provides only general information for respiratory safety devices. See the manufacturer's technical data for detailed operating maintenance instructions. See the DO43 System for proper National Stock Numbers (NSNs) and to convert Part Numbers (PNs) to NSNs.

Item Number	Nomenclature	Specifications/PN	NSN	Unit Issue	Intended Use
1	Particulate Respirator (1/2 Facepiece Mask), Disposable Type	3M Co. (Commer- cial and Govern- ment Entity (CAGE) Code No. 50378) PN 8511	4240-01-247-2348	BX (80 EA)	Personnel protection from inhalation of dust particulates during light sanding and grinding operations
2	Full Facepiece Respirator, Air Filtering (without Cartridges or Retainers)	3M Co. (CAGE Code No. 50378) PN 7800S-S (Small) PN 7800S-M	4240-01-314-2780 4240-01-342-5239	EA EA	Personnel protection from inhalation of organic vapors, dust, particulates, and paint spray in non-confined areas during spraying, sanding, and grinding operations
		(Medium) PN 7800S-L (Large)	4240-01-301-3200	EA	grinding operations
3	Full Facepiece Respirator, Air Filtering (without Cartridges or Retainers)	3M Co. (CAGE Code No. 50378) PN 6700 (Small) PN 6800 (Me- dium)	4240-01-454-8531 4240-01-454-8535	BX (4 EA) BX (4 EA)	Personnel protection from inhalation of organic vapors, dust, particulates and paint sprays in non-confined areas during spraying, sanding, and grinding operations
4	Half Facepiece Respirator, Air Filtering (without Cartridges or Retainers)	PN 6900 (Large) 3M Co. (CAGE Code No. 50378) PN 6100 (Small) PN 6200 (Me- dium)	4240-01-454-8538 4240-01-342-2852 4240-01-342-2853	BX (4 EA) BX (24 EA) BX (24 EA)	Personnel protection from inhalation of organic vapors, dust, particulates and paint sprays in non-confined areas during spraying, sanding, and grinding operations
5	Filter Cartridges (Organic Vapor (OV)/P100 Type)	PN 6300 (Large) 3M Co. (CAGE Code No. 50378) PN 60921	4240-01-342-2854 4240-01-455-7353	BX (24 EA) BX (60 EA)	3M Co. half and full Face- piece respirators
6	Respirator Lens Assembly for 3M Co. Full Face- piece	3M Co. (CAGE Code No. 50378)			
	Respirators (With Plastic Film Covers)	PN 7884	4240-01-247-8929	BX (5 EA)	7800S Series Replacement Lens
		PN 6898	Open Purchase	BX (5 EA)	6000 Series Replacement Lens

## Table C-1. Respirator Protection Equipment

Item	Nonconstations	Succif actions/DNL	NCN	I In it I amo	Inter de d I les
Number 7	Nomenclature Lens Covers for	Specifications/PN 3M Co. (CAGE	NSN 4240-01-248-4634	Unit Issue BX (25 EA)	Intended Use 7800S Series Lens Covers
1	3M Co. Full Facepiece	Code No. 50378) PN 7899-25	4240-01-248-4634		
	Respirators	PN 7899-100	4240-01-248-6435	BX (100 EA)	7800S Series Lens Covers
	(Peel-Away Plastic Film)	PN 6885	4240-01-455-2787	BX (100 EA)	6800 Series Lens Covers
8	Inhalation Valve for 3M Co. Full	3M Co. (CAGE Code No. 50378)			
	Facepiece Respirators	PN 7282	Open Purchase	BX (200 EA)	7800S Series Replacement Valves
		PN 6893	4240-01-455-2811	BX (200 EA)	6800 Series Replacement Valves
9	Exhalation Valve for 3M Co. Full	3M Co. (CAGE Code No. 50378)			
	Facepiece Respirators	PN 7283	4240-01-248-2608	BX (50 EA)	7800S Series Replacement Valves
		PN 6889	4240-01-455-2809	BX (10 EA)	6800 Series Replacement Valves
10	Tyvek <sup>™</sup> Shroud for 3M Co. Full Facepiece Respirators	3M Co. (CAGE Code No. 50378) PN 7915-5	4240-01-320-1957	PG (5 EA)	Used with full Facepiece respirators to protect the head and neck from painting and/or abrasive blasting overspray.
11	Spectacle Kit for 3M Co. Full Facepiece Respirators	3M Co. (CAGE Code No. 50378)			
		PN 6878	4240-01-455-2346	EA	Frame & Retainer Clip 6000 Series Spectacle Kit
		PN 7925	4240-01-395-4128	EA	7800S Series Spectacle Kit
12	Respirator Cleaning Wipes (Alcohol-Free Towelettes)	3M Co. (CAGE Code No. 50378) PN 504	4240-01-372-3078	BX (100 EA)	Hygienic cleaning of respira- tors and other personal protective equipment.
13	Pump/Compres- sor, Breathable Air, Pneumatic	Rhine Air, Inc. (CAGE Code No. 58501)			Used to supply breathable air to hoods and full Facepiece respirators for abrasive blastin
	(Air Motor) Driven, Portable	PN NF-1100 E. D. Bullard Co.	4240-01-363-4699	EA	and other corrosion removal operations. These small,
		(CAGE Code No. 09729)			air-driven, portable compres- sors are very convenient as they may be easily transported
		PN ADP-16/ ADP-20	4310-01-168-7302	EA	and set up almost anywhere.

 Table C-1.
 Respirator Protection Equipment - Continued

## NOTE

Use MIL-PRF-32033 oil, NSN 9150-00-231-6689/1 QT CN, or MIL-PRF-17672 hydraulic fluid (10 wt. oil equivalent), NSN 9150-00-985-7231/1 QT CN, to fill in-line oiler of air motor after each use, as required, to maintain lubrication and prevent motor oxidation.

Item Number	Nomenclature	Specifications/PN	NSN	Unit Issue	Intended Use
14	Replacement Filter Cartridges for Breathable Air Pumps	Rhine Air, Inc. (CAGE Code No. 58501)			Rhine Air's NF-1100 and NF 15-3 pumps
		PN CF8080	4240-01-084-0921	BX (10 EA)	
15	Compressed Air Inlet Hose Assembly, 1/2 inch Inside Diameter (ID) Hose	Rhine Air, Inc. (CAGE Code No. 58501)			Used only for supplying fresh, breathable air to the air motor on the breathable air pump unit
		PN ED1313B-50 (50 foot L)	4240-01-251-8159	EA	
		PN ED1313B-100 (100 foot L)	4240-01-251-8160	EA	
16	Quick Disconnect Fittings for Inlet Hose	Tuthill Corp (CAGE Code No. 73992)			Replacement fittings for the Rhine Air PN ED1313B inlet air hose assemblies
		PN 3L25 (Male Plug)	4730-01-442-1809	EA	
		PN 3R25 (Female Coupler)	4730-01-442-1808	EA	
17	Outlet Manifold, Quick Disconnect (Female Coupler	Rhine Air, Inc. (CAGE Code No. 58501)			Connects respirator air hose assemblies to the breathable a pump. Can be used with both
	Assembly)	PN ED-06-430	Open Purchase	EA	Rhine Air and Bullard units

Table C-1.	<b>Respirator Protection E</b>	<b>Equipment - Continued</b>
------------	--------------------------------	------------------------------

# GLOSSARY

## Α

ACCELERATOR — A substance which speeds up the polymerization of a synthetic resin.

ACRYLIC RESIN — Any of a group of transparent thermo-plastic resins formed by polymerizing esters of acrylic acid or methacrylic acid.

ALIPHATIC — An organic chemical whose carbon atoms are not in a ring form. A straight-chain compound. Mineral spirits, some naphthas, and kerosene are typical aliphatic compounds.

**ALKYD RESIN** — One of the major synthetics formed by polybasic acid reaction with polyhydric alcohols. Primarily used in enamels but also in combinations in some other types of coatings.

**ALLIGATORING** — A condition where cracks in the film are caused by contraction of the coating when a sudden change in temperature occurs during drying. It may also occur because of insufficient drying time between lacquer coats, or because of poor penetration or wetting, or when a hard topcoat has been applied over a soft undercoat. These cracks usually penetrate to the metal surface.

**AMINE** — An organic chemical containing carbon hydrogen and nitrogen. Certain amines may be used as convertors for epoxy resins.

ANHYDROUS — Containing no water.

**AROMATIC** — An organic chemical possessing the benzene ring structure. Benzene and toluene are typical aromatic hydrocarbons.

# В

**BAKING FINISH** — Any paint or varnish which requires temperatures in excess of 150 °F for the development of desired properties. The usual baking difficulties are the result of over-baking or under-baking schedules. Over-baking will result in a hard, brittle film with less adhesion than requirements demand. Proper correction of baking faults demands strict adherence to the instructions of the manufacturer.

**BINDER** — The non-volatile portion of a coating vehicle. It generally consists of drying oils, resins, or combinations thereof.

**BLEEDING** — A condition caused by pigments or dyes in the under surfaces floating up into the top coating. Bleeding may occur when material is applied with unclean spraying equipment or when a topcoat/second coat is applied too soon.

**BLISTERING (OR BUBBLING)** — Blistering may occur when there is poor air circulation during drying of the coating. Unbalanced solvents in the structure of the coating will also cause this effect. Temperature differences between the part being sprayed and the coating will also cause air pockets or blisters. Water in air lines can cause blistering, and daily draining of the water filters on air lines will help minimize this problem.

**BLOOMING (OR HAZING)** — The appearance of blooming is similar to blushing, though the underlying reasons are different. Blooming is the result of rubbing the finish too soon after application, the use of too coarse an abrasive or too hard a rubbing stroke. When blooming does occur, it may be removed by washing with a mild soap solution and warm water, fol-

### TO 1-1-8

lowed by chamois skin. Properly dried and hardened surfaces will not bloom when rubbed or polished.

**BLUSHING** — Commonly referred to as clouding or whitening, blushing is the result of moisture being present on the film surface during the drying period. Although the fault commonly lies in improper drainage of the air line during finishing operations, the condition is also caused by high humidity conditions within the finishing room. Improper selection of solvents will also cause blushing.

**BODY OF PAINT** — The liquid portion without the volatile solvents and water.

**BODYING** — See Gelling.

**BROWN SPOTS** — Spots which occur in a lacquer film when oil is permitted to get into the material. As a precautionary measure, drain the water and oil separators daily.

**BUBBLES** — When improper quality or quantity of thinner is used, bubbles often occur (also known as "solvent pop"). To help prevent this defect, use correct proportions of thinner at all times. Application of a topcoat before the initial coat has cored properly or at too high a temperature can also cause bubbles.

**BUCKLING** — A nitrocellulose lacquer film may shrink or buckle when sprayed over an oil base undercoat. If necessary to overcoat oil paint with lacquer, make the first top coat as light as possible.

## С

**CASE HARDENING** — The formation of a hardened top surface with a soft underbody. Proper relative humidity conditions within the drying room will assist in eliminating this condition.

**CATALYST** — A substance which changes the rate of a chemical reaction without itself undergoing permanent change in its composition.

**CHALKING** — Deterioration of an organic coating upon exposure that results in a powdery, chalky residue on a painted surface.

**CHECKING** — Slight breaks in the film which do not penetrate to the underlying surface. It occurs when lacquer coats are applied too heavily or without sufficient time allowed for drying between coats.

**COBWEBBING** — Filaments of paint which appear as cobwebs instead of fine droplets.

**COLLOID** — A very finely divided (but not molecular) dispersion of a solid in a liquid. Colloidal dispersions do not settle and the particles are too small to be observed by ordinary microscope.

**CONSISTENCY** — Consistency is another word for viscosity of a wet material. The term may also be applied to the resistance to deformation of a cured film.

**CONVERTER** — A substance which causes a resin to polymerize or cure. Polyamides and amines are two examples of epoxy converters.

**COVERAGE** — The surface area which can be coated with a given volume of coating applied at a given film thickness. Coverage is usually expressed in square feet per gallon at one mil dry film thickness. Coverage is not related to hiding power.

CRACKING - Cracking occurs when the various components of a lacquer are not blended or mixed properly, or when coat-

ings not compatible with one another are used together.

**CRATERING** — A defect in a coating resulting in craters or fish eyes. Most often caused by the presence of grease, oil, silicone polishes or other similar contaminants on the surface.

CRAWLING — The reverse of crazing, that is, a more flexible coating is applied over a hard or brittle film.

**CRAZING** — When lacquer films expand and contract, a series of fine hair line cracks (crazing) results. Crazing frequently occurs when a very heavily pigmented surface coat is applied over a more flexible undercoating. The elastic coating of lower filler content will expand and contract more easily than the heavily pigmented coating.

**CRYSTAL LACQUERS** — A decorative finish which is achieved by re-cyrstallization of dissolved lacquer bases. It occurs after the thinners have evaporated. Pearl essence or mother of pearl finishes may be produced in this fashion.

**CRYSTALLINE FINISH** — A crystalline like, decorative finish is accomplished by using certain gas checking oils which on drying produce the pattern.

**CURDLING** — Curdling usually occurs when a high evaporative but weak solvency thinner is used with a lacquer or enamel. Control of solvency and evaporation rate will prevent curdling.

## D

**DECAL** — A plastic film with an adhesive on one side that adheres to glass, wood, metal, etc., that transfers decorative pictures or designs printed on the specially prepared film to the surface.

DILUENT — A thinner blended with an organic coating mixture to increase its volume and/or reduce its viscosity.

**DISPERSION** — An intimate mixture of finely divided solid particles in a liquid substance. Paints are dispersions of pigments in a vehicle.

**DOUBLE COAT** — A double application of paint. This does not mean two consecutive passes of the spray gun. One coat is applied by a double or cross pass of the gun followed by a second similar application after the first coat has set up.

**DRIER** — A catalytic material which when added to a drying oil or drying oil modified coating accelerates the rate of drying. A substance which speeds the reaction of a binder with oxygen. Naphthenates of cobalt and manganese are common driers.

**DRYING OIL** — An oil which readily absorbs oxygen from the air to form a durable film.

**DRYING TIME** — The time required for a coating to attain various stages of dryness. Three commonly referred to drying times are: dry to touch, dry to handle, and dry hard (recoat). Drying time is greatly affected by temperature, humidity, and air movement.

**DUST COAT** — a very light coat of a coating, which will improve adhesion.

### Ε

**EMULSION** — An intimate suspension of two or more liquid substances which are not mutually soluble but which do not ordinarily separate. Examples: milk (butterfat and water), self-polishing floor waxes (wax, solvent, water), vehicle for water-thinned latex paints.

### TO 1-1-8

**ENAMEL** — A coating characterized by an ability to form an especially smooth finish film.

**EPOXY RESIN** — A synthetic resin produced by the reaction of epichlorohydrin and bisphenol. Epoxy resins may be used alone (unmodified) or modified with drying oils (epoxy esters) for coating vehicles.

**EXTENDER PIGMENTS** — Pigments used to provide texture, bulk or hardness to a coating. Also known as inert pigments. Magnesium silicate and diatomaceous silica are examples of extender pigments.

F

FERROUS — Magnetic metals derived from steel or iron.

**FILLER** — A material of pigmented composition used to fill irregularities and undesirable depressions after a primer coating is applied and prior to finish coating application.

FILLING POWER — The degree a filler material hides irregularities of texture.

**FLASH POINT** — The minimum temperature at which the vapors of a liquid will ignite. An indication of the flammability of a product; the higher the flash point, the safer the product.

FLATTENING AGENT — A material added to a coating to reduce the gloss of the cured film.

**FLOODING** — A change in color of a coating from the time it is applied until the time it sets caused by fines in the pigment portion floating to the surface. The result is a final shade different from the original.

**FORCE DRYING TEMPERATURE** — A temperature between room temperature and 175 °F to which a coating is exposed to accelerate curing.

## G

**GELLING** — The irreversible transformation of a liquid to a solid without the loss of weight through evaporation.

**GLOSS, SPECULAR** — The luster, shininess, or reflective ability of a surface; or the ability of a surface to reflect light regularly when light strikes the surface at a 60-degree angle. It is based upon the degree of optical smoothness of a surface, variations in smoothness being microscopic. Values above 90 are classified as high gloss, 80 to 90 as full gloss, 35 to 45 as semi-gloss, 5 to 7 as flat or camouflage, and 3 or less as gunship quality. Seven or less is also classified as lusterless.

## Η

**HIDING POWER** — For an organic coating, it is either the degree to which the base material has been obliterated from view or the relative smoothness or surface leveling a coating may produce.

**HOLIDAY** — An unintentional skipped area, missed while applying a coating. Holidays can be avoided by using contrasting colors for alternating coats.

HYGROSCOPIC — The ability to attract or absorb water.

**INFRARED LAMP** — A heat lamp commonly used in paint drying operations that emits infrared light.

**INHIBITOR** — A substance which slows down a chemical reaction.

**INORGANIC** — Chemical compounds based chiefly on elements other than the carbon-hydrogen-oxygen group. Inorganic compounds are divided into four classifications:

Acids — Materials such as sulfuric, hydrochloric (muriatic), nitric, and phosphoric acids.

Alkalies — A base material such as sodium hydroxide (caustic soda), potassium hydroxide (caustic potash), ammonium hydroxide (ammonia).

**Salts** — Materials produced by the reaction of an acid and an alkali. Sodium chloride (table salt), magnesium sulfate (epsom salt), calcium chloride, copper sulfate.

**Oxides** — A combination of a metal and oxygen such as iron oxide (rust), zinc oxide, titanium dioxide (white pigment), silicone dioxide (sand and glass).

**INTERCOAT** — A layer of paint that is "sandwiched" between two others. Also refers to something occurring between coats, as in "intercoat adhesion".

### L

LATEX — A water suspension of fine particles of rubber or rubber-like materials.

**LEVELING** — The degree to which a film will smooth out after application is its leveling ability. Improper solvent or driers may prevent proper leveling.

**LEAFING** — The ability of an aluminum or gold bronze paint to exhibit a brilliant or silvery appearance. This occurs when the flat pigment particles align themselves parallel with the coated surface so as to give the appearance of a solid sheet of metal.

**LIFTING** — Separation of a coating film from a surface when solvents from a topcoat penetrate an existing coating which has not dried sufficiently to permit proper adhesion. In all instances where one finish is applied over another it is important that the undercoat be sufficiently dry; otherwise, poor adhesion will result.

**LIVERING** — Gelling of a paint that occurs when the pH of a paint is lowered, such as when acid-producing reactions occur in the material. In many cases, this difficulty can be remedied by slowly stirring into the livered material a very slow evaporating paint reducer.

#### Μ

MIL — A unit of measurement for the thickness of a coating film. One mil equals 1/1000 (0.001) inch.

#### Ν

**NAPHTHA** — The product of the distillation of the solvent fractions obtained from the thermal decomposition (cracking) of coal or petroleum. A volatile, flammable fluid consisting chiefly of mixed hydrocarbons. It can be aromatic with a benzene ring structure or aliphatic with a linear structure.

**NITROCELLULOSE** — A binder used in most lacquers; principally air drying. It may be modified with resins and plasticizers for improved gloss, adhesion and flexibility. An ester of nitric acid and cellulose produced by the action of nitric acid

### TO 1-1-8

upon wood, cotton, or some other form of cellulose in the presence of concentrated sulfuric acid.

NON-FERROUS — A description of metals other than iron.

**NON-VOLATILE VEHICLE** — The liquid portion of a paint, enamel, varnish, or related products not including the volatile thinners and water.

0

**ORANGE PEEL** — Pebble effect appearance caused by too low an air pressure during spraying, the spray gun being held too close to the surface, or using a highly volatile thinner which prevents the normal flow of lacquer solids.

**ORGANIC** — Chemical compounds chiefly composed of carbon, hydrogen, and oxygen in a multitude of molecular arrangements. The term organic was established when it was thought that organic compounds could be produced only by living organisms. Many organic compounds are produced synthetically today. However, even these are derived from former living plants and animals (coal and oil are the chief sources of raw materials for organic chemicals). Examples of organic compounds: gasoline, alcohol, sugar, fish oil, glycerin.

**ORGANIC COATING** — A finish/paint system such as a lacquer or an enamel that cures/dries by solvent or volatile component evaporation only and not by chemical reaction.

**ORGANISOL** — Finely divided or colloided dispersion of a resin in a plasticizer with solvents or other materials.

**OXIDATION** — A chemical reaction involving the reaction of a substance with oxygen. Iron rusts by oxidation. Oil-containing coatings dry or cure by oxidation.

Ρ

**PERMEABILITY** — The extent to which a coating or other film will allow air or water to pass through it.

pH — A term used to indicate acidity or alkalinity. The pH scale runs from 0 to 14; pH 7 is neutral, less than 7 is acid, 7 to 14 is alkaline. The further the rating is from seven, the greater the acidity or alkalinity.

**PIGMENT** — The solid particles used in the preparation of paints, lacquers and enamels which are substantially insoluble in the vehicle and provide color, under film protection and special effects.

**PITTING** — A condition which occurs when a lacquer is sprayed at high pressures and at temperatures below 65 °F. It will occur if a lacquer used in spraying has been stored in a cool place and has not been allowed to attain room temperature.

**PLASTICIZER** — Substances added to soften or otherwise modify the properties of a finished resin without excessive sacrifice of strength and rigidity.

PLASTISOL — Colloidal dispersion of a resin in a plasticizer without solvent.

**POCK MARKS** — Marks caused by bursting of trapped air bubbles in a porous film. Too high an air pressure or too thick a coating can result in pock marks. To overcome this condition, apply thinner coatings, use less air pressure, and use a high solvency thinner.

**POLYMER** — A substance composed of large molecules formed by the combination of a number of simple molecules with one another by chemical reaction.

#### **Glossary 6**

**PRIMER** — A coating applied directly to the basic metal or pretreated metal and upon which a subsequent coating or topcoat is applied.

R

**RAISING** — The appearance of wrinkles or blisters in a film; often due to a reaction of lacquer solvents with unoxidized oil films in oil base undercoats.

**RELATIVE HUMIDITY** — The ratio of the actual amount of moisture in the air to the maximum amount it could contain at the same temperature, expressed as a percentage.

**RESIN** — A natural or synthetic substance usually organic in composition, characterized by being amorphous (noncrystalline), isotropic (properties being the same in all directions), plastic, often sticky and usually fusible and soluble at some stage in its manufacture or processing.

**RUNS** — Rivulets in a coating caused by too much organic coating material or thinner being applied to an area at one time.

## S

**SILOXANE** — A compound composed of alternating silicon and oxygen atoms with hydrogen side chains. Cyclic siloxanes are used for environmentally preferred cleaner alternatives for dry cleaning and industrial cleaning applications.

**SOLVENT** — Any liquid which will dissolve another substance. Solvent power of a liquid is specific, that is, it can dissolve certain substances but not others.

**SOLVENT RESISTANT COATING** — A finish/paint system such as an epoxy or a polyurethane that is catalyzed and cures by chemical reaction in conjunction with solvent evaporation. These coatings are highly resistant to solvents/thinners after they completely cure.

**SPRAY DUST** — Paint dust that causes surface roughness when a spray gun is held too far from the work, especially when a highly volatile thinner is used. This is caused by solid particles in the coating material drying up while traveling from the nozzle to the surface being sprayed. Insufficient thinning or too high air pressure may also cause spray dust. Correct by spraying at lower air pressures, adjusting distances to between 6 to 10 inches from the work, and/or by increasing the thinner content.

**STRIPPING** — Removal of paint from a surface.

**SURFACE TENSION** — The property of a liquid by which the surface film of a liquid tends to form into a sphere. Surface tension affects the ability of a liquid to wet a surface. The higher the surface tension, the poorer the wetting.

Т

**TIECOAT** — A two-component, VOC, solvent-borne, lead and chromate free epoxy coating particularly formulated for its adhesion properties to other coatings.

**THIXOTROPY** — The property of a coating which causes it to undergo a gel-sol-gel transformation upon agitation and subsequent rest. Upon agitation it becomes quite fluid but readily falls back again to the semi-solid form after the agitation is stopped.

TONER — Organic pigments which do not contain inorganic pigments or inorganic carrier bases.

V

VARNISH — A liquid resin material which after application converts to a transparent or translucent solid material.

**VEHICLE** — The liquid carrier portion of a paint/coating.

**WET SPOTS** — If metals are not thoroughly cleaned of oils and greases before painting, those areas which retain the foreign material become wet spots or fish-eyes. The condition is characterized by a sticky coating film which requires extremely long drying time and often remains soft or wrinkled. Stripping of the paint film, cleaning, and refinishing is required to correct this condition.

W

**WRINKLE FINISH** — In those cases where wrinkling is undesirable, it is a defect caused by improper application, usually of too heavy a coating, an abnormally high or too rapid a rise in temperature, or high humidity. Avoid these conditions by applying thinner films, allowing sufficient drying time between coatings, and avoiding extremes of temperatures and humidity.

## Ζ

No. 2 ZAHN Cup/No. 4 Ford Cup — A small portable viscosity measuring device.